



SLOVENSKI STANDARD
SIST EN 12420:2014

01-september-2014

Nadomešča:
SIST EN 12420:1999

Baker in bakrove zlitine - Izkovki

Copper and copper alloys - Forgings

Kupfer und Kupferlegierungen - Schmiedestücke

Cuivre et alliages de cuivre - Pièces forgées

iTeh STANDARD PREVIEW
(standards.iteh.ai)

Ta slovenski standard je istoveten z: ~~SIST EN 12420~~ EN 12420:2014

<https://standards.iteh.ai/catalog/standards/sist/0553ba5f-1162-4d10-afe9-bf10dbc07b2b/sist-en-12420-2014>

ICS:

77.150.30 Bakreni izdelki Copper products

SIST EN 12420:2014 **en,fr,de**

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN 12420:2014](#)

<https://standards.iteh.ai/catalog/standards/sist/0553ba5f-1162-4d10-afe9-bf10dbe07b2b/sist-en-12420-2014>

EUROPEAN STANDARD

EN 12420

NORME EUROPÉENNE

EUROPÄISCHE NORM

June 2014

ICS 77.150.30

Supersedes EN 12420:1999

English Version

Copper and copper alloys - Forgings

Cuivre et alliages de cuivre - Pièces forgées

Kupfer und Kupferlegierungen - Schmiedestücke

This European Standard was approved by CEN on 24 April 2014.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.

(standards.iteh.ai)

[SIST EN 12420:2014](https://standards.iteh.ai/catalog/standards/sist/0553ba5f-1162-4d10-afe9-bf10dbe07b2b/sist-en-12420-2014)

<https://standards.iteh.ai/catalog/standards/sist/0553ba5f-1162-4d10-afe9-bf10dbe07b2b/sist-en-12420-2014>



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Avenue Marnix 17, B-1000 Brussels

Contents

Page

Foreword.....	4
Introduction	6
1 Scope	7
2 Normative references	7
3 Terms and definitions	7
4 Designations	8
4.1 Material	8
4.1.1 General.....	8
4.1.2 Symbol	8
4.1.3 Number	8
4.2 Material condition	8
4.3 Product	8
5 Ordering information	10
6 Requirements	10
6.1 Composition	10
6.2 Mechanical properties	11
6.2.1 Hardness properties	11
6.2.2 Tensile properties	11
6.3 Electrical properties	11
6.4 Resistance to dezincification	11
6.5 Residual stress level	11
6.6 Tolerances for die forgings	11
6.6.1 General.....	11
6.6.2 Tolerances for dimensions within the die cavity and for dimensions across the die parting line.....	12
6.6.3 Mismatch	13
6.6.4 Flash projection	14
6.6.5 Ejector marks	15
6.6.6 Flatness tolerances	15
6.6.7 Angular tolerances	16
6.7 Tolerances for cored forgings	16
6.8 Tolerances for hand forgings	17
6.8.1 General.....	17
6.8.2 Tolerances on dimensions	18
6.8.3 Flatness tolerance	18
6.9 Surface quality	19
6.10 Drawings.....	19
7 Sampling	19
7.1 General.....	19
7.2 Analysis	19
7.3 Hardness, stress corrosion resistance, dezincification resistance and electrical property tests.....	20
8 Test methods.....	20
8.1 Analysis	20
8.2 Hardness test	20

8.3	Electrical conductivity test	20
8.4	Dezincification resistance test	20
8.5	Stress corrosion resistance test.....	20
8.6	Retests	21
8.6.1	Analysis, hardness, electrical conductivity and dezincification resistance tests	21
8.6.2	Stress corrosion resistance test.....	21
8.7	Rounding of results	21
9	Declaration of conformity and inspection documentation	21
9.1	Declaration of conformity	21
9.2	Inspection documentation	21
10	Marking, labelling, packaging	22
Annex A (informative) Recommended guidelines for design		39
A.1	Introduction	39
A.2	General information	39
A.3	Guidelines for die forgings	40
A.3.1	Drafts	40
A.3.2	Web thicknesses	40
A.3.3	Side wall thicknesses	41
A.3.4	Rib design	42
A.3.5	Cores	43
A.3.6	Flash	44
A.3.7	Transition radii	45
A.3.8	Clamping lengths and clamping areas for finish machining	47
A.3.9	Design for cross-sectional shapes	47
A.3.10	Recommended machining allowances and total allowances	48
A.4	Guidelines for hand forgings	50
A.4.1	General	50
A.4.2	General information	50
A.4.3	Section changes and transitions	51
A.4.4	Recommended machining allowances	51
A.4.5	Total allowances per side of forging	52
A.5	Guidelines for marking	52
Annex B (informative) Tensile properties		54
Annex ZA (informative) Relationship between this European Standard and the Essential Requirements of EU Directive 97/23/EC, Pressure Equipment Directive (PED)		58
Bibliography		59

EN 12420:2014 (E)

Foreword

This document (EN 12420:2014) has been prepared by Technical Committee CEN/TC 133 “Copper and copper alloys”, the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by December 2014 and conflicting national standards shall be withdrawn at the latest by December 2014.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN 12420:1999.

This document has been prepared under a mandate given to CEN by the European Commission and the European Free Trade Association, and supports essential requirements of EU Pressure Equipment Directive (PED) 97/23/EC.

For relationship with EU Directive 97/23/EC, see informative Annex ZA, which is an integral part of this document.

This is one of a series of European Standards for the copper and copper alloy products rod, wire, profile and forgings. Other products are specified as follows:

- STANDARD PREVIEW**
(standards.iteh.ai)
- EN 12163, *Copper and copper alloys* — *Rod for general purposes*;
 - EN 12164, *Copper and copper alloys* — *Rod for free machining purposes*;
 - EN 12165, *Copper and copper alloys* — *Wrought and unwrought forging stock*;
 - EN 12166, *Copper and copper alloys* — *Wire for general purposes*;
 - EN 12167, *Copper and copper alloys* — *Profiles and rectangular bars for general purposes*;
 - EN 12168, *Copper and copper alloys* — *Hollow rod for free machining purposes*.

Within its programme of work, Technical Committee CEN/TC 133 requested CEN/TC 133/WG 4 “Extruded and drawn products, forgings and scrap” to revise the following standard: EN 12420:1999, *Copper and copper alloys* — *Forgings*.

In comparison with EN 12420:1999, the following significant technical changes were made:

- 1) new text has been introduced concerning optional restrictions to chemical compositions of materials with respect to individual uses or regulations for the use in contact with drinking water;
- 2) materials have been considered coherently with EN 12165:2011;
- 3) four new materials have been added: CuZn35Pb1,5AlAs (CW625N), CuZn33Pb1,5AlAs (CW626N), CuZn21Si3P (CW724R) and CuZn33Pb1AlSiAs (CW725R);
- 4) the mechanical properties have been modified to reflect market needs;
- 5) an informative Annex B Tensile properties has been introduced.

According to the CEN-CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[SIST EN 12420:2014](#)

<https://standards.iteh.ai/catalog/standards/sist/0553ba5f-1162-4d10-afe9-bf10dbe07b2b/sist-en-12420-2014>

EN 12420:2014 (E)**Introduction**

The European Committee for Standardization (CEN) draws attention to the fact that it is claimed that compliance with this document may involve the use of a patent concerning the alloys CuZn21Si3P (CW724R) and CuZn33Pb1AlSiAs (CW725R).

CEN takes no position concerning the evidence, validity and scope of this patent right.

The holder of this patent right has ensured the CEN that he/she is willing to negotiate licences under reasonable and not-discriminatory terms and conditions with applicants throughout the world. In this respect, the statement of the holder of this patent right is registered with CEN.

— For CuZn21Si3P (CW724R) information may be obtained from:

Wieland-Werke AG
Graf Arco Straße 36
89079 Ulm
GERMANY

— For CuZn33Pb1AlSiAs (CW725R) information may be obtained from:

Diehl Metall Messing
Heinrich-Diehl-Straße 9
D-90552 Röthenbach/Pegnitz
GERMANY

iTeh STANDARD PREVIEW
(standards.iteh.ai)

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights other than those identified above. CEN shall not be held responsible for identifying any or all such patent rights.

<https://standards.iteh.ai/catalog/standards/sist/0553ba5f-1162-4d10-afe9-bf10dbe07b2b/sist-en-12420-2014>

CEN (<http://www.cen.eu/cen/WorkArea/IPR/Pages/default.aspx>) and CENELEC (<http://www.cenelec.eu/membersandexperts/toolsandapplications/index.html>) maintain on-line lists of patents relevant to their standards. Users are encouraged to consult the lists for the most up to date information concerning patents.

Due to developing legislation, the composition of a material may be restricted to the composition specified in this European Standard with respect to individual uses (e.g. for the use in contact with drinking water in some Member States of the European Union). These individual restrictions are not part of this European Standard. Nevertheless, for materials for which traditional and major uses are affected, these restrictions are indicated. The absence of an indication, however, does not imply that the material can be used in any application without any legal restriction.

1 Scope

This European Standard specifies the composition, the property requirements and tolerances on dimensions and form for copper and copper alloy die and hand forgings.

The sampling procedures, the methods of test for verification of conformity to the requirements of this standard, and the delivery conditions are also specified.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 1173, *Copper and copper alloys — Material condition designation*

EN 1655, *Copper and copper alloys — Declarations of conformity*

EN 1976, *Copper and copper alloys — Cast unwrought copper products*

EN 10204:2004, *Metallic products — Types of inspection documents*

EN 14977, *Copper and copper alloys — Detection of tensile stress — 5 % ammonia test*

EN ISO 6506-1, *Metallic materials — Brinell hardness test — Part 1: Test method (ISO 6506-1)*

EN ISO 6509, *Corrosion of metals and alloys — Determination of dezincification resistance of brass (ISO 6509)*

<https://standards.iteh.ai/catalog/standards/sist/0553ba5f-1162-4d10-afe9-bf10dbe07b2b/sist-en-12420-2014>

ISO 2768-1, *General tolerances — Part 1: Tolerances for linear and angular dimensions without individual tolerance indications*

ISO 6957, *Copper alloys — Ammonia test for stress corrosion resistance*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

forging

wrought product, hot formed by hammering or pressing

3.1.1

die forging

forging produced between closed dies

3.1.2

hand forging

forging produced between open dies

3.1.3

cored forging

forging produced between closed dies including cores

EN 12420:2014 (E)

3.2 deviation from concentricity
half of the difference between the maximum and the minimum wall thickness (s_{\max} and s_{\min}), measured in the same plane perpendicular to the axis of the forging

Note 1 to entry: Deviation from concentricity (mm) = $(s_{\max} - s_{\min})/2$.

3.3 inspection lot
definite quantity of products of the same cross-sectional dimensions, the same material and material condition, collected together for inspection (testing)

4 Designations**4.1 Material****4.1.1 General**

The material is designated either by symbol or number (see Tables 1 to 8).

4.1.2 Symbol

The material symbol designation is based on the designation system given in ISO 1190-1.

NOTE Although material symbol designations used in this standard might be the same as those in other standards using the designation system given in ISO 1190-1, the detailed composition requirements are not necessarily the same.

4.1.3 Number

[SIST EN 12420:2014
https://standards.iteh.ai/catalog/standards/sist/0553ba5f-1162-4d10-afe9-bf10dbe07b2b/sist-en-12420-2014](https://standards.iteh.ai/catalog/standards/sist/0553ba5f-1162-4d10-afe9-bf10dbe07b2b/sist-en-12420-2014)

The material number designation is in accordance with the system given in EN 1412.

4.2 Material condition

For the purposes of this standard, the following designations, which are in accordance with the system given in EN 1173, apply for the material condition:

- | | |
|------------|--|
| M | Material condition for the product as manufactured without specified mechanical properties; |
| H... | Material condition designated by the minimum value of hardness requirement for the product with mandatory hardness requirements; |
| S (suffix) | Material condition for a product which is stress relieved. |

Products in the M or H... condition may be specially processed (i.e. mechanically or thermally stress relieved) in order to lower the residual stress level to improve the resistance to stress corrosion and the dimensional stability on machining [see Clause 5, list entry g) and list entry h)].

Except when the suffix S is used, material condition is designated by only one of the above designations.

4.3 Product

The product designation provides a standardized pattern of designation from which a rapid and unequivocal description of a product is conveyed in communication. It provides mutual comprehension at the international level with regard to products which meet the requirements of the relevant European Standard.

The product designation is no substitute for the full content of the standard.

The product designation for products to this standard shall consist of:


- denomination (Forging);
- number of this European Standard (EN 12420);
- material designation, either symbol or number (see Tables 1 to 8);
- for the use in contact with drinking water: DW for compliance in the chemical composition according to 4 MS Common Composition List;
- material condition designation (see Tables 9 and 10).

The derivation of a product designation is shown in the following examples.

EXAMPLE 1 Forging conforming to this standard, in material designated either CuZn40Pb2 or CW617N, for standard applications, in material condition H070, will be designated as follows:



EXAMPLE 2 Forging conforming to this standard, in material designed either CuZn40Pb2 or CW617N, for the use in contact with drinking water DW, in material condition H070, will be designated as follows:

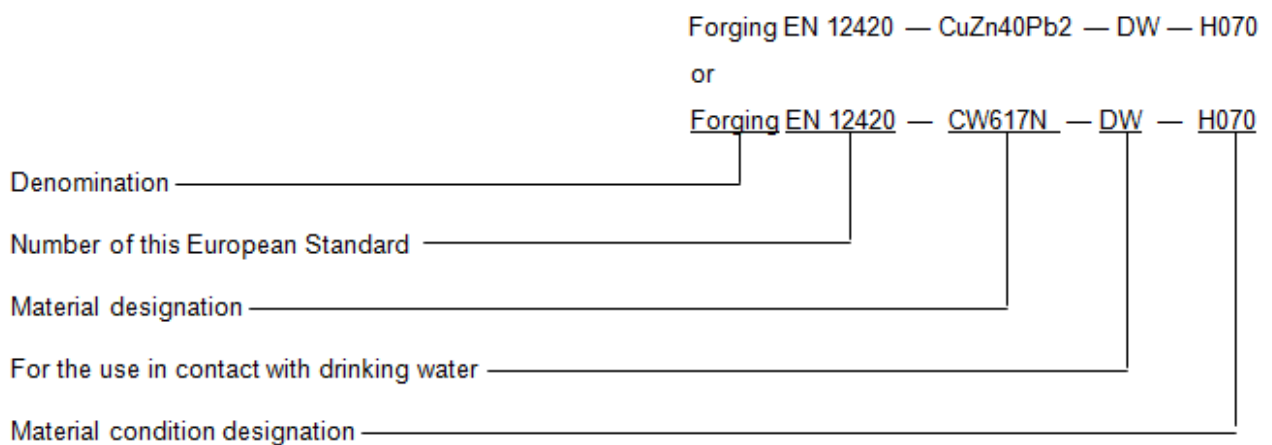

EN 12420:2014 (E)**5 Ordering information**

In order to facilitate the enquiry, order and confirmation of order procedures between the purchaser and the supplier, the purchaser shall state on his enquiry and order the following information:

- a) quantity of product required (mass or number of pieces);
- b) denomination (Forging);
- c) number of this European Standard (EN 12420);
- d) material designation (see Tables 1 to 8);
- e) material condition designation (see 4.2 and Tables 9 and 10) if it is other than M;
- f) for the use in contact with drinking water: DW for compliance in the chemical composition according to 4 MS Common Composition List;
- g) nominal dimensions and/or tolerance drawing of the forging or finished part including the number of the drawing (see 6.6):

It is recommended that the product designation, as described in 4.3, is used for items b) to e).

In addition, the purchaser shall also state on the enquiry and order any of the following, if required:

- h) whether the products are required to pass a stress corrosion resistance test. If so, which test method is to be used (see 8.5) if the choice is not to be left to the discretion of the supplier. If the purchaser chooses ISO 6957, the pH value for the test solution is to be selected;
- i) whether the products are to be supplied in a thermally stress relieved condition;
- j) when requested, tensile properties have to be agreed between purchaser and supplier (see 6.2.2 and Tables B.1 to B.3);
- k) whether a declaration of conformity is required (see 9.1);
- l) whether an inspection document is required, and if so, which type (see 9.2);
- m) whether there are any special requirements for marking, labelling or packaging (see Clause 10).

EXAMPLE Ordering details for 200 forgings conforming to EN 12420, in material designated either CuZn40Pb2 or CW617N, for the use in contact with drinking water DW, in material condition H070, according to drawing number XY000:

200 pieces Forging EN 12420 — CuZn40Pb2 — DW — H070 — drawing number XY000

or

200 pieces Forging EN 12420 — CW617N — DW — H070 — drawing number XY000

6 Requirements**6.1 Composition**

The composition shall conform to the requirements for the appropriate material given in Tables 1 to 8. In the same tables the hot working attitude is also reported.

Due to developing legislation, specific applications (see 4.3) may require restrictions in the chemical composition. In this case the limitations shall be stated in the ordering information [see Clause 5 list entry f)].

NOTE As the materials specified in this standard vary considerably e.g. in their resistance to forming, forging temperature and pressure, die wear and stresses, they have been classified into three groups of similar hot working attitudes (I, II or III in descending order of hot working attitude).

A direct proportionality exists between the group and preheating temperature.

6.2 Mechanical properties

6.2.1 Hardness properties

The hardness properties shall conform to the appropriate requirements given in Tables 9 and 10. For the alloys not mentioned in these tables the hardness values shall be agreed between purchaser and supplier.

6.2.2 Tensile properties

This standard does not specify mandatory tensile properties. The values for the tensile properties given in Tables B.1 to B.3 are for information only.

6.3 Electrical properties

Forgings materials listed in Table 11 shall conform to the electrical properties specified in the same table.

6.4 Resistance to dezincification (standards.iteh.ai)

The maximum depth of dezincification, in any direction, of CuZn38As (CW511L), CuZn36Pb2As (CW602N), CuZn35Pb1,5AlAs (CW625N), CuZn33Pb1,5AlAs (CW626N), CuZn32Pb2AsFeSi (CW709R), CuZn21Si3P (CW724R) and CuZn33Pb1AlSiAs (CW725R) products shall be 150 μm .

The amount of β phase for CuZn38As (CW511L), CuZn36Pb2As (CW602N), CuZn35Pb1,5AlAs (CW625N), CuZn33Pb1,5AlAs (CW626N), CuZn32Pb2AsFeSi (CW709R) and CuZn33Pb1AlSiAs (CW725R) shall be less than 3 %.

The test shall be carried out in accordance with 8.4.

NOTE The supplied material for forgings may not necessarily meet this requirement unless suitably heat treated. The test is intended to demonstrate that forgings produced are capable of being processed so as to pass the test requirement.

Products in alloys other than CuZn21Si3P (CW724R) shall be subjected to heat treatment approximately in the range 500 °C to 550 °C after hot stamping. Should the user need to heat the material above 530 °C (i.e. soldering, brazing or welding operations) then advice should be sought from the supplier.

6.5 Residual stress level

Forgings ordered in the stress relieved condition (see 4.2, 2nd paragraph) shall show no evidence of cracking when tested. The tests shall be carried out in accordance with 8.5.

6.6 Tolerances for die forgings

6.6.1 General

Tolerances on dimensions and on form indicated in the drawings of a forging shall conform to the tolerances specified in this standard. If no tolerances are indicated in the drawings, the tolerances according to

EN 12420:2014 (E)

ISO 2768-1, Tolerance Class c, shall apply. When more than one general tolerance is applicable, the larger of the possible general tolerances shall be used.

It is recommended that reference to this standard is made on the drawings.


Two different types of dimensions are distinguished for die forgings:

- a) dimensions within the die cavity which originate from the forging shape in one separate die part and which does not have components moving towards one another, see dimensions n in Figure 1.

These die parts may consist of one single piece or of several components immovable towards one another.

- b) dimensions across the die parting line which originate from two or more die parts moving towards one another, see dimensions t in Figure 2.

The die forging produced in the dies demonstrated in Figure 1 and Figure 2 is shown in Figure 3.

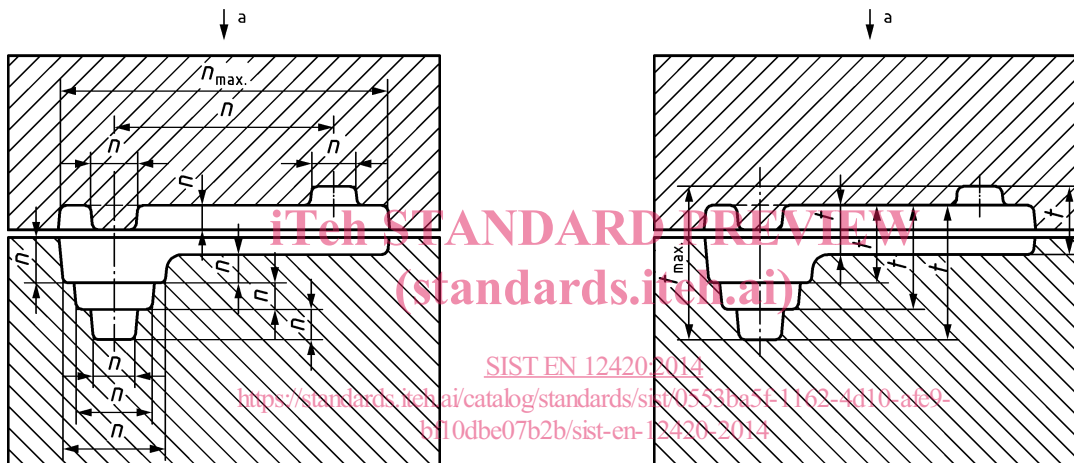

Key

a direction of forging

a direction of forging

Figure 1 — Dimensions n within the die cavity

Figure 2 — Dimensions t across the die parting line

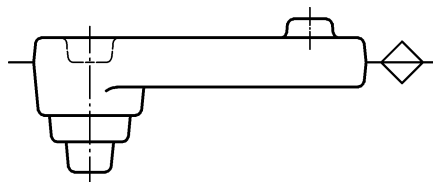


Figure 3 — Die forging

For recommended machining allowances and total allowances see A.3.10 and Table A.6.

6.6.2 Tolerances for dimensions within the die cavity and for dimensions across the die parting line

The dimensions n and t shall conform to the tolerances given in Table 12 for material group I, Table 13 for material group II and Table 14 for material group III.

The polygonal shapes shall conform to the tolerances given in Table 15 for material group I.

The largest dimension t_{\max} in the direction of forging is the basic dimension for applying tolerances for dimensions t across the die parting line. The tolerance for t_{\max} depends on the area A of the part viewed in the direction of blow. The area A in the case of round parts is equal to the area of the circle and in the case of irregularly shaped parts is equal to the area of the circumscribing rectangle (see Figure 4). All smaller dimensions t have the same tolerance as t_{\max} .

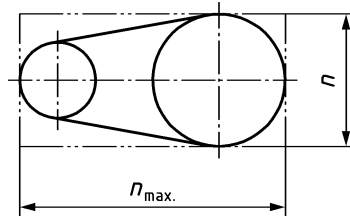


Figure 4 — Area A (in mm^2) = $n_{\max} \times n$

The tolerances given in Tables 12 to 14 are also applicable for die forgings which are produced with a die cavity in one die half only facing a plane opposite die half.

The tolerance need not necessarily be applied symmetrically about the nominal dimension; it may be all plus or all minus.

6.6.3 Mismatch

Mismatch is not associated with a particular direction (see Figure 5).

The mismatch shall be determined by reference to the largest nominal dimension n_{\max} as viewed in the direction of forging (see Figure 5).

The permissible mismatch is given in Tables 12 to 14.

The maximum permitted mismatch shall be indicated above the title block or in the title block of the drawing of the forging, e.g.: mismatch max. 0,5 mm.

Mismatch is not included in the tolerances for dimensions within the die cavity: the tolerances for dimensions within the die cavity and for mismatch are in this case independently applied (see Figure 6 and Figure 7).