
**Road vehicles — Multicore connecting
cables —**

Part 1:

Test methods and requirements for basic
performance sheathed cables

iTeh STANDARD PREVIEW
(standards.iteh.ai)

Véhicules routiers — Câbles de raccordement multiconducteurs —

*Partie 1: Méthodes d'essai et exigences pour les câbles gainés
à performance de base*

[ISO 4141-1:1998](https://standards.iteh.ai/catalog/standards/sist/66335618-7401-4852-8fb9-657bf5735432/iso-4141-1-1998)

<https://standards.iteh.ai/catalog/standards/sist/66335618-7401-4852-8fb9-657bf5735432/iso-4141-1-1998>



Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 4141-1 was prepared by Technical Committee ISO/TC 22, *Road vehicles*, Subcommittee SC 3, *Electrical and electronic equipment*.

Together with ISO 4141-2 and ISO 4141-3, this first edition of ISO 4141-1 cancels and replaces ISO 4141:1988, which has been technically revised.

ISO 4141 consists of the following parts, under the general title *Road vehicles – Multicore connecting cables*:

- *Part 1: Test methods and requirements for basic performance sheathed cables*
- *Part 2: Test methods and requirements for high performance sheathed cables*
- *Part 3: Construction, dimensions and marking of unscreened sheathed low-voltage cables*
- *Part 4: Test methods and requirements for coiled cable assemblies*

Annex A forms an integral part of this part of ISO 4141. Annex B is for information only.

© ISO 1998

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization
Case postale 56 • CH-1211 Genève 20 • Switzerland
Internet central@iso.ch
X.400 c=ch; a=400net; p=iso; o=isocs; s=central

Printed in Switzerland

Road vehicles — Multicore connecting cables —

Part 1:

Test methods and requirements for basic performance sheathed cables

1 Scope

This part of ISO 4141 specifies the test methods and requirements for basic performance multicore sheathed cables for the connection of towing and towed vehicles, suitable for a temperature range of – 40 °C to + 85 °C.

2 Normative references

The following standards contain provisions which, through reference in this text, constitute provisions of this part of ISO 4141. At the time of publication, the editions indicated were valid. All Standards are subject to revision, and parties to agreements based on this part of ISO 4141 are encouraged to investigate the possibility of applying the most recent editions of the standards indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 1431-1:1989, *Rubber, vulcanized or thermoplastic — Resistance to ozone cracking — Part 1: Static strain test.*

ISO 1817:–¹⁾, *Rubber, vulcanized — Determination of the effect of liquids.*

[https://standards.iteh.ai/catalog/standards/sist/66335618-7401-4852-8fb9-](https://standards.iteh.ai/catalog/standards/sist/66335618-7401-4852-8fb9-657b5725432/iso-4141-1-1998)

ISO 4141-3:1998, *Road vehicles — Multicore connecting cables — Part 3: Construction, dimensions and marking of unscreened sheathed low-voltage cables.*

ISO 4892-1:1994, *Plastics — Methods of exposure to laboratory light sources — Part 1: General guidance.*

ISO 4892-2:1994, *Plastics — Methods of exposure to laboratory light sources — Part 2: Xenon-arc sources.*

ISO 6722-1:1996, *Road vehicles — Unscreened low-tension cables — Part 1: Test methods.*

ISO 6722-2:1996, *Road vehicles — Unscreened low-tension cables — Part 2: Requirements.*

IEC 811-1-1:1993, *Insulating and sheathing of electrical cables, common test methods — Part 1: Methods for general application — Section 1: Measurement of thickness and overall dimensions — Tests for determining the mechanical properties.*

IEC 811-2-1:1993, *Insulating and sheathing of electrical cables, common test methods — Part 2: Methods specific to elastomeric compounds. Section 1: Ozone resistance test, hot set test, mineral oil immersion test.*

3 Test temperature

All tests unless otherwise stated shall be performed at (23 ± 5) °C.

1) To be published. (Revision of ISO 1817:1985)

4 Tests and requirements

4.1 Single cores

The single cores of multicore sheathed cables shall comply with ISO 6722-2 and shall meet the requirements in 4.2 and 4.3. Single core identification shall conform to ISO 4141-3.

4.2 Continuity and withstand voltage

4.2.1 Test

Check the continuity of each single core and perform a withstand voltage test on a cable as delivered and on the test samples after the tests specified in 4.13, 4.14, 4.15, 4.18 and 4.20. For the withstand voltage test, apply a test voltage of 3 kV r.m.s. at a frequency of 50 Hz or 60 Hz for 1 min, between each conductor and the remaining conductors connected together.

4.2.2 Requirement

Breakdown shall not occur.

4.3 Capacitance test

4.3.1 Test

Lay up cores for data transmission separately from the remaining cores, and subject them to the three different capacitance measurements (measurements A, B and C in figure 1), as follows, using a standard capacitance measuring device with alternating current and a frequency of 1 kHz:

- C_a : capacitance between the conductor of core a²⁾ and ground³⁾ (result of measurement A);
- C_b : capacitance between the conductor of core b²⁾ and ground³⁾ (result of measurement B);
- C_{ab} : capacitance between the conductor of core a²⁾ and core b²⁾:

the result of measurement C is a capacitance C_c , which is equal to $C_a + \frac{C_{ab} \times C_b}{C_{ab} + C_b}$.

From this value, the capacity C_{ab} can be calculated as follows:

$$C_{ab} = \frac{C_b (C_c - C_a)}{C_b + C_a - C_c}.$$

4.3.2 Requirements

Cores for data transmission shall have a capacitance of 50 pF/m maximum between the data cores and a capacitance of 100 pF/m maximum between each data core and ground.

NOTE — These values are based on the worst case assumption of a cable length of 40 m. If this value is exceeded and/or when installation may increase the capacitance, this is to be taken into consideration.

4.4 Lay length

4.4.1 Test



Fasten the test sample at its ends. Measure the length of five lays.

4.4.2 Requirement

The length measured shall not exceed 250 mm.

2) Cores a and b are cores for data transmission of the connecting cable, i.e. cores 6 and 7 of the "EBS" cable, and cores 14 and 15 of the "24-15" cable: see ISO 7638-1 and ISO 7638-2, and ISO 12098, respectively.

3) "Ground" is described as all other cores of the cable connected in parallel.

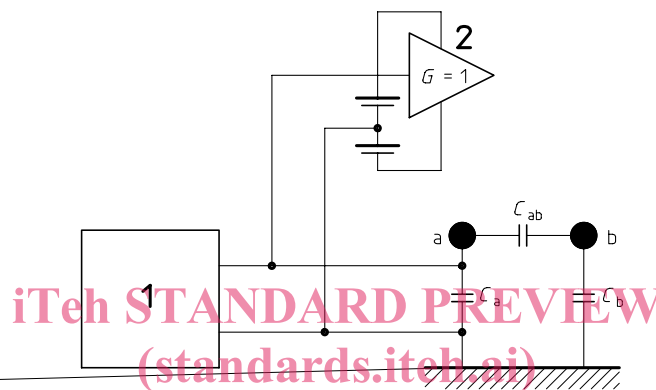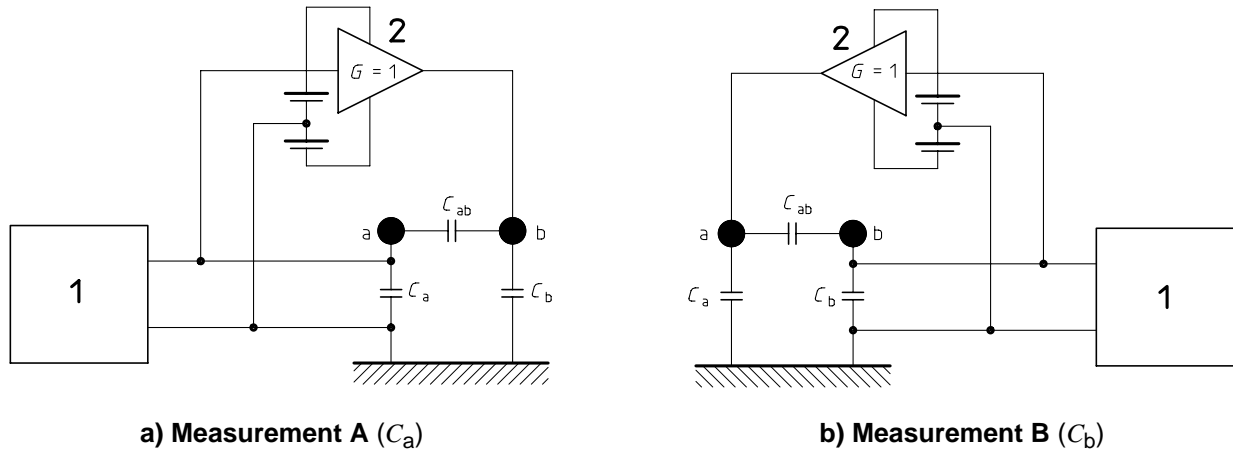

ISO 4141-1:1998
<https://standards.iteh.ai/catalog/standards/sist/66335618-7401-4852-8fb9-657bf5735432/iso-4141-1-1998>

eliminated. $C_{ab} + C_b$ (measurement A), and $C_{ab} + C_a$ (measurement B) is

Figure 1 — Capacitance measurement methods

4.5 Outside diameter and ovality of the multi-core cable (for round cables)

4.5.1 Test

Determine the maximum and minimum cable outside diameters by taking three sets of measurements at places at least 200 mm apart.

Calculate the ovality, in percent, for each set of measurements by the following equation:

$$\frac{d_{\max} - d_{\min}}{0,5 (d_{\max} + d_{\min})} \times 100 \%$$

where d_{\max} and d_{\min} are the maximum and minimum cable outside diameters respectively.

4.5.2 Requirement

Each diameter measured and ovality calculated shall be within the dimensional limits specified in ISO 4141-3.

4.6 Thickness of the sheath

4.6.1 Test

Strip three test samples from the cable to be tested from places at least 1 m apart. A test sample consists of a thin slice of the complete sheath, cut with a suitable device (sharp knife, razor-blade, etc.) perpendicular to the core axis. If core marking causes indentation of the sheath, the first test sample shall be taken through this indentation.

Measure the complete sheath thickness at its thinnest portion perpendicular to the cable axis.

4.6.2 Requirement

Each value measured shall not be less than the minimum wall thickness as specified in ISO 4141-3.

4.7 Visual appearance

On visual examination, the sheath shall be smooth, even and free from surface imperfections such as lumps, voids, particles, or other contamination.

4.8 Durability of the sheath marking

4.8.1 Test

NOTE — The following test only applies if marking is required.

Prepare three test samples of at least 300 mm length and apply the test fluids listed below:

- sample 1: test fuel C in accordance with ISO 1817;^{552, 4141-1:1998}
- sample 2: oil No. 1 in accordance with ISO 1817;^{<https://standards.iteh.ai/catalog/standards/sist/66335618-7401-4852-8fb9-05763735432/iso-4141-1-1998>}
- sample 3: DOT 4 braking fluid⁴⁾.

After 15 s, place the sample in a hot air-oven with natural draught at (50 ± 2) °C for 48 h. Then pull each sample twice between two pieces of felt (approximate dimensions 50 mm x 50 mm) without dressing, having a minimum wool content of 75%, and with a packing density of 0,171 g/cm³ to 0,191 g/cm³. Carry out this operation so that the sheath marking is wiped at a speed of approximately 100 mm/s over a length of 200 mm. Apply a force of (10 ± 1) N while pulling the test samples through the felt. Replace the felt after 10 test applications.

4.8.2 Requirement

The marking shall remain legible.

4.9 Resistance of the sheath to fluids

4.9.1 Test

Verify the material specifications by checking the guaranteed material features of the material manufacturer, in particular in relation to the following:

- resistance to base (5% KOH, 25% K₂CO₃, 70% H₂O);
- resistance to liquid B specified in ISO 1817;

4) Test fluid in preparation for inclusion in an Amendment to ISO 1817.

- resistance to lubricating oil No. 1 specified in ISO 1817;
- resistance to liquid F specified in ISO 1817;
- resistance to lubricating grease specified in ISO 1817.

4.9.2 Requirement

The sheath material shall be resistant to the products specified in 4.9.1.

4.10 Stripping of the sheath

It shall be possible to remove at least 100 mm of the sheath, cleanly and without difficulty, by a method agreed on by the manufacturer and user, without causing damage to the inner cores.

4.11 Shrinkage by heat of the sheath

4.11.1 Test

Perform the test specified in ISO 6722-1, but with a sample length of 200 mm. Condition the sheath for 15 min at (150 ± 2) °C.

4.11.2 Requirement

The sheath of the sample shall not shrink by more than 4% in length.

4.12 Pressure at high temperature

4.12.1 Test

Take two samples of 100 mm length each from two places at least 1 m apart.

Cut a strip from each of the samples. If the sheath shows ridges caused by the individual cores, cut the strip in the direction of the ridges so that it contains at least one groove throughout its length.

Support the strips by a metal pin. If the sheath shows ridges, the pin diameter shall be approximately equal to the core diameter; if the sheath shows no ridges, the pin diameter shall be approximately equal to the inner diameter of the sheath.

Place the strips and the metal support pins with the apparatus shown in figure 2 in a heating cabinet at a temperature of (85 ± 2) °C for 16 h. Then arrange them as shown in figure 2 so that the pin supports the sheath, the pin lying in the groove, if any, of the sample, and with the blade pressing against the outer surface of the sheath with the following force F , in newtons:

$$F = 0,8\sqrt{(2De - e^2)}$$

where

- D is the maximum specified outside diameter, in millimetres;
- e is the minimum specified sheath thickness, in millimetres.


NOTE — The coefficient 0,8 is expressed in newtons per millimetre.

Apply the force in a direction perpendicular to the axis of the pin with the blade also perpendicular to the axis of the pin.

Maintain the apparatus, with the samples in position, in this condition in the heating cabinet for 4 h. Remove the samples from the apparatus and cool them, within 10 s, by immersion in cold water.

Measure the thickness of the sheath immediately, at the point of impression and at points about 10 mm to either side of the impression, by means of a measuring microscope.

Dimensions in millimetres

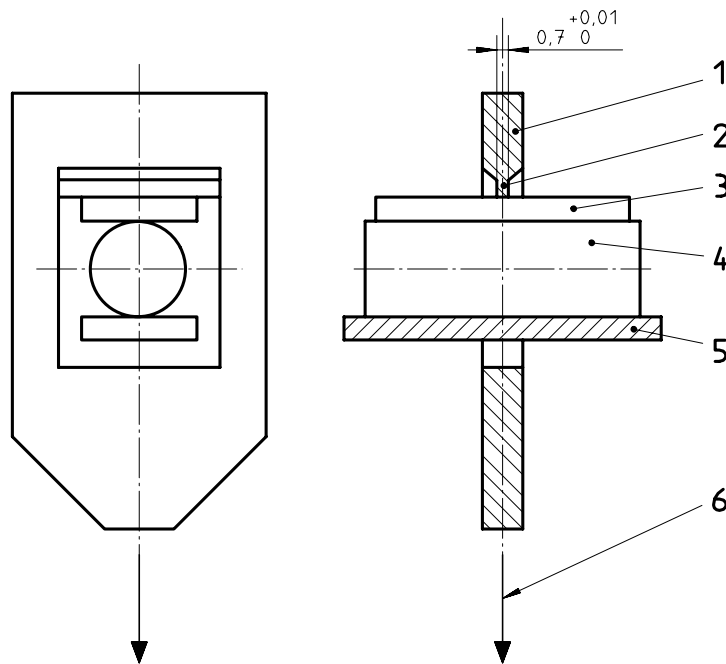

Key

- 1 Test frame
- 2 Blade
- 3 Test strip
- 4 Pin
- 5 Support
- 6 Force

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 4141-1:1998
Figure 2 — Test apparatus for pressure at high temperature
<https://standards.iteh.ai/catalog/standards/sist/66555017-7401-4892-8109-657bf5735432/iso-4141-1-1998>

4.12.2 Requirements

The thickness within the area of the impression shall not be less than 40% of the mean of the thicknesses at the other two measuring points.

The sheath shall not rupture.

4.13 Impact at low temperature

4.14 Bending at low temperature

4.14.1 Test

Take two test samples of 300 mm length from the cable to be tested from places at least 1 m apart and condition them together with a metallic mandrel of 80 mm diameter in a freezing chamber at $(- 40 \pm 2) \text{ }^\circ\text{C}$ for 4 h.

After conditioning, bend the samples 180° around the mandrel. The bending shall take place within 5 s in the freezing chamber.

Then allow the test samples to regain a room temperature of $(23 \pm 5) \text{ }^\circ\text{C}$ and examine them visually.

4.14.2 Requirement

The test samples shall show no signs of fracture or cracking to the sheath.

If the test samples meet this requirement, perform the test specified in 4.2.

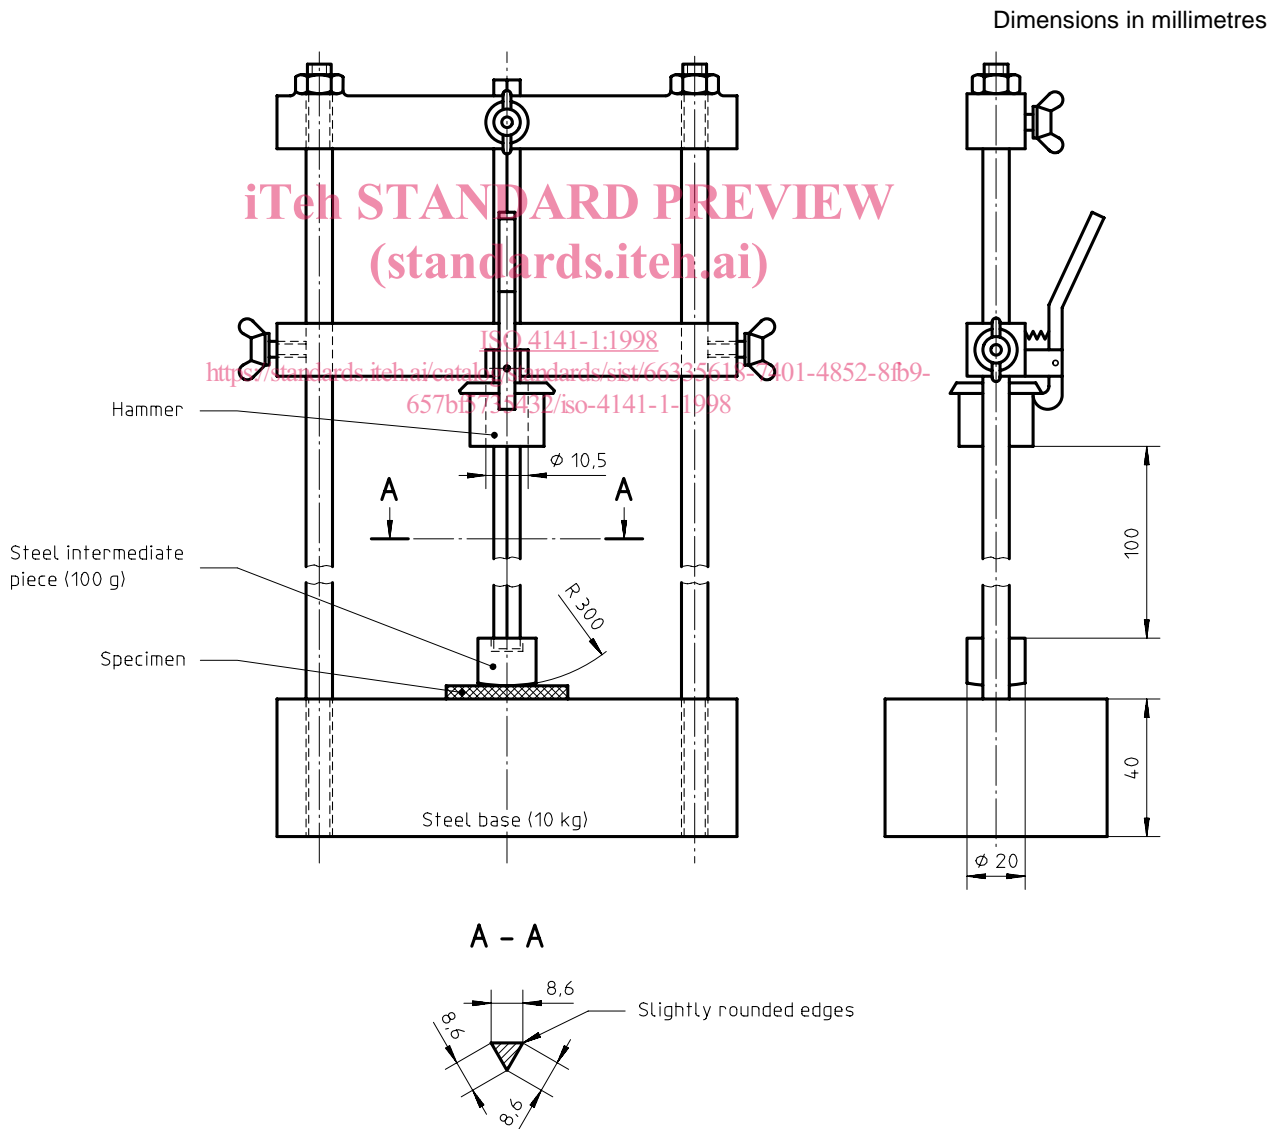


Figure 3 — Test apparatus for impact at low temperature