
**Textile floor coverings — Determination of
resistance to damage at cut edges using the
modified Vettermann drum test**

*Revêtements de sol textiles — Détermination de la résistance des joints par
l'essai au tambour Vettermann modifié*

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 10833:2001](https://standards.iteh.ai/catalog/standards/sist/1e081b31-1ec6-4a79-922c-284062480126/iso-10833-2001)

[https://standards.iteh.ai/catalog/standards/sist/1e081b31-1ec6-4a79-922c-
284062480126/iso-10833-2001](https://standards.iteh.ai/catalog/standards/sist/1e081b31-1ec6-4a79-922c-284062480126/iso-10833-2001)



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 10833:2001

<https://standards.iteh.ai/catalog/standards/sist/1e081b31-1ec6-4a79-922c-284062480126/iso-10833-2001>

© ISO 2001

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.ch
Web www.iso.ch

Printed in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 3.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this International Standard may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

International Standard ISO 10833 was prepared by Technical Committee ISO/TC 219, *Floor coverings*.

This second edition cancels and replaces the first edition (ISO 10833:1992), which has been technically revised.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO 10833:2001](https://standards.iteh.ai/catalog/standards/sist/1e081b31-1ec6-4a79-922c-284062480126/iso-10833-2001)

<https://standards.iteh.ai/catalog/standards/sist/1e081b31-1ec6-4a79-922c-284062480126/iso-10833-2001>

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 10833:2001

<https://standards.iteh.ai/catalog/standards/sist/1e081b31-1ec6-4a79-922c-284062480126/iso-10833-2001>

Textile floor coverings — Determination of resistance to damage at cut edges using the modified Vettermann drum test

1 Scope

This International Standard describes a method to determine the susceptibility of textile floor coverings to mechanical damage at cut edges.

It is applicable to all textile floor coverings both as sheet materials and as tiles.

2 Normative references

The following normative documents contain provisions which, through reference in this text, constitute provisions of this International Standard. For dated references, subsequent amendments to, or revisions of, any of these publications do not apply. However, parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent editions of the normative documents indicated below. For undated references, the latest edition of the normative document referred to applies. Members of ISO and IEC maintain registers of currently valid International Standards.

ISO 139, *Textiles — Standard atmospheres for conditioning and testing*

ISO 1957, *Machine-made textile floor coverings — Selection and cutting of specimens for physical tests*

ISO 2424, *Textile floor coverings — Vocabulary*

ISO 9405, *Textile floor coverings — Assessment of changes in appearance*

ISO 10361:2000, *Textile floor coverings — Production of changes in appearance by means of Vettermann drum and hexapod tumbler testers*

3 Terms and definitions

For the purposes of this International Standard, the terms and definitions in ISO 2424 as well as the following apply.

3.1 delamination

separation of the use-surface and/or foundation/primary substrate of a textile floor covering from the secondary substrate

3.2 fraying

loss of pile or substrate material of a textile floor covering from a cut edge

3.3 tufting out

loss of tufts from the use-surface of a textile floor covering

3.4 sprouting

release and appearance during use of extra long tuft legs which were accidentally trapped within the pile of a textile floor covering during manufacture

3.5

laddering/shooting

loss of consecutive loops of the same column from the use-surface of a textile floor covering

4 Principle

A steel ball with six rubber studs rolls freely inside a rotating drum which is lined with the textile floor covering specimens.

On sheet materials a cut is made along the length of the specimens at an acute angle such that the cut edges are stressed in the test.

Tiles are put together so that the original edges of the tiles form the joint which is stressed in the test.

After the test the appearance of the fatigued cut edges is assessed in accordance with ISO 9405.

5 Apparatus

5.1 Drum tester, conforming to 5.1.1 of ISO 10361:2000, including a vacuum cleaner with an air change rate at the nozzle of 25 l/s to 40 l/s. See Figure 1.

5.2 Steel ball, fitted with six cylindrical rubber studs these being fitted so as to be equally spaced from each other on the surface of the ball. The mass of the ball without rubber studs shall be $(7\,000 \pm 100)$ g. The diameter of the ball shall be $(120 \pm 0,2)$ mm. See Figure 2.

A standard 14 stud ball with eight studs removed is not acceptable because of the wear it causes to the drum segments.


5.3 Rubber studs, conforming to ISO 10361 that are replaced before each test.

5.4 External vacuum cleaner, upright type with rotating brush and beater bar.

5.5 Single-sided adhesive tape, of width ≥ 50 mm.

5.6 Double-sided adhesive tape, of width ≥ 50 mm.

Dimensions in millimetres

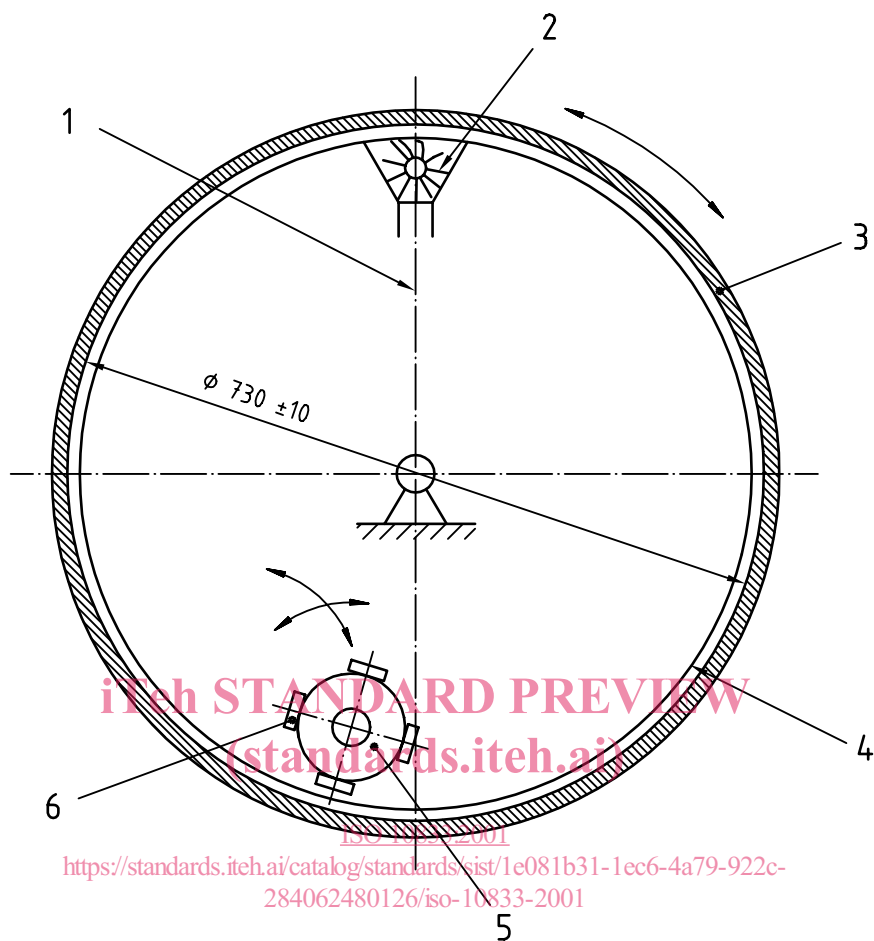**Key**

- 1 Vacuum extraction of brushed fibres
- 2 Circular brush
- 3 Metal drum
- 4 Vulcanized fibre backing sheet
- 5 Steel ball
- 6 Rubber stud

Figure 1 — Vettermann drum

Dimensions in millimetres
Surface roughness in micrometres

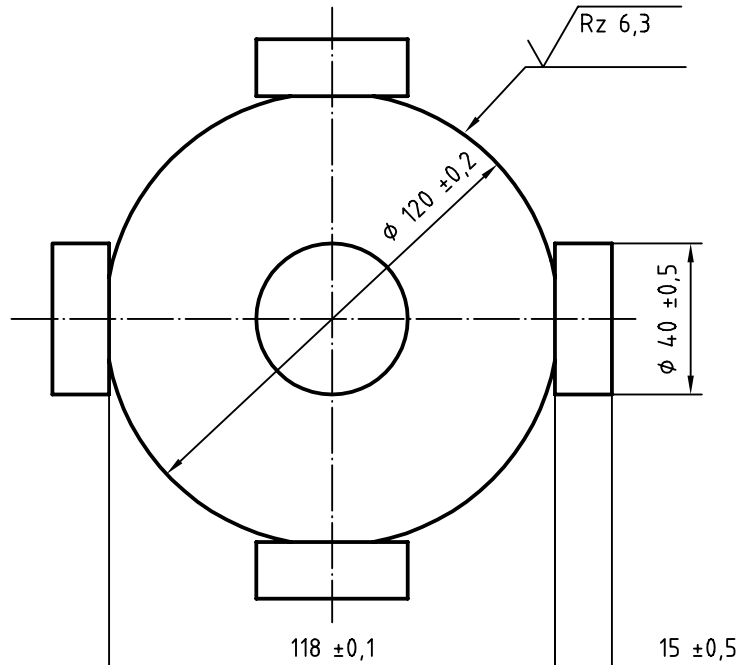


Figure 2 — Steel ball
(standards.iteh.ai)

6 Sampling and preparation of specimens ISO 10833:2001

<https://standards.iteh.ai/catalog/standards/sist/1e081b31-1ec6-4a79-922c-284062480126/iso-10833-2001>

6.1 Sampling

6.1.1 General

Sampling shall be carried out in accordance with ISO 1957.

6.1.2 Sheet materials

Take four test specimens approximately 570 mm long (in the direction of manufacture) and approximately 265 mm wide. The longitudinal edge of the specimens shall be parallel to the direction of manufacture.

6.1.3 Tiles

Take at least four tiles of dimensions 500 mm × 500 mm or of lesser dimensions, but not smaller than 265 mm × 265 mm.

Before cutting mark the corners of the tiles and the direction of manufacture on the back of the specimen as shown in Figure 3.

From the tiles cut a total of eight specimens of width approximately 132 mm, four of them in the direction of manufacture and four in the transverse direction (crosswise), as shown in Figure 3.

Ensure that the drum is filled to capacity using fillers of similar height and construction.

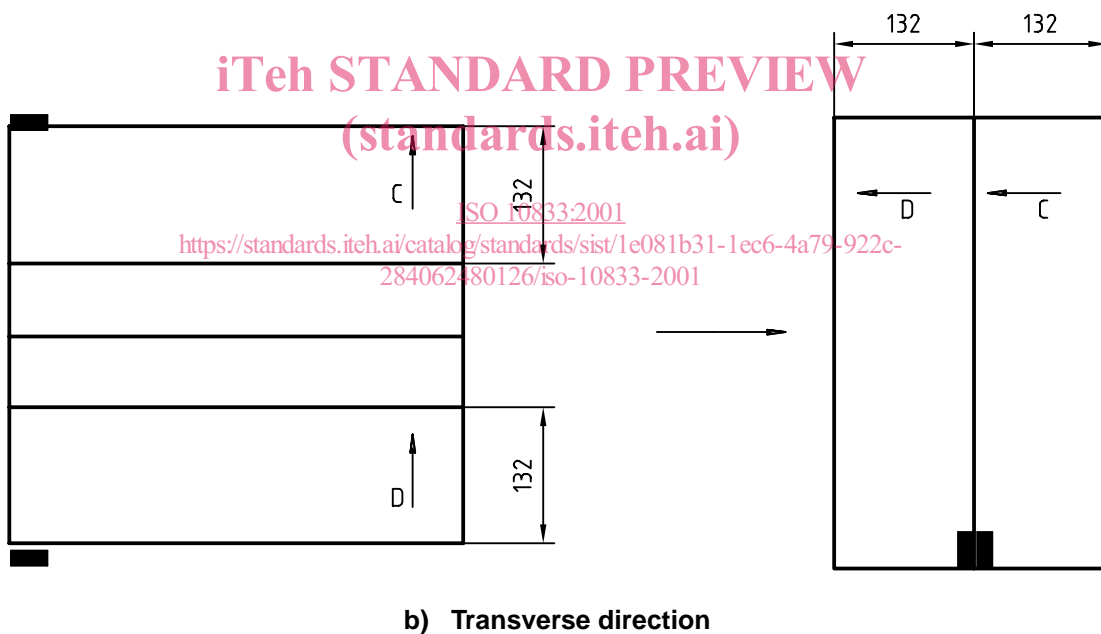
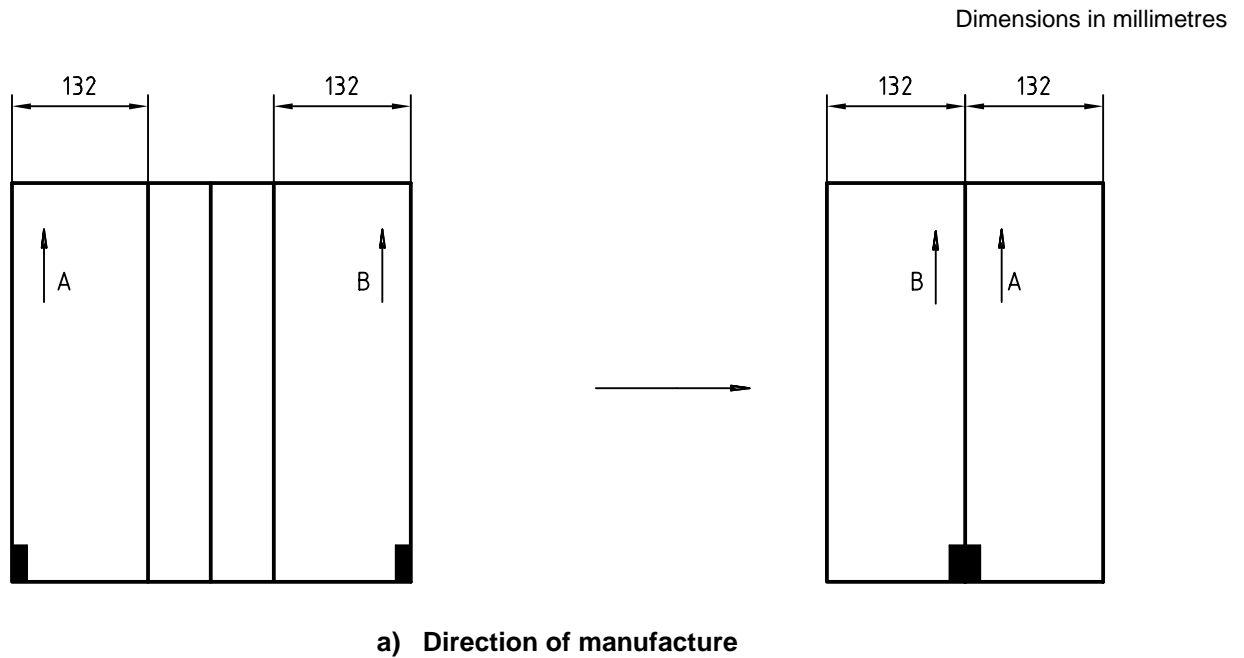


Figure 3 — Specimen preparation by cutting of tiles

6.2 Preparation of specimens

6.2.1 Sheet materials

Make a cut in the centre of the test specimens making an acute angle with the direction of manufacture (see Figure 4). The cut shall cross at least one pile row. The cut shall be made with a sharp cutting tool (carpet knife or a press cutter) cutting from the pile side through pile and backing.

Connect the two sides of the cut test specimens on the back with single-sided adhesive tape (5.5). Apply the adhesive tape firmly. Ensure that the two edges are as close as possible.