



SLOVENSKI STANDARD

SIST EN 15720:2010

01-marec-2010

Sanitarne naprave - Kadi za prhanje, izdelane iz udarno modificiranih koekstrudiranih ABS/akrilnih plošč - Zahteve in preskusne metode

Sanitary appliances - Shower trays made from impact modified coextruded ABS/acrylic sheets - Requirements and test methods

Sanitärausstattungsgegenstände - Duschwannen, hergestellt aus schlagzäh-modifizierten coextrudierten ABS/Acrylplatten - Anforderungen und Prüfverfahren

Appareils sanitaires - Receveurs de douche en feuilles d'ABS/acrylique coextrudées modifiées choc - Exigences et méthodes d'essai

<https://standards.iteh.ai/catalog/standards/sist/57da671b-5667-4a92-869f-fac34530c77f/sist-en-15720-2010>

Ta slovenski standard je istoveten z: **EN 15720:2009**

ICS:

91.140.70 Sanitarne naprave Sanitary installations

SIST EN 15720:2010

en,fr,de

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN 15720:2010

<https://standards.iteh.ai/catalog/standards/sist/57da671b-5667-4a92-869f-fac34530c77f/sist-en-15720-2010>

EUROPEAN STANDARD

EN 15720

NORME EUROPÉENNE

EUROPÄISCHE NORM

December 2009

ICS 91.140.70

English Version

Sanitary appliances - Shower trays made from impact modified coextruded ABS/acrylic sheets - Requirements and test methods

Appareils sanitaires - Receveurs de douche en feuilles
d'ABS/acrylique coextrudées modifiées choc - Exigences et
méthodes d'essai

Sanitärausstattungsgegenstände - Duschwannen,
hergestellt aus schlagzäh-modifizierten coextrudierten
ABS/Acrylplatten - Anforderungen und Prüfverfahren

This European Standard was approved by CEN on 7 November 2009.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

[SIST EN 15720:2010](https://standards.iteh.ai/catalog/standards/sist/57da671b-5667-4a92-869f-fac34530c77f/sist-en-15720-2010)

<https://standards.iteh.ai/catalog/standards/sist/57da671b-5667-4a92-869f-fac34530c77f/sist-en-15720-2010>



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: Avenue Marnix 17, B-1000 Brussels

Contents

Page

Foreword.....	3
1 Scope	4
2 Normative references	4
3 Terms and definitions	4
4 Requirements	4
4.1 General	4
4.2 Material	4
4.3 Surface appearance	4
4.4 Waste outlet hole	4
4.5 Overflow hole	5
4.6 Hole edges	5
4.7 Dimensional deviations	5
4.8 Geometric deviations	5
4.8.1 General	5
4.8.2 Squaring	5
4.8.3 Straightness of the rim sides	5
4.8.4 Straightness of the bottom edge of the rim	5
4.8.5 Flatness of the top surface of rim	5
4.9 Bottom of the shower tray	5
4.10 Resistance to temperature changes	6
4.11 Resistance to impact	6
4.12 Permitted deflections	6
4.13 Shower tray rim	6
5 Marking	6
Annex A (normative) Shower tray test methods	7
A.1 Sequence of tests	7
A.2 Geometric deviations	7
A.2.1 Test apparatus	7
A.2.2 Squaring	7
A.2.3 Straightness of the rim side	8
A.2.4 Straightness of the bottom edge of the rim	9
A.2.5 Flatness of the top surface of the rim	10
A.3 Resistance to temperature change	11
A.3.1 Test apparatus	11
A.3.2 Procedure	11
A.4 Resistance to impact	12
A.4.1 Test apparatus	12
A.4.2 Procedure	12
A.5 Determination of deflections	12
A.5.1 General	12
A.5.2 Test apparatus	13
A.5.3 Preloading	13
A.5.4 Deflection test 1 - Deflection of the rim and the bottom due to a load on the bottom	14
A.5.5 Deflection test 2 - Deflection of the rim due to a load on the rim on the side of entry	15
Bibliography	18

Foreword

This document (EN 15720:2009) has been prepared by Technical Committee CEN/TC 163 “Sanitary appliances”, the secretariat of which is held by UNI.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by June 2010, and conflicting national standards shall be withdrawn at the latest by June 2010.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

Attention is drawn to EN 14527 [1], which has been prepared under the Mandate M/110 “Sanitary Appliances” which was given to CEN by the European Commission and the European Free Trade Association and supports the Essential Requirements to allow CE marking under Construction Products Directive (89/106/EEC).

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and the United Kingdom.

(standards.iteh.ai)

[SIST EN 15720:2010](https://standards.iteh.ai/catalog/standards/sist/57da671b-5667-4a92-869f-fac34530c77f/sist-en-15720-2010)

<https://standards.iteh.ai/catalog/standards/sist/57da671b-5667-4a92-869f-fac34530c77f/sist-en-15720-2010>

EN 15720:2009 (E)**1 Scope**

This European Standard specifies the requirements for shower trays for domestic purposes made from crosslinked cast acrylic sheets conforming to EN 13559 with the aim of ensuring that the product, when installed in accordance with the manufacturer's instructions, will provide satisfactory performance in use.

This European Standard is applicable to all sizes and shapes of shower trays.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 13559, *Specifications for impact modified coextruded ABS/Acrylic sheets for baths and shower trays for domestic purposes*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1 domestic purposes

use in homes, hotels, accommodation for students, hospitals and similar buildings, except when special medical provisions are required

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN 15720:2010](https://standards.iteh.ai/catalog/standards/sist/57da671b-5667-4a92-869f-fac34530c77f/sist-en-15720-2010)

<https://standards.iteh.ai/catalog/standards/sist/57da671b-5667-4a92-869f-fac34530c77f/sist-en-15720-2010>

4 Requirements**4.1 General**

The manufacturer shall provide instructions for installation and care with each shower tray.

The shower tray shall be free from sharp edges that would be exposed after the installation of the shower tray in accordance with the manufacturer's instructions.

4.2 Material

The shower tray shall be manufactured from impact modified coextruded ABS/acrylic sheets complying with EN 13559.

4.3 Surface appearance

When the shower tray is visually inspected under strong and oblique illumination there shall be no evidence of cracks, chips, or other surface defects, such as unexpected changes in colours, etc. that will impair the appearance or performance of the shower tray.

4.4 Waste outlet hole

The shower tray shall have at least one outlet hole. The dimensions of the waste outlet hole and the clearance around the waste outlet hole shall either be in accordance with the requirements of EN 251 or the manufacturer shall supply or recommend a suitable waste outlet fitting.

4.5 Overflow hole

When the shower tray is provided with an overflow hole the dimensions of the overflow hole and the clearance around the overflow hole shall either be in accordance with the requirements of EN 251 or the manufacturer shall supply or recommend a suitable overflow fitting.

4.6 Hole edges

The edges of any holes in the shower tray shall not show evidence of chips, cracks, or any other defects that may impair the appearance or performance of the shower tray.

4.7 Dimensional deviations

The dimensions of shower trays shall not deviate from the size quoted by the manufacturer by greater than ± 5 mm.

If the manufacturer states two sizes (e.g. both a work size and a nominal size) he shall state to which size the permitted deviations apply.

For round shower trays, length and width correspond to the diameter.

4.8 Geometric deviations

4.8.1 General

The straight sides or edges of the shower tray that might abut independent surroundings or supporting structures shall comply with the requirements of 4.8.2 to 4.8.4 and all shower trays shall comply with 4.8.5. These requirements are not applicable to sides or edges that are purposely designed as curves or slopes.

[SIST EN 15720:2010](https://standards.iteh.ai/catalog/standards/sist/57da671b-5667-4a92-869f-fac34530c77f/sist-en-15720-2010)

4.8.2 Squaring

When tested in accordance with A.2.2 the deviation from square, Δq , shall be less than or equal to 5 mm.

4.8.3 Straightness of the rim sides

When tested in accordance with A.2.3 the deviation from straightness of the rim sides, Δs , shall be less than or equal to 5 mm.

4.8.4 Straightness of the bottom edge of the rim

When tested in accordance with A.2.4 the deviation from straightness of the bottom edge of the rim, Δr , shall be less than or equal to 5 mm.

4.8.5 Flatness of the top surface of rim

When tested in accordance with A.2.5 the deviation from flatness of the top surface of the rim, c , shall be less than or equal to 5 mm.

4.9 Bottom of the shower tray

When the shower tray is installed in accordance with the manufacturer's instructions and the waste outlet hole is open, all water shall empty from the shower tray unless prevented by surface tension.

EN 15720:2009 (E)

4.10 Resistance to temperature changes

When tested in accordance with A.3 the shower tray shall show no evidence of distortion or other defects which will impair the appearance or functioning of the shower tray and any deflection shall be less than or equal to 4 mm.

4.11 Resistance to impact

When tested in accordance with A.4 the bottom and the rim of the shower tray shall show no evidence of distortion or other defects that impair the appearance or functioning of the shower tray.

4.12 Permitted deflections

When tested in accordance with A.5 the deflections shall be less than or equal to the values given in Table 1.

Table 1 — Permitted deflections

Test method	Deflection under load ^a mm	Residual deflection ^a mm
A.5.4	2	0,3
A.5.5	4	0,3
^a Values in addition to any deflection of the test rig (see A.5.2).		

4.13 Shower tray rim

SIST EN 15720:2010

<https://standards.iteh.ai/catalog/standards/sist/57da671b-5667-4a92-869f-34530c778sist-en-15720-2010>

When a shower tray is installed in accordance with the manufacturer's instructions, the rim shall not encourage water to drain away from the inside of the shower tray. Roll top rims and rims incorporating special features are not subject to this requirement.

5 Marking

Every shower tray shall be legibly marked on the underside with the following information:

- a) reference to this European Standard (EN 15720);
- b) name or trademark of the manufacturer or supplier.

Annex A (normative)

Shower tray test methods

A.1 Sequence of tests

The tests shall be carried out on one shower tray of each type in sequence A.2, A.3, A.5, A.4.

A.2 Geometric deviations

A.2.1 Test apparatus

- a) length measuring device with an accuracy of 0,5 mm;
- b) reference plane surface with flatness tolerance of 0,5 mm;
- c) fixed square, fixed to the reference plane surface, at least 25 mm deeper than the depth of the rim side to be measured, one arm at least 300 mm longer than the length to be measured and the other arm at least as long as the width to be measured;
- d) movable square, at least 25 mm deeper than the depth of the rim side to be measured, one side at least 300 mm long and the other side at least as long as the width to be measured;
- e) thickness comparator or gauge with an accuracy of $\pm 0,1$ mm;
- f) spacing rollers made of metallic material, at least 25 mm deeper than the depth of the rim side to be measured and with a diameter D_{sr} with a tolerance of $\pm 0,25$ mm;
- g) thickness wedge with a thickness of $5_{-0,1}^0$ mm.

A.2.2 Squaring

Place the shower tray upside down on the reference plane surface as shown in Figure A.4.

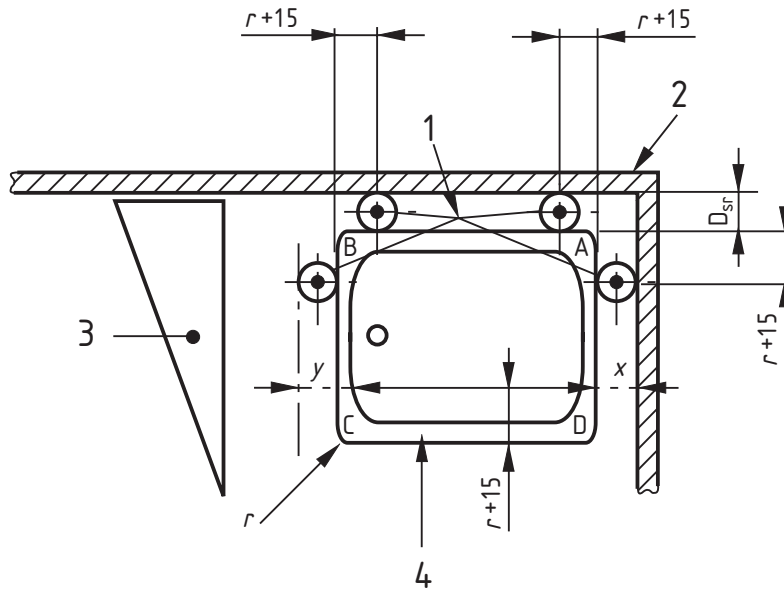
Position sides AB and AD adjacent to the fixed square and place three spacing rollers with diameter D_{sr} each at a distance of $r + 15$ mm from the corners A and B, as shown in Figure A.1, where r is the radius of the corners. Measure the distance x between the corner D and the fixed square and calculate Δq as the difference $D_{sr} - x$.

Position the movable square along the side BC and place a fourth spacing roller at a distance of $r + 15$ mm from the corner B. Measure the distance y between the corner C and the moveable square and calculate Δq as the difference $D_{sr} - y$.

Turn the shower tray through 180° and check the distances x and y at corners A and B respectively.

Record the deviation.

Dimensions in millimetres

**Key**

- 1 spacing rollers
- 2 fixed square
- 3 movable square
- 4 shower tray
- r radius of the corner

D_{sr} diameter of spacing roller

x distance between the rim and the fixed square

y distance between the rim and the moveable square

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN 15720:2010

<https://standards.iteh.ai/catalog/standards/sist/57da671b-5667-4a92-869f-4e34930c77f/sist-en-15720-2010>

Figure A.1 — Squaring

A.2.3 Straightness of the rim side

Place the shower tray upside down on the reference plane surface as shown in Figure A.4.

Position two spacing rollers with diameter D_{sr} between the rim side of the shower tray and one side of the fixed square, each at a distance of $r + 15$ mm from the corners, as shown in Figure A.2, where r is the radius of the corners of the shower tray.

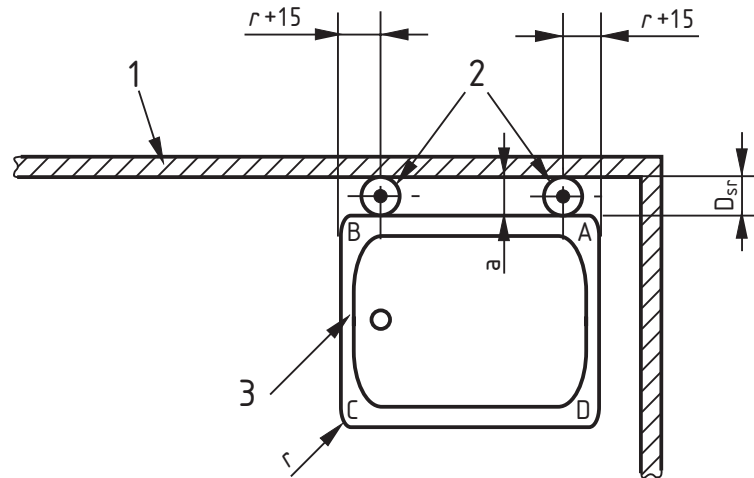
Measure the maximum and minimum distances a_{max} and a_{min} between the rim side and the fixed square using the thickness comparator or gauge.

Calculate the deviation Δs as the difference $a_{max} - a_{min}$.

Record the deviation.

Repeat the procedure for each rim of the shower tray.

Dimensions in millimetres

**Key**

- 1 fixed square
- 2 spacing rollers
- 3 shower tray
- a* distance between rim side and fixed square
- r* radius of the corner
- D_{sr} diameter of spacing roller

ITeH STANDARD PREVIEW
(standards.iteh.ai)

Figure A.2 — Straightness of the rim side

SIST EN 15720:2010

A.2.4 Straightness of the bottom edge of the rim

Place the shower tray upside down on the reference plane surface as shown in Figure A.4.

Position the shower tray against the fixed square as shown in Figure A.3.

Measure the maximum and minimum distances b_{max} and b_{min} between the bottom edge of the rims and the top surface of the fixed square using the thickness comparator or gauge.

Calculate the deviation Δr as the difference $b_{max} - b_{min}$.

Record the total deviation.