



Standard Test Methods for Rigid Tubes Used for Electrical Insulation¹

This standard is issued under the fixed designation D 348; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last approval. A superscript epsilon (ε) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 These test methods cover the testing of rigid tubes used in electrical insulation. These tubes include many types made from fibrous sheets of basic materials, such as cellulose, asbestos, glass, or nylon, in the form of paper, woven fabrics, or mats, bonded together by natural or synthetic resins or by adhesives. Such tubes include vulcanized fiber and thermosetting laminates, as well as tubes made from cast, molded, or extruded natural or synthetic resins, with or without fillers or reinforcing materials.

1.2 Tubes tested by these test methods are most commonly circular in cross section; however, noncircular shapes are also in commercial use. To the extent that the individual methods are compatible with a particular noncircular shape, these test methods are applicable to these other shapes. For tests on noncircular tubes, appropriate comments should be included in the test report, including details of orientation of test specimens with respect to the cross section of the tube.

1.3 The procedures appear in the following sections:

Procedure	Sections	ASTM Test Method Reference
Compressive Strength (Axial and Diametral)	12 to 17	E 4
Conditioning	4	...
Density	20 to 24	...
Dielectric Strength	25 to 32	D 149
Dimensional Measurements	5	D 668
Dissipation Factor and Permittivity	33 to 35	D 150
Tensile Strength	6 to 11	E 4
Water Absorption	18 to 19	D 570

1.4 The values stated in inch-pound units are to be regarded as the standard. SI units in parentheses are for information only.

1.5 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.* For a specific hazard statement, see 27.1.1.

2. Referenced Documents

2.1 ASTM Standards:

- D 149 Test Method for Dielectric Breakdown Voltage and Dielectric Strength of Solid Electrical Insulating Materials at Commercial Power Frequencies²
- D 150 Test Methods for A-C Loss Characteristics and Permittivity (Dielectric Constant) of Solid Electrical Insulating Materials²
- D 570 Test Method for Water Absorption of Plastics³
- D 668 Test Methods for Measuring Dimensions of Rigid Rods and Tubes Used for Electrical Insulation²
- D 1711 Terminology Relating to Electrical Insulation²
- E 4 Practices for Force Verification of Testing Machines⁴

3. Terminology

3.1 *Definitions*—For definitions of terms used in these test methods, refer to Terminology D 1711.

4. Conditioning

4.1 In order to eliminate the effects of previous history of humidity exposure and to obtain reproducible results (Note 1), the test specimens in all cases of dispute, shall be given a conditioning treatment for physical tests (Note 2) as follows:

4.1.1 *Tensile Strength, Compressive Strength (Axial and Diametral), and Density*—Condition the machined specimens prior to test by drying in an air-circulating oven for 48 h at 50 ± 3°C, followed by cooling to room temperature in a desiccator. In either case, all specimens shall be tested at room temperature maintained at 23 ± 2°C, 50 % relative humidity.

NOTE 1—Conditioning of specimens may be undertaken: (a) for the purpose of bringing the material into equilibrium with standard laboratory atmospheric conditions of 23°C and 50 % relative humidity; (b) simply to obtain reproducible results, irrespective of previous history of exposure; or (c) to subject the material to abnormal conditions of temperature or humidity in order to predict its service behavior.

The conditions given here to obtain reproducible results may give physical values somewhat higher or somewhat lower than values under equilibrium at normal conditions, depending upon the particular material and test. To ensure substantial equilibrium under normal conditions of humidity and temperature, however, will require from 20 to 100 days or

¹ These test methods are under the jurisdiction of ASTM Committee D09 on Electrical and Electronic Insulating Materials and are the direct responsibility of Subcommittee D09.07 on Flexible and Rigid Insulating Materials.

Current edition approved Apr. 10, 2000. Published June 2000. Originally published as D 348 – 32T. Last previous edition D 348 – 95.

² *Annual Book of ASTM Standards*, Vol 10.01.

³ *Annual Book of ASTM Standards*, Vol 08.01.

⁴ *Annual Book of ASTM Standards*, Vol 03.01.

more depending upon thickness and type of material and its previous history. Consequently, conditioning for reproducibility must of necessity be used for general purchase specifications and product control tests.

NOTE 2—Conditioning of specimens for electrical tests is also necessary to obtain consistent results. In order to secure comparative results, specimens should be conditioned at the same temperature and humidity.

5. Dimensional Measurements

5.1 Dimensional measurements of tube shall be made in accordance with Test Methods D 668.

TENSILE STRENGTH

6. Significance and Use

6.1 Tension tests, properly interpreted, provide information with regard to the tensile properties of rigid tubing, when employed under conditions approximating those under which the tests are made. The tensile strength values may vary with the size of the tube and with the temperature and atmospheric conditions. Tension tests may provide data for research and development and for engineering design, and are useful for quality control purposes.

7. Apparatus

7.1 Any universal testing machine may be used provided it is accurate to 1 % of the lowest breaking load to be applied. Jaws that tighten under load, such as wedge-grip jaws, shall be used with the specimen properly aligned.

7.2 The machine shall be verified in accordance with Practices E 4.

8. Test Specimens

8.1 The test specimens shall be as shown in Fig. 1. The length, L , shall be as shown in Table 1. A groove shall be machined around the outside of the specimen at the center of its length so that the wall section after machining shall be 60 % of the original nominal wall thickness. This groove shall consist of a straight section 2.25 in. (57 mm) in length with a radius of 3 in. (76 mm) at each end joining it to the outside diameter. Steel or brass plugs having diameters such that they will fit snugly inside the tube, and having a length equal to the full jaw length plus 1 in. (25 mm) shall be placed in the ends of the specimen to prevent crushing. They can be located in the tube conveniently by separating and supporting them on a threaded metal rod. Details of plugs and test assembly are shown in Fig. 1.

9. Procedure

9.1 Test five specimens. Measure the average inside and outside diameters, determined from at least two measurements 90° apart, at the groove to the nearest 0.001 in. (0.03 mm) and calculate the cross-sectional area from these dimensions. Assemble the metal plugs with the tube as shown in Fig. 1. Grasp this assembly in the V-notched jaws of the testing machine.

9.2 *Speed of Testing*—The crosshead speed of the testing machine shall be such that the load can be accurately weighed, but shall not exceed 0.05 in./min (1.3 mm/min) when the machine is running idle.

10. Report

10.1 Report the following information:

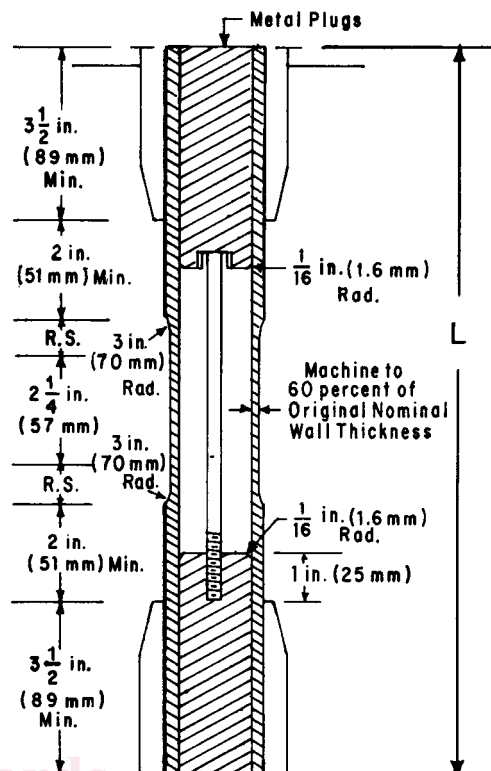


FIG. 1 Diagram Showing Location of Tube Tension Test Specimen in Testing Machine

10.1.1 The average inside and outside diameters of the specimen expressed to the nearest 0.001 in. (0.03 mm), each determined from at least two measurements 90° apart,

10.1.2 The average outside diameter of the reduced section expressed to the nearest 0.001 in. (0.03 mm),

10.1.3 The full wall thickness of the specimen,

10.1.4 The net area of the test section, in.² or mm²,

10.1.5 The breaking load of each specimen, lbf or N,

10.1.6 The tensile strength of each specimen, psi or MPa, and

10.1.7 The room temperature.

11. Precision and Bias

11.1 *Precision*—This test method has been in use for many years, but no information has been presented to ASTM upon which to base a statement of precision. No activity has been planned to develop such information.

11.2 *Bias*—This test method has no bias because the value for tensile strength is determined solely in terms of this test method.

COMPRESSIVE STRENGTH (AXIAL AND DIAMETRAL)

12. Significance and Use

12.1 Compressive tests, properly interpreted, provide information with regard to the compressive properties of rigid tubing when employed under conditions approximating those under which the tests are made. The compressive strength values may vary with the size of the tube, and with temperature

TABLE 1 Dimensions of Tension Specimens, in. (mm)

Nominal Wall Thickness	Length of Radial Sections, 2R.S.	Total Calculated Minimum Length of Specimen	Standard Length, <i>L</i> , of Specimen to be Used for 3½-in. (89-mm) Jaws ^A
1/32 (0.79)	0.547 (13.9)	13.80 (350.0)	15 (381.0)
3/64 (1.2)	0.670 (17.0)	13.92 (354.0)	15 (381.0)
1/16 (1.6)	0.773 (19.6)	14.02 (356.0)	15 (381.0)
3/32 (2.4)	0.946 (24.0)	14.20 (361.0)	15 (381.0)
1/8 (3.2)	1.091 (27.7)	14.34 (364.0)	15 (381.0)
3/16 (4.8)	1.333 (33.9)	14.58 (370.0)	15 (381.0)
1/4 (6.4)	1.536 (39.0)	14.79 (376.0)	15.75 (400.0)
5/16 (7.9)	1.714 (43.5)	14.96 (380.0)	15.75 (400.0)
3/8 (9.5)	1.873 (47.6)	15.12 (384.0)	15.75 (400.0)
7/16 (11.1)	2.019 (51.3)	15.27 (388.0)	15.75 (400.0)
1/2 (12.7)	2.154 (54.7)	15.40 (391.0)	16.5 (419.0)

^A For other jaws greater than 3½ in. (89 mm), the standard length shall be increased by twice the length of the jaws minus 7 in. (178 mm). The standard length permits a slippage of approximately ¼ to ½ in. (6.4 to 12.7 mm) in each jaw while maintaining maximum length of jaw grip.

and atmospheric conditions. Compression tests may provide data for research and development, engineering design, quality control, and acceptance or rejection under specifications.

13. Apparatus

13.1 Any universal testing machine may be used provided it is accurate to 1 % of the lowest breaking load to be applied, in accordance with Practices E 4. One end of the specimen for axial loading or the side of the specimen for diametral loading shall bear upon an accurately centered spherical bearing block, located whenever practicable at the top. The metal bearing plates shall be directly in contact with the test specimen.

NOTE 3—Off-center loading of the diametral compressive test may cause the tube to push to one side.

14. Test Specimens

14.1 Unless otherwise specified, the material shall be tested in the as-received condition.

14.2 Test specimens shall consist of 1-in. (25-mm) long sections of the tubing.

14.3 Care shall be taken in cutting the test specimens for the axial tests, to have the ends of the specimens cut accurately and smoothly at right angles to the axis of the tube.

NOTE 4—If the tubing is too large in diameter, or is too high in breaking strength to be tested with the available testing equipment, a segment of the test specimen specified in 14.2 and 14.3 may be substituted for axial tests. Such segments should not be used for testing tubes less than 2 in. (51 mm) in outside diameter. Unless otherwise specified, use segments having a circumferential length of 2 in. (51 mm).

15. Procedure

15.1 Test five specimens axially, with the load applied perpendicular to the faces or ends of the specimen, or test five specimens diametrically, with the load applied perpendicular to the tangent at point of application.

15.2 Discard specimens that break at some obvious fortuitous flaw and retest, unless such flaws constitute a variable, the effect of which it is desired to study.

15.3 Retain results (on specimens) that deviate markedly from the mean value of all tests unless 15.2 applies. In this case run additional tests, the exact number to be fixed by the desired (statistical) significance level.

15.4 *Speed of Testing*—The crosshead speed of the testing machine shall be 0.050 in./min (1.3 mm/min) when the

machine is running idle. In cases of diametral loading of certain tubing, especially the larger diameter tubes, it may be necessary to operate the crosshead at a speed of loading greater than 0.050 in./min. In this event the speed should be stated in the report.

16. Report

16.1 Report the following information:

16.1.1 The average inside and outside diameters of the specimen expressed to the nearest 0.001 in. (0.03 mm), each determined from at least two measurements 90° apart,

16.1.2 The average wall thickness of the specimen expressed to the nearest 0.001 in. (0.03 mm),

16.1.3 The segment length, if segmental specimens are used for axial tests,

16.1.4 The direction of application of the load,

16.1.5 The load on each specimen at the first sign of rupture, lbf or N, and

16.1.6 The ultimate compressive strength in force per unit area for axial loading and force for diametral loading.

17. Precision and Bias

17.1 *Precision*—Same as 11.1.

17.2 *Bias*—Same as 11.2 except for the property of compressive strength.

WATER ABSORPTION

18. Significance and Use

18.1 The moisture content of a rigid tube has a definite influence on the electrical properties, as well as on mechanical strength, dimensional stability, and appearance. The effect upon these properties of changes in moisture content, due to water absorption, depends largely upon the inherent properties of the rigid tube. The rate of water absorption may be widely different through each edge and surface. A water absorption determination will provide data useful for research and development, engineering design, quality control, and acceptance or rejection under specifications.

19. Procedure

19.1 Determine and report the rate of water absorption in accordance with Test Method D 570, immersing specimens for 24 h in distilled water at 23°C after preliminary conditioning for 1 h at 105°C.