



SLOVENSKI STANDARD

SIST EN 12473:2014

01-julij-2014

Nadomešča:
SIST EN 12473:2000

Splošna načela za katodno zaščito v morski vodi

General principles of cathodic protection in seawater

Allgemeine Grundsätze des kathodischen Korrosionsschutzes in Meerwasser

Principes généraux de la protection cathodique en eau de mer

iTeh STANDARD PREVIEW
(standards.iteh.ai)

Ta slovenski standard je istoveten z: **EN 12473:2014**

<https://standards.iteh.ai/catalog/standards/sist/ece386b9-f5d5-47bb-8587-00ba7fbb889/sist-en-12473-2014>

ICS:

25.220.40	Kovinske prevleke	Metallic coatings
47.020.01	Splošni standardi v zvezi z ladjedelništvom in konstrukcijami na morju	General standards related to shipbuilding and marine structures

SIST EN 12473:2014

en,fr,de

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN 12473:2014

<https://standards.iteh.ai/catalog/standards/sist/ece386b9-f5d5-47bb-8587-00ba7ffb889/sist-en-12473-2014>

EUROPEAN STANDARD
NORME EUROPÉENNE
EUROPÄISCHE NORM

EN 12473

February 2014

ICS 47.020.01; 77.060

Supersedes EN 12473:2000

English Version

General principles of cathodic protection in seawater

Principes généraux de la protection cathodique en eau de mer

Allgemeine Grundsätze des kathodischen Korrosionsschutzes in Meerwasser

This European Standard was approved by CEN on 16 November 2013.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.

[SIST EN 12473:2014](https://standards.iteh.ai/catalog/standards/sist/ece386b9-f5d5-47bb-8587-00ba7fbb889/sist-en-12473-2014)

<https://standards.iteh.ai/catalog/standards/sist/ece386b9-f5d5-47bb-8587-00ba7fbb889/sist-en-12473-2014>



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Avenue Marnix 17, B-1000 Brussels

Contents

Page

Foreword.....	4
1 Scope	5
2 Normative references	5
3 Terms, definitions, abbreviations and symbols	5
4 Application of cathodic protection in seawater.....	9
4.1 General.....	9
4.2 Galvanic anode method	9
4.3 Impressed current method	10
4.4 Hybrid systems	10
5 Determination of level of cathodic protection	12
5.1 Measurement of protection level.....	12
5.2 Reference electrodes	12
5.3 Potentials of reference electrodes	12
5.4 Verification of reference electrodes.....	12
5.5 Potential measurement	12
6 Cathodic protection potential criteria.....	13
6.1 General.....	13
6.2 Carbon-manganese and low alloy steels	13
6.3 Other metallic materials	15
6.3.1 General.....	15
6.3.2 Stainless steels	15
6.3.3 Nickel alloys	16
6.3.4 Aluminium alloys	16
6.3.5 Copper alloys	17
7 Design considerations	17
7.1 Introduction	17
7.2 Technical and operating data	17
7.2.1 Design life	17
7.2.2 Materials of construction	17
7.3 Surfaces to be protected.....	18
7.4 Protective coatings.....	18
7.5 Availability of electrical power	18
7.6 Weight limitations	18
7.7 Adjacent structures	18
7.8 Installation considerations	18
7.9 Current demand	19
8 Effect of environmental factors on current demand	19
8.1 Introduction	19
8.2 Dissolved oxygen	19
8.3 Sea currents	19
8.4 Calcareous deposits.....	19
8.5 Temperature	20
8.6 Salinity	20
8.7 pH	21
8.8 Marine fouling	21
8.9 Effect of depth.....	21
8.10 Seasonal variations and storms.....	21

9	Secondary effects of cathodic protection.....	21
9.1	General	21
9.2	Alkalinity.....	22
9.3	Environmentally-assisted cracking	22
9.3.1	General	22
9.3.2	Hydrogen embrittlement.....	22
9.3.3	Corrosion fatigue.....	22
9.4	Chlorine	23
9.5	Stray currents and interference effects	23
10	Use of cathodic protection in association with coatings	24
10.1	Introduction.....	24
10.2	Coating selection.....	24
10.3	Coating breakdown	25
Annex A	(informative) Corrosion of carbon-manganese and low-alloy steels	26
A.1	Nature of metallic corrosion.....	26
A.2	Polarization	27
Annex B	(informative) Principles of cathodic protection.....	30
Annex C	(informative) Reference electrodes	33
C.1	General	33
C.2	Silver/silver chloride/seawater electrode.....	33
C.3	The zinc/seawater electrode.....	35
C.4	Verification of reference electrodes	35
Annex D	(informative) Corrosion of metallic materials other than carbon-manganese and low-alloy steels typically subject to cathodic protection in seawater	37
D.1	Stainless steels.....	37
D.2	Nickel alloys	37
D.3	Aluminium alloys.....	37
D.4	Copper alloys.....	38
Bibliography	39

EN 12473:2014 (E)**Foreword**

This document (EN 12473:2014) has been prepared by Technical Committee CEN/TC 219 "Cathodic protection", the secretariat of which is held by BSI.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by August 2014, and conflicting national standards shall be withdrawn at the latest by August 2014.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN 12473:2000.

According to the CEN-CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN 12473:2014

<https://standards.iteh.ai/catalog/standards/sist/ece386b9-f5d5-47bb-8587-00ba7ffb8889/sist-en-12473-2014>

1 Scope

This European Standard covers the general principles of cathodic protection when applied in seawater, brackish waters and marine mud. It is intended to be an introduction, to provide a link between the theoretical aspects and the practical applications, and to constitute a support to the other European Standards devoted to cathodic protection of steel structures in seawater.

This European Standard specifies the criteria required for cathodic protection. It provides recommendations and information on reference electrodes, design considerations and prevention of the secondary effects of cathodic protection.

The practical applications of cathodic protection in seawater are covered by the following standards:

- EN 12495, *Cathodic protection for fixed steel offshore structures*;
- EN ISO 13174, *Cathodic protection of harbour installations (ISO 13174)*;
- EN 12496, *Galvanic anodes for cathodic protection in seawater and saline mud*;
- EN 13173, *Cathodic protection for steel offshore floating structures*;
- EN 16222, *Cathodic protection of ship hulls*;
- EN 12474, *Cathodic protection of submarine pipelines*;
- ISO 15589-2, *Petroleum, petrochemical and natural gas industries — Cathodic protection of pipeline transportation systems — Part 2: Offshore pipelines*.

For cathodic protection of steel reinforced concrete, whether exposed to seawater or to the atmosphere, EN ISO 12696 applies.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 50162, *Protection against corrosion by stray current from direct current systems*

EN ISO 8044, *Corrosion of metals and alloys — Basic terms and definitions (ISO 8044)*

3 Terms, definitions, abbreviations and symbols

For the purposes of this document, the terms and definitions given in EN ISO 8044 and the following apply.

NOTE The definitions given below prevail on their versions in EN ISO 8044.

3.1

acidity

presence of an excess of hydrogen ions over hydroxyl ions ($\text{pH} < 7$)

3.2

alkalinity

presence of an excess of hydroxyl ions over hydrogen ions ($\text{pH} > 7$)

EN 12473:2014 (E)**3.3****anaerobic condition**

absence of free oxygen dissolved in the electrolyte

3.4**calcareous deposits**

minerals precipitated on the metallic cathode because of the increased alkalinity caused by cathodic protection

3.5**cathodic disbondment**

failure of adhesion between a coating and a metallic surface that is directly attributable to the application of cathodic protection

3.6**cathodic protection system**

entire installation that provides cathodic protection

Note 1 to entry: It may include anodes, power source, cables, test facilities, isolation joints, electrical bonds.

3.7**coating breakdown factor**

f_c

ratio of cathodic current density for a coated metallic material to the cathodic current density of the bare material

iTeh STANDARD PREVIEW
(standards.iteh.ai)

3.8**copper/copper sulphate reference electrode**

reference electrode consisting of copper in a saturated solution of copper sulphate

[SIST EN 12473:2014](https://standards.iteh.ai/catalog/standards/sist/ece386b9-f5d5-47bb-8587-00ba7ffb889/sist-en-12473-2014)

3.9**dielectric shield**

alkali resistant organic coating applied to the structure being protected in the immediate vicinity of an impressed current anode to enhance the spread of cathodic protection and minimize the risk of hydrogen damage to the protected structure in the vicinity of the anode

<https://standards.iteh.ai/catalog/standards/sist/ece386b9-f5d5-47bb-8587-00ba7ffb889/sist-en-12473-2014>

3.10**driving voltage**

difference between the structure/electrolyte potential and the anode/electrolyte potential when the cathodic protection is operating

3.11**electro-osmosis**

passage of a liquid through a porous medium under the influence of a potential difference

3.12**environmentally assisted cracking**

cracking of a susceptible metal or alloy due to the conjoint action of an environment and stress

3.13**groundbed**

system of immersed electrodes connected to the positive terminal of an independent source of direct current and used to direct the cathodic protection current onto the structure being protected

3.14**hydrogen embrittlement**

process resulting in a decrease of the toughness or ductility of a metal due to absorption of hydrogen

3.15**hydrogen stress cracking**

HSC

cracking that results from the presence of hydrogen in a metal and tensile stress (residual and/or applied)

Note 1 to entry: HSC describes cracking in metals which may be embrittled by hydrogen produced by cathodic polarization without any detrimental effect caused by specific chemicals such as sulphides.

3.16**isolating joint (or coupling)**

electrically discontinuous joint or coupling between two lengths of pipe, inserted in order to provide electrical discontinuity between them

3.17**master reference electrode**

reference electrode, calibrated with the primary calibration reference electrode, used for verification of reference electrodes used for field or laboratory measurements

3.18**over-polarization**

occurrence in which the structure to electrolyte potentials are more negative than those required for satisfactory cathodic protection

Note 1 to entry: Over-polarization provides no useful function and might even cause damage to the structure.

3.19**pitting resistance equivalent**

PREN

indication of the resistance of a corrosion resistant alloy to pitting in the presence of water, chlorides and oxygen or oxidation environment, accounting for the beneficial effects of nitrogen

Note 1 to entry: For the purposes of this standard, PREN is calculated as follows:

$$\text{PREN} = \% \text{Cr} + 3,3[(\% \text{Mo}) + 0,5 (\% \text{W})] + 16 (\% \text{N}).$$

3.20**potential gradient**

difference in potential between two separate points in the same electric field

3.21**primary calibration reference electrode**

reference electrode used for calibration of master reference electrodes is the normal hydrogen electrode (N.H.E.)

Note 1 to entry: The official reference electrode, standard hydrogen electrode (S.H.E.), which considers the fugacity coefficient for hydrogen gas and the activity coefficient for H^+ ions, is practically impossible to manufacture.

3.22**protection current**

current made to flow into a metallic structure from its electrolytic environment in order to achieve cathodic protection of the structure

3.23**reference electrode**

electrode having a stable and reproducible potential that is used as a reference in the measurement of electrode potentials

iTeh STANDARD PREVIEW
(standards.iteh.ai)

<https://standards.iteh.ai/catalog/standards/sist/ece386b9-f5d5-47bb-8587-000a71000000/sist-en-12473-2014>

EN 12473:2014 (E)

Note 1 to entry: Some reference electrodes use the electrolyte in which the measurement is carried out. Their potential varies according to the composition of this electrolyte.

3.24**resistivity (of an electrolyte)**

resistivity is the resistance of an electrolyte of unit cross section and unit length

Note 1 to entry: It is expressed in ohm.metres ($\Omega\cdot m$). The resistivity depends, amongst other things, upon the amount of dissolved salts in the electrolyte.

3.25**saturated calomel reference electrode**

reference electrode consisting of mercury and mercurous chloride in a saturated solution of potassium chloride

3.26**silver/silver chloride reference electrode**

reference electrode consisting of silver, coated with silver chloride, in an electrolyte containing a known concentration of chloride ions

Note 1 to entry: Silver/silver chloride/ saturated KCl electrodes are electrodes currently used in the laboratory and for master reference electrode.

Note 2 to entry: Silver/silver chloride/seawater (Ag/AgCl/seawater) electrodes are electrodes currently used for field measurements in seawater.

3.27**slow strain rate test**

test for evaluating susceptibility of a metal to environmentally assisted cracking (3.12 in this document) that most commonly involves pulling a tensile specimen to failure in a representative environment at a constant displacement rate chosen to generate nominal strain rates usually in the range 10^{-5} s^{-1} to 10^{-8} s^{-1}

Note 1 to entry: Slow strain rate testing may also be applied to other specimen geometries, e.g. bend specimens.

3.28**specified minimum yield strength**

SMYS

minimum yield strength prescribed by the specification under which steel components are manufactured, obtained through standard analysis and representing a probabilistic value

Note 1 to entry: It is an indication of the minimum stress steel components may experience that will cause plastic (permanent) deformation (typically 0,2 %).

3.29**stray currents**

current flowing through paths other than the intended circuits

3.30**structure to electrolyte potential**

difference in potential between a structure and a specified reference electrode in contact with the electrolyte at a point sufficiently close to, but without actually touching the structure, to avoid error due to the voltage drop associated with any current flowing in the electrolyte

3.31**sulphate reducing bacteria**

SRB

group of bacteria that are found in most soils and natural waters, but active only in conditions of near neutrality and absence of oxygen and that reduce sulphates in their environment, with the production of sulphides and accelerate the corrosion of structural materials

3.32**telluric currents**

electrical currents induced by time varying changes in the earth's magnetic field

Note 1 to entry: They are able to flow in metallic conductors laid in the soil or in the sea.

3.33**zinc reference electrode**

electrode consisting of pure zinc or zinc alloy specific for anodes in contact with the electrolyte in which the measurements are carried out

Note 1 to entry: Zinc reference electrodes are currently used for measurements in seawater carried out at permanent locations.

4 Application of cathodic protection in seawater**4.1 General**

Metallic materials in aqueous environments such as seawater are susceptible to corrosion produced by electrochemical reactions. General information on corrosion of carbon-manganese or low alloy steels is given in Annex A.

Cathodic protection is an electrochemical corrosion prevention system based on the decrease of corrosion potential to a level at which the corrosion rate of the metal is significantly reduced (EN ISO 8044). For industrial structures, residual corrosion rates less than 10 µm / yr are typically achieved with a fully effective cathodic protection system.

Cathodic protection is achieved by applying a voltage able to supply sufficient current to the metallic surface to lower the potential. General information on the principles of cathodic protection is given in Annex B.

There are two methods whereby the protection current can be supplied to polarize the surface:

- a) galvanic anode systems in which the current for protection is provided by a metal of more negative corrosion potential than the item to be protected i.e. aluminium, zinc and magnesium alloys for steel and iron for copper and copper based alloys,
- b) impressed current systems in which direct current (normally produced from alternating current by a transformer rectifier) is used in conjunction with relatively inert anodes such as graphite, thin coatings of platinum or activated mixed metal oxides on metals such as titanium or niobium, lead alloys, silicon-iron, etc; in some cases a consumable anode such as scrap iron or steel is used.

4.2 Galvanic anode method

If two dissimilar metals are connected in the same electrolyte, a galvanic cell is produced. The open circuit voltage is the natural potential difference which exists between the two metals. If the circuit is closed, the potential difference drives an electrical current. The more negative electrode behaves as an anode and it releases electrons to the circuit and dissolves more rapidly while the more positive electrode behaves as a cathode and dissolves less readily. The use of galvanic anodes in cathodic protection is based on this phenomenon.

Assuming the structure to be protected is made of steel, aluminium or zinc alloy galvanic anodes can be used to form the cell, because these alloys are less noble (more electronegative) than steel. Anode attachment to the structure is made through a steel core on to which the anode material is cast. Thus the structure is in metallic contact with the anode material and also in electrolytic contact with it once the structure is immersed. This is represented in Figure 1, where it is seen that the electrons released by the dissolution of metal atoms are consumed in the cathodic reduction of oxygen on the structure and hydroxyl ions are produced at the structure surface.

4.3 Impressed current method

Most impressed current anodes are of a type that do not dissolve readily on anodic polarization but sustain alternative reactions which involve decomposition of the aqueous environment, or oxidizing of dissolved chloride ions in it, i.e:





Figure 2 represents an impressed current cathodic protection system using an inert anode in seawater where in the secondary reactions hydrogen and chlorine are evolved.

The advantages of the impressed current system are that it is possible to have a large adjustable driving voltage so that relatively few anodes need to be installed even to protect large uncoated structures in comparatively high resistivity environments. A comparison of galvanic and impressed current anode systems is given in Table 1.


4.4 Hybrid systems

These comprise a combination of galvanic anodes and externally powered impressed current anodes.

Because there can be a significant time between the initial immersion of a structure and the full commissioning of the impressed current system it is usual to fit sufficient galvanic anodes to polarize the critical region of the structure.

The galvanic anodes should also provide protection when the impressed current system is shut down for subsea survey and maintenance during the life of the structure.


<https://standards.iteh.ai/catalog/standards/sist/ece386b9-f5d5-47bb-8587-00ba7ffb889/sist-en-12473-2014>

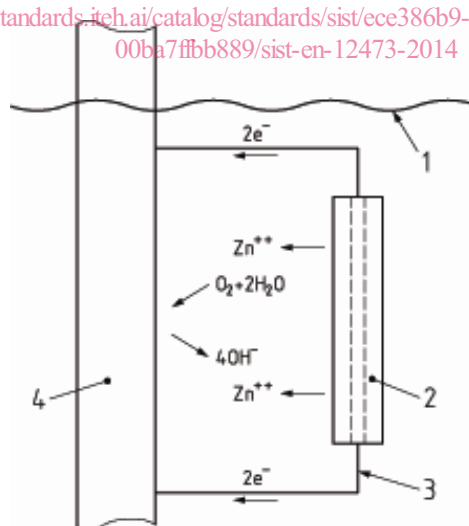

Key

- | | |
|--------------------|-----------------------------------|
| 1 seawater | 2 galvanic anode |
| 3 anode attachment | 4 protected structure in seawater |

Figure 1 — Representation of cathodic protection using a galvanic anode on a structure in the seawater

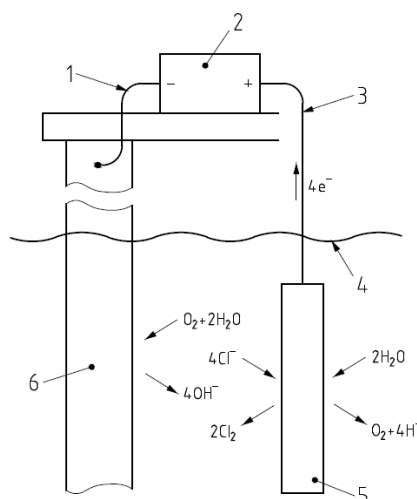

Key

- | | | |
|---------------------------|---------------------------|-----------------------------------|
| 1 insulated cathode cable | 2 power supply (dc) | 3 insulated anode cable |
| 4 seawater | 5 impressed current anode | 6 protected structure in seawater |

Figure 2 — Representation of impressed current cathodic protection using inert anode in seawater

Table 1 — Comparison of galvanic and impressed current systems

	Galvanic systems	Impressed current systems
Environment	Use can be impracticable in soils or waters of high resistivity.	Use is not restricted by resistivity of soils or waters
Installation	Simple to install.	Needs careful design otherwise can be complicated.
Power source	Independent of any source of electric power. Cannot be wrongly connected electrically.	External supply necessary. Care needs to be taken to avoid electrical connection in wrong direction.
Anodes	Bulk of anode material can restrict water flow and introduce turbulence and drag penalties.	Usually lighter and few in number. Anodes can be designed to have minimum effect on water flow.
Control	Tendency for their current to be self adjusting.	Controllable. Control usually automatic and can be continuous.
Interaction	They are less likely to affect any neighbouring structures.	Effects on other structures situated near the anodes need to be assessed.
Maintenance	Generally not required. May be renewed in some circumstances.	Equipment designed for long life but regular checks required on electrical equipment in service. Continual power required.
Damage	Anodes are robust and not very susceptible to mechanical damage. Where a system comprises a large number of anodes, the loss of a few anodes has little overall effect on the system. Connections have to be able to withstand any forces applied to the structure. Electrical insulation of cables is not necessary.	Anodes lighter in construction and therefore less resistant to mechanical damage. Loss of anodes can be more critical to the effectiveness of a system. Complete electrical insulation of positive cables exposed to electrolyte is mandatory.