SLOVENSKI STANDARD
SIST EN 583-6:2009

01-april-2009

Neporuġitveno preskuġanje - Ultrazvoļ ne preiskave - 6. del: Tehnika zvoļ ne poti kot metoda za odkrivanje in ugotavljanje velikosti nezveznosti

Non-destructive testing - Ultrasonic examination - Part 6: Time-of-flight diffraction technique as a method for detection and sizing of discontinuities

Zerstörungsfreie Prüfung - Ultraschallprüfung - Teil 6: Beugungslaufzeittechnik, eine Technik zum Auffinden und Ausmessen von Inhomogenitäten

Essais non destructifs - Contrôle ultrasonore - Partie 6: Technique de diffraction du temps de vol utilisée comme méthode de détection et de dimensionnement des discontinuités

Ta slovenski standard je istoveten z: EN 583-6:2008

ICS:

19.100	Neporušitveno preskušanje	Non-destructive testing

SIST EN 583-6:2009 **en,fr,de**

EUROPEAN STANDARD
NORME EUROPÉENNE
EUROPÄISCHE NORM

EN 583-6

December 2008

ICS 19.100

Supersedes ENV 583-6:2000

English Version

Non-destructive testing - Ultrasonic examination - Part 6: Time-of-flight diffraction technique as a method for detection and sizing of discontinuities

Essais non destructifs - Contrôle ultrasonore - Partie 6: Technique de diffraction du temps de vol utilisée comme méthode de détection et de dimensionnement des discontinuités

Zerstörungsfreie Prüfung - Ultraschallprüfung - Teil 6: Beugungslaufzeittechnik, eine Technik zum Auffinden und Ausmessen von Inhomogenitäten

This European Standard was approved by CEN on 29 October 2008.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: rue de Stassart, 36 B-1050 Brussels

Ref. No. EN 583-6:2008: E

Contents

Page

Foreword ... 4
1 Scope ... 5
2 Normative references ... 5
3 Terms, definitions, symbols and abbreviations ... 6
3.1 Terms and definitions ... 6
3.2 Abbreviations ... 6
3.3 Symbols ... 6
4 General ... 7
4.1 Principle of the technique ... 7
4.2 Requirements for surface condition and couplant ... 9
4.3 Materials and process type ... 9
5 Qualification of personnel ... 9
6 Equipment requirements ... 9
6.1 Ultrasonic equipment and display ... 9
6.2 Ultrasonic probes ... 10
6.3 Scanning mechanisms ... 11
7 Equipment set-up procedures ... 11
7.1 General ... 11
7.2 Probe choice and probe separation ... 12
7.2.1 Probe selection ... 12
7.2.2 Probe separation ... 13
7.3 Time window setting ... 13
7.4 Sensitivity setting ... 13
7.5 Scan resolution setting ... 14
7.6 Setting of scanning speed ... 14
7.7 Checking system performance ... 14
8 Interpretation and analysis of data ... 14
8.1 Basic analysis of discontinuities ... 14
8.1.1 General ... 14
8.1.2 Characterisation of discontinuities ... 14
8.1.3 Estimation of discontinuity position ... 15
8.1.4 Estimation of discontinuity length ... 15
8.1.5 Estimation of discontinuity depth and height ... 16
8.2 Detailed analysis of discontinuities ... 16
8.2.1 General ... 16
8.2.2 Additional scans ... 17
8.2.3 Additional algorithms ... 18
9 Detection and sizing in complex geometries ... 18
10 Limitations of the technique ... 18
10.1 General ... 18
10.2 Accuracy and resolution ... 19
10.2.1 General ... 19
10.2.2 Errors in the lateral position ... 19
10.2.3 Timing errors ... 19
10.2.4 Errors in sound velocity ... 19
10.2.5 Errors in probe centre separation ... 19
10.2.6 Spatial resolution ... 20
10.3 Dead zones ... 20

11 TOFD examination without data recording ... 20
12 Test procedure ... 21
13 Test report ... 21
Annex A (normative) **Reference blocks** ... 22
Bibiliography ... 23

Foreword

This document (EN 583-6:2008) has been prepared by Technical Committee CEN/TC 138 “Non-destructive testing”, the secretariat of which is held by AFNOR.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by June 2009, and conflicting national standards shall be withdrawn at the latest by June 2009.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes ENV 583-6:2000.

The relevant changes from the previous edition are as follows:

– the terminology was revised;

– the references were updated.

EN 583, *Non-destructive testing — Ultrasonic examination* consists of the following parts:

— EN 583-1, *Non-destructive testing — Ultrasonic examination — Part 1: General principles*

— EN 583-2, *Non-destructive testing — Ultrasonic examination — Part 2: Sensitivity and range setting*

— EN 583-3, *Non-destructive testing — Ultrasonic examination — Part 3: Transmission technique*

— EN 583-4, *Non-destructive testing — Ultrasonic examination — Part 4: Examination for discontinuities perpendicular to the surface*

— EN 583-5, *Non-destructive testing — Ultrasonic examination — Part 5: Characterization and sizing of discontinuities*

— EN 583-6, *Non-destructive testing — Ultrasonic examination — Part 6: Time-of-flight diffraction technique as a method for detection and sizing of discontinuities*

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and the United Kingdom.

1 Scope

This European Standard defines the general principles for the application of the Time-Of-Flight Diffraction (TOFD) technique for both detection and sizing of discontinuities in low alloyed carbon steel components. It could also be used for other types of materials, provided the application of the TOFD technique is performed with necessary consideration of geometry, acoustical properties of the materials and the sensitivity of the examination.

Although it is applicable, in general terms, to discontinuities in materials and applications covered by EN 583-1, it contains references to the application on welds. This approach has been chosen for reasons of clarity as to the ultrasonic probe positions and directions of scanning.

Unless otherwise specified in the referencing documents, the minimum requirements of this standard are applicable.

Unless explicitly stated otherwise, this standard is applicable to the following product classes as defined in EN 583-2:

— class 1, without restrictions;

— classes 2 and 3, restrictions will apply as stated in Clause 9.

The inspection of products of classes 4 and 5 will require special procedures. These are addressed in Clause 9 as well.

The techniques to use TOFD for weld inspection are described in CEN/TS 14751.

The related acceptance criteria are given in prEN 15617.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 473, *Non-destructive testing — Qualification and certification of NDT personnel — General principles*

EN 583-1, *Non-destructive testing — Ultrasonic examination — Part 1: General principles*

EN 583-2, *Non-destructive testing — Ultrasonic examination — Part 2: Sensitivity and range setting*

EN 12668-1, *Non-destructive testing — Characterization and verification of ultrasonic examination equipment — Part 1: Instruments*

EN 12668-2, *Non-destructive testing — Characterization and verification of ultrasonic examination equipment — Part 2: Probes*

EN 12668-3, *Non-destructive testing — Characterization and verification of ultrasonic examination equipment — Part 3: Combined equipment*

3 Terms, definitions, symbols and abbreviations

3.1 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1.1
scanning surface dead zone
zone where indications may be obscured due to the interface echo (lateral wave)

3.1.2
back wall dead zone
dead zone where signals may be obscured by the presence of the back wall echo

3.1.3
A-scan
display of the ultrasonic signal amplitude as a function of time

3.1.4
B-scan
display of the time-of-flight of the ultrasonic signal as a function of probe displacement

3.1.5
non-parallel scan
scan perpendicular to the ultrasonic beam direction (see Figure 4)

3.1.6
parallel scan
scan parallel to the ultrasonic beam direction (see Figure 5)

3.2 Abbreviations

— TOFD: Time-Of-Flight Diffraction

3.3 Symbols

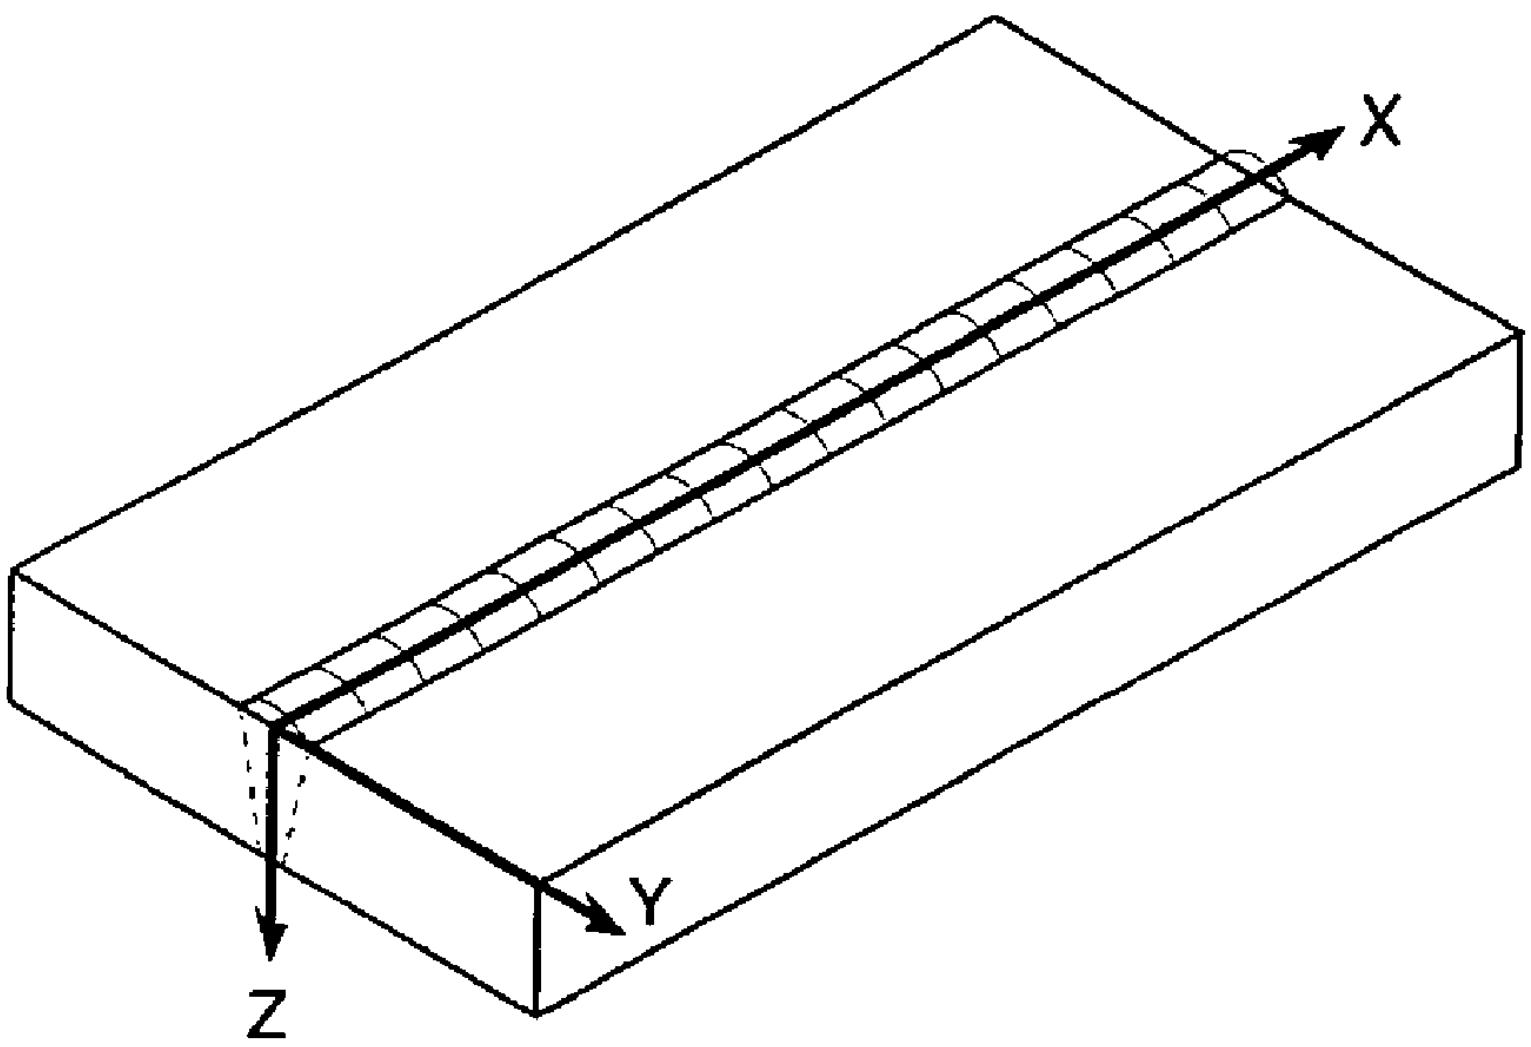

Figure 1 — Coordinate definition

x coordinate parallel to the scanning surface and parallel to a predetermined reference line. In case of weld inspection this reference line should coincide with the weld. The origin of the axes may be defined as best suits the specimen under examination (see Figure 1);

Δx discontinuity length;

y coordinate parallel to the scanning surface, perpendicular to the predetermined reference line (see Figure 1);

δy error in lateral position;

z coordinate perpendicular to the scanning surface (see Figure 1);

Δz discontinuity height;

d depth of a discontinuity tip below the scanning surface;

δd error in depth;

D_{ds} scanning-surface dead zone;

D_{dw} back wall dead zone;

c sound velocity;

δc error in sound velocity;

R spatial resolution;

t time-of-flight from the transmitter to the receiver;

Δt time-of-flight difference between the lateral wave and a second ultrasonic signal;

δt error in time-of-flight;

t_d time-of-flight at depth d;

t_p duration of the ultrasonic pulse measured at 10 % of the peak amplitude;

t_w time-of-flight of the back wall echo;

S half the distance between the index points of two ultrasonic probes;

δS error in half the probe separation;

W wall thickness.

4 General

4.1 Principle of the technique

The TOFD technique relies on the interaction of ultrasonic waves with the tips of discontinuities. This interaction results in the emission of diffracted waves over a large angular range. Detection of the diffracted waves makes it possible to establish the presence of the discontinuity. The time-of-flight of the recorded signals is a measure for the height of the discontinuity, thus enabling sizing of the defect. The dimension of the discontinuity is always determined from the time-of-flight of the diffracted signals. The signal amplitude is not used in size estimation.

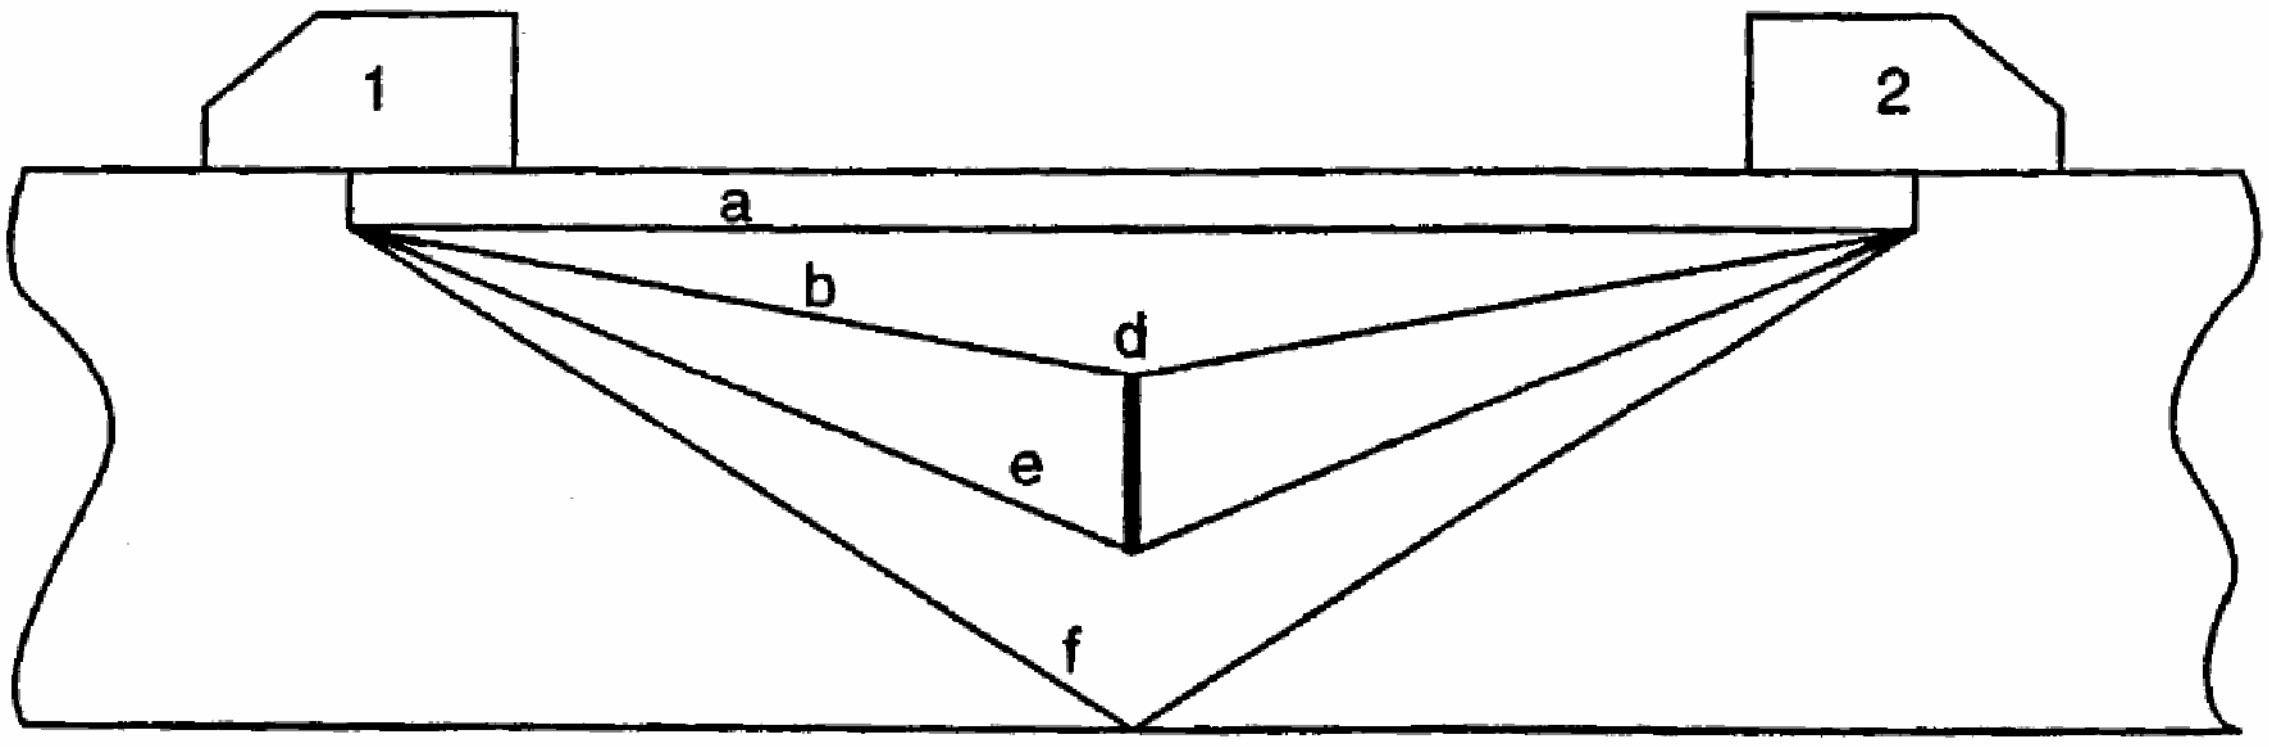

Key

1 transmitter
2 receiver
a lateral wave
b upper tip
d discontinuity
e lower tip
f back wall echo

Figure 2 — Basic TOFD configuration

The basic configuration for the TOFD technique consists of a separate ultrasonic transmitter and receiver (see Figure 2). Wide-angle beam compression wave probes are normally used since the diffraction of ultrasonic waves is only weakly dependent on the orientation of the discontinuity tip. This enables the inspection of a certain volume in one scan. However, restrictions apply to the size of the volume that can be inspected during a single scan (see 7.2).

The first signal to arrive at the receiver after emission of an ultrasonic pulse is usually the lateral wave which travels just beneath the upper surface of the test specimen.

In the absence of discontinuities, the second signal to arrive at the receiver is the back wall echo.

These two signals are normally used for reference purposes. If mode conversion is neglected, any signals generated by discontinuities in the material should arrive between the lateral wave and the back wall echo, since the latter two correspond, respectively, to the shortest and longest paths between transmitter and receiver. For similar reasons the diffracted signal generated at the upper tip of a discontinuity will arrive before the signal generated at the lower tip of the discontinuity. A typical pattern of indications (A-scan) is shown in Figure 3. The height of the discontinuity can be deduced from the difference in time-of-flight of the two diffracted signals (see 8.1.5). Note the phase reversal between the lateral wave and the back wall echo, and between echoes of the upper and lower tip of the discontinuity.

Where access to both surfaces of the specimen is possible and discontinuities are distributed throughout the specimen thickness, scanning from both surfaces will improve the overall precision, particularly in regard to discontinuities near the surfaces.

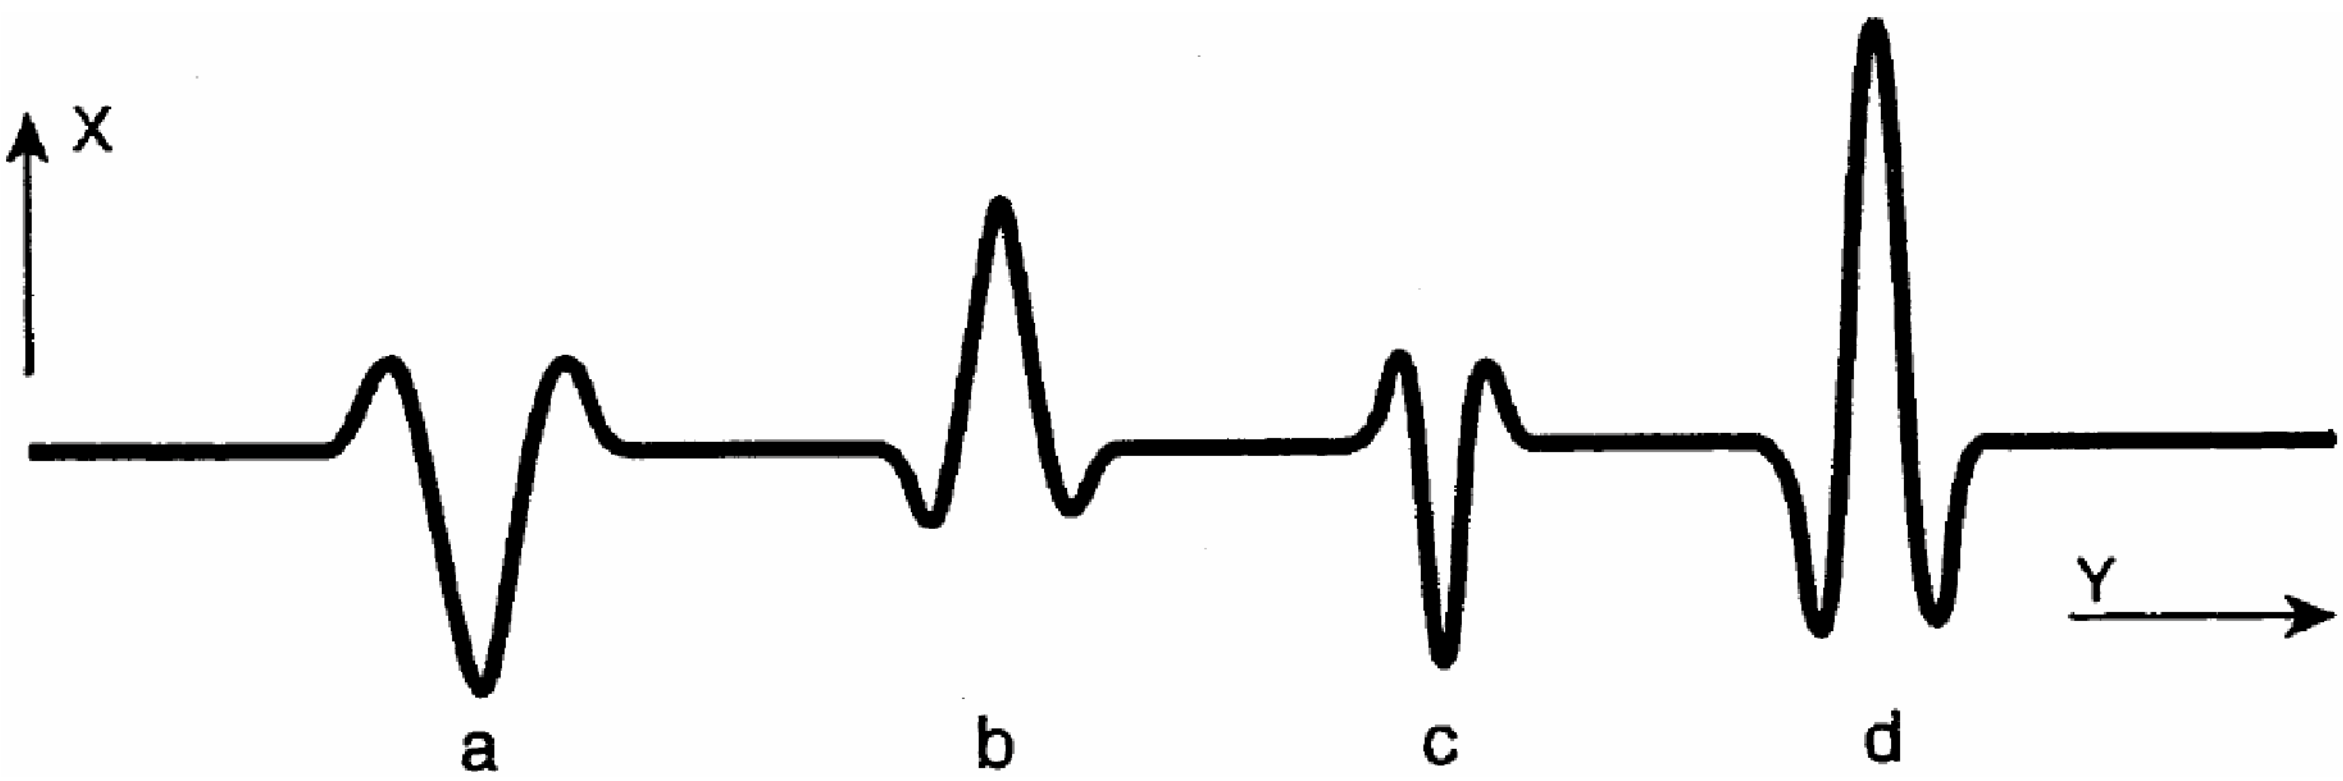

Key

X amplitude
Y time
a lateral wave
b upper tip
c lower tip
d back wall echo

Figure 3 — Schematic A-scan of an embedded discontinuity

4.2 Requirements for surface condition and couplant

Care shall be taken that the surface condition meets at least the requirements stated in EN 583-1. Since the diffracted signals may be weak, the degradation of signal quality due to poor surface condition will have a severe impact on inspection reliability.

Different coupling media can be used, but their type shall be compatible with the materials to be examined. Examples are: water (possibly containing an agent e.g. wetting, anti-freeze, corrosion inhibitor), contact paste, oil, grease, cellulose paste containing water, etc.

The characteristics of the coupling medium shall remain constant throughout the examination. It shall be suitable for the temperature range in which it will be used.

4.3 Materials and process type

Due to the relatively low signal amplitudes that are used in the TOFD technique, the method can be applied routinely on materials with relatively low levels of attenuation and scatter for ultrasonic waves. In general, application on unalloyed and low alloyed carbon steel components and welds is possible, but also on fine grained austenitic steels and aluminium.

Coarse-grained materials and materials with significant anisotropy however, such as cast iron, austenitic weld materials and high-nickel alloys, will require additional validation and additional data-processing.

By mutual agreement, a representative test specimen with artificial and/or natural discontinuities can be used to confirm inspectability. Remember that diffraction characteristics of artificial defects can differ significantly from those of real defects.

5 Qualification of personnel

Personnel performing examinations with the TOFD technique shall, as a minimum, be qualified in accordance with EN 473, and shall have received additional training and examination on the use of the TOFD technique on the product classes to be tested, as specified in a written practice.

6 Equipment requirements

6.1 Ultrasonic equipment and display

Ultrasonic equipment used for the TOFD technique shall, as a minimum, comply with the requirements of EN 12668-1, EN 12668-2 and EN 12668-3.

In addition, the following requirements shall apply:

— receiver bandwidth shall, as a minimum, range between 0,5 and 2 times the nominal probe frequency at -6 dB, unless specific materials and product classes require a larger bandwidth. Appropriate band filters can be used;

— transmitting pulse can either be unipolar or bipolar. The rise time shall not exceed 0,25 times the period corresponding to the nominal probe frequency;