
**Plastics — Film and sheeting — Biaxially
oriented polyamide (nylon) films**

Plastiques — Film et feuille — Films en polyamide (nylon) bi-orientés

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 15987:2003](https://standards.iteh.ai/catalog/standards/sist/2c941711-d75c-4c98-98cb-2a491273c15c/iso-15987-2003)

<https://standards.iteh.ai/catalog/standards/sist/2c941711-d75c-4c98-98cb-2a491273c15c/iso-15987-2003>



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 15987:2003](https://standards.iteh.ai/catalog/standards/sist/2c941711-d75c-4c98-98cb-2a491273c15c/iso-15987-2003)

<https://standards.iteh.ai/catalog/standards/sist/2c941711-d75c-4c98-98cb-2a491273c15c/iso-15987-2003>

© ISO 2003

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 15987 was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 11, *Products*.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO 15987:2003](https://standards.iteh.ai/catalog/standards/sist/2c941711-d75c-4c98-98cb-2a491273c15c/iso-15987-2003)

<https://standards.iteh.ai/catalog/standards/sist/2c941711-d75c-4c98-98cb-2a491273c15c/iso-15987-2003>

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 15987:2003

<https://standards.iteh.ai/catalog/standards/sist/2c941711-d75c-4c98-98cb-2a491273c15c/iso-15987-2003>

Plastics — Film and sheeting — Biaxially oriented polyamide (nylon) films

1 Scope

This International Standard specifies biaxially oriented transparent polyamide (nylon) films, mainly used for packaging.

NOTE Biaxially oriented transparent polyamide (nylon) films are used alone and/or as laminated film with other films.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 291:1997, *Plastics — Standard atmospheres for conditioning and testing*

ISO 527-3:1995, *Plastics — Determination of tensile properties — Part 3: Test conditions for films and sheets*

ISO 4593:1993, *Plastics — Film and sheeting — Determination of thickness by mechanical scanning*

ISO 8296:1987, *Plastics — Film and sheeting — Determination of wetting tension*

ISO 14782:1999, *Plastics — Determination of haze for transparent materials*

ISO 15105-1:2002, *Plastics — Film and sheeting — Determination of gas-transmission rate — Part 1: Differential-pressure method*

ISO 15105-2:2003, *Plastics — Film and sheeting — Determination of gas-transmission rate — Part 2: Equal-pressure method*

3 Classification

Films are classified into two groups as follows.

- 1) Film treated with corona discharge.
- 2) Film not treated with corona discharge.

4 Requirements

4.1 Appearance

The films shall be visibly free of flaws, slackness, wrinkles, stains, foreign matter or any marks that impair its serviceability.

The splicing of two films in a roll shall be prominently marked in order to provide a visible indication from the side of the roll. The interested parties shall agree upon the method of marking the splice.

NOTE One acceptable method of marking is the use of coloured adhesive tape.

4.2 Dimensions

4.2.1 General

For any individual film selected at random from any delivery, the dimensions listed in 4.2.2 to 4.2.5, including their nominal values, shall be agreed upon among interested parties.

4.2.2 Width

The tolerance of film width shall be within $+4_0$ mm of the nominal value.

An example of film width with corresponding tolerance is given in Table 1.

Table 1 — Example of a film width and its tolerance

Width mm	Tolerance mm
$500 + 40n$	$+4_0$
NOTE <i>n</i> : integer, 0, 1, 2, ..., in width steps of 40 mm.	

4.2.3 Length of film in a roll

The tolerance of film length in a roll shall be within $+1_0$ % of the nominal value.

Examples of film length and corresponding tolerance in a roll are shown in Table 2.

Table 2 — Examples of film length in a roll and their tolerances

Length of film		Tolerance of length of film
Nominal length m	Length in a roll km	m
4 000	4	$+40_0$
6 000	6	$+60_0$
8 000	8	$+80_0$
> 8 000	> 8	1 % of nominal length

4.2.4 Inside diameter of core of a roll

The inside diameter tolerance of a core of a roll shall be within $+2_0$ mm of the nominal value.

Examples of inside diameter of core in a roll, and corresponding tolerance are given in Table 3.

4.2.5 Thickness

The thickness tolerance shall be within ± 10 % of the nominal value.

Examples of thicknesses and corresponding tolerances are given in Table 4.

Table 3 — Examples of inside diameters of a core in a roll and their tolerances

Inside diameter of core mm	Tolerance on inside diameter of core mm
76	+2 0
152	+2 0

Table 4 — Examples of thicknesses and their tolerances

Thickness		Tolerance
Nominal thickness No.	Thickness μm	μm
12	12	$\pm 1,2$
15	15	$\pm 1,5$
25	25	$\pm 2,5$

4.3 Physical properties

Films shall meet the requirements of physical properties listed in Table 5.

Table 5 — Properties of film

Properties	Unit	Test method	Requirements		Testing in accordance with subclause
			Longitudinal ^a	Transverse ^b	
Tensile strength at break	MPa	ISO 527-3	≥ 150	≥ 150	5.4
Tensile strain at break	%	ISO 527-3	≤ 200	≤ 200	5.4
Dimensional change on heating	%	ISO 15105-1 or ISO 15105-2	$\leq 6,0$	$\leq 6,0$	5.5
Coefficient of oxygen transmission ^c	$\text{fmol} \cdot 100 \mu\text{m} / (\text{m}^2 \cdot \text{s} \cdot \text{Pa})$	ISO 15105-1 or ISO 15105-2	≤ 41		5.6
Haze	%	ISO 14782	$\leq 8,0$		5.7
Wetting tension ^d	mN/m	ISO 8296	≥ 40		5.8

^a Longitudinal: direction parallel to extrusion or "machine direction".

^b Transverse: direction perpendicular to extrusion.

^c 23 °C, 0 % relative humidity.

^d The wetting tension shall only apply to films treated with corona discharge

4.4 Physiological behaviour

For applications involving food contact, the film shall conform to all applicable regulatory requirements.

5 Test methods

5.1 Conditioning and testing of specimens

Testing of tensile properties, haze and wetting tension shall be carried out in a standard atmosphere of $(23 \pm 2) ^\circ\text{C}$, $(50 \pm 5) \%$ in accordance with ISO 291, after conditioning the specimens for at least 8 h under the same conditions. Specimens for the testing of dimensional change on heating shall also be conditioned under these conditions.

5.2 Visual examination

The appearance of the film shall be checked with the naked eye.

5.3 Dimensions

5.3.1 Width

The width of the film shall be measured using a calibrated metal rule.

5.3.2 Inside diameter of core of roll

The Inside diameter of the core of a roll shall be measured using a vernier calliper.

5.3.3 Thickness


The average thickness of films shall be measured to the nearest 1 μm using a dial gauge or equivalent in accordance with ISO 4593. Five piles of films shall be used for thicknesses over 15 μm and ten piles of films shall be used for film thicknesses not more than 15 μm . The thickness of films shall be measured at ten equidistant points across the film width. The thickness shall be reported as the arithmetic average of these measurements.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

5.4 Tensile strength and tensile strain at break

Tensile strength and tensile strain at break shall be determined by tensile testing at least five specimens in accordance with ISO 527-3. The specimen dimensions are shown in Figure 1. The test speed shall be (200 ± 20) mm/min.

<https://standards.iteh.ai/catalog/standards/sist/2c941711-d75c-4c98-98cb-2a491273c15c/iso-15987-2003>

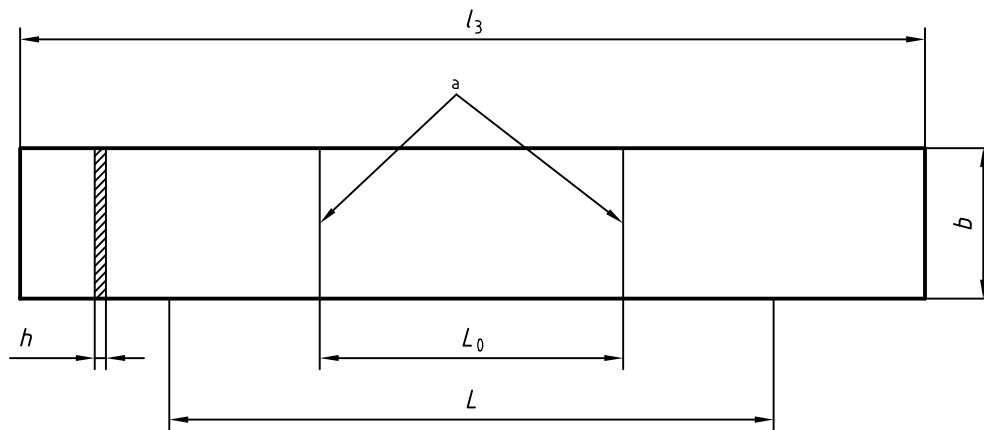

- b Width: 10 mm to 25 mm
- h Thickness: ≤ 1 mm
- L_0 Gauge length: $50 \text{ mm} \pm 0,5 \text{ mm}$
- L Initial distance between grips: $100 \text{ mm} \pm 5 \text{ mm}$
- l_3 Overall length: $\geq 150 \text{ mm}$
- ^a Gauge marks

Figure 1 — Tensile test specimen

5.5 Dimensional change on heating

5.5.1 Preparation of specimen

Prepare 5 specimens, 20 mm in width and approximately 150 mm in length for both the longitudinal direction and the transverse direction. Mark off a 100 mm gauge length centred on the specimen (each mark approximately 25 mm from the end).

5.5.2 Procedure

Suspend the specimens vertically in a circulating air oven which is kept at $(160 \pm 3) ^\circ\text{C}$ for 30 min. After removal from the oven, allow them to cool for 20 min to room temperature. Measure the length between marks. Calculate an arithmetic mean of 5 specimens using the following equation:

$$S = \frac{L_1 - L_2}{L_1} \times 100$$

where

- S is the numerical value of the dimensional change on heating, expressed as a percentage;
- L_1 is the numerical value of the length between marks before heating, expressed in millimetres;
- L_2 is the numerical value of the length between marks after heating, expressed in millimetres.

5.6 Coefficient of oxygen transmission

The coefficient of oxygen transmission shall be determined in accordance with ISO 15105-1 or ISO 15105-2 <https://standards.iteh.ai/catalog/standards/sist/2c941711-d75c-4c98-98cb->
The result is calculated by the following equation, expressed per 100 μm thickness.

$$PO_2 = O_2\text{GTR} \times (d/0,1)$$

where

- PO_2 is the numerical value of the coefficient of oxygen transmission, expressed in $\text{fmol } 100 \mu\text{m per square metre second pascal}$;
- $O_2\text{GTR}$ is the numerical value of the transmission rate of oxygen, expressed in $\text{fmol per square metre second pascal}$;
- d is the numerical value of the thickness of specimen, expressed in millimetres.

5.7 Haze

Haze shall be determined in accordance with ISO 14782.

5.8 Wetting tension

Wetting tension shall be determined in accordance with ISO 8296.

6 Packaging

Packaging and size of unit packaging shall be agreed upon between interested parties taking into account conditions of transportation and storage.