

SLOVENSKI STANDARD

SIST EN 13765:2011

01-november-2011

Nadomešča:
SIST EN 13765:2003

Plastomerne večslojne (nevulkanizirane) cevi in cevni priključki za pretok ogljikovodikov, topil in kemikalij - Specifikacija

Thermoplastic multi-layer (non-vulcanized) hoses and hose assemblies for the transfer of hydrocarbons, solvents and chemicals - Specification

Thermoplastische, mehrlagige (nicht vulkanisierte) Schläuche und Schlauchleitungen für die Förderung von Kohlenwasserstoffen, Lösungsmitteln und Chemikalien - Spezifikation

Tuyaux et assemblages flexibles thermoplastique multicouches (non vulcanisés) pour le dépotage d'hydrocarbures, solvants et produits chimiques - Spécifications

Ta slovenski standard je istoveten z: **EN 13765:2010**

ICS:

83.140.40 Gumene cevi Hoses

SIST EN 13765:2011 **en,fr,de**

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN 13765:2011](#)

<https://standards.iteh.ai/catalog/standards/sist/07aaa129-b0ed-4e4e-8c0d-2b495f79c343/sist-en-13765-2011>

EUROPEAN STANDARD

EN 13765

NORME EUROPÉENNE

EUROPÄISCHE NORM

April 2010

ICS 23.040.70

Supersedes EN 13765:2003

English Version

Thermoplastic multi-layer (non-vulcanized) hoses and hose assemblies for the transfer of hydrocarbons, solvents and chemicals - Specification

Tuyaux et assemblages flexibles thermoplastique multicouches (non vulcanisés) pour le dépotage d'hydrocarbures, solvants et produits chimiques - Spécifications

Thermoplastische, mehrlagige (nicht vulkanisierte) Schläuche und Schlauchleitungen für die Förderung von Kohlenwasserstoffen, Lösungsmitteln und Chemikalien - Spezifikation

This European Standard was approved by CEN on 18 March 2010.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: Avenue Marnix 17, B-1000 Brussels

Contents

page

Foreword.....	3
1 Scope	4
2 Normative references	4
3 Terms and definitions	5
4 Classification.....	5
5 Materials and construction	5
5.1 General.....	5
5.2 Internal and external wire	6
6 Dimensions.....	7
6.1 Internal diameters, with tolerances and minimum bend radii.....	7
6.2 Tolerance on length.....	7
7 Performance requirements of hoses and hose assemblies.....	7
7.1 Cover.....	7
7.2 Hoses	7
7.3 End fittings	8
7.4 Hose assemblies.....	8
7.5 Electrical continuity.....	9
8 Test frequency	9
9 Type tests	10
10 Marking	10
10.1 Hose marking	10
10.2 Hose assembly marking.....	10
Annex A (informative) Resistance to chemical(s) conveyed	11
Annex B (normative) Carbon steel wire	12
B.1 Manufacture.....	12
B.2 Condition of finished wire.....	12
B.3 Properties	13
Annex C (normative) Galvanized zinc coating	14
C.1 Adhesion of coating	14
C.2 Minimum mass of coating.....	14
Annex D (normative) Method of test for crush recovery.....	15
Annex E (normative) Method of test for fuel resistance	17
Annex F (normative) Method of test for thermal ageing	18
Annex G (normative) Method of test for flammability	19
Annex H (normative) Sequence of hydrostatic tests.....	21
Annex I (normative) Method of test for fitting security	22
Annex J (normative) Method of test for leak tightness	23
Annex K (normative) Type and routine tests for hoses and hose assemblies.....	24
Annex L (informative) Batch tests for hoses and hose assemblies	25

Foreword

This document (EN 13765:2010) has been prepared by Technical Committee CEN/TC 218 "Rubber and plastic hoses and hose assemblies", the secretariat of which is held by BSI.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by October 2010, and conflicting national standards shall be withdrawn at the latest by October 2010.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN 13765:2003.

Annexes B, C, D, E, F, G, H, I, J and K are normative. Annexes A and L are informative.

Compared to the 2003 version, changes have been made to the following clauses:

- in Clause 1, Scope, addition of EN 1474-2;
- addition of "NOTE 2" concerning polymeric coated wire;
- in Clause 2, Normative references, wire reference changed to EN 10088-3;
- in Table 3, length and torsion tests have been refined;
- in Table 4, electrical resistance test have been refined;
- addition of 7.5, Electrical continuity;
- in Annex C, coating weight reduced;
- in Annex K, Tests moved from hose to hose assemblies;
- in Annex L, Tests moved from hose to hose assemblies.

This document has also been presented to ISO/TC 45/SC 1 for adoption as an ISO standard under the Vienna agreement.

WARNING — Persons using this European Standard should be familiar with normal laboratory practice. This standard does not purport to address all the safety problems, if any, associated with its use. It is the responsibility of the user to establish appropriate health and safety practices and to ensure compliance with any national regulatory conditions.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and the United Kingdom.

EN 13765:2010 (E)**1 Scope**

This European Standard specifies requirements for four types of thermoplastic multi-layer (non-vulcanized) hoses and hose assemblies for carrying hydrocarbons, solvents and chemicals. It specifies bore sizes from 25 mm to 300 mm, working pressures from 4 bar¹ to 14 bar and working temperatures from –30 °C to 150 °C.

Type 1 hoses are suitable for vapour applications. Types 2 to 4 hoses are suitable for liquid applications.

NOTE 1 The attention of users is drawn to Annex A concerning the selection of the material for the inner wall of layers and any polymeric coating of the internal wire helix related to the chemical(s) to be conveyed by the hoses and/or hose assemblies.

NOTE 2 The manufacturer should be consulted where a polymeric coated internal wire is being considered for use with low conductivity hydrocarbons or chemicals.

This European Standard does not apply to hoses and hose assemblies for:

Aircraft refuelling	(EN 1361);
Fuel dispensing	(EN 1360);
Oil burners	(EN ISO 6806);
Liquefied petroleum gas and liquefied natural gas	(EN 13766);
Fire fighting	(EN ISO 14775);
Offshore liquefied natural gas	(EN 1474-2);
Refrigeration circuits	(SIST EN 13765:2011)

<https://standards.iteh.ai/catalog/standards/sist/07aaa129-b0ed-4e4e-8c0d-2b495f79c343/sist-en-13765-2011>

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 590, *Automotive fuels — Diesel — Requirements and test methods*

EN 10088-3:2005, *Stainless steels — Part 3: Technical delivery conditions for semi-finished products, bars, rods, wire, sections and bright products of corrosion resisting steels for general purposes*

EN ISO 1043-1:2001, *Plastics — Symbols and abbreviated terms — Part 1: Basic polymers and their special characteristics (ISO 1043-1:2001)*

EN ISO 1402:2009, *Rubber and plastics hoses and hose assemblies — Hydrostatic testing (ISO 1402:2009)*

EN ISO 1746, *Rubber or plastics hoses and tubing — Bending tests (ISO 1746:1998, including technical corrigendum 1:1999)*

EN ISO 2411, *Rubber — or plastics-coated fabrics — Determination of coating adhesion (ISO 2411:2000)*

1) 1 bar = 0,1 MPa.

EN ISO 4671, *Rubber and plastics hoses and hose assemblies — Methods of measurement of dimensions of hoses and the lengths of hose assemblies (ISO 4671:2007)*

EN ISO 4672, *Rubber and plastics hoses — Sub-ambient temperature flexibility tests (ISO 4672:1997)*

EN ISO 7233:2008, *Rubber and plastics hoses and hose assemblies — Determination of resistance to vacuum (ISO 7233:2006)*

EN ISO 7326, *Rubber and plastics hoses — Assessment of ozone resistance under static conditions (ISO 7326:2006)*

EN ISO 8031:2009, *Rubber and plastics hoses and hose assemblies — Determination of electrical resistance (ISO 8031:2009)*

EN ISO 8330:2008, *Rubber and plastics hoses and hose assemblies — Vocabulary (ISO 8330:2007)*

ISO 209, *Aluminium and aluminium alloys — Chemical composition*

ISO 1817:2005, *Rubber, vulcanised — Determination of the effect of liquids*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in EN ISO 8330:2008 apply.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

4 Classification

Hoses shall be classified according to working pressure and working temperature range as given in Table 1.

<https://standards.iteh.ai/catalog/standards/sist/07aaa129-b0ed-4e4e-8c0d-b495770c590c/en-13765-2010>

Table 1 — Pressure and temperature range

	Type 1	Type 2	Type 3	Type 4
Maximum working pressure (bar)	4	10	14	14
Proof pressure (bar)	6	15	21	21
Minimum burst pressure (bar)	16	40	56	56
Vacuum rating (bar)	0,5	0,9	0,9	0,9
Working temperature range (°C)	– 20 to + 60	– 30 to + 80	– 30 to + 80	– 30 to + 150
NOTE	1 bar = 0,1 MPa.			

5 Materials and construction

5.1 General

Hoses shall be constructed as shown in Figure 1 and shall consist of the following:

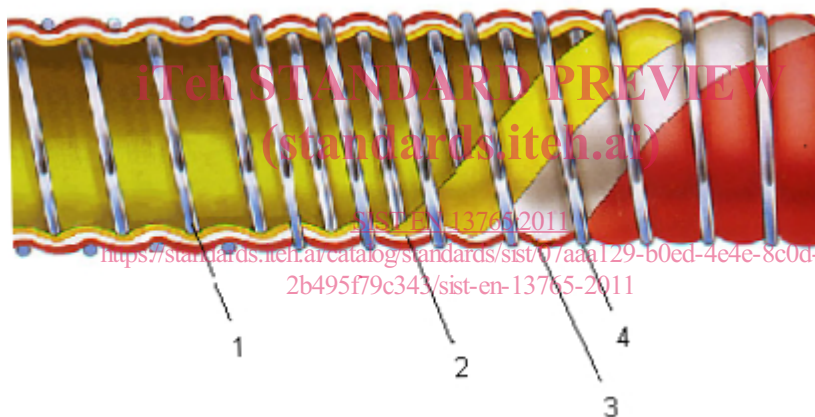
EN 13765:2010 (E)

- an internal wire helix (see 5.2);
- a multi-ply wall of layers of films and fabrics made of thermoplastics that in combination give the required properties and provide a complete seal (see also Annex A);
- a cover consisting of a fabric with abrasion resistant polymeric coating;
- an external wire helix (see 5.2).

5.2 Internal and external wire

Wire shall be chosen in accordance with its chemical resistance from one of the following materials:

- stainless steel wire conforming to EN 10088-3:2005, Table 4, numbers 1.4306, 1.4401, 1.4404 or 1.4436;
- carbon steel wire conforming to Annex B and either galvanised in accordance with Annex C or sheathed in a polymeric material of a minimum wall thickness of 0,5 mm, resistant to liquid hydrocarbon or liquid chemicals as agreed between purchaser and manufacturer (see Annex A);
- aluminium wire conforming to ISO 209.

**Key**

- 1 internal wire
- 2 film
- 3 fabric
- 4 external wire

Figure 1 — Section of a typical thermoplastic multi-layer hose

6 Dimensions

6.1 Internal diameters, with tolerances and minimum bend radii

When measured in accordance with EN ISO 4671, the values of the internal diameters of the hose shall conform to Table 2. When tested by the method described in EN ISO 1746 the values of the minimum bend radius shall be as given in Table 2. The hose shall show no sign of permanent deformation of the cross section i.e. kinking.

Table 2 — Dimensions and minimum bend radii

Dimensions in millimetres

Internal diameter	Tolerance	Minimum bend radii			
		Type 1	Type 2	Type 3	Type 4
25	± 1	125	125	200	200
32	± 1	150	150	200	200
38	± 1	150	150	200	200
40	± 1	150	150	200	200
50	± 1	200	200	225	225
65	± 2	200	200	225	225
75	± 2	280	280	300	300
80	± 2	300	300	350	350
100	± 2	400	400	400	400
125	± 2	500	500	500	—
150	± 2	575	575	575	—
200	± 3	800	800	800	—
250	± 3	1 000	1 000	1 000	—
300	+ 3	1 200	1 200	1 200	—

6.2 Tolerance on length

When tested in accordance with EN ISO 4671 the tolerance on the measured length of delivered hose assemblies shall be $^{+2}_{-1}$ %.

7 Performance requirements of hoses and hose assemblies

7.1 Cover

When tested in accordance with EN ISO 2411, the adhesion between the fabric used for the outer cover and its abrasion resistant coating shall be no less than 1,5 kN/m.

7.2 Hoses

When tested in accordance with the methods given in Table 3, the physical properties of the hoses shall conform to Table 3.

Table 3 — Physical properties of hoses

Property	Unit	Requirements	Method(s)
Proof pressure	bar	No leakage or other signs of damage at pressure given in Table 1.	EN ISO 1402 with pressure increase not less than 1,7 bar/min
Change in length at proof pressure (max.)	%	10	EN ISO 1402:2009, clause 8.2 with the initial hose length measured when the hose is pressurized to 0,7 bar for 2 min
Twist at proof pressure (max.)	°/m	10	EN ISO 1402:2009, clause 8.2 with the initial reading taken when the hose is pressurized to 0,7 bar for 2 min
Burst pressure	bar	≥ Values in Table 1	EN ISO 1402
Bend	—	No leakage or visible damage when the hose is bent to the radius given in Table 2 and subjected to proof pressure.	EN ISO 1746
Vacuum	bar	No damage after 30 min when subjected to values in Table 1.	EN ISO 7233:2008, method B
Crush recovery (max.)	%	3	Annex D
Fuel resistance	bar	No leakage at proof pressure	Annex E
Ozone resistance 72 h at 40 °C	—	No cracking observed at x 2 magnification	EN ISO 7326
Thermal ageing	—	No leakage at proof pressure given in Table 1.	Annex F
Flammability	—	See Annex G.	Annex G
Low temperature flexibility	—	Test at minimum temperature given in Table 1	EN ISO 4672

7.3 End fittings

End fittings shall be made from materials depending on their chemical resistance to the product conveyed.

For all types of end fittings, the part of the fitting that enters the hose and forms the means by which the fitting is connected to the hose shall be provided with scrolls or protrusions on the surface that correspond to the pitch of the internal helix wire of the hose.

7.4 Hose assemblies

Hose assemblies shall be fitted with end fittings as described in 7.3.

End fittings shall be attached to the hose by one of the following methods:

- a) by the use of a seal and a metal ferrule which is swaged or crimped;

b) by the use of a thermoset resin e.g. epoxy and a metal ferrule that is swaged or crimped.

When tested in accordance with the methods given in Table 4, hose assemblies shall conform to Table 4.

Table 4 — Physical properties of hose assemblies

Property	Unit	Requirements	Method(s)
Proof pressure	Bar	No leakage or other signs of weakness at pressure given in Table 1	EN ISO 1402 with a pressure increase not less than 1,7 bar/min
Bend	—	No leakage or visible damage when the hose is bent to the radius given in Table 2 and subjected to proof pressure	EN ISO 1746
Series of hydrostatic tests	Bar % °/m	≥ burst pressure given in Table 1, change in length given in Table 3 twist as given in Table 3	Annex H
Security of end fitting	Bar	No leakage at proof pressure given in Table 1	Annex I and EN ISO 1402
Electrical resistance between end fittings	Ω	≤ 2,5 ohm/m for sizes less than 50 mm. ≤ 1,0 ohm/m for the 50 mm size and above sizes	EN ISO 8031:2009, 4.7
Burst pressure	Bar	≥ value given in Table 1	EN ISO 1402
Leak tightness	—	No leakage of air when subjected to 3,5 bar for 5 min	Annex J

7.5 Electrical continuity

There shall be electrical continuity between both internal and external wires and the end fittings. Where a wire is sheathed in polymeric material the sheath shall be stripped back for some of the length that engages with the fittings or the ferrule to ensure continuity.

Manufacturers shall demonstrate by testing or calculation that the measured overall electrical resistance of the hose assembly incorporates both internal and external wires being part of the circuit.

For the transfer of non conductive fluids the use of a hose with a non polymeric coated internal wire should be considered.

8 Test frequency

Routine tests shall be carried out on each hose assembly and in accordance with Annex K.

It is recommended that batch tests are carried out for every 10 000 m of manufacture or once a year, varying the sizes and types and in accordance with Annex L.