



DRAFT INTERNATIONAL STANDARD ISO/DIS 17640.2

ISO/TC 44/SC 5

Secretariat: **ANSI**

Voting begins on:
2003-04-03

Voting terminates on:
2003-06-03

INTERNATIONAL ORGANIZATION FOR STANDARDIZATION • МЕЖДУНАРОДНАЯ ОРГАНИЗАЦИЯ ПО СТАНДАРТИЗАЦИИ • ORGANISATION INTERNATIONALE DE NORMALISATION

Non-destructive examination of welds — Ultrasonic examination of welded joints

Contrôle non destructif des assemblages soudés — Contrôle par ultrasons des assemblages soudés

ICS 25.160.40

iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO/DIS 17640.2](https://standards.iteh.ai/catalog/standards/sist/fbd40f44-3a9d-452c-880d-9ac1d3184ca5/iso-dis-17640-2)

<https://standards.iteh.ai/catalog/standards/sist/fbd40f44-3a9d-452c-880d-9ac1d3184ca5/iso-dis-17640-2>

To expedite distribution, this document is circulated as received from the committee secretariat. ISO Central Secretariat work of editing and text composition will be undertaken at publication stage.

Pour accélérer la distribution, le présent document est distribué tel qu'il est parvenu du secrétariat du comité. Le travail de rédaction et de composition de texte sera effectué au Secrétariat central de l'ISO au stade de publication.

THIS DOCUMENT IS A DRAFT CIRCULATED FOR COMMENT AND APPROVAL. IT IS THEREFORE SUBJECT TO CHANGE AND MAY NOT BE REFERRED TO AS AN INTERNATIONAL STANDARD UNTIL PUBLISHED AS SUCH.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO/DIS 17640.2](https://standards.iteh.ai/catalog/standards/sist/fbd40f44-3a9d-452c-880d-9ac1d3184ca5/iso-dis-17640-2)

<https://standards.iteh.ai/catalog/standards/sist/fbd40f44-3a9d-452c-880d-9ac1d3184ca5/iso-dis-17640-2>

Copyright notice

This ISO document is a Draft International Standard and is copyright-protected by ISO. Except as permitted under the applicable laws of the user's country, neither this ISO draft nor any extract from it may be reproduced, stored in a retrieval system or transmitted in any form or by any means, electronic, photocopying, recording or otherwise, without prior written permission being secured.

Requests for permission to reproduce should be addressed to either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Reproduction may be subject to royalty payments or a licensing agreement.

Violators may be prosecuted.

Contents	Page
Foreword	v
Introduction.....	vi
1 Scope	1
2 Normative references	1
3 Terms and definitions.....	2
4 Symbols and abbreviated terms	2
5 Information requirements.....	3
5.1 Information required prior to testing	3
5.2 Additional pre-test information	3
5.3 Written examination procedure	4
6 Requirements for personnel and equipment	4
6.1 Personnel qualifications.....	4
6.2 Equipment	4
6.3 Probe parameters	4
6.3.1 Frequency.....	4
6.3.2 Angles of incidence	4
6.3.3 Adaptation of probes to curved scanning surfaces.....	4
6.3.4 Coupling media	5
7 Examination volume	5
8 Preparation of scanning surfaces	5
9 Parent material examination	5
10 Range and sensitivity setting.....	6
10.1 General	6
10.2 Reference level.....	7
10.3 Evaluation levels	8
10.4 Transfer correction	8
10.5 Signal to noise ratio.....	8
11 Examination levels.....	8
12 Examination technique.....	9
12.1 General	9
12.2 Manual scan path.....	9
12.3 Examination for imperfections perpendicular to the examination surface	9
12.4 Location of indications.....	9
12.5 Evaluation of indications.....	10
12.5.1 General	10
12.5.2 Maximum echo amplitude	10
12.5.3 Indication length	10
12.5.4 Indication height	10
12.5.5 Characterization of imperfections	10
13 Examination report	11
13.1 General	11
13.2 General data	11
13.3 Information relating to equipment	11
13.4 Information relating to examination technique.....	11
13.5 Results of the examination	12

Annex A (normative) Examination levels for various types of welded joints 13
Bibliography 27

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO/DIS 17640.2](https://standards.iteh.ai/catalog/standards/sist/fbd40f44-3a9d-452c-880d-9ac1d3184ca5/iso-dis-17640-2)

<https://standards.iteh.ai/catalog/standards/sist/fbd40f44-3a9d-452c-880d-9ac1d3184ca5/iso-dis-17640-2>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

ISO 17640.2 was prepared by Technical Committee ISO/TC 44, *Welding and allied processes*, Subcommittee SC 5, *Testing and inspection of welds*.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO/DIS 17640.2](https://standards.iteh.ai/catalog/standards/sist/fbd40f44-3a9d-452c-880d-9ac1d3184ca5/iso-dis-17640-2)

<https://standards.iteh.ai/catalog/standards/sist/fbd40f44-3a9d-452c-880d-9ac1d3184ca5/iso-dis-17640-2>

Introduction

This International Standard describes general methods for ultrasonic examination, using standard criteria, of the most commonly used welded joints. This standard specifies requirements for equipment, surface preparation, inspection performance and reporting. The parameters specified, in particular those for the probes, are compatible with the requirements of EN 1712 and EN 1713, and are suitable for use with other acceptance criteria standard. The inspection techniques are suitable for the detection of weld imperfections specified in typical weld acceptance standards. The methods used for ultrasonic assessment of indications and acceptance criteria shall be specified for example by reference to an application standards.

NOTE If the acceptance criteria require a more precise determination of the height and nature of the defect, e.g. when fitness for purpose criteria are applied, this may necessitate the use of techniques outside the scope of this standard.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO/DIS 17640.2](https://standards.iteh.ai/catalog/standards/sist/fbd40f44-3a9d-452c-880d-9ac1d3184ca5/iso-dis-17640-2)

<https://standards.iteh.ai/catalog/standards/sist/fbd40f44-3a9d-452c-880d-9ac1d3184ca5/iso-dis-17640-2>

Non-destructive examination of welds — Ultrasonic examination of welded joints

1 Scope

This International Standard specifies methods for manual ultrasonic examination of fusion welded joints in metallic materials, greater than or equal to 8 mm thick, which exhibit low ultrasonic attenuation (especially that due to scatter). This standard is primarily intended for full penetration welded joints where both the welded and parent materials are ferritic.

This standard specifies four examination levels, each corresponding to a different probability of detection of imperfections. Guidance on the selection of examination levels A, B and C is given in annex A. The requirements for D, the fourth examination level, which is intended for special applications, are in accordance with the general requirements of this standard but shall be specified prior to testing, for example by reference to an application standard.

This standard may be used for assessment of indications, for acceptance purposes, by either of the following methods:

- 1) Evaluation based primarily on length and echo amplitude of the signal indication;
- 2) Evaluation based on characterization and sizing of the indication by probe movement methods.

The techniques described in this standard may be specified, for example in an application standard, for use with:

- materials other than those stated;
- partial penetration welds;
- automated equipment.

In each case, the technique should be verified as having adequate sensitivity.

NOTE Where material dependent ultrasonic values are specified in this standard they are based on steels having an ultrasonic sound velocity of 5920 ± 50 m/s for longitudinal waves, and 3255 ± 30 m/s for transverse waves. This is to be taken into account when examining materials with a different velocity.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 5577, *Non-destructive testing - Ultrasonic inspection - Vocabulary*

ISO 5817, *Arc-welded joints in steel - Guidance on quality levels for imperfections*

ISO/DIS 17635, *Non-destructive testing of welds - General rules for metallic materials*

ISO/DIS 17637, *Non-destructive testing welds - Visual examination of fusion welded joints*

EN 583-1, *Non-destructive testing - Ultrasonic examination - Part 1: General principles*

EN 583-2, *Non-destructive testing - Ultrasonic examination - Part 2: Sensitivity and range setting*

EN 1712, *Non-destructive examination of welds - Ultrasonic examination of welded joints - Acceptance levels*

EN 1713, *Non-destructive examination of welds - Ultrasonic examination - Characterization of indications in welds*

EN 12668 (all parts), *Non-destructive testing - Characterization and verification of ultrasonic examination equipment*

3 Terms and definitions

For the purposes of this International Standard, the terms and definitions given in ISO/DIS 17635 and ISO 5577 apply.

4 Symbols and abbreviated terms

The symbols and abbreviated terms used in this International standard are given in table 1.

Table 1 — Symbols and abbreviated terms

Symbol	Term	Unit
t	Thickness of parent material (at the thinnest point)	mm
D_{DSR}	Diameter of a disc shaped reflector	mm
D_{SDH}	Diameter of a side-drilled hole	mm
l	Indication length	mm
h	Extension of an in the depth direction	mm
x	Position of an indication in the longitudinal direction	mm
y	Position of an indication in the transverse direction	mm
z	Position of an indication in the depth direction	mm
l_z	Projected length of the indication in the z-direction	mm
l_x	Projected length of the indication in the x-direction	mm
l_y	Projected length of the indication in the y-direction	mm
p	Full skip distance	mm

5 Information requirements

5.1 Information required prior to testing

Prior to testing, the following items shall be specified (where applicable):

- method for setting the reference level;
- manufacturing and operation stage(s) at which the examination is to be carried out;
- examination level;
- acceptance levels;
- method to be used for evaluation of indications;
- qualification of personnel;
- extent of the examination for transverse indications;
- requirements for tandem examination;
- parent material examination prior to and/or after welding;
- requirements for written examination procedures.

5.2 Additional pre-test information

Prior to testing, the operator shall have access to the following information:

- written examination procedure, if required (see 5.3);
- type(s) of parent material and product form (i.e. cast, forged, rolled);
- manufacturing or stage of operation, including any heat treatment, at which examination is to be made;
- time and extent of any post-weld heat treatment;
- joint preparation and dimensions;
- requirements for surface conditions;
- welding procedure or relevant information on the welding process;
- reporting requirements;
- acceptance levels;
- extent of examination, including requirements for transverse indications, if relevant;
- examination level;
- personnel qualification level;
- procedures for corrective actions when unacceptable indications are revealed.

NOTE Visual examination in accordance with ISO 17637 may be specified prior to any ultrasonic examination. In this case, the result shall also be made available.

5.3 Written examination procedure

This standard will normally satisfy the need for a written examination procedure. Where additional written procedures are required, they shall be specified prior to testing, for example by reference to an application standard.

6 Requirements for personnel and equipment

6.1 Personnel qualifications

Ultrasonic examination of welds and the evaluation of results for final acceptance shall be performed by qualified and capable personnel. It is recommended that personnel are qualified in accordance with ISO 9712 or an equivalent standard at an appropriate level in the relevant industry sector.

6.2 Equipment

All ultrasonic testing equipment shall comply with the requirements of EN 12668 (all parts).

6.3 Probe parameters

6.3.1 Frequency

The frequency shall be within the range 2 MHz to 5 MHz, and selected to comply with the specified acceptance levels.

For the initial examination, when the evaluation is carried out according to acceptance levels based on length and amplitude e.g. EN 1712, the frequency shall be as low as possible within the above range. Higher frequencies may be used to improve range resolution if necessary when using standards for acceptance levels based on characterization of imperfections e.g. EN 1713.

NOTE Frequencies of approximately 1 MHz may be used for examination of long sound paths where the material shows above average attenuation.

6.3.2 Angles of incidence

When examination is carried out with transverse waves and techniques that require the ultrasonic beam to be reflected from an opposite surface, care shall be taken to ensure that the incident angle of the beam, with the opposite reflecting surface, is not less than 35 ° and preferably not greater than 70 °. Where more than one probe angle is used, at least one of the angle probes used shall conform with this requirement. One of the probe angles used shall ensure that the weld fusion faces are examined at, or as near as possible to, normal incidence. When the use of two or more probe angles is specified, the difference between the nominal beam angles shall be 10 ° or greater.

Angles of incidence at the probe and opposite reflecting surface, when curved, may be determined by drawing a sectional view of the weld or in accordance with the methods given in EN 583-2. Where angles of incidence cannot be determined as specified by this standard the examination report shall contain a comprehensive description of the scans used and the extent of any incomplete coverage caused together with an explanation of the difficulties encountered.

6.3.3 Adaptation of probes to curved scanning surfaces

The gap between test surface and bottom of the probe shoe shall not be greater than 0,5 mm. For cylindrical or spherical surfaces this requirement will normally be met when $D \geq 15a$, where D is the diameter in millimetres of the component and a is the dimension in millimetres of the probe shoe in the direction of examination.

If this requirement cannot be met the probe shoe shall be adapted to the surface and the sensitivity and range shall be set accordingly.

6.3.4 Coupling media

The coupling media shall be in accordance with EN 583-1.

7 Examination volume

The examination volume (see figure 1) is defined as the zone which includes the weld and parent material for at least 10 mm on each side of the weld, or the width of the heat affected zone, whichever is greater.

In all cases, scanning shall cover the whole examination volume. If individual sections of this volume cannot be covered in at least one scanning direction, or if the angles of incidence with the opposite surface do not meet the requirements of 6.3.2, alternative or supplementary ultrasonic techniques or other non-destructive methods shall be specified. This may require removal of the weld reinforcement.

Alternative or supplementary techniques may require examination using twin crystal angle beam probes, creeping wave probes and additional ultrasonic techniques. Other non-destructive methods may include liquid penetrant, magnetic particle and radiographic examination. In selecting alternative or supplementary methods, due consideration should be given to the type of weld and probable orientation of any imperfections to be detected.

8 Preparation of scanning surfaces

The width of the scanning surfaces should be sufficient to enable full coverage of the examination volume by scanning from one surface (see figure 1). The width of the scanning surfaces may be smaller if full coverage of the examination volume can be achieved by scanning from both the upper and the lower surfaces of the joint.

The scanning surfaces shall be even and free from foreign matter likely to interfere with probe coupling (e.g. rust, loose scale, weld spatter, notches, grooves). The maximum permitted gap between the probe and the scanning surface, from which the evaluation of indications is to be carried out, shall be 0,5 mm. Any unevenness in the test surface which exceeds 0,5 mm shall be dressed in order to ensure these requirements.

Scanning surfaces and surfaces from which the sound beam is reflected may be assumed to be satisfactory if the surface roughness, R_a , is not greater than 6,3 μm for machined surfaces, or not greater than 12,5 μm for shot-blasted surfaces.


Local variations in surface contour, e.g. along the edge of the weld, which result in a gap beneath the probe of up to 1 mm, are only be permitted if at least one additional probe angle is employed from the affected side at the weld. This additional scanning is necessary to compensate for the reduced weld coverage that occurs with such a gap.

9 Parent material examination

The parent material, in the scanning zone area, shall be examined with straight beam probes prior to or after welding, unless it can be demonstrated (e.g. by previous examination during the fabrication process) that examination of the weld using an angle probe will not be influenced by the presence of imperfections or high attenuation.

If imperfections are found in the parent material, their influence on the subsequent weld examination using an angle probe shall be assessed and, if necessary, the weld examination techniques shall be adjusted. When ultrasonic examination of the weld is seriously affected by the presence of imperfections in the parent material, other examination methods (e.g. radiography) shall be considered.

All dimensions in millimetres

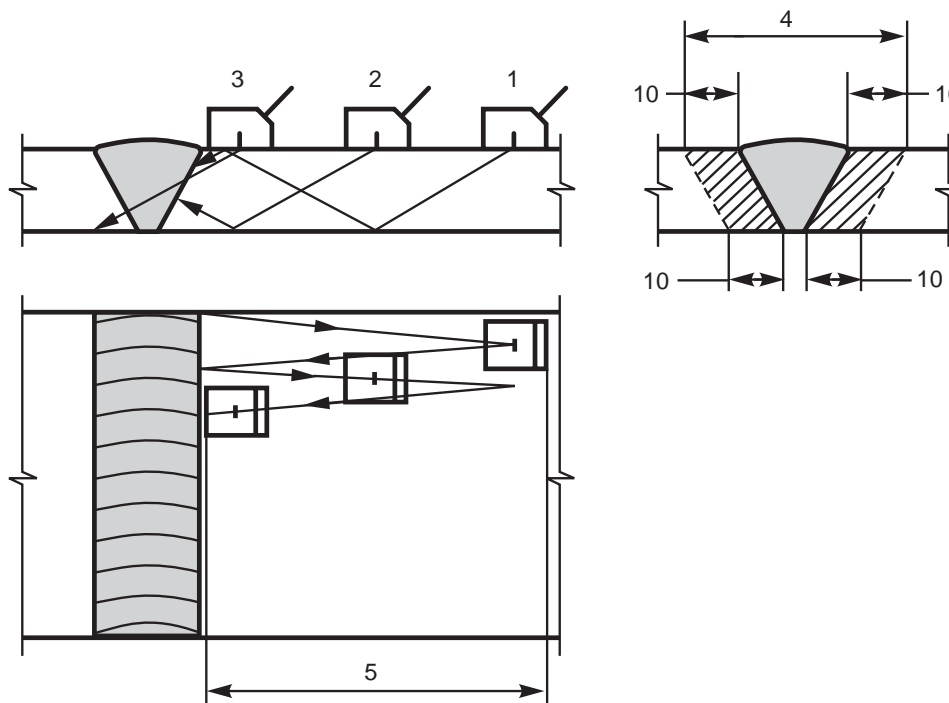

- 1.— Angle probe position 1
- 2.— Angle probe position 2
- 3.— Angle probe position 3
- 4 – Width of examination volume
- 5 – Scanning surface

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO/DIS 17640.2](https://standards.iteh.ai/catalog/standards/sist/fbd40f44-3a9d-452c-880d-9ac1d3184ca5/iso-dis-17640-2)

[https://standards.iteh.ai/catalog/standards/sist/fbd40f44-3a9d-452c-880d-](https://standards.iteh.ai/catalog/standards/sist/fbd40f44-3a9d-452c-880d-9ac1d3184ca5/iso-dis-17640-2)

[9ac1d3184ca5/iso-dis-17640-2](https://standards.iteh.ai/catalog/standards/sist/fbd40f44-3a9d-452c-880d-9ac1d3184ca5/iso-dis-17640-2)

Figure 1 — Example of examination volume to be covered when scanning for longitudinal indications

10 Range and sensitivity setting

10.1 General

The range and sensitivity shall be set prior to each examination in accordance with this standard and EN 583-2. Checks to confirm these settings shall be performed at least every 4 hours and on completion of the examination. Checks shall also be carried out whenever a system parameter is changed or changes in the equivalent settings are suspected.

If deviations in range or sensitivity are found during these checks, corrections shall be made in accordance with table 2.