INTERNATIONAL STANDARD

ISO 8458-2

Second edition 2002-08-01

Steel wire for mechanical springs — Part 2: Patented cold-drawn non-alloy steel wire

Fils en acier pour ressorts mécaniques —

iTeh STANDARD PRE VIEW (standards.iteh.ai)

ISO 8458-2:2002 https://standards.iteh.ai/catalog/standards/sist/c53c2685-d6bc-4031-b39d-c68afb00d306/iso-8458-2-2002



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 8458-2:2002 https://standards.iteh.ai/catalog/standards/sist/c53c2685-d6bc-4031-b39dc68afb00d306/iso-8458-2-2002

© ISO 2002

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.ch
Web www.iso.ch

Printed in Switzerland

Contents Page Foreword 1 Scope1 2 3 Classification and designation......2 Dimensions and supply conditions2 4.1 4.2 4.3 Cast of the wire ______2 4.4 Requirements......3 5 5.1 Material3 Coating and surface finish4 5.2 Surface quality4 5.3 5.4 Mechanical properties......5 5.5 Technological properties......7 Inspection and testing eh. STANDARD PREVIEW 8 6 Test methods and other requirements......8 6.1 6.2

ISO 8458-2:2002

https://standards.iteh.ai/catalog/standards/sist/c53c2685-d6bc-4031-b39d-c68afb00d306/iso-8458-2-2002

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 3.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this part of ISO 8458 may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 8458-2 was prepared by Technical Committee ISO/TC 17, Steel, Subcommittee SC 17, Steel wire rod and wire products.

This second edition cancels and replaces the first edition (iso 8458-2:1989) which has been technically revised.

(standards.iteh.ai)
ISO 8458 consists of the following parts, under the general title Steel wire for mechanical springs:

- Part 1: General requirements https://standards.iteh.ai/catalog/standards/sist/c53c2685-d6bc-4031-b39d-
- Part 2: Patented cold-drawn non-alloy steel wire
- Part 3: Oil-hardened and tempered wire

Steel wire for mechanical springs —

Part 2:

Patented cold-drawn non-alloy steel wire

1 Scope

This part of ISO 8458 specifies requirements for cold-drawn non-alloy steel wire for the manufacture of mechanical springs for static duty and dynamic duty applications, complying with the general requirements of ISO 8458-1.

2 Normative references

The following normative documents contain provisions which, through reference in this text, constitute provisions of this part of ISO 8458. For dated references, subsequent amendments to, or revisions of, any of these publications do not apply. However, parties to agreements based on this part of ISO 8458 are encouraged to investigate the possibility of applying the most recent editions of the normative documents indicated below. For undated references, the latest edition of the normative document referred to applies. Members of ISO and IEC maintain registers of currently valid International Standards.

ISO 7989:1988, Zinc coatings for steel wire https://standards.iteh.ai/catalog/standards/sist/c53c2685-d6bc-4031-b39d-

ISO 8458-1, Steel wire for mechanical springs Part 1. General requirements

ISO 16120-1:2001, Non-alloy steel wire rod for conversion to wire — Part 1: General requirements

ISO 16120-2:2001, Non-alloy steel wire rod for conversion to wire — Part 2: Specific requirements for general purpose wire rod

ISO 16120-4:2001, Non-alloy steel wire rod for conversion to wire — Part 4: Specific requirements for rod for special applications

© ISO 2002 – All rights reserved

3 Classification and designation

The wire diameter ranges and tensile strength grades normally available for static duty and dynamic duty are shown in Table 1.

Table 1 — Tensile strength grades and diameter range

Tensile strength ^a	Static duty	Diameter range	Dynamic duty	Diameter range	
Low tensile strength	SL	1-10	_	_	
Medium tensile strength	SM	0,30-20,00	DM	0,08-20,00	
High tensile strength	SH	0,30-20,00	DH	0,05-20,00	
^a For specific applications, other tensile strength requirements may be agreed.					

4 Dimensions and supply conditions

4.1 Dimensional tolerances

The dimensional tolerances on wire diameters shall be in accordance with ISO 8458-1.

4.2 Welds

iTeh STANDARD PREVIEW

The wire of a unit coil shall consist of one single length of wire originating from only one heat.

For coiled and cut lengths of wire, welds prior to the dast patenting operation are allowed. All other welds shall be removed or, if so agreed, properly marked teh ai/catalog/standards/sist/c53c2685-d6bc-4031-b39d-c68afb00d306/iso-8458-2-2002

4.3 Cast of the wire

- **4.3.1** The wire shall be uniformly cast.
- **4.3.2** By agreement, for sizes up to 5 mm, the cast requirements may be considered as being fulfilled if the following statement is satisfied.

An individual ring taken from the coil and freely hung on a hook may show an axial displacement, f, at the ends of the ring (see Figure 1).

This displacement, f, shall not exceed a value given by the following inequality:

$$f \leqslant 0.2D/(4\sqrt{d})$$

where

- f is the axial displacement in millimetres;
- D is the diameter of a free ring in millimetres;
- d is the nominal diameter of the wire in millimetres.

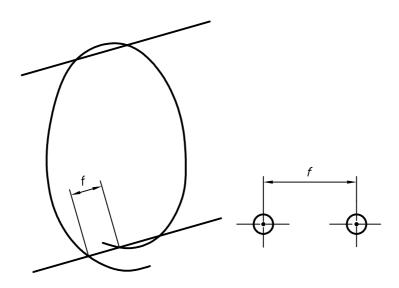


Figure 1 — Cast of wire

4.4 Straightness of cut lengths

For the straightness of cut lengths, the following requirements apply.

For 500 mm test lengths – 0,5 mm maximum deviation from straightness;

For 1 000 mm test lengths – 2 mm maximum deviation from straightness. (Standards.iten.al)

NOTE 1 000 mm test lengths are recommended for wire diameter above 6 mm and 500 mm test lengths for those below.

ISO 8458-2:2002

https://standards.iteh.ai/catalog/standards/sist/c53c2685-d6bc-4031-b39d-

5 Requirements

c68afb00d306/iso-8458-2-2002

5.1 Material

5.1.1 General

Spring wire shall be made from steel complying with ISO 16120-1.

For grades SL, SM and SH the steel shall comply to ISO 16120-2.

For grades DM and DH the steel shall comply with ISO 16120-4.

5.1.2 Chemical composition

The steel is characterized by the heat analysis, which shall be in accordance with the values of Table 2. The permissible deviation of the product analysis from the heat analysis shall be in accordance with ISO 16120-2 or ISO 16120-4.

Table 2 — Chemical composition, % (m/m) (heat analysis)

Grade	Ca	Si	Mn ^b	P max.	S max.	Cu max.
SL, SM, SH	0,35-1,00	0,10-0,30	0,30-1,20	0,030	0,030	0,20
DH. DM	0.45-1.00	0.10-0.30	0.30-1.20	0.020	0.025	0.12

^a Such a wide range is stipulated I order to accommodate the whole range of sizes. For individual sizes the carbon range is substantially more restricted.

© ISO 2002 – All rights reserved

b The range of manganese content in the table is so wide in order to cope with various processing situations and the broad size range. The real figures per size shall be more restricted.

5.2 Coating and surface finish

5.2.1 The spring wire may be supplied lime coated, borax coated or phosphate coated, and may be produced by either dry drawing or wet drawing.

A metallic coating, where required, be it copper, zinc or zinc/aluminium alloy, shall be applied to the wire.

Other coatings may be agreed upon between the purchaser and the manufacturer.

If no specific surface finish is nominated, it shall be at the manufacturer's discretion.

5.2.2 In the case of zinc and zinc/aluminium alloy coated spring wire, the mass of zinc or zinc/aluminium alloy coating shall satisfy the minimum values specified in Table 3.

Table 3 — Minimum required zinc or zinc/aluminium alloy coating mass

Diameter, d, mm	Coating mass, g/m ²
0,20 ≤ <i>d</i> < 0,25	20
0,25 ≤ <i>d</i> < 0,40	25
0,40 ≤ <i>d</i> < 0,50	30
0,50 ≤ <i>d</i> < 0,60	35
0,60 ≤ d < 0,70	RD PRE 40 EW
$0.70 \leqslant d < 0.80$	ds itab ai) 45
$0.80 \leqslant d < 0.90$	50
0,90 ≤ <i>d</i> < 1,00 <u>ISO 84</u>	58-2 <u>:2002</u> 55
https//0012/a/deit/20ai/catalog/stand	ards/sist/c53c2685-d60c-4031-b39d-
1,20 ≤ <i>d</i> < 1,40	65
1,40 ≤ <i>d</i> < 1,65	70
1,65 <i>≤ d</i> < 1,85	75
1,85 ≤ <i>d</i> < 2,15	80
2,15 ≤ <i>d</i> < 2,50	85
2,50 ≤ <i>d</i> < 2,80	95
2,80 ≤ <i>d</i> < 3,20	100
3,20 ≤ <i>d</i> < 3,80	105
3,80 ≤ <i>d</i> ≤ 10,00	110

Other levels may be agreed upon between supplier and manufacturer. The adherence of the coating shall be tested by a wrapping or bend test (see ISO 7989).

NOTE The usual coating processes may alter the properties of the steel wire. The ductility and endurance of the wire may thereby be reduced so that one cannot guarantee for zinc coated or zinc/aluminium alloy coated spring steel wire the same torsion values or expect the same dynamic performance (DM and DH) as for the respective uncoated material.

5.3 Surface quality

5.3.1 Surface quality tests shall be applied to wires intended for use in dynamic duty spring only (DM and DH). The radial depth of seams or other surface discontinuities shall be not greater than 1 % of the nominal diameter of the wire.

5.3.2 For spring wire grade DH and DM, the cross-section shall show no completely decarburized layer and partial decarburization shall not have an average radial depth greater than 1,5 % of the nominal diameter of the wire.

5.4 Mechanical properties

The tensile strength of the wire shall be in accordance with Table 4 for the appropriate tensile strength grade, nominal wire diameter and type of spring use.

Table 4 — Tensile strength requirements

Nominal Diameter	Tensile strength, N/mm ²					
mm ^a	Type SL	Type SM	Type DM	Type SH	Type DH ^b	
0,05					2 800 to 3 520	
0,06					2 800 to 3 520	
0,07					2 800 to 3 520	
0,08			2 780 to 3 100		2 800 to 3 480	
0,09			2 740 to 3 060		2 800 to 3 430	
0,10			2 710 to 3 020		2 800 to 3 380	
0,11	iTeh	STANDA	2 690 to 3 000	EW	2 800 to 3 350	
0,12	TICH		2 660 to 2 960		2 800 to 3 320	
0,14		(standard	2 620 to 2 910		2 800 to 3 250	
0,16		ISO 8458	2.570 to 2 860		2 800 to 3 200	
0,18	https://standards	s.iteh.ai/catalog/standar		-4031-b39d-	2 800 to 3 160	
0,20		c68afb00d306/is	2 500 to 2 790		2 800 to 3 110	
0,22			2 470 to 2 760		2 770 to 3 080	
0,25			2 420 to 2 710		2 720 to 3 010	
0,28			2 390 to 2 670		2 680 to 2 970	
0,30		2 370 to 2 650	2 370 to 2 650	2 660 to 2 940	2 660 to 2 940	
0,32		2 350 to 2 630	2 350 to 2 630	2 640 to 2 920	2 640 to 2 920	
0,34		2 330 to 2 600	2 330 to 2 600	2 610 to 2 890	2 610 to 2 890	
0,36		2 310 to 2 580	2 310 to 2 580	2 590 to 2 890	2 590 to 2 890	
0,38		2 290 to 2 560	2 290 to 2 560	2 570 to 2 850	2 570 to 2 850	
0,40		2 270 to 2 550	2 270 to 2 550	2 560 to 2 830	2 570 to 2 830	
0,43		2 250 to 2 520	2 250 to 2 520	2 530 to 2 800	2 570 to 2 800	
0,45		2 240 to 2 500	2 240 to 2 500	2 510 to 2 780	2 570 to 2 780	
0,48		2 220 to 2 480	2 240 to 2 500	2 490 to 2 760	2 570 to 2 760	
0,50		2 200 to 2 470	2 200 to 2 470	2 480 to 2 740	2 480 to 2 740	
0,53		2 180 to 2 450	2 180 to 2 450	2 460 to 2 720	2 460 to 2 720	
0,56		2 170 to 2 430	2 170 to 2 430	2 440 to 2 700	2 440 to 2 700	
0,60		2 140 to 2 400	2 140 to 2 400	2 410 to 2 670	2 410 to 2 670	
0,63		2 130 to 2 380	2 130 to 2 380	2 390 to 2 650	2 390 to 2 650	

© ISO 2002 – All rights reserved