



SLOVENSKI STANDARD
SIST EN 14151:2010
01-september-2010

Geosintetika - Ugotavljanje razpočne trdnosti

Geosynthetics - Determination of burst strength

Geokunststoffe - Bestimmung der Berstdruckfestigkeit

Géosynthétiques - Détermination de la résistance à l'éclatement

Ta slovenski standard je istoveten z: EN 14151:2010

[SIST EN 14151:2010](https://standards.iteh.ai/catalog/standards/sist/68441c1f-7e1b-481f-bdb5-b08c3025c1f6/sist-en-14151-2010)

<https://standards.iteh.ai/catalog/standards/sist/68441c1f-7e1b-481f-bdb5-b08c3025c1f6/sist-en-14151-2010>

ICS:

59.080.70 Geotekstilije Geotextiles

SIST EN 14151:2010 **en,de**

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN 14151:2010

<https://standards.iteh.ai/catalog/standards/sist/68441c1f-7e1b-481f-bdb5-b08c3025c1f6/sist-en-14151-2010>

EUROPEAN STANDARD

EN 14151

NORME EUROPÉENNE

EUROPÄISCHE NORM

June 2010

ICS 59.080.70; 91.100.50

English Version

Geosynthetics - Determination of burst strength

Géosynthétiques - Détermination de la résistance à
l'éclatement

Geokunststoffe - Bestimmung der Berstdruckfestigkeit

This European Standard was approved by CEN on 12 May 2010.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

[SIST EN 14151:2010](https://standards.iteh.ai/catalog/standards/sist/68441c1f-7e1b-481f-bdb5-b08c3025c1f6/sist-en-14151-2010)

<https://standards.iteh.ai/catalog/standards/sist/68441c1f-7e1b-481f-bdb5-b08c3025c1f6/sist-en-14151-2010>



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: Avenue Marnix 17, B-1000 Brussels

Contents

Page

Foreword.....	3
1 Scope	4
2 Normative references	4
3 Terms and definitions	4
4 Principle.....	4
5 Apparatus	4
5.1 General.....	4
5.2 Cell	5
5.3 Deflection measurement.....	5
5.4 Pressure measurement	6
5.5 Volume control.....	6
6 Specimens	6
7 Conditioning.....	6
8 Procedure	6
8.1 General.....	6
8.2 Volume control.....	7
8.3 Diaphragm correction	7
9 Calculations.....	7
10 Test report	9
Bibliography.....	10

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN 14151:2010](#)

<https://standards.iteh.ai/catalog/standards/sist/68441c1f-7e1b-481f-bdb5-b08c3025c1f6/sist-en-14151-2010>

Foreword

This document (EN 14151:2010) has been prepared by Technical Committee CEN/TC 189 “Geosynthetics”, the secretariat of which is held by NBN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by December 2010, and conflicting national standards shall be withdrawn at the latest by December 2010.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document has been prepared under a mandate given to CEN by the European Commission and the European Free Trade Association.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and the United Kingdom.

iTeh STANDARD PREVIEW **(standards.iteh.ai)**

[SIST EN 14151:2010](https://standards.iteh.ai/catalog/standards/sist/68441c1f-7e1b-481f-bdb5-b08c3025c1f6/sist-en-14151-2010)

<https://standards.iteh.ai/catalog/standards/sist/68441c1f-7e1b-481f-bdb5-b08c3025c1f6/sist-en-14151-2010>

EN 14151:2010 (E)**1 Scope**

This European Standard specifies a method for the determination of bi-axial properties (burst strength) of geosynthetics.

This method applies to geotextiles, geosynthetic barriers and their related products. It applies to clay geosynthetic barriers only when tested in dry conditions.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN ISO 10318:2005, *Geosynthetics — Terms and definitions (ISO 10318:2005)*

ISO 554, *Standard atmospheres for conditioning and/or testing — Specifications*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in EN ISO 10318:2005 apply.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

4 Principle

A circular specimen, clamped around its edge, is subjected to a gradually increasing normal hydraulic stress, with a constant rate of increase of volume, until rupture occurs.

<https://standards.iteh.ai/catalog/standards/sist/68441c1f-7e1b-481f-bdb5-b08c3025c1f6/sist-en-14151-2010>

The main parameters measured during the test are the hydraulic pressure under the specimen and the deflection of the specimen.

For geotextiles, dry clay geosynthetic barriers and products with apertures, e.g. geogrids, it is necessary to use an appropriately thin, impermeable and deformable membrane (diaphragm) under the specimen. If any composite material comprises an impermeable layer it is not necessary to use a diaphragm in the tests.


5 Apparatus**5.1 General**

The equipment is composed of:

- a test cell with two parts;
- a deflection measuring device;
- a pressure measuring device;
- a means of controlling flow rate

An example is shown in Figure 1.

Dimensions in millimetres

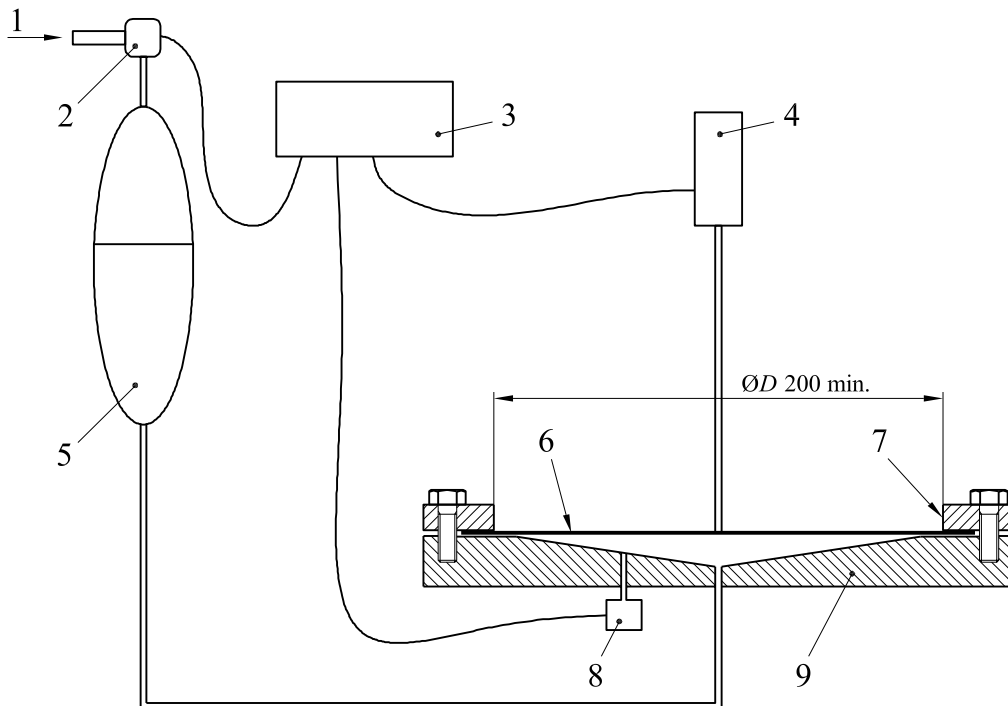

iTeh STANDARD PREVIEW
(standards.iteh.ai)

Key

- 1 air
- 2 pneumatic servo valve
- 3 computer
- 4 displacement sensor
- 5 water vessel
- 6 specimen
- 7 clamping ring
- 8 pressure transducer
- 9 base

SIST EN 14151:2010

<https://standards.iteh.ai/catalog/standards/sist/68441c1f-7e1b-481f-bdb5-b08c3025c1f6/sist-en-14151-2010>

Figure 1 — Example of testing apparatus

5.2 Cell

The cell is composed of a base and a clamping ring. The inner diameter (D) of the ring, shall be (200 ± 2) mm. This diameter is the effective diameter of the tested specimen. The lower inner edge of the clamping ring shall be rounded (approximately a 3 mm radius). The bottom (base) of the cell, maintained horizontally, can be either flat or recessed with a liquid inlet at its centre.

The cell shall be designed so that no essential deformation occurs under the applied pressure. The clamping device shall be designed in order to avoid any slippage of the specimen during the test. Clamping shall not damage the specimen.

5.3 Deflection measurement

The deflection of the centre of the specimen is measured with a deflection measuring device. Any measuring method meeting the following criteria is acceptable:

- ability to measure deflection up to the diameter of the cell;

EN 14151:2010 (E)

- an accuracy of $\pm 0,5$ mm;
- creation of negligible stress on the specimen.

This measurement is used to calculate the deformation of the specimen.

5.4 Pressure measurement

A pressure measuring device with an accuracy of ± 1 % shall be used to measure the liquid pressure in the cell. The temperature of the liquid shall be (20 ± 2) °C and shall be maintained constant during the test.

5.5 Volume control

The equipment shall allow control of the incoming liquid flow.

6 Specimens

Five specimens shall be cut from the test sample. They shall be clean and without any visible defects. Clay geosynthetic barriers may only be tested in dry condition.

NOTE If the surface of the specimen is rough, it can be necessary to smooth the clamping area in order to ensure a perfect seal.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

7 Conditioning

The test specimens shall be conditioned and the test performed in the standard atmosphere for testing as defined in ISO 554 ((20 ± 2) °C and (65 ± 5) % relative humidity).

The specimens can be considered to have been conditioned when the change in mass in successive weightings made at intervals of not less than 2 h does not exceed 0,25 % of the mass of the test specimen.

Conditioning and/or testing in standard atmosphere may only be omitted when it can be shown that results obtained for the same specific type of product (both structure and polymer type) are not affected by changes in temperature and humidity exceeding the limits.

8 Procedure**8.1 General**

If the cell is not flat, fill the base up to its flange with liquid.

Put the specimen on the base of the cell and, if necessary, put the thin membrane (diaphragm) under it.

NOTE The mechanical properties of the thin membrane in theory should not affect the measurements. Its bi-axial mechanical strength should be negligible compared with the tested geosynthetic. However, the influence of the membrane should be taken into account for calculations.

If the cell is flat, apply a little vacuum under the specimen before clamping. Place the deflection measuring device in the centre of the specimen. If the specimen is not flat, the zero deflection is determined by the level of the lower face of the clamping ring.

Non-spherical or non-symmetrical deformation, e.g. as it occurs with anisotropic materials, shall be reported.

The test is not valid if the specimen breaks at the edge of the clamping ring.

8.2 Volume control

The test is conducted with an incoming liquid flow rate of 3 cm³/s.

Ensure no slippage or fluid leakage has occurred around the perimeter of the clamp.

8.3 Diaphragm correction

With the same rate of liquid flow as employed in the tests, distend the diaphragm (without the presence of the specimen) and note the pressure required to distend it by an amount equal to the average distension of the specimens. This pressure is the “diaphragm correction”.

9 Calculations

Strain and stress calculations are based on the following assumptions (see also Figure 2):

- spherical deformation;
- constant and uniform thickness of the specimen.

Geometrical considerations lead to:

$$R = \frac{H^2 + \frac{D^2}{4}}{2H} \quad (1)$$

where

D is the inner diameter of the cell (in m);

H is the deflection of the specimen at the centre (in m);

R is the radius of the sphere (in m);

$$\alpha = \text{Arc cos} \left[\frac{R - H}{R} \right] \quad (2)$$

where

H is the deflection of the specimen at the centre point (in m);

R is the radius of the sphere (in m);

α is the half-angle of the portion of circle (in radians).

The strain is: