

---

---

**Textiles — Test methods for nonwovens —  
Part 12:  
Demand absorbency**

*Textiles — Méthodes d'essai pour nontissés —*

*Partie 12: Absorption par contact unifacial*

iTeh STANDARD PREVIEW  
(standards.iteh.ai)

ISO 9073-12:2002

<https://standards.iteh.ai/catalog/standards/sist/0a713c71-867a-4734-976a-29f627520b8a/iso-9073-12-2002>



**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO 9073-12:2002

<https://standards.iteh.ai/catalog/standards/sist/0a713c71-867a-4734-976a-29f627520b8a/iso-9073-12-2002>

© ISO 2002

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.ch](mailto:copyright@iso.ch)  
Web [www.iso.ch](http://www.iso.ch)

Printed in Switzerland

## Contents

	Page
Foreword .....	iv
1 Scope .....	1
2 Normative references .....	1
3 Terms and definitions .....	1
4 Principle .....	2
5 Apparatus .....	2
6 Assembly of the apparatus .....	3
7 Preparation and conditioning of test pieces .....	4
8 Procedure .....	4
9 Expression of the results .....	5
10 Test report .....	8
<b>Annex A</b> (normative) <b>Determination of flow through the porous medium using the data acquisition system</b> .....	<b>9</b>
<b>Annex B</b> (informative) <b>MAR calculation explanation</b> .....	<b>11</b>
<b>Annex C</b> (informative) <b>Precision</b> .....	<b>12</b>

ISO 9073-12:2002

<https://standards.iteh.ai/catalog/standards/sist/0a713c71-867a-4734-976a-29f627520b8a/iso-9073-12-2002>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 3.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this part of ISO 9073 may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 9073-12 was prepared by Technical Committee ISO/TC 38, *Textiles*.

ISO 9073 consists of the following parts, under the general title *Textiles – Test methods for nonwovens*:

- *Part 1: Determination of mass per unit area*
- *Part 2: Determination of thickness*
- *Part 3: Determination of tensile strength and elongation*
- *Part 4: Determination of tear resistance*
- *Part 6: Absorption*
- *Part 7: Determination of bending length*
- *Part 8: Determination of liquid strike-through time (simulated urine)*
- *Part 9: Determination of drape coefficient*
- *Part 10: Generation of lint and other particles in the dry state*
- *Part 11: Run-off*
- *Part 12: Demand absorbency*

Annex A forms a normative part of this part of ISO 9073. Annexes B and C are for information only.

# Textiles — Test methods for nonwovens —

## Part 12: Demand absorbency

### 1 Scope

This part of ISO 9073 describes a method for the evaluation of the absorbency of fabrics when one side is in contact with a liquid and the fabric is under mechanical pressure.

This test is designed to allow comparison of absorbent materials such as nonwovens and is not intended to simulate in-use conditions of finished products.

NOTE Demand absorbency is also called demand wettability.

### 2 Normative references

The following normative documents contain provisions which, through reference in this text, constitute provisions of this part of ISO 9073. For dated references, subsequent amendments to, or revisions of, any of these publications do not apply. However, parties to agreements based on this part of ISO 9073 are encouraged to investigate the possibility of applying the most recent editions of the normative documents indicated below. For undated references, the latest edition of the normative document referred to applies. Members of ISO and IEC maintain registers of currently valid International Standards.

ISO 139:1973, *Textiles — Standard atmospheres for conditioning and testing*

ISO 3696:1987, *Water for analytical laboratory use — Specification and test methods*

### 3 Terms and definitions

For the purposes of this part of ISO 9073 the following terms and definitions apply.

#### 3.1

##### maximum absorbed mass

$A_f$

mass of liquid absorbed, in grams, at time  $T_f$ , when the absorbed mass variation in the previous 5 s time period is lower than 1 % of the absorbed mass corresponding to  $T_f$

#### 3.2

##### demand absorbency capacity

DAC

maximum absorbed mass of liquid,  $A_f$ , divided by the mass of the test piece,  $m$ , expressed in grams per gram

#### 3.3

##### maximum absorption rate

MAR

maximum change in liquid absorbed mass per time interval, expressed in grams per second


NOTE The MAR is calculated over a 1 s time period from data recorded with sampling intervals of 0,25 s or less. The maximum absorption rate is observed at the point of inflexion of the curve absorbed mass of liquid versus time.

4 Principle

The method measures the demand absorbency of a fabric under constant mechanical pressure. The test piece is placed on a specified porous plate, which is connected by a siphon to a liquid reservoir. The level in the reservoir is set below the upper surface of the porous plate. The demand absorbency is measured in terms of the change in mass of the reservoir with time.

5 Apparatus

See Figure 1.

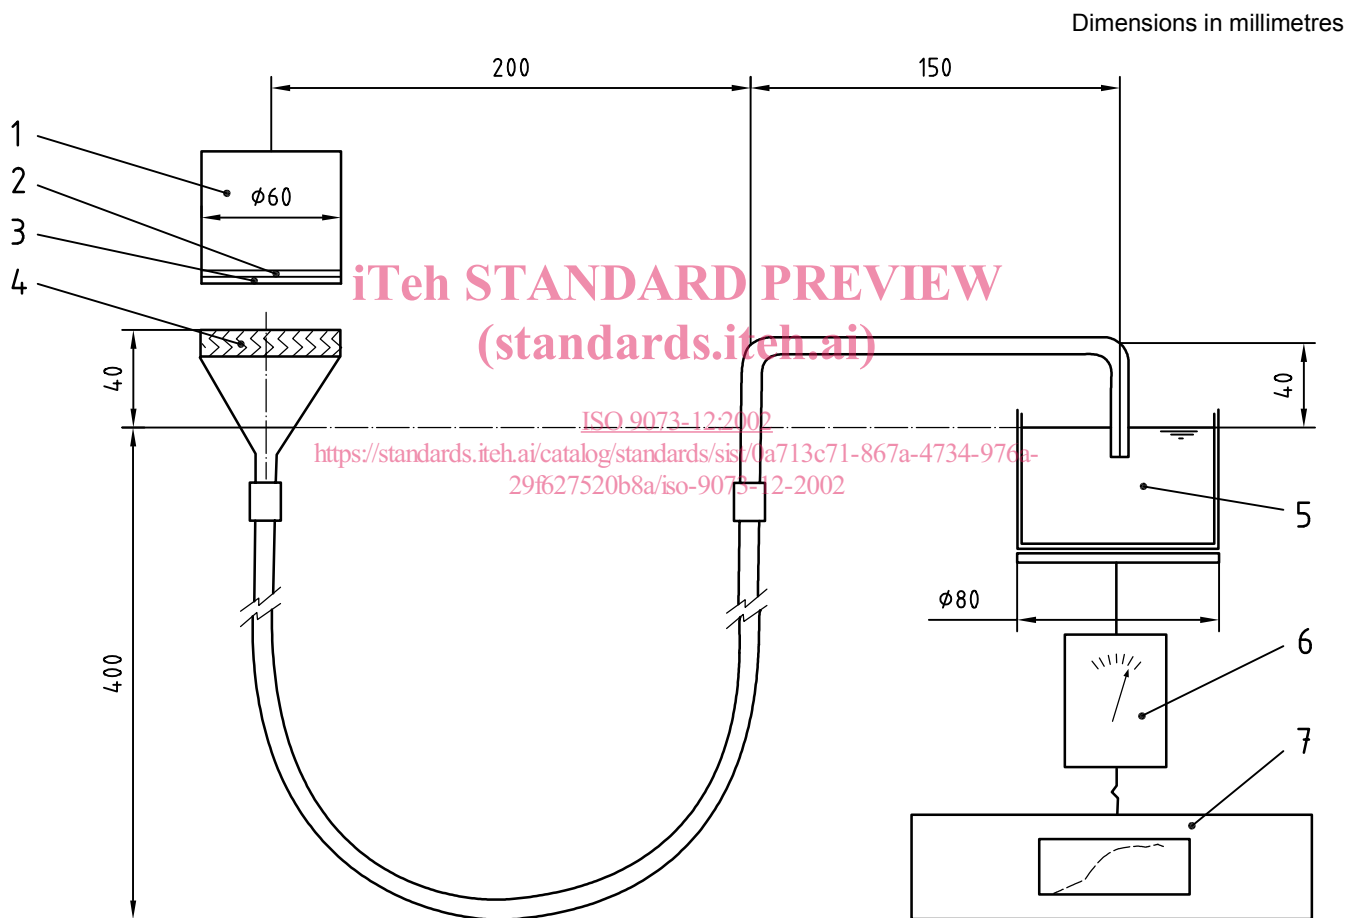

Key

- |                      |                      |
|----------------------|----------------------|
| 1 Cylindrical weight | 5 Reservoir          |
| 2 Foam piece         | 6 Electronic balance |
| 3 Sample             | 7 Data system        |
| 4 Porous glass plate |                      |

Figure 1 — Siphon assembly

**5.1 Plain porous glass plate**, diameter  $(60 \pm 1)$  mm set into the top of a funnel which has a minimum outlet diameter of  $(7,0 \pm 0,2)$  mm. The plate  $(4 \pm 1)$  mm thick has a porosity rating of 2 ( $4 \mu\text{m}$  to  $90 \mu\text{m}$ ) and a flow rate of 2,5 g/s to 3,5 g/s under the conditions specified in the calibration procedure (see annex A).

**5.2 Glass reservoir**, cylindrical, with a diameter  $\geq 80$  mm.

**5.3 Siphon assembly**, consisting of a glass U-tube and a flexible silicone rubber tube each with an internal diameter of  $(8,0 \pm 0,2)$  mm (see Figure 1).

**5.4 Electronic balance**, to weigh the reservoir and its content, capable of determining the mass to an accuracy of 0,01 g.

**5.5 Data acquisition system**, that allows the change of mass of the reservoir to be recorded against time (e.g. microprocessing device, data analysis and printing device). If this is a digital system it shall be able to take readings at least four times per second.

NOTE High absorbent rate materials may need readings taken eight times per second. (See 9.4, note 1.)

**5.6 Hydrophobic polyether-polyurethane foam piece**,  $(55 \pm 1)$  mm in diameter and  $(2,0 \pm 0,5)$  mm thick, with 20 regular open cells per centimetre and a density of  $(28 \pm 3)$  kg/m<sup>3</sup>.

**5.7 Cylindrical weight**,  $(60 \pm 1)$  mm in diameter. The total mass of the weight and the foam piece shall be  $(605 \pm 5)$  g, which corresponds to an imposed pressure on the test piece of  $(2,50 \pm 0,05)$  kPa.

**5.8 Test liquid**, normally demineralized water (in accordance with ISO 3696), but other appropriate liquids can be used. The liquid used shall be specified and identified in the test report and used at temperature of  $(20 \pm 2)$  °C.

**5.9 Cleaning product**, e.g. sulfochromic acid ( $1/3 \text{K}_2\text{Cr}_2\text{O}_7$  at 50 g/l and  $2/3 \text{H}_2\text{SO}_4$  at 95 %) or equivalent.

**5.10 Spirit level.**

[ISO 9073-12:2002](https://standards.iteh.ai/catalog/standards/sist/0a713c71-867a-4734-976a-29f627520b8a/iso-9073-12-2002)

<https://standards.iteh.ai/catalog/standards/sist/0a713c71-867a-4734-976a-29f627520b8a/iso-9073-12-2002>

## 6 Assembly of the apparatus

**6.1** The layout of the apparatus is shown in Figure 1. The components shall be assembled according to the dimensions given.


**6.2** The hydrophobic foam (5.6) is attached to the bottom of the cylindrical weight (5.7) using hydrophobic double-sided tapes so that the foam can be changed from time to time.

**6.3** In order that the apparatus be filled with liquid without the entrainment of air bubbles, ensure that all the tubes are filled and then connect them to the funnel containing the porous medium under water as shown in Figure 2.

**6.4** Using a spirit level (5.10), align the top surface of the porous medium and the horizontal part of the top external surface of the glass U-tube (5.3) ensuring both are  $(40,0 \pm 0,5)$  mm above the liquid level in the reservoir.

**6.5** Set up the data acquisition system (5.5) and check it for effectiveness.

NOTE The flow resistance of the apparatus itself will affect the results and this is governed by the dimensions and shapes of the tubes, the water level and the porosity of the porous medium. Consequently it is essential to adhere to the specifications of the apparatus and the defined procedure if good reproducibility is to be obtained.

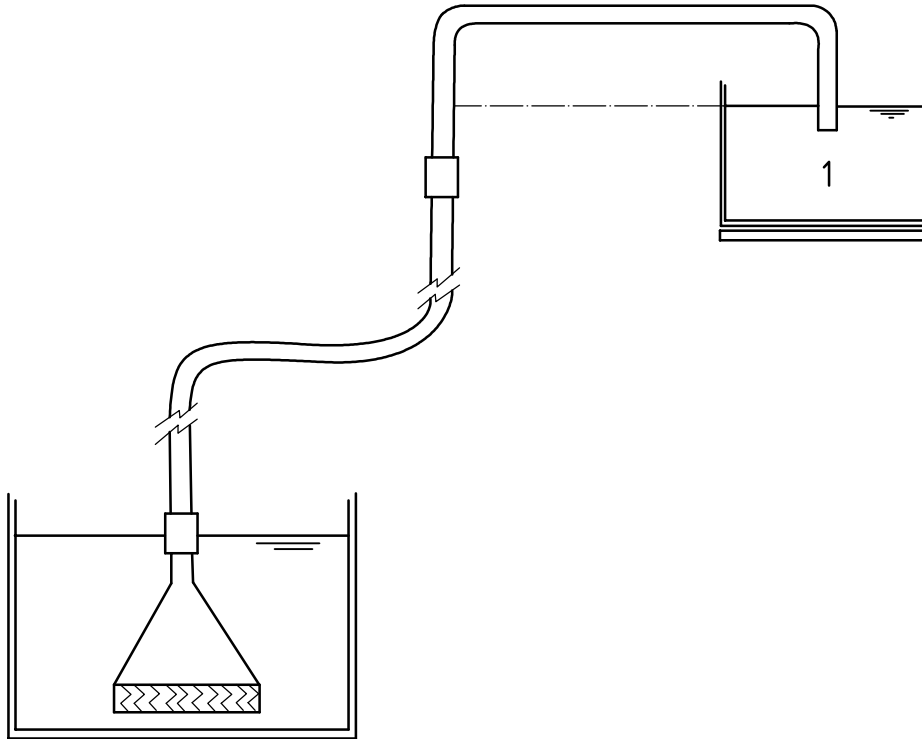

**Key**

- 1 Reservoir

**iTeh STANDARD PREVIEW**  
(standards.iteh.ai)

**Figure 2 — Method of tube and funnel connection**

<https://standards.iteh.ai/catalog/standards/sist/0a713c71-867a-4734-976a-29f627520b8a/iso-9073-12-2002>

**7 Preparation and conditioning of test pieces**

- 7.1 Mark the nonwoven samples so that the face to be in contact with the porous plate is readily identifiable.
- 7.2 Cut out 5 test pieces from each sample ( $55 \pm 1$ ) mm in diameter.
- 7.3 Condition the test pieces as specified in ISO 139.

**8 Procedure**

- 8.1 Weigh the test piece and record the mass,  $m$ , in grams.
- 8.2 If necessary, dry the foam attached to the weight with a hair drier.
- 8.3 Attach the test piece to the foam face of the weight (5.7) using 3 pieces of 1 cm<sup>2</sup> hydrophobic double-sided tape.
- 8.4 Ensure that the height of the porous plate (5.1) and the horizontal part of the top external surface of the U-tube (5.3) are ( $40,0 \pm 0,5$ ) mm above the liquid's surface.
- 8.5 Weigh the reservoir of liquid and record the mass  $m_0$ , in grams.
- 8.6 Start the data acquisition system (5.5).

- 8.7** Place the weight with the foam (5.6) and test piece attached on the porous medium. As far as possible, ensure that the face of the test piece is parallel to the face of the porous medium and also that the test piece is concentric to the medium at the time the test piece and the porous medium come into contact.
- 8.8** Record the decreasing mass of the reservoir and liquid,  $m_t$ , using the data acquisition system.
- 8.9** Run the test and record the mass until the mass variation within the previous 5 s is lower than 1 % of the maximum absorbed liquid. Stop the data acquisition system.
- 8.10** Remove the weight from the porous medium and remove the test piece from it.
- 8.11** Repeat steps 8.1 to 8.10 with the other four test pieces.
- 8.12** Use fresh conditioned test liquid (5.8) for each set of five test pieces.
- 8.13** After each set of five tests, clean the porous medium with sulfochromic acid or equivalent cleaning product (5.9) and then rinse with distilled water.

## 9 Expression of the results

### 9.1 Mass versus time curve

Several characteristics can be determined for each test piece on the basis of absorbed mass,  $A$ , against time,  $t$ . Calculate and draw the curve of  $A$  against  $t$  (see Figure 3 for an example)

$$A_t = m_0 - m_t$$

ISO 9073-12:2002

### 9.2 Maximum absorbed mass ( $A_f$ )

<https://standards.iteh.ai/catalog/standards/sist/0a713c71-867a-4734-976a-29f627520b8a/iso-9073-12-2002>

Calculate for each test piece:

The maximum absorbed mass ( $A_f$ ) is recorded at the time  $T_f$  at which the mass variation within the previous 5 s time period is lower than 1 % of the maximum absorbed mass.

In practice the calculation is made on a time period  $\Delta T$  close to 5 s and equal to a full number  $n$  of time steps  $\Delta t$ , i.e.:

$$\Delta T = n\Delta t > 5 \text{ s}$$

with

$$(n-1)\Delta t < 5 \text{ s}$$

and

$$A_f - A_{(T_f - \Delta T)} < \frac{1}{100} A_f$$

NOTE 1 The sampling time interval is defined by  $\Delta t \leq 0,25 \text{ s}$ .

Generally the 5 s are a multiple of  $\Delta t$  and  $\Delta T = 5 \text{ s}$ , but if it is not the case, the maximum difference between  $\Delta T$  and 5 s could be  $\pm 1 \%$   $\Delta T$ , in which case the resulting error on  $T_f$  and more conclusively on  $A_f$  is completely negligible.

NOTE 2 Independently of the method of calculation, the final time  $T_f$  usually presents a large coefficient of variation (contrary to the maximum absorbed mass  $A_f$ ). For this reason,  $T_f$  is mentioned in the test report only if requested.