# INTERNATIONAL STANDARD

Second edition 1998-11-01

# Metallic materials — Tube — Ring tensile test

Matériaux métalliques — Tubes — Essai de traction sur anneaux

# iTeh STANDARD PREVIEW (standards.iteh.ai)

<u>ISO 8496:1998</u> https://standards.iteh.ai/catalog/standards/sist/42976586-a633-459c-9bbe-0df4811d57ae/iso-8496-1998



## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 8496 was prepared by Technical Committee ISO/TC 164, *Mechanical testing of metals*, Subcommittee SC 2, *Ductility testing*.

This second edition cancels and replaces the first edition (ISO 8496:1986), of which it constitutes a technical revision.

## iTeh STANDARD PREVIEW (standards.iteh.ai)

<u>ISO 8496:1998</u> https://standards.iteh.ai/catalog/standards/sist/42976586-a633-459c-9bbe-0df4811d57ae/iso-8496-1998

© ISO 1998

International Organization for Standardization Case postale 56 • CH-1211 Genève 20 • Switzerland Internet iso@iso.ch

Printed in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

## Metallic materials — Tube — Ring tensile test

## 1 Scope

This International Standard specifies a method for a ring tensile test of tubes to reveal surface and internal defects by subjecting the test piece to strain until fracture occurs. This test may also be used to assess the ductility of tubes.

The ring tensile test is applicable to tubes having an outside diameter exceeding 150 mm and a wall thickness no greater than 40 mm. The inside diameter shall be greater than 100 mm.

## 2 Principle

Subjecting a ring cut from the end of a tube to strain in the circumferential direction until fracture occurs.

#### **3** Apparatus

## iTeh STANDARD PREVIEW

**3.1 Two circular pins**, of equal diameter with parallel axes, and movable in relation to each other while still remaining parallel.

In principle, the diameter of the pins shall be the <u>iminimum permissible</u> from strength considerations but, provided that the inside diameter of the tube allows, should be at least 3 times the wall thickness of the tube to be tested (see figure 1). 0df4811d57ae/iso-8496-1998

Dimensions in millimetres

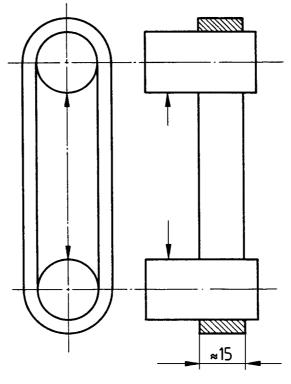


Figure 1

## 4 Test piece

**4.1** The test piece shall be a ring cut from the tube with the end faces perpendicular to the axis.

**4.2** The length of the test piece (width of the ring) shall be approximately 15 mm. If the thickness exceeds 15 mm, the length of the test piece may be equal to the thickness.

**4.3** The ends of the test piece shall be free from burrs. The edges may be rounded by filing or chamfered by other methods.

NOTE - Non-rounded or non-chamfered edges are permissible, if the test result meets the test requirements.

## 5 Procedure

**5.1** In general, the test shall be carried out at ambient temperature within the limits of 10 °C to 35 °C. The test carried out under controlled conditions shall be made at a temperature of 23 °C  $\pm$  5 °C.

**5.2** Place the ring cut from the tube over the pins. Subject the ring to strain by moving the pins away from each other at a specified rate until it fractures.

In cases of dispute, the rate shall not exceed 5 mm/s.

**5.3** Interpretation of the ring tensile test shall be carried out in accordance with the requirements of the relevant product standard. When these requirements are not specified, the test piece shall be considered to have passed the test if no cracks are visible without the use of magnifying aids.

## (standards.iteh.ai)

## 6 Test report

#### ISO 8496:1998

A test report shall be provided when so specified in the relevant product standard. In this case, the test report shall include at least the following information:

a) reference to this International Standard, i.e. ISO 8496;

- b) identification of the test piece;
- c) dimensions of the test piece;
- d) result of the test.

# iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 8496:1998 https://standards.iteh.ai/catalog/standards/sist/42976586-a633-459c-9bbe-0df4811d57ae/iso-8496-1998

# iTeh STANDARD PREVIEW (standards.iteh.ai)

<u>ISO 8496:1998</u> https://standards.iteh.ai/catalog/standards/sist/42976586-a633-459c-9bbe-0df4811d57ae/iso-8496-1998

## ICS 77.040

Ξ

Descriptors: metal products, metal tubes, tests, tension tests.

Price based on 2 pages