
**Steels — Determination of depth of
decarburization**

Aciers — Détermination de la profondeur de décarburation

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 3887:2003

<https://standards.iteh.ai/catalog/standards/sist/4c9a4329-86ea-40be-bb91-79545fe1caea/iso-3887-2003>



Reference number
ISO 3887:2003(E)

© ISO 2003

PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 3887:2003

<https://standards.iteh.ai/catalog/standards/sist/4c9a4329-86ea-40be-bb91-79545fe1caea/iso-3887-2003>

© ISO 2003

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 3887 was prepared by Technical Committee ISO/TC 17, *Steel*, Subcommittee SC 7, *Methods of testing (other than mechanical tests and chemical analysis)*.

This second edition cancels and replaces the first edition (ISO 3887:1976), which has been technically revised.

iTeh STANDARD PREVIEW
(standards.iteh.ai)
ISO 3887:2003
<https://standards.iteh.ai/catalog/standards/sist/4c9a4329-86ea-40be-bb91-79545fe1caea/iso-3887-2003>

iTeh STANDARD PREVIEW **(standards.iteh.ai)**

ISO 3887:2003

<https://standards.iteh.ai/catalog/standards/sist/4c9a4329-86ea-40be-bb91-79545fe1caea/iso-3887-2003>

Steels — Determination of depth of decarburization

1 Scope

This International Standard defines decarburization and specifies three methods of measuring the depth of decarburization of non-alloy and low-alloy steels.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 4545, *Metallic materials — Hardness test — Knoop test*

ISO 6507-1, *Metallic materials — Vickers hardness test — Part 1: Test method*

ISO 9556, *Steel and iron — Determination of total carbon content — Infrared absorption method after combustion in an induction furnace*

ISO 15349-2, *Unalloyed steel — Determination of low carbon content — Part 2: Infrared absorption method after combustion in an induction furnace (with preheating)*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

decarburization

loss of carbon from the surface zone of the steel where the loss is:

- a) either partial decarburization, d_3 ;
- b) or complete decarburization, d_1 , measured as the distance between the surface of the product and the point at which carbon is detectable

NOTE The depth of complete decarburization as described in b) is determined by examination of the microstructure.

3.2

depth of functional decarburization

d_2

distance between the surface of the product and the point at which the carbon content or hardness is at the level where the performance of the product would be unaffected by a reduction in carbon (i.e., at the minimum level specified in the product standard)

3.3

depth of total decarburization

d_4

distance between the surface of the product and the point at which the carbon content is that of the unaffected core, the sum of the partial and the complete decarburization $d_3 + d_1$ being designated by the letters DD and expressed in millimetres, e.g., DD = 0,08 mm

NOTE The various bands of decarburization are shown diagrammatically in Figure 1. The boundaries separating the various types of decarburization are shown as hatched bands with the width of the band illustrating the practical variability in measurements due to uncertainty of interpretation.

3.4

depth of ferrite decarburization


depth of complete decarburization in the surface layer

NOTE The depth of ferrite decarburization is determined by examination of the microstructure.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 3887:2003

<https://standards.iteh.ai/catalog/standards/sist/4c9a4329-86ea-40be-bb91-79545fe1caea/iso-3887-2003>

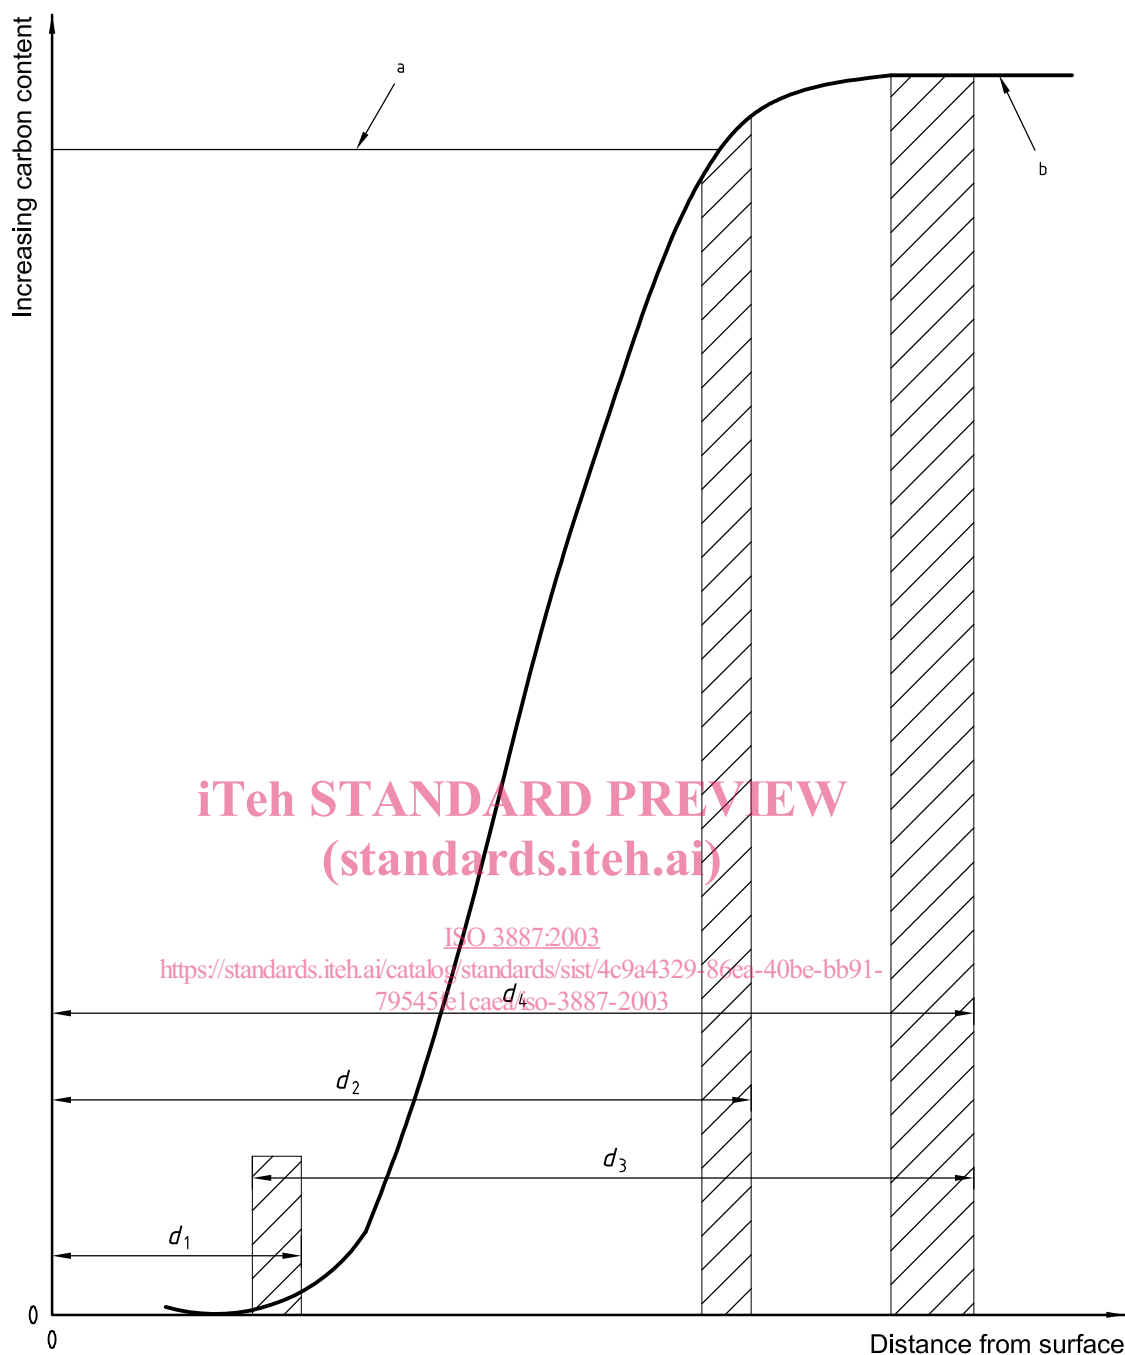

a Minimum carbon content specified in the product standard

b Core carbon content

If the product has undergone a process involving carburization, the definition of the “core” shall form the subject of an agreement between the parties concerned.

The permissible depth of decarburization shall be specified in the appropriate standard covering the product or shall be the subject of an agreement between the parties concerned.

Figure 1 — Carbon content as a function of distance from the surface: schematic representation for a typical decarburized steel

4 Measuring methods

4.1 General

The choice of the method and its accuracy depend on the degree of decarburization, the microstructure, the carbon content of the product examined and the shape of the component.

The usual methods employed on finished products are:

- a micrographic method (see 4.2);
- a method for measuring the microindentation hardness (Vickers or Knoop) for steels in the hardened or quenched and tempered condition (see 4.3);
- a method for the determination of the carbon content by chemical or spectrographic analysis (see 4.4).

The inclusion of several methods of measurement, each having its own sphere of application, avoids the necessity for further heat treatment. The sample shall be examined in the condition of delivery. Nevertheless if, by agreement between the parties concerned, a supplementary heat treatment is applied, every precaution shall be taken to prevent changes in mass percentage and/or in the distribution of carbon, i.e., a small sample, a short austenitization time, a neutral atmosphere.

In the absence of an indication of the choice of method in the product standard, this shall form the subject of an agreement between the parties concerned.

4.2 Micrographic method

4.2.1 General

Unless otherwise specified, this method shall only be applied in situations where changes in carbon content are reflected by resulting variations in microstructure.

This method is especially valid for steels showing an annealed or normalized (ferrite-pearlite) structure. It may apply, with reservations, for products showing a hardened, or tempered, or as-rolled, or forged structure where the interpretation of the structural variations becomes difficult.

4.2.2 Selection and preparation of the sample

The sample selected shall consist of a section perpendicular to the longitudinal axis of the product. For products with no longitudinal axis, selection of the sample shall form the subject of an agreement between the parties concerned.

Wherever possible, small samples (section area less than 4 cm²) shall be examined over their entire periphery. If this is impractical, e.g. for large samples, several sections shall be taken in order to ensure that the sampling is representative. The number and the relative positions of the various samples shall be specified by agreement between the parties concerned.

The micrographic polishing, carried out by applying the usual methods, shall not round the edges. In order to achieve this, the sample may be mounted or held in a clamp, and the surface of the product may, if necessary, be protected by a metallic deposit obtained by electroless or electrolytic plating. Automatic/semi-automatic preparation techniques are recommended, where possible.

Etching in a solution of 1,5 % to 4 % nitric acid in ethanol (nital) or 2 % to 5 % picral will reveal the structure of the steel.

4.2.3 Measurement proper

As a rule, the reduction in carbon content can be determined for:

- a) ferrite and pearlite: from the decrease in the amount of pearlite;
- b) pearlite and carbides developing hypereutectoidally: from the decrease in the amount of carbides developing hypereutectoidally and/or of pearlite;
- c) ferrite matrix with dispersed carbides: from the decrease in the amount of carbides in the ferrite matrix.

Hardened or quenched and tempered microstructures can be assessed by this method if the change in carbon content leads to clear changes in the microstructure.

This method can also be applied for other structural conditions, e.g., for hardened or quenched and tempered microstructures, but only if a distinct boundary exists within the structure characteristic, which is decisive for the depth of decarburization.

The distance from the surface to the point at which the structure does not differ from that of the core shall be measured (total decarburization). The measurement shall be conducted using suitably calibrated equipment.

The choice of magnification depends on the depth of decarburization and shall be chosen by the assessor unless specifically agreed upon between the parties. It is recommended that the maximum magnification that allows the full extent of decarburization to be viewed is adopted. A magnification of $\times 100$ is recommended as a useful magnification for the majority of instances.

A preliminary examination of the whole surface at low magnification ensures that any great variation in the depth of decarburization along the periphery will be observed for further evaluation.

The point of the maximum depth of decarburization, uninfluenced by surface defects and corner effects, is determined by preliminary examination of the surface of the section. Beginning at this point, the first measurement point, the surface is divided into parts of equal size, at the ends of which the depth of decarburization shall also be measured. Unless agreed otherwise, four individual measured values shall be determined. The depth of total decarburization of the sample (see 3.3) is defined as the average of these measurements. Measuring points that are affected by surface defects shall not be taken into account when determining the average.

4.3 Methods for measuring the microindentation hardness

4.3.1 General

The methods under consideration are that of Vickers, in accordance with ISO 6507-1, and of Knoop, in accordance with ISO 4545.

Each method consists of determining the gradient of the microindentation hardness on a cross-section of the product along a line perpendicular to the surface.

This technique applies only to hypoeutectoid steels in the hardened, tempered or heat-treated condition, and to decarburized zones that are within a hardened zone, in order to avoid the occurrence of variations in hardness due to imperfect penetration. The technique becomes inaccurate for low-carbon steels.

4.3.2 Selection and preparation of the sample

The selection and preparation of the sample shall be identical to that used in the micrographic method (see 4.2.2) although, in general, the sample shall not be etched, in order to facilitate the measurement of the size of the impression. Precautions shall be taken to avoid overheating the sample.