

6]li a Yb`]b`V]li a Ybg_Uj Yn]j U!`8 c`c Yj Ub`Y`bUHyNb] `Uglbcgh`V]li a Ybg_] `j Yn]j n`bUHyNbc`dfYg_i gbc`a YrcXc

Bitumen and bituminous binders - Determination of the tensile properties of bituminous binders by the tensile test method

Bitumen und bitumenhaltige Bindemittel - Bestimmung der Streckeigenschaften von bitumenhaltigen Bindemitteln mit dem Zugprüfverfahren

Bitumes et liants bitumineux - Détermination des caractéristiques de traction des liants bitumineux par la méthode d'essai de traction

Ta slovenski standard je istoveten z: FprEN 13587

ICS:

75.140	Voski, bitumni in drugi naftni proizvodi	Waxes, bituminous materials and other petroleum products
91.100.50	Veziva. Tesnilni materiali	Binders. Sealing materials

kSIST FprEN 13587:2010

en,de

EUROPEAN STANDARD
NORME EUROPÉENNE
EUROPÄISCHE NORM

FINAL DRAFT
FprEN 13587

October 2009

ICS 75.140; 91.100.50

Will supersede EN 13587:2003

English Version

**Bitumen and bituminous binders - Determination of the tensile
properties of bituminous binders by the tensile test method**

Bitumes et liants bitumineux - Détermination des
caractéristiques de traction des liants bitumineux par la
méthode d'essai de traction

Bitumen und bitumenhaltige Bindemittel - Bestimmung der
Streckeigenschaften von bitumenhaltigen Bindemitteln mit
dem Zugprüfverfahren

This draft European Standard is submitted to CEN members for unique acceptance procedure. It has been drawn up by the Technical Committee CEN/TC 336.

If this draft becomes a European Standard, CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

This draft European Standard was established by CEN in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

Warning : This document is not a European Standard. It is distributed for review and comments. It is subject to change without notice and shall not be referred to as a European Standard.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: Avenue Marnix 17, B-1000 Brussels

Contents

Page

Foreword.....	3
1 Scope	4
2 Normative references	4
3 Terms and definitions	4
4 Principle	5
5 Apparatus	5
6 Preparation and conservation of samples	6
7 Procedure	6
8 Calculation and expression of results.....	7
9 Precision	7
10 Test report	7

Foreword

This document (FprEN 13587:2009) has been prepared by Technical Committee CEN/TC 336 “Bituminous binders”, the secretariat of which is held by AFNOR.

This document is currently submitted to the Unique Acceptance Procedure.

This document will supersede EN 13587:2003.

1 Scope

This document specifies a method for determining the tensile properties of a bituminous binder, in particular those of a polymer modified bitumen, by means of a tensile test.

NOTE The tensile properties, more particularly the tensile stress, the elongation and energy, at the yield point and on fracture, are customarily used as a criterion for assessing the quality of these materials.

WARNING — The use of this European Standard may involve hazardous materials, operations and equipment. This European Standard does not purport to address all of the safety problems associated with its use. It is the responsibility of the user of this European Standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 58, *Bitumen and bituminous binders — Sampling bituminous binders*

EN 12594, *Bitumen and bituminous binders — Preparation of test samples*

EN 13703, *Bitumen and bituminous binders — Determination of deformation energy*

EN ISO 527 (all parts), *Plastics — Determination of tensile properties*

ISO 5893, *Rubber and plastics test equipment — Tensile, flexural and compression types (constant rate of traverse) — Specification*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1 tensile force

force undergone by a specimen subjected to extension

NOTE The unit is expressed in Newton (N).

3.2 tensile stress

ratio of the tensile force per unit area of the original cross-section

NOTE The unit is expressed in Newton per square meter (N/m²).

3.3 elongation

increase in length of a specimen, expressed in metres

NOTE Elongation is also expressed in % from the initial length. It is calculated as [(new length – initial length)/initial length] x 100.

3.4 brittle break

rupture happening at the beginning of the test before the flowing threshold when the stress-strain curve is still linear

3.5**flowing threshold**

maximum of the stress-strain curve

4 Principle

A specimen, held by its ends between two jaws, is extended in a chamber, regulated at the test temperature, at constant speed until fracture or a given percent elongation is achieved. In general, stress and percent elongation are noted at the flowing threshold, at breaking and at a percent elongation of 400 %.

5 Apparatus

Usual laboratory equipment and glassware, together with the following:

5.1 Test machine, in accordance with ISO 5893.

5.1.1 The machine shall be capable of maintaining a constant speed of the moving element at the speed chosen for the test to an accuracy of within 2 % of the chosen speed.

5.1.2 The specimen attachment device (located on the stationary part and on the moving part) shall:

- ensure sufficient clamping of the specimen heads throughout the entire test, to prevent slipping;
- not exert, on any part of the ends of the specimen, localized stresses liable to cause tearing or fracture of the specimen.

5.1.3 Appropriate facilities shall permit the following measurements to be made:

- tensile force applied on the specimen over the range 1 N to 500 N to an accuracy of ± 1 %;
- elongation of the specimen, either by following the movement of the attachment points or by means of an optical extensometer over the range 0 mm to not less than 250 mm to an accuracy of ± 1 mm.

5.1.4 Optical extensometer

If an optical extensometer is used its reflectory devices shall be positioned on the bituminous specimen as near as possible to the specimen heads.

The distance between the two reflectory devices is approximately 45 mm to 50 mm.

The facilities used shall be recorded in the test report.

5.2 Temperature controlled chamber, capable of maintaining the specimen and the attachment device at the specified temperature throughout the test to an accuracy of $\pm 0,5$ °C, provided with a means of checking the test temperature. The control thermometer shall be placed near the specimen.

5.3 Recording device, for force applied and elongation of the test specimen.

5.4 Measurement apparatus, capable of measuring the thickness of the test specimen to an accuracy of $\pm 0,1$ mm.

5.5 Moulds allowing moulding of specimens (see Figure 1), e.g. made in silicone elastomer.

Table 1 — Dimensions of the mould H2 in millimetres

Type of specimen	A	B	E	F	C	G	R	R'
H2	$25 \pm 0,5$	$4,0 \pm 0,1$	$3,0 \pm 0,3$	75 ± 2	$12,5 \pm 1,0$	$12,5 \pm 1,0$	$8,0 \pm 0,3$	$12,5 \pm 0,3$

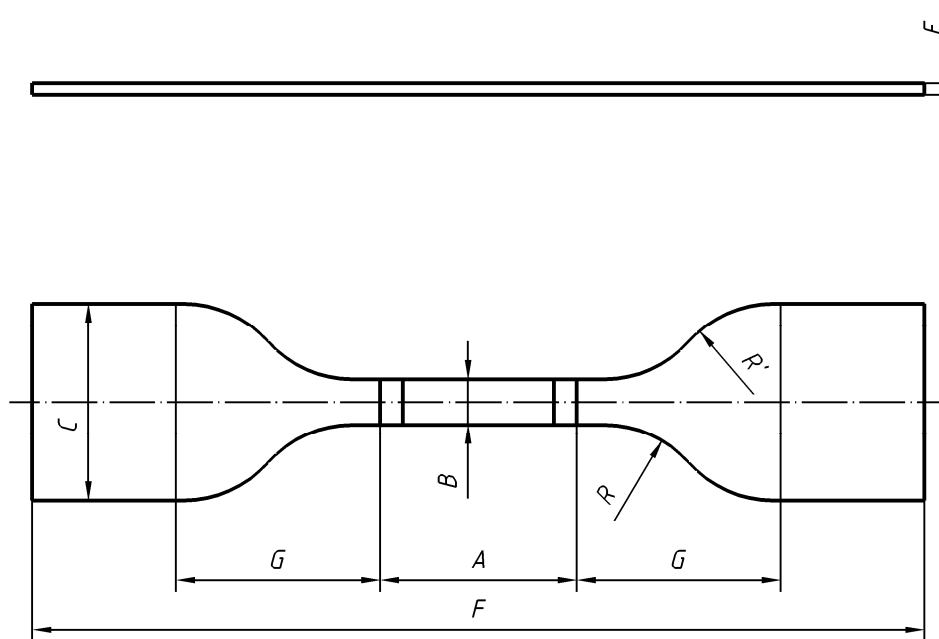


Figure 1 — Dumbbell-shaped binder specimen H2

The reference length or initial length of the H2 specimens is $K_0 = A + 2G$. Specimens of different geometry can be used (if the preparation of H2 specimens is too difficult or impossible) but should be in accordance with the reference standards; this should be mentioned explicitly in the test report. The results obtained from such specimens can be used only for comparison with a binder tested under the same conditions.

6 Preparation and conservation of samples

Take the sample in accordance with EN 58. Prepare the sample in accordance with EN 12594. Pour surplus of material directly in the mould, let the specimens cool for about one hour to room temperature, and cut off the surplus with a heated spatula.

As an alternative for sample preparation the dumbbell-shaped specimen can be produced by cutting a thin sheet of the bituminous binder having the correct thickness by a model which will produce a specimen with the dimensions given in Table 1.

Reject specimens exhibiting defects. Keep specimens in their moulds and in a refrigerator at a maximum temperature of 10 °C and for a maximum of four days before the test.

7 Procedure

Measure the thickness, E , of the specimen with an accuracy of 0,1 mm.

Set the apparatus to the test temperature.