
Gumeni in plastični priključki, cevovodi in cevi za propan, butan in njune zmesi v plinastem stanju - 1. del: Cevi in cevovodi

Rubber and plastics hoses, tubing and assemblies for use with propane and butane and their mixture in the vapour phase - Part 1: Hoses and tubings

Gummi- und Kunststoff-Schläuche und -Schlauchleitungen mit und ohne Einlage zur Verwendung mit Propan, Butan und deren Gemische in der Gasphase - Teil 1: Schläuche mit und ohne Einlage

Tuyaux, tubes et flexibles en caoutchouc et en plastique pour utilisation avec le propane, le butane et leurs mélanges en phase vapeur - Partie 1: Tuyaux et tubes

Ta slovenski standard je istoveten z: EN 16436-1:2014

ICS:

83.140.40 Gumene cevi Hoses

SIST EN 16436-1:2014 **en,fr,de**

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN 16436-1:2014](https://standards.iteh.ai/catalog/standards/sist/65cabf5a-415d-40b1-bbf9-76d60201afc5/sist-en-16436-1-2014)

<https://standards.iteh.ai/catalog/standards/sist/65cabf5a-415d-40b1-bbf9-76d60201afc5/sist-en-16436-1-2014>

EUROPEAN STANDARD
NORME EUROPÉENNE
EUROPÄISCHE NORM

EN 16436-1

May 2014

ICS 23.040.70

English Version

**Rubber and plastics hoses, tubing and assemblies for use with
propane and butane and their mixture in the vapour phase - Part
1: Hoses and tubings**

Tuyaux, tubes et flexibles en caoutchouc et en plastique
pour utilisation avec le propane, le butane et leurs
mélanges en phase vapeur - Partie 1: Tuyaux et tubes

Gummi- und Kunststoffschläuche mit und ohne Einlage zur
Verwendung mit Propan, Butan und deren Gemische in der
Gasphase

This European Standard was approved by CEN on 6 March 2014.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Avenue Marnix 17, B-1000 Brussels

Contents	Page
Foreword.....	3
1 Scope	4
2 Normative references	4
3 Terms and definitions	5
4 Classification of tubing and hose	5
5 Materials and construction of tubing and hoses.....	6
6 Dimensions of tubing and hoses	7
6.1 Inside diameters, wall thicknesses and concentricity	7
6.2 Measurement of ovality	7
7 Properties of materials for tubing, lining and cover of hoses	7
7.1 Tensile strength and elongation at break	7
7.2 Accelerated ageing	8
7.3 Resistance to n-pentane	8
8 Performance requirements of tubing and hoses.....	8
8.1 Visible defects evaluation	8
8.2 Cleanliness	8
8.3 Pressure requirements.....	8
8.4 Adhesion in hoses	9
8.5 Resistance to kinking.....	9
8.6 Resistance to crushing	9
8.7 Low temperature flexibility	9
8.8 Flame propagation.....	9
8.9 Permeability to propane.....	9
8.10 Resistance to ozone	10
8.11 UV (xenon arc lamp) test.....	10
8.12 Loss in mass on heating (for non vulcanized (plastics) materials only)	10
8.13 Durability of the marking	10
9 Marking	10
Annex A (normative) Test methods for tubing and hoses.....	12
Bibliography.....	17

Foreword

This document (EN 16436-1:2014) has been prepared by Technical Committee CEN/TC 181 “Dedicated liquefied petroleum gas appliances”, the secretariat of which is held by AFNOR.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by November 2014 and conflicting national standards shall be withdrawn at the latest by November 2014.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document has been prepared under a mandate given to CEN by the European Commission and the European Free Trade Association, and supports essential requirements of EU Directive(s).

According to the CEN-CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN 16436-1:2014

<https://standards.iteh.ai/catalog/standards/sist/65cabf5a-415d-40b1-bbf9-76d60201afc5/sist-en-16436-1-2014>

EN 16436-1:2014 (E)**1 Scope**

This European Standard specifies the characteristics and performance requirements for tubing and hoses made of either rubber or plastics for use with commercial propane and commercial butane and mixtures thereof, in the vapour phase, for connection of appliances, from:

- pressurized gas container to a regulating device,
- pressurized gas container to an appliance,
- regulating device to an appliance, and
- regulating device to installation pipework,

in environments of a temperature range from $-30\text{ }^{\circ}\text{C}$ to $+70\text{ }^{\circ}\text{C}$. Working pressures are from 0 bar to 30 bar.

Three classes are defined in Table 1 according to the maximum working pressures and minimum ambient temperatures.

This European Standard only covers the tubing or hose part of assemblies. The assemblies themselves will be covered by EN 16436-2.

This European Standard does not apply to hoses for:

- welding purposes (see EN ISO 3821, EN 1327);
- propulsion purposes;
- LPG transfer purposes (see EN 1762).

STANDARD PREVIEW
(standards.iteh.ai)
SIST EN 16436-1:2014
<https://standards.iteh.ai/catalog/standards/sist/65cabf5a-415d-40b1-bbf9-76d60201afc5/sist-en-16436-1-2014>

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN ISO 176, *Plastics - Determination of loss of plasticizers - Activated carbon method (ISO 176)*

EN ISO 1402, *Rubber and plastics hoses and hose assemblies - Hydrostatic testing (ISO 1402)*

EN ISO 4080, *Rubber and plastics hoses and hose assemblies - Determination of permeability to gas (ISO 4080)*

EN ISO 4671, *Rubber and plastics hoses and hose assemblies - Methods of measurement of the dimensions of hoses and the lengths of hose assemblies (ISO 4671)*

EN ISO 7326, *Rubber and plastics hoses - Assessment of ozone resistance under static conditions (ISO 7326)*

EN ISO 8033, *Rubber and plastics hoses - Determination of adhesion between components (ISO 8033)*

EN ISO 8330:2008, *Rubber and plastics hoses and hose assemblies - Vocabulary (ISO 8330:2007)*

EN ISO 10619-2, *Rubber and plastics hoses and tubing - Measurement of flexibility and stiffness - Part 2: Bending tests at sub-ambient temperatures (ISO 10619-2)*

EN ISO 30013, *Rubber and plastics hoses - Methods of exposure to laboratory light sources - Determination of changes in colour, appearance and other physical properties (ISO 30013)*

ISO 37, *Rubber, vulcanized or thermoplastic - Determination of tensile stress-strain properties*

ISO 105-A02, *Textiles - Tests for colour fastness - Part A02: Grey scale for assessing change in colour*

ISO 188, *Rubber, vulcanized or thermoplastic - Accelerated ageing and heat resistance tests*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in EN ISO 8330:2008 and the following apply.

3.1

commercial butane

hydrocarbon product composed predominantly of butanes and/or butenes

Note 1 to entry: The remaining part can consist mainly of propane/propene and pentane/pentene isomers.

[SOURCE: ISO 9162]

3.2

commercial propane

hydrocarbon product composed predominantly of propane and/or propene

Note 1 to entry: The remaining part can consist mainly of ethane/ethene and butane/butene isomers.

[SOURCE: ISO 9162]

3.3

tubing

single core of plastic or rubber with no reinforcement or cover

3.4

hose

rubber or flexible thermoplastic lining with a reinforcement made of natural or synthetic textile material applied either spirally wound or braided, and a flexible rubber or thermoplastic outer cover

4 Classification of tubing and hose

One class of tubing and two classes of hose are specified in Table 1 depending on the maximum working pressure and minimal ambient temperatures.

Table 1 — Classification of tubings and hoses

Class	Maximum working pressure bar	Minimum ambient temperature °C
1 (tubing)	0,2	-20
2 (hose)	10	-30
3 (hose)	30	

NOTE Classes 1 and 2 are usually used downstream of a pressure regulating device.

EN 16436-1:2014 (E)**5 Materials and construction of tubing and hoses**

Class 1 tubing shall be made of rubber or thermoplastic material.

Class 2 and class 3 hoses shall comprise a

- rubber or thermoplastics lining;
- reinforcement of natural or synthetic fibres applied either spirally wound or braided;
- rubber or plastics cover. The outer cover may be pricked to allow any gas trapped between the inner lining and outer cover to be released.


The surface colour of the tubing or hose shall be:

- orange (see Figure 1a); or
- black with the marking above, on, or below a continuous orange line of 5 mm minimum width (see Figure 1b); or
- white for classes 1 and 2 with the marking above, on, or below a continuous orange line of 5 mm minimum width (see Figure 2).



a) option 1

<https://standards.iteh.ai/catalog/standards/sist/65cabf5a-415d-40b1-bbf9-76d60201afc5/sist-en-16436-1-2014>

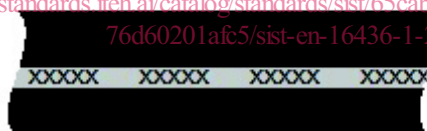

b) option 2


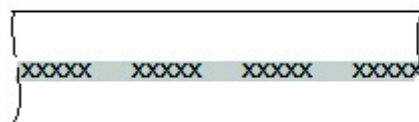
Key

Figure 1 – Possible marking for classes 1, 2 or 3

**Key**

	orange colour
	white colour

Figure 2 – Possible marking for classes 1 or 2**6 Dimensions of tubing and hoses****6.1 Inside diameters, wall thicknesses and concentricity**

When measured in accordance with EN ISO 4671 the inside diameters, tolerances and concentricity shall conform to the values given in Table 2.

Table 2 — Dimensions of hoses or tubing

Dimensions in millimetres									
Inside diameters	3,2	4,0	5,0	6,3	8,0	9,0	10,0	10,5	12,5
Tolerance of inside diameter	± 0,3	± 0,4	± 0,4	± 0,5	± 0,5	± 0,5	± 0,6	± 0,6	± 0,6
Maximum variation in concentricity	0,3	0,4	0,4	0,4	0,5	0,5	0,5	0,5	0,5
Wall thickness class 1 and class 2	2,5	3,5	3,5	3,5	3,5	3,5	5,0	5,0	5,0
Wall thickness class 3	3,5	4,0	4,0	5,0	5,0	5,0	5,0	5,0	6,0
Tolerance of wall thickness	± 0,4	± 0,4	± 0,4	± 0,4	± 0,5	± 0,5	± 0,5	± 0,5	± 0,5

6.2 Measurement of ovality

When measuring on a hose cross section, the minimum diameter D_{\min} and the maximum diameter D_{\max} , the ratio D_{\min}/D_{\max} shall not be less than 0,80.

7 Properties of materials for tubing, lining and cover of hoses**7.1 Tensile strength and elongation at break**

When tested in accordance with A.2, the materials used for tubing, lining and cover of hoses shall conform to the values given in Table 3.