
**Wood-based panels — Determination of
swelling in thickness after immersion in
water**

*Panneaux à base de bois — Détermination du gonflement en épaisseur
après immersion dans l'eau*

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 16983:2003](https://standards.iteh.ai/catalog/standards/sist/3365f842-36e7-4392-ab87-3da98e4520a6/iso-16983-2003)

<https://standards.iteh.ai/catalog/standards/sist/3365f842-36e7-4392-ab87-3da98e4520a6/iso-16983-2003>



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 16983:2003](https://standards.iteh.ai/catalog/standards/sist/3365f842-36e7-4392-ab87-3da98e4520a6/iso-16983-2003)

<https://standards.iteh.ai/catalog/standards/sist/3365f842-36e7-4392-ab87-3da98e4520a6/iso-16983-2003>

© ISO 2003

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 16983 was prepared by Technical Committee ISO/TC 89, *Wood-based panels*. ISO 16983 is based on European Standard EN 317.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO 16983:2003](https://standards.iteh.ai/catalog/standards/sist/3365f842-36e7-4392-ab87-3da98e4520a6/iso-16983-2003)

<https://standards.iteh.ai/catalog/standards/sist/3365f842-36e7-4392-ab87-3da98e4520a6/iso-16983-2003>

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 16983:2003

<https://standards.iteh.ai/catalog/standards/sist/3365f842-36e7-4392-ab87-3da98e4520a6/iso-16983-2003>

Wood-based panels — Determination of swelling in thickness after immersion in water

1 Scope

This International Standard specifies a method for determining the swelling in thickness of flat-pressed or drum-pressed particleboards, fibreboards, OSB, and cement-bonded particleboards, after immersion in water.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 9424, *Wood-based panels — Determination of dimensions of test pieces*

ISO 16999, *Wood-based panels — Sampling and cutting of test pieces*

3 Principle

[ISO 16983:2003](https://standards.iteh.ai/catalog/standards/sist/3365f842-36e7-4392-ab87-16983-2003)

[https://standards.iteh.ai/catalog/standards/sist/3365f842-36e7-4392-ab87-](https://standards.iteh.ai/catalog/standards/sist/3365f842-36e7-4392-ab87-16983-2003)

Swelling in thickness is determined by measuring the increase in thickness of the test piece after complete immersion in water.

4 Apparatus

4.1 Micrometer, as specified in ISO 9424.

4.2 Thermostatically controlled water bath, capable of maintaining a temperature of $(20 \pm 1)^\circ\text{C}$ and in which the test pieces can be maintained in the conditions specified in 6.2.

5 Test pieces

5.1 Sampling

Sampling and cutting of the test pieces shall be carried out according to ISO 16999.

5.2 Dimensions

The test pieces shall be square with a side length of (50 ± 1) mm.

5.3 Conditioning


Test pieces shall be conditioned to constant mass in an atmosphere with a mean relative humidity of $(65 \pm 5) \%$ and a temperature of $(20 \pm 2) ^\circ\text{C}$. Constant mass is considered as having been reached when the results of two successive weighing operations, carried out at an interval of 24 h, do not differ by more than 0,1 % of the mass of the test piece.

6 Procedure

6.1 Thickness measurement

Measure the thickness of each test piece to an accuracy of 0,01 mm at the intersection of the diagonals, according to ISO 9424 (see Figure 1).

Dimensions in millimetres

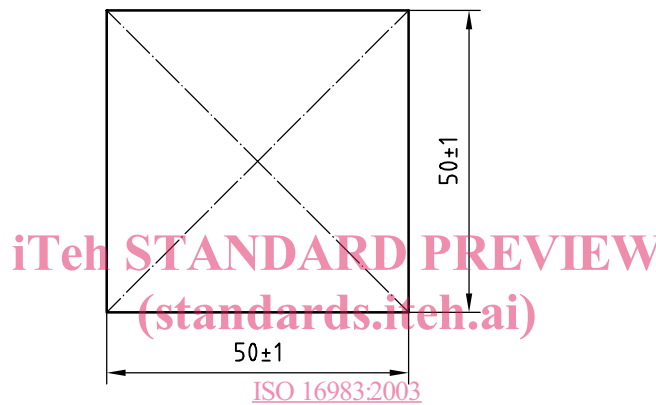

<https://standards.iteh.ai/catalog/standards/sist/3365f842-36e7-4392-ab87-3da98e4520a6/iso-16983-2003>

Figure 1 — Test piece for the measurement of swelling in thickness

6.2 Immersion

Immerse the test pieces with their faces vertical in clean water, having a pH of 7 ± 1 and a temperature of $(20 \pm 1) ^\circ\text{C}$. This temperature shall be maintained throughout the test period. During the test, the test pieces shall be separated from each other and from the bottom and sides of the water bath by at least 15 mm. The upper edges of the test pieces shall be covered by (25 ± 5) mm of water throughout the test. The water shall be changed after each test.

The immersion times shall be as specified by the individual standards for the different panel types.

6.3 Further procedure

After the immersion time has elapsed, take the test pieces out of the water, remove excess water and measure the thickness of each test piece (see 6.1) within 10 min after removal from the water bath.

7 Expression of results

7.1 Test piece

The swelling in thickness of each test piece, G_t , expressed as a percentage of original thickness, shall be calculated according to the following equation:

$$G_t = \frac{t_2 - t_1}{t_1} \times 100$$

where

t_1 is the thickness of the test piece before immersion, in millimetres (mm);

t_2 is the thickness of the test piece after immersion, in millimetres (mm).

7.2 Panel

The swelling in thickness of a panel is the arithmetic mean of the results of all test pieces taken from that panel. Express these values, as a percentage, to one decimal place.

8 Test report

The test report shall contain the following information:

- name and address of test laboratory;
- sampling report according to ISO 16999;
<https://standards.iteh.ai/catalog/standards/sist/3365f842-36e7-4392-ab87-3da98e4520a6/iso-16983-2003>
- date of the test report;
- reference to this International Standard;
- type and thickness of the panel;
- relevant product specification;
- surface treatment, if relevant;
- specific apparatus used, in case of different possibilities allowed in this International Standard;
- test results expressed as stated in Clause 7;
- all deviations from this International Standard.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 16983:2003

<https://standards.iteh.ai/catalog/standards/sist/3365f842-36e7-4392-ab87-3da98e4520a6/iso-16983-2003>

ICS 79.060.01

Price based on 3 pages