
Popis in kvalifikacija varilnih postopkov za kovinske materiale - Preskušanje varilnih postopkov - 11. del: Varjenje z elektronskim snopom in varjenje z laserjem (ISO 15614-11:2002)

Specification and qualification of welding procedures for metallic materials - Welding procedure test - Part 11: Electron and laser beam welding (ISO 15614-11:2002)

Anforderung und Qualifizierung von Schweißverfahren für metallische Werkstoffe - Schweißverfahrensprüfung - Teil 11: Elektronen- und Laserstrahlschweißen (ISO 15614-11:2002)

(standards.iteh.ai)

Descriptif et qualification d'un mode opératoire de soudage pour les matériaux métalliques - Epreuve de qualification d'un mode opératoire - Partie 11: Soudage par faisceau d'électrons et par faisceau laser (ISO 15614-11:2002)

Ta slovenski standard je istoveten z: EN ISO 15614-11:2002

ICS:

25.160.10

SIST EN ISO 15614-11:2003

en

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 15614-11:2003

<https://standards.iteh.ai/catalog/standards/sist/c1142ef4-9e5f-47b4-a58f-53a4e7fdda79/sist-en-iso-15614-11-2003>

ICS 25.160.10

English version

Specification and qualification of welding procedures for metallic materials - Welding procedure test - Part 11: Electron and laser beam welding (ISO 15614-11:2002)

Descriptif et qualification d'un mode opératoire de soudage pour les matériaux métalliques - Epreuve de qualification d'un mode opératoire - Partie 11: Soudage par faisceau d'électrons et par faisceau laser (ISO 15614-11:2002)

Anforderung und Qualifizierung von Schweißverfahren für metallische Werkstoffe - Schweißverfahrensprüfung - Teil 11: Elektronen- und Laserstrahlschweißen (ISO 15614-11:2002)

This European Standard was approved by CEN on 2 May 2001.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Malta, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: rue de Stassart, 36 B-1050 Brussels

Contents

	page
Foreword.....	3
Introduction	4
1 Scope	5
2 Normative references	5
3 Terms and definitions.....	6
4 Welding procedure specification (WPS).....	6
5 Welding procedure test	6
6 Test piece.....	6
6.1 General.....	6
6.2 Shape and dimensions of test pieces.....	6
6.3 Welding of test pieces	11
7 Examination and testing	11
7.1 Extent of examination and testing	11
7.2 Location and cutting of test specimens	14
7.3 Non-destructive examination.....	18
7.4 Destructive tests	18
7.5 Re-testing.....	20
8 Range of qualification	20
8.1 General.....	20
8.2 Related to the manufacturer.....	20
8.3 Related to the equipment	20
8.4 Related to the jigs, fixtures and tooling	20
8.5 Related to the parent material	20
8.6 Related to the filler materials.....	21
8.7 Related to the joint geometry	21
8.8 Related to the presence of a weld backing	21
8.9 Related to the weld type.....	21
8.10 Related to the welding position.....	22
8.11 Related to the welding parameters	22
8.12 Related to preheating	22
8.13 Related to post weld heat treatment	22
8.14 Related to the number of passes	22
8.15 Duration of validity	22
9 Welding Procedure Qualification Record (WPQR)	22
Annex A (informative) Welding Procedure Qualification Record form (WPQR)	23
Annex ZA (normative) List of ISO corresponding standards to European Standards given in clause 2	27
Annex ZB (informative) Clauses of this European Standard addressing essential requirements or other provisions of EU directives.....	28

ITC STANDARD PREVIEW
 (standards.iteh.ai)

Foreword

The text of EN ISO 15611:2002 has been prepared by Technical Committee CEN/TC 121 "Welding", the secretariat of which is held by DS, in collaboration with Technical Committee ISO/TC 44 "Welding and allied processes".

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by September 2002, and conflicting national standards shall be withdrawn at the latest by September 2002.

This European Standard has been prepared under a mandate given to CEN by the European Commission and the European Free Trade Association, and supports essential requirements of EU Directive(s).

For relationship with EU Directive(s), see informative annex ZB, which is an integral part of this standard.

Annexes A and ZB are informative.

The annex ZA is normative.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Malta, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

ITEH STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN ISO 15614-11:2003](https://standards.iteh.ai/catalog/standards/sist/c1142ef4-9e5f-47b4-a58f-53a4e7fdda79/sist-en-iso-15614-11-2003)
<https://standards.iteh.ai/catalog/standards/sist/c1142ef4-9e5f-47b4-a58f-53a4e7fdda79/sist-en-iso-15614-11-2003>

Introduction

Qualification of welding procedures serves to demonstrate that production operations fully comply with the agreed welding procedure including preliminary and subsequent treatment.

Before a particular welding procedure is used in a production operation, the manufacturer should determine and document the suitability of the Welding Procedure Specification (WPS) to produce a weld of the required quality.

To date the suitability of welding procedures has been established for weldments as part of the quality assurance activity. Until now, establishing the suitability of welding procedures by weld procedure testing was carried out and documented only for weldments involving safety and the public interest. The European harmonisation of the provision for welding procedure tests is currently being sought by means of European Standards. In this way greater confidence will be generated for the customer by the manufacturer.

The proofs also serve as the basis for the mutual recognition of performance reached by the relevant authorities. In this standard, the term "welding procedure" comprises all the activities which influence the welding result, such as preparation, welding parameters, post treatment and reworking.

iTeh STANDARD PREVIEW (standards.iteh.ai)

SIST EN ISO 15614-11:2003

<https://standards.iteh.ai/catalog/standards/sist/c1142ef4-9e5f-47b4-a58f-53a4e7fdda79/sist-en-iso-15614-11-2003>

1 Scope

This European Standard specifies how a welding procedure specification for electron or laser beam welding is qualified by a welding procedure test.

This standard is a part of a series of standards, details of this series are given in prEN ISO 15607, annex A.

It defines the conditions for the execution of welding procedure qualification tests and the limits of validity of a qualified welding procedure for all practical welding operations within the range of variables listed in clause 8.

Tests shall be carried out in accordance with this standard together with additional tests when specified.

This standard applies to metallic materials, irrespective of the shape of the parts, their thicknesses, manufacturing method (rolling, forging, casting, sintering, etc.) and their heat treatment. It covers unlimitedly the production of new parts and repair work.

2 Normative references

This European Standard incorporates by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European Standard only when incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies (including amendments).

EN 571-1, *Non destructive testing — Penetrant testing — Part 1: General principles.*

EN 895, *Destructive tests on welds in metallic materials — Transverse tensile test.*

EN 910, *Destructive tests on welds in metallic materials — Bend tests.*

EN 970, *Non-destructive examination of fusion welds — Visual examination.*

EN 1043-2, *Destructive test on welds in metallic materials — Hardness test — Part 2: Micro hardness testing on welded joints.*

EN 1290, *Non-destructive examination of welds — Magnetic particle examination of welds.*

EN 1321, *Destructive tests on welds in metallic materials — Macroscopic and microscopic examination of welds.*

EN 1435, *Non-destructive examination of welds — Radiographic examination of welded joints.*

EN 1714, *Non destructive examination of welds — Ultrasonic examination of welded joints.*

EN ISO 6947, *Welds — Working positions — Definitions of angles of slope and rotation (ISO 6947:1993).*

prEN ISO 15607, *Specification and approval of welding procedures for metallic materials – General rules (ISO/DIS 15607:2000).*

prEN ISO 15609-3:2000, *Specification and approval of welding procedures for metallic materials - Welding procedure specification — Part 3: Electron beam welding (ISO/DIS 15609-3:2000).*

prEN ISO 15609-4:2000, *Specification and approval of welding procedures for metallic materials - Welding procedure specification — Part 4: Laser beam welding (ISO/DIS 15609-4:2000).*

EN ISO 13919-1, *Welding — Electrons and laser beam welded joints — Guidance on quality levels for imperfections — Part 1: Steel (ISO 13919-1:1996).*

prEN ISO 13919-2, *Welding — Electron and laser beam welded joints — Guidance on quality levels for imperfections — Part 2: Aluminium and its weldable alloys (ISO/FDIS 13919-2:1999).*

3 Terms and definitions

For the purposes of this European Standard, the terms and definitions given in prEN ISO 15607, prEN ISO 15609-3 and prEN ISO 15609-4 apply.

4 Welding procedure specification (WPS)

A pWPS (preliminary welding procedure specification) shall be prepared in accordance with prEN ISO 15609-3 for electron beam welding and prEN ISO 15609-4 for laser beam welding. It shall specify the tolerances for all the relevant parameters.

A WPS shall be classified as pWPS until it is qualified in accordance with this standard.

The welding procedure specification (WPS) shall give details on how a welding operation is to be performed, including tacking and fixturing.

5 Welding procedure test

The manufacture and testing of test pieces shall be in accordance with clauses 6 and 7 of this standard.

In order to take into account the service performance needs of the products, the qualification may be made according to any of the acceptance levels B, C or D as defined in EN ISO 13919-1 for steels or in prEN ISO 13919-2 for aluminium and its alloys.

The quality level necessary in each case should be specified by the application standard or the responsible designer.

(standards.iteh.ai)
SIST EN ISO 15614-11:2003
<https://standards.iteh.ai/catalog/standards/sist/c1142ef4-9e5f-47b4-a58f-53a4e7fdda79/sist-en-iso-15614-11-2003>

6 Test piece

6.1 General

The assembly to which the electron or laser beam welding procedure applies in production may be represented by one or more standardized test pieces as defined in 6.2.

6.2 Shape and dimensions of test pieces

The test pieces shall be of sufficient size to ensure an adequate heat distribution and for the application of non-destructive and/or destructive tests.

The test piece shall be designed to represent, as far as possible, the component and joint geometry and shall be specified.

One or more additional test pieces or a longer test piece than the minimum size, may be used in order to allow for extra and/or for re-testing specimens, according to 7.5.


For plate material, the principal direction of rolling shall be marked on the test piece, if requested by the application standard or the specification.

The thickness and/or pipe outside diameter of the test pieces shall be selected in accordance with 8.5.2.1 to 8.5.2.2.

Unless otherwise specified, the shape and minimum dimensions of the test piece shall be as defined hereafter. Nonetheless, the length of the test piece shall be such as to permit the appropriate number of test specimens (as given in Tables 1 to Table 3) to be prepared.

6.2.1 Linear butt weld

The test piece shall be in accordance with Figure 1.

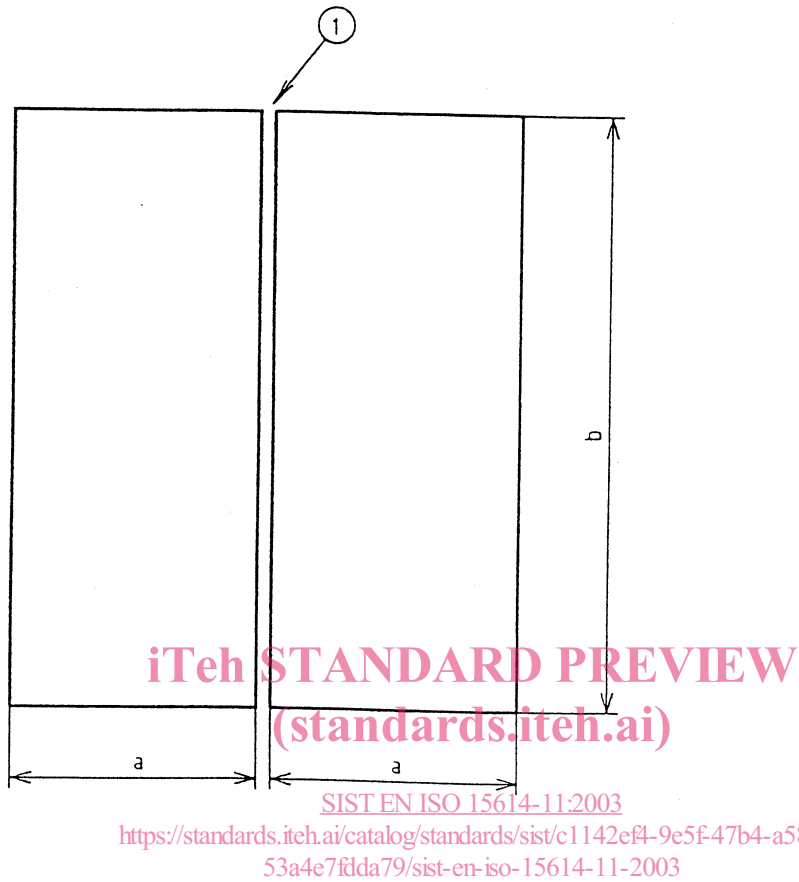

Key

- 1 Edge preparation and fit-up as detailed in the preliminary Welding Procedure Specification (pWPS)
 $a = 3 \times t$; minimum value 150 mm
 $b = 6 \times t$; minimum value 300 mm
 t = thickness of the thinner material in a dissimilar thickness joint

Figure 1 — Test piece for a linear butt weld

6.2.2 Circular butt weld


The test piece shall be in accordance with Figures 2 a) or 2 b). When small pipe diameters are used, several test pieces may be necessary.

In cases where the diameter, D , of the part is greater than 150 mm and $D > 20 t$, the qualification of the procedure may be achieved by welding a linear test piece. The test shall be designed to incorporate the weld overlap and slope down areas.

NOTE The word pipe is used to mean "pipe", "tube" or "hollow section".

6.2.2.1 Radial butt weld in pipe (in accordance with Figure 2 a)

6.2.2.2 Axial weld in pipe to pipe or pipe to plate (in accordance with Figure 2 b)

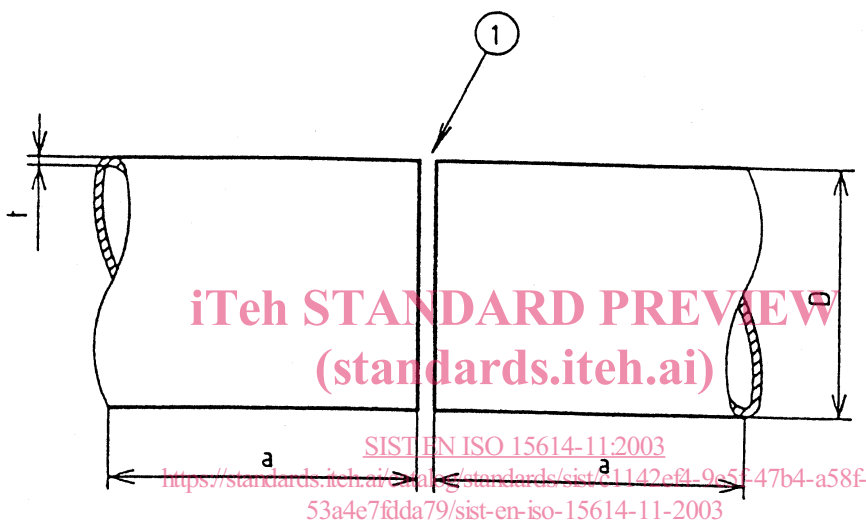

Key


1 Edge preparation and fit-up as detailed in the preliminary Welding Procedure Specification (pWPS)

$a = 3 \times t$; minimum value 150 mm

D = outside dimension of the pipe

t = wall thickness of the thinner pipe in a dissimilar thickness joint

a) Test piece for a radial butt weld in pipe

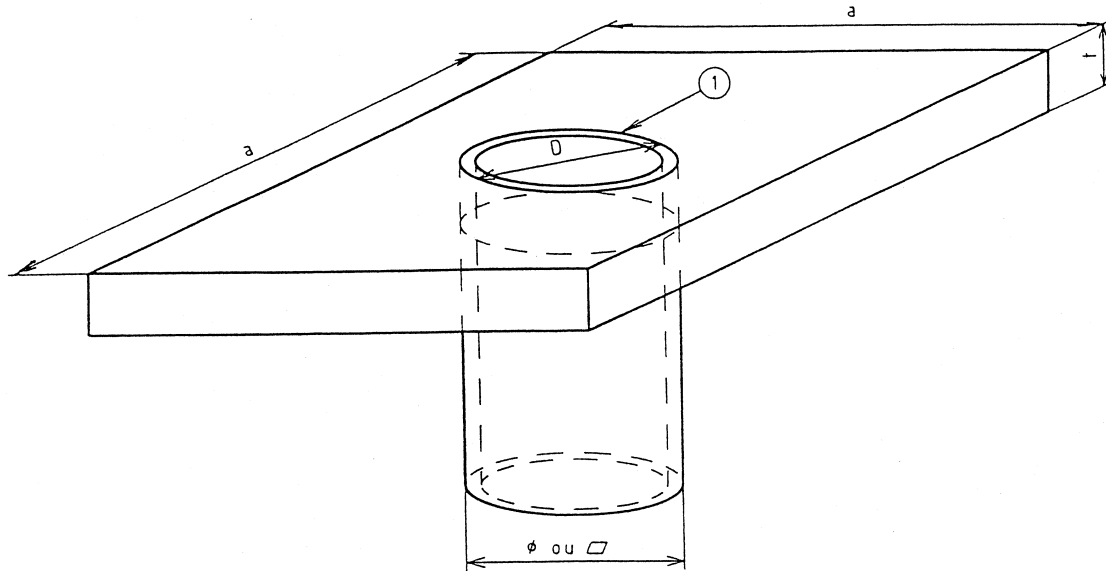**Key**

1 Edge preparation and fit-up as detailed in the preliminary Welding Procedure Specification (pWPS)

a = minimum plate dimension or component diameter

D = outside dimension of the pipe

$a \geq D + 6t$; minimum value $D + 150$ mm

t = plate thickness

b) Test piece for an axial weld in pipe to pipe or pipe to plate

<https://standards.iteh.ai/catalog/standards/sist/c1142ef4-9e5f-47b4-a58f-53a76f4d79/sist-en-iso-15614-11-2003>

Figure 2 — Test pieces for circular butt welds


6.2.3 Other types

6.2.3.1 T-joint

The test piece shall be in accordance with Figure 3.

T-joint of the following types can be made :

- a) T-butt from one side ;
- b) T-butt from two sides ;
- c) fillet weld (partial penetration) from one or two side(s) ;
- d) a stake weld(s).

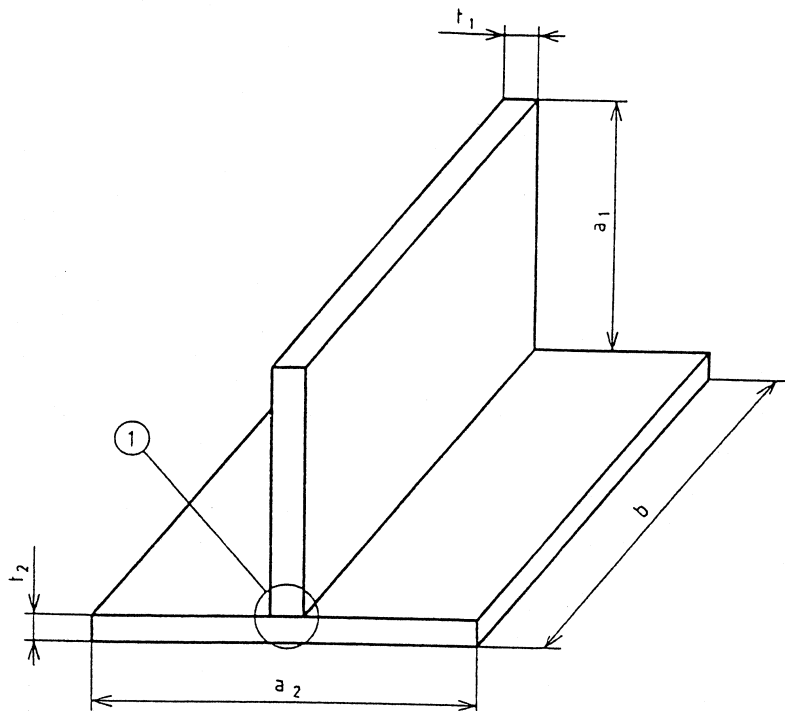

iTech STANDARD PREVIEW
(standards.itech.ai)

Key

1 Edge preparation and fit-up as detailed in the preliminary Welding Procedure Specification (pWPS)

For a), b) and c) configurations :

$a_1 \geq 6 \times t_1$; minimum value 50 mm

$a_2 \geq 6 \times t_1$; minimum value 100 mm

$b \geq 300$ mm

t_1 and t_2 = plate thicknesses

For d) configuration :

$a_1 \geq 6 \times t_2$; minimum value 50 mm

$a_2 \geq 6 \times t_2$; minimum value 100 mm

$b \geq 300$ mm

Figure 3 — Test piece for a T-joint

6.2.3.2 Lap weld

The test piece for a two layer lap weld shall be in accordance with the assembly shown in Figure 4.

The weld may be either partial or full penetration through all sheets or plates.