



SLOVENSKI STANDARD
SIST EN ISO 12224-2:2001

01-februar-2001

Flux cored solder wire - Specification and test methods - Part 2: Determination of flux content (ISO 12224-2:1997)

Flußmittelgefüllte Röhrenlote - Festlegung und Prüfverfahren - Teil 2: Bestimmung des Flußmittelgehalts (ISO 12224-2:1997)

Fils d'apport de brasage, pleins et à flux incorporé - Spécifications et méthodes d'essai - Partie 2: Détermination de la teneur en flux (ISO 12224-2:1997)

Ta slovenski standard je istoveten z: EN ISO 12224-2:1999

ICS:

25.160.50 Trdo in mehko lotanje Brazing and soldering

SIST EN ISO 12224-2:2001

en

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 12224-2:2001

<https://standards.iteh.ai/catalog/standards/sist/b2b3f349-9ed9-4687-8839-38471a4cdfb3/sist-en-iso-12224-2-2001>

EUROPEAN STANDARD
NORME EUROPÉENNE
EUROPÄISCHE NORM

EN ISO 12224-2

March 1999

ICS 25.160.20

English version

Flux cored solder wire - Specification and test methods - Part 2:
Determination of flux content (ISO 12224-2:1997)

Fils d'apport de brasage, pleins et à flux incorporé -
Spécifications et méthodes d'essai - Partie 2:
Détermination de la teneur en flux (ISO 12224-2:1997)

Flußmittelgefüllte Röhrenlote - Festlegung und
Prüfverfahren - Teil 2: Bestimmung des Flußmittelgehalts
(ISO 12224-2:1997)

This European Standard was approved by CEN on 20 February 1999.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

(standards.iteh.ai)

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

[SIST EN ISO 12224-2:2001](https://standards.iteh.ai/catalog/standards/sist/b2b3f349-9ed9-4687-8839-38471a4cdfb3/sist-en-iso-12224-2-2001)

<https://standards.iteh.ai/catalog/standards/sist/b2b3f349-9ed9-4687-8839-38471a4cdfb3/sist-en-iso-12224-2-2001>



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Central Secretariat: rue de Stassart, 36 B-1050 Brussels

Page 2
EN ISO 12224-2:1999

Foreword

The text of the International Standard from Technical Committee ISO/TC 44 "Welding and allied processes" of the International Organization for Standardization (ISO) has been taken over as an European Standard by Technical Committee CEN/TC 121 "Welding", the secretariat of which is held by DS.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by September 1999, and conflicting national standards shall be withdrawn at the latest by September 1999.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

Endorsement notice


The text of the International Standard ISO 12224-2:1997 has been approved by CEN as a European Standard without any modification.

NOTE: Normative references to International Standards are listed in annex ZA (normative).

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 12224-2:2001

<https://standards.iteh.ai/catalog/standards/sist/b2b3f349-9ed9-4687-8839-38471a4cdfb3/sist-en-iso-12224-2-2001>

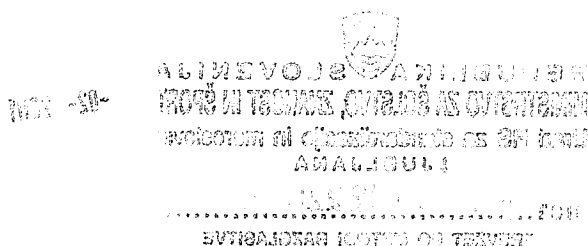

INTERNATIONAL STANDARD

ISO
12224-2

First edition
1997-12-15

Flux cored solder wire — Specification and test methods —

Part 2: Determination of flux content

*Fils d'apport de brasage, pleins et à flux incorporé — Spécifications et
méthodes d'essai*

Partie 2: Détermination de la teneur en flux

[SIST EN ISO 12224-2:2001](https://standards.iteh.ai/catalog/standards/sist/b2b3f349-9ed9-4687-8839-38471a4cdfb3/sist-en-iso-12224-2-2001)

<https://standards.iteh.ai/catalog/standards/sist/b2b3f349-9ed9-4687-8839-38471a4cdfb3/sist-en-iso-12224-2-2001>



Reference number
ISO 12224-2:1997(E)

ISO 12224-2:1997(E)

Foreword

ISO (the International Organisation for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an international Standard requires approval by at least 75 % of the member bodies casting a vote.

iTeh STANDARD PREVIEW

International Standard ISO 12224-2 was prepared by Technical Committee ISO/TC 44, *Welding and allied processes*, Subcommittee SC 12, *Soldering and brazing materials*.

ISO 12224 consists of the following parts, under the general title *Solder wire, solid and flux cored — Specification and test methods*:

- *Part 1: Classification and performance requirements*
- *Part 2: Determination of flux content*
- *Part 3: Wetting balance test*

Annex A of this part of ISO 12224 is for information only.

© ISO 1997

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization
Case postale 56 • CH-1211 Genève 20 • Switzerland
Internet central@iso.ch
X.400 c=ch; a=400net; p=iso; o=isocs; s=central

Printed in Switzerland

Flux cored solder wire — Specification and test methods —

Part 2:

Determination of flux content

1 Scope

This Part of ISO 12224 specifies two methods for the determination of the flux content of a sample flux cored solder wire.

iTeh STANDARD PREVIEW (standards.iteh.ai)

2 Principle

A known mass of the sample of flux cored solder wire is melted, separated from the flux medium and weighed. The flux content is calculated and expressed as a percentage by mass of the original wire.

<https://standards.iteh.ai/catalog/standards/sist/b2b51549-9cd9-4687-8839-38471a4cdfb3/sist-en-iso-12224-2-2001>

3 Apparatus and materials

3.1 Degreasing solvent, such as propan-2-ol or the solvent recommended by the manufacturer.

3.2 Balance, having an accuracy of $\pm 0,001$ g.

3.3 Porcelain crucible, capacity 30 ml.

3.4 Scraper, stainless.

3.5 Crucible tongs

3.6 Solder bath, containing solder, such as ISO 9453, grade S-Sn60Pb40, maintained at a temperature of $50\text{ °C} \pm 5\text{ °C}$ above the liquidus temperature of the wire under test.

3.7 Tissues

3.8 Glycerol

3.9 Glass beaker, pyrex, 100 ml - 150 ml.

4 Procedure

Clean the sample length of the flux cored solder wire under test with a tissue (3.7) soaked in the degreasing solvent (3.1). Follow either method A or method B below.

4.1 Method A

Carry out the test in duplicate.

Using the balance (3.2) weigh $50 \text{ g} \pm 5 \text{ g}$ of the cleaned wire to 0,001 g. Record the mass of the sample (m_1). Form the sample into a ball and transfer it to the cleaned crucible (3.3) or the beaker (3.9).

Clean the surface of the molten solder in the solder bath (3.6) by means of the scraper (3.4).

Holding the crucible or beaker with the tongs (3.5), partially immerse it in the solder bath (3.6), maintained at a temperature $50 \text{ °C} \pm 5 \text{ °C}$ above the liquidus temperature of the wire under test. Turn the crucible or beaker gently until the solder has melted into one pellet. Leave the crucible or beaker immersed in the solder bath for 10 s - 15 s after the solder has melted.

Remove the crucible or beaker from the solder bath and allow it to cool until the solder has just solidified. Pour off as much flux as possible while the flux remains warm.

Remove the pellet from the crucible or beaker. Clean it thoroughly with degreasing solvent (3.1) to remove all traces of flux. Dry the pellet with a clean tissue (3.7). Using the balance (3.2) weigh the dry pellet to a constant weight to 0,001 g. Record the mass of the pellet (m_2).

4.2 Method B

[SIST EN ISO 12224-2:2001
https://standards.iteh.ai/catalog/standards/sist/b2b3f349-9ed9-4687-8839-38471a4cdfb3/sist-en-iso-12224-2-2001](https://standards.iteh.ai/catalog/standards/sist/b2b3f349-9ed9-4687-8839-38471a4cdfb3/sist-en-iso-12224-2-2001)

Carry out the test in duplicate.

Using the balance (3.2) weigh $30 \text{ g} \pm 2 \text{ g}$ of the cleaned wire to 0,001 g. Record the mass of the sample (m_1).

Transfer the solder wire to the beaker (3.9) with sufficient glycerol (3.8) to cover the sample (approximately 50 ml of glycerol).

Clean the surface of the molten solder in the solder bath (3.6) by means of the scraper (3.4).

Holding the beaker with the tongs (3.5), partially immerse it in the solder bath (3.6), maintained at a temperature $50 \text{ °C} \pm 5 \text{ °C}$ above the liquidus temperature of the wire under test. Turn the beaker until the solder has melted into one pellet. Leave the beaker immersed in the solder bath for 10 s - 15 s after the solder has melted, while turning gently.

Allow the solder to solidify and then decant as much of the flux/glycerol mixture as possible from the molten solder. Allow the solder to cool and solidify.

Remove the solder pellet and wash it in water. Clean it thoroughly with degreasing solvent (3.1) to remove all traces of flux. Dry the pellet with a clean tissue (3.7).

Using the balance (3.2) measure the mass of the dry pellet to a constant weight, to 0,001 g (m_2).

NOTE — In cases of dispute. It is recommended that the method to be used be agreed between supplier and purchaser.

5 Expression of results for both methods

Calculate the flux content of the sample wire as the percentage by mass, using the following formula:

$$\text{Flux content} = \left[\frac{m_1 - m_2}{m_1} \right] \times 100 \% (m / m)$$

where

m_1 is the mass, in grams, of the flux cored solder wire used in the test;

m_2 is the mass, in grams, of the solder pellet.

If the values of the two determinations differ by more than 0,2 %, the determination shall be repeated completely.

Calculate the arithmetic mean of the two determinations.

6 Test report

The test report shall include the following information:

- a) the identification of the test sample;
- b) reference to this part of ISO 12224;
- c) the test method used;
- d) the results obtained;
- e) any unusual features noted during the test;
- f) details of any operation not included in this part of ISO 12224, or regarded as optional.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN ISO 12224-2:2001](https://standards.iteh.ai/catalog/standards/sist/b2b3f349-9ed9-4687-8839-38471a4cdfb3/sist-en-iso-12224-2-2001)

<https://standards.iteh.ai/catalog/standards/sist/b2b3f349-9ed9-4687-8839-38471a4cdfb3/sist-en-iso-12224-2-2001>