



SLOVENSKI STANDARD

SIST-TP CEN/TR 15149-3:2015

01-februar-2015

Nadomešča:

SIST-TS CEN/TS 15149-3:2006

Trdna biogoriva - Določevanje porazdelitve velikosti delcev - 3. del: Metoda z vrtečim sitom

Solid biofuels - Determination of particle size distribution - Part 3: Rotary screen method

Feste Biobrennstoffe - Bestimmung der Teilchengrößenverteilung - Teil 3: Verfahren mit rotierendem Sieb

iTeh STANDARD PREVIEW
(standards.iteh.ai)

Combustibles solides - Détermination de la distribution granulométrique - Partie 3 :
Méthode au tamis rotatif

[SIST-TP CEN/TR 15149-3:2015](#)

<https://standards.iteh.ai/catalog/standards/sist/fd866b80-2624-4aec-85a2-954e8b7dc5dc/sist-tp-cen-tr-15149-3-2015>

Ta slovenski standard je istoveten z: CEN/TR 15149-3:2014

ICS:

27.190	Biološki viri in drugi alternativni viri energije	Biological sources and alternative sources of energy
75.160.10	Trda goriva	Solid fuels

SIST-TP CEN/TR 15149-3:2015

en

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST-TP CEN/TR 15149-3:2015](#)

<https://standards.iteh.ai/catalog/standards/sist/fd866b80-2624-4aec-85a2-954e8b7dc5dc/sist-tp-cen-tr-15149-3-2015>

TECHNICAL REPORT
RAPPORT TECHNIQUE
TECHNISCHER BERICHT

CEN/TR 15149-3

November 2014

ICS 75.160.10

Supersedes CEN/TS 15149-3:2006

English Version

Solid biofuels - Determination of particle size distribution - Part 3: Rotary screen method

Biocombustibles solides - Détermination de la distribution
granulométrique - Partie 3 : Méthode au tamis rotatif

Feste Biobrennstoffe - Bestimmung der
Teilchengrößenverteilung - Teil 3: Verfahren mit
rotierendem Sieb

This Technical Report was approved by CEN on 18 July 2011. It has been drawn up by the Technical Committee CEN/TC 335.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST-TP CEN/TR 15149-3:2015](https://standards.iteh.ai/catalog/standards/sist/fd866b80-2624-4aec-85a2-954e8b7dc5dc/sist-tp-cen-tr-15149-3-2015)

<https://standards.iteh.ai/catalog/standards/sist/fd866b80-2624-4aec-85a2-954e8b7dc5dc/sist-tp-cen-tr-15149-3-2015>



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Avenue Marnix 17, B-1000 Brussels

Contents

	Page
Foreword.....	3
Introduction	4
1 Scope	5
2 Normative references	5
3 Terms and definitions	5
4 Principle	5
5 Apparatus	5
6 Sample preparation	7
6.1 Sample size	7
6.2 Sample preparation	7
7 Procedure	7
8 Calculation.....	8
9 Precision and bias	9
10 Test report	10
Annex A (informative) Example of a rotary sieving machine	11
Bibliography	12

[SIST-TP CEN/TR 15149-3:2015](https://standards.iteh.ai/catalog/standards/sist/fd866b80-2624-4aec-85a2-954e8b7dc5dc/sist-tp-cen-tr-15149-3-2015)
<https://standards.iteh.ai/catalog/standards/sist/fd866b80-2624-4aec-85a2-954e8b7dc5dc/sist-tp-cen-tr-15149-3-2015>

Foreword

This document (CEN/TR 15149-3:2014) has been prepared by Technical Committee CEN/TC 335 “Solid biofuels”, the secretariat of which is held by SIS.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes CEN/TS 15149-3:2006.

This document has been prepared under a mandate given to CEN by the European Commission and the European Free Trade Association.

EN 15149, *Solid biofuels — Determination of particle size distribution*, consists of the following parts:

- *Part 1: Oscillating screen method using sieve apertures of 1 mm and above;*
- *Part 2: Vibrating screen method using sieve apertures of 3,15 mm and below;*
- *Part 3: Rotary screen method* [Technical Report; the present document].

The most significant changes since the latest edition of this text are the following ones:

- The former edition was a Technical Specification; it was turned into the present Technical Report.
- References have been consistently updated.

iTeh STANDARD PREVIEW
(standards.iteh.ai)
[SIST-TP CEN/TR 15149-3:2015](https://standards.iteh.ai/catalog/standards/sist/fd866b80-2624-4aec-85a2-954e8b7dc5dc/sist-tp-cen-tr-15149-3-2015)
<https://standards.iteh.ai/catalog/standards/sist/fd866b80-2624-4aec-85a2-954e8b7dc5dc/sist-tp-cen-tr-15149-3-2015>

CEN/TR 15149-3:2014 (E)**Introduction**

Part 1 describes the reference method for size classification of samples with a nominal top size of 3,15 mm and over.

Part 2 describes the reference methods for all samples with a nominal top size below 3,15 mm.

Part 3 describes an innovative method, by which the degree of overestimating the fine particle fractions is reduced. As it is currently not generally available, it is here proposed for research and development purposes or for individual quality management processes, in which the quality requirements are bilaterally defined between the suppliers and consumers based on this method.

NOTE The nominal top size is defined as the aperture size of the sieve where at least 95 % by mass of the material passes (see Bibliography).

**iTeh STANDARD PREVIEW
(standards.iteh.ai)**

[SIST-TP CEN/TR 15149-3:2015](https://standards.iteh.ai/catalog/standards/sist/fd866b80-2624-4aec-85a2-954e8b7dc5dc/sist-tp-cen-tr-15149-3-2015)

<https://standards.iteh.ai/catalog/standards/sist/fd866b80-2624-4aec-85a2-954e8b7dc5dc/sist-tp-cen-tr-15149-3-2015>

1 Scope

This Technical Report specifies a method for the determination of the size distribution of particulate biofuels by the rotary screen method. The method described is meant for particulate biofuels only, namely materials that either have been reduced in size, such as most wood fuels, or are physically in a particulate form e.g. olive stones, nutshells, grain, etc. This document applies to particulate uncompressed fuels with a nominal top size of 3,15 mm and over, e.g. wood chips, hog fuel, olive stones, etc.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 14778, *Solid biofuels — Sampling*

EN 14780, *Solid biofuels — Sample preparation*

EN 14774-1, *Solid biofuels — Determination of moisture content - Oven dry method — Part 1: Total moisture — Reference method*

EN 14774-2, *Solid biofuels — Determination of moisture content — Oven dry method — Part 2: Total moisture — Simplified method*

EN 15149-2, *Solid biofuels — Determination of particle size distribution — Part 2: Vibrating screen method using sieve apertures of 3,15 mm and below*

EN ISO 16559, *Solid biofuels — Terminology, definitions and descriptions (ISO 16559)*

ISO 3310-2, *Test sieves — Technical requirements and testing — Part 2: Test sieves of perforated metal plate*

3 Terms and definitions

For the purpose of this document, the terms and definitions given in EN ISO 16559 apply.

3.1

nominal top size

aperture size of the sieve where at least 95 % by mass of the material passes

4 Principle

A sample is subjected to sieving through sieves in a rotary sieving machine sorting the particles by increasing size.

5 Apparatus

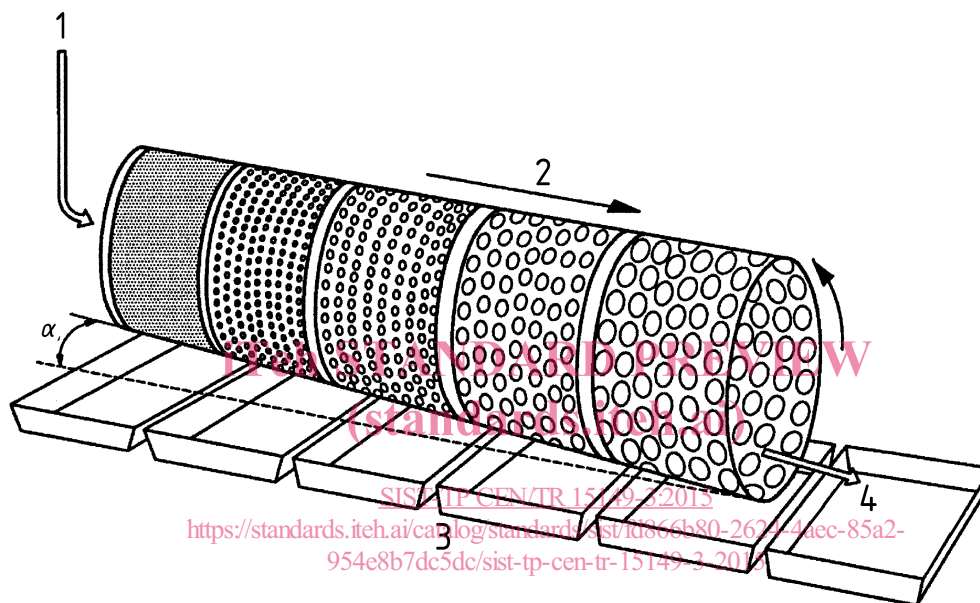
5.1 Rotary screen.

For the test a rotary sieving device is required for which the operating principle is shown in Figure 1. The rotary sieving device consists of five joined cylindrical sieve rings each with an inner diameter of 500 mm

CEN/TR 15149-3:2014 (E)

(± 15 mm). The height (length) of each of the 5 sieve rings is 400 mm with a maximum of 20 mm imperforated ("blind") surface at each side; as a consequence each ring is having an effective sieving length of 360 mm or higher. All five cylinder rings (sieves) are evenly long and consecutively connected to each other, thus forming a drum. The inner surface of the drum shall be constructed in a way, which allows the particles to slide from one ring to another without interruption. Downward to the direction of flow the drum is inclined at an angle of 3° ($\pm 0,2^\circ$) towards the horizontal ground. The drum shall be rotating at a speed 16 rotations per minute.

Due to both, inclination and rotation of the drum, the sample is continuously being transported forward in the drum over the rotating sieves. Thereby the particles are separated by their size by passing through the sieve holes and falling into individual collecting pans underneath each sieve cylinder. Large particles, which have not passed through any sieve holes, are finally being discharged from the drum into a final collecting pan. The size of each individual pan should be at least 70 % of the initial test sample volume.

**Key**

- 1 material addition
- 2 increasing hole diameter
- 3 material flow direction
- 4 collecting pans

Figure 1 — Operating principle of rotating sieves

The geometry of the apertures and the thickness of the sieves shall be in accordance with the requirements of ISO 3310-2. The aperture sizes of the sieves shall be chosen according to the size specification of the sample material. It is recommended that the diameters of the holes in the sieves are 3,15 mm, 8 mm, 16 mm, 45 mm and 63 mm. On the rotating drum the cylinders shall be arranged by increasing sieve hole diameters, starting with the smallest sieve holes where the sample material shall be fed on (see Figure 1).

5.2 Balance.

A balance capable of measuring the mass of the sample to be sieved to the nearest 0,1 g is required.

6 Sample preparation

6.1 Sample size

The minimum size of the test sample for the determination of the size distribution shall be 8 l and shall have been sampled according to EN 14778. For fine grade biofuels, where 100 % of the particles pass sieve holes of 45 mm diameter, a smaller sample size of minimum 4 l can be used.

The sample should include material for determination of size distribution and moisture content.

6.2 Sample preparation

The sample shall be sieved at a moisture content below 20 % wet base, thus preventing the particles from sticking together or losing moisture during the sieving process. If necessary the sample shall be pre-dried. Drying is done according to EN 14780.

NOTE By pre-drying, as described in EN 14780, the sample is brought into equilibrium with the humidity of the surrounding atmosphere.

Determine the moisture content of the material to be sieved on a separate sub-sample following the procedure given in EN 14774-1 or EN 14774-2. The moisture content shall be determined and reported concurrently with the particle size distribution determination.

iTeh STANDARD PREVIEW (standards.iteh.ai)

7 Procedure

Assemble and operate the rotary sieve with the appropriate sieves in accordance with 5.1.

Weigh the sample to the nearest 0,1 g of the total sample mass.

Feed the sample material continuously into the rotating sieve at a constant feeding rate of 1 l per min. This can, for example, be achieved by letting the sample material fall over an infeed slide onto the edge of the first cylinder.

The homogeneous feeding rate can be achieved either by a mechanical feeding mechanism or by hand feeding onto the slide. If feeding is done by hand, the sample should be divided into several portions (for example 8 portions) of equal volume; these portions are then dropped onto the slide sequentially in a way that ensures an even and uninterrupted flow throughout the total feeding time (e.g. 8 × 1 min).

If a larger sample size (more than 8 l) is processed, the capacity of the collecting pans may be exceeded or the sample may have to be separated in two or more portions and be processed subsequently.

Stop the rotation when no more material is remaining in the rotating drum. In case that a particle sticks in a sieving hole, the sieve shall be stopped and the particle shall be re-fed in the sieve. Restart the rotary sieve and let the sieve empty.

All particles larger than 100 mm (maximum dimension) shall be hand sorted into one or more fractions regardless from which sieve or collecting pan they are collected.

Weigh the net material in each fraction with an accuracy of 0,1 g and record the mass in a scheme equal to Table 1.

NOTE In many cases it is useful to identify the largest particle (maximum dimension) and record it in a scheme equal to Table 1. The information on the longest particle may be required for computing the median particle size or for illustrating the results in a cumulative size distribution curve.