



SLOVENSKI STANDARD

SIST EN 15150:2011

01-december-2011

Nadomešča:

SIST-TS CEN/TS 15150:2005

Trdna biogoriva - Določevanje prostorninske mase

Solid biofuels - Determination of particle density

Feste Biobrennstoffe - Bestimmung der Partikeldichte

Combustibles solides - Détermination de la masse volumique des particules

iTeh STANDARD PREVIEW
(standards.iteh.ai)

Ta slovenski standard je istoveten z: EN 15150:2011

<https://standards.iteh.ai/catalog/standards/sist/5d7780d0-4e93-4e6f-bd7d-3eba4886e099/sist-en-15150-2011>

ICS:

75.160.10 Trda goriva

Solid fuels

SIST EN 15150:2011

en,fr,de

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN 15150:2011

<https://standards.iteh.ai/catalog/standards/sist/5d7780d0-4e93-4e6f-bd7d-3cba4886ef99/sist-en-15150-2011>

EUROPEAN STANDARD
NORME EUROPÉENNE
EUROPÄISCHE NORM

EN 15150

November 2011

ICS 75.160.10

Supersedes CEN/TS 15150:2005

English Version

Solid biofuels - Determination of particle density

Biocombustibles solides - Détermination de la masse
volumique des particules

Feste Biobrennstoffe - Bestimmung der Partikeldichte

This European Standard was approved by CEN on 18 September 2011.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

SIST EN 15150:2011

<https://standards.iteh.ai/catalog/standards/sist/5d7780d0-4e93-4e6f-bd7d-3cba4886ef99/sist-en-15150-2011>



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: Avenue Marnix 17, B-1000 Brussels

Contents

Page

Foreword.....	3
1 Scope	4
2 Normative references	4
3 Terms and definitions	4
4 Principle.....	4
5 Reagents.....	4
6 Apparatus	5
6.1 General apparatus requirements	5
6.2 Apparatus for pellet testing	5
6.3 Apparatus for briquette testing	6
7 Sample preparation	7
8 Procedure	9
8.1 Procedure for pellets (up to a diameter of 25 mm according to EN 14961-1 and EN 14961-3).....	9
8.2 Procedure for briquettes (with a diameter equal or higher than 25 mm, according to EN 14961-1 and EN 14961-3).....	9
9 Calculation.....	10
10 Precision.....	11
11 Test report	11
Annex A (informative) Stereometric volume estimation	12
Bibliography	14

Foreword

This document (EN 15150:2011) has been prepared by Technical Committee CEN/TC "Solid biofuels", the secretariat of which is held by SIS.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by May 2012, and conflicting national standards shall be withdrawn at the latest by May 2012.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes CEN/TS 15150:2005.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and the United Kingdom.

iTeh STANDARD PREVIEW (standards.iteh.ai)

SIST EN 15150:2011

<https://standards.iteh.ai/catalog/standards/sist/5d7780d0-4e93-4e6f-bd7d-3cba4886ef99/sist-en-15150-2011>

EN 15150:2011 (E)

1 Scope

This European Standard describes the method for determining the particle density of compressed fuels such as pellets or briquettes. Particle density is not an absolute value and conditions for its determination have to be standardised to enable comparative determinations to be made.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 14588, *Solid biofuels – Terminology, definitions and descriptions*

EN 14961-1, *Solid biofuels – Fuel specifications and classes – Part 1: General requirements*

EN 14961-3, *Solid biofuels – Fuel specifications and classes – Part 3: Wood briquettes for non-industrial use*

EN 14778, *Solid biofuels – Sampling*

EN 14780, *Solid biofuels – Sample preparation*

EN 14774-1, *Solid biofuels – Determination of moisture content – Oven dry method – Part 1: Total moisture – Reference method*

EN 14774-2, *Solid biofuels – Determination of moisture content – Oven dry method – Part 2: Total moisture – Simplified method*

SIST EN 15150:2011
<https://standards.iteh.ai/catalog/standards/sist/5d7780d0-4e93-4e6f-bd7d-3cba4886ef99/sist-en-15150-2011>

3 Terms and definitions

For the purpose of this document, the terms and definitions given in EN 14588 apply.

4 Principle

Both mass and volume of an individual particle or a group of particles are determined. The volume is measured by determining the buoyancy in a liquid. This procedure follows the physical principle that the buoyancy of a body is equal to the weight of the displaced volume of a liquid. The apparent loss in weight between a measurement in air and a subsequent measurement in liquid marks its buoyancy. The volume of the sample body is calculated via the density of the applied liquid.

NOTE The particle density of briquettes could also be estimated by stereometric means (see informative Annex A). This estimation could also be made if pellets are cut to determine their volume by stereometric means. Be aware of a higher variability between the replications when applying the stereometric measuring principle.

5 Reagents

5.1 Water with low content of ions (e.g. drinking water quality) in a temperature range of 10 °C to 30 °C.

5.2 A detergent named O-[4-(1,1,3,3-Tetramethylbutyl)-phenyl]-deca(oxyethylen), Octylphenoldecaethylen-glycolether, Polyethylenglycol-mono-[p-(1,1,3,3-tetramethylbutyl)-phenyl]-ether.

NOTE The exclusive use of this specific detergent with given characteristics allows to apply a fixed value for the density of the liquid (mixture with water) and ensures constant properties as wetting agent. The detergent is, for example, traded under the name Triton® X-100. The density at 20 °C is 1,07 g/l.

5.3 Paraffin with a melting point of 52 °C to 54 °C.

6 Apparatus

6.1 General apparatus requirements

6.1.1 Thermometer for liquids having a measuring accuracy of 1 °C


6.1.2 Facilities for moisture content determination according to EN 14774-1 or EN 14774-2

6.2 Apparatus for pellet testing

6.2.1 A balance, having sufficient accuracy to determine the weight to the nearest 0,001 g. Due to the high sensitivity of the balance, the test rig shall be placed into a wind protection cabinet to allow undisturbed and immediate reading of the displayed values.

6.2.2 A transparent beaker glass of about 200 ml filling volume.

6.2.3 A density determination rig which can be placed on the balance. The rig consists of a bridge which overstretches the weighing plate of the balance in order to prevent the balance from being loaded. The bridge is capable of carrying the beaker glass (6.2.2). Through a supporting frame with suspension rods a weighing dish ("submergence dish") is hung into the beaker glass (Figure 1) which is filled with liquid. The dish shall be able to accommodate at least four pellets at once. Both, the supporting frame and the submergence dish are directly loaded on the balance plate. The submergence apparatus (the dish and the suspension) can be removed for being loaded with pellets. Through the dish suspension, the submergence depth is always kept constant. The bottom of the submergence dish is perforated by openings which are smaller in diameter than the diameter of the pellets. This perforation allows the liquid to fill the dish from underneath when it is submerged. If sample material of low density shall be applied (below 1,0 g/cm³) a modified suspension having an inverted submergence dish is required; this is to force the pellets underneath the liquid surface and prevent them from floating atop of the liquid. For the determination of the mass in air it is useful to use a combined test rig where an additional upper weighing dish is fixed to the suspension (Figure 1).

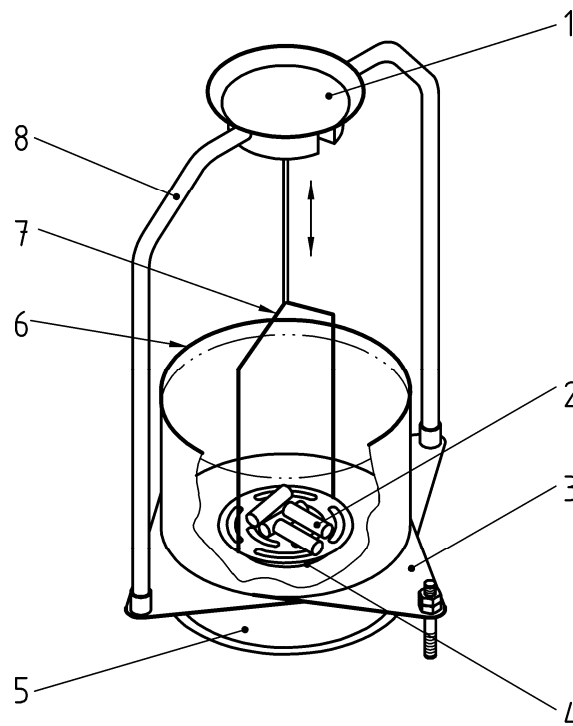

Key

- 1 weighing dish (weighing in air)
- 2 pellets
- 3 bridge
- 4 perforated submergence dish (weighing in water)
- 5 weighing plate (balance)
- 6 beaker glass
- 7 dish suspension
- 8 supporting frame

Figure 1 — Buoyancy determination rig on a balance (method for pellets)

6.3 Apparatus for briquette testing

6.3.1 A balance, having sufficient accuracy to determine the weight to the nearest 0,01 g. If briquettes of more than 500 g each are tested the accuracy of the balance can be reduced to 0,1 g. The balance must have a connecting point for hanging a weight to its load cell.

6.3.2 A transparent container for liquids having a sufficient filling volume to accommodate the liquid and the submerged briquette.


NOTE A sufficient filling volume is usually achieved when the container's cross section is about 8 times larger than the cross section of the briquette. In this case any effects by level changes of the liquid caused by submersion of the briquette are negligible. Such error would be due to a larger part of the holding steel string (see 6.3.3) being submerged.

6.3.3 A non absorbent thin steel string which can be hung to the connecting point of the balance. The end of the string is equipped with a hook or a ring, which allows an easy appending of the sample.

6.3.4 A tripod where the balance can be placed on. The tripod must have a plate with an opening which allows the string to pass through unhindered while hanging to the balance (Figure 2).

6.3.5 A technical support (e.g. steel loops or bracket) to hang up the briquette on the lower connecting point while it is being submerged in the liquid.

6.3.6 If sample material of low density shall be tested (below $1,0 \text{ g/cm}^3$) a removable weight is required, which is positioned onto the sample in a way which prevents the briquette from floating atop of the liquid.

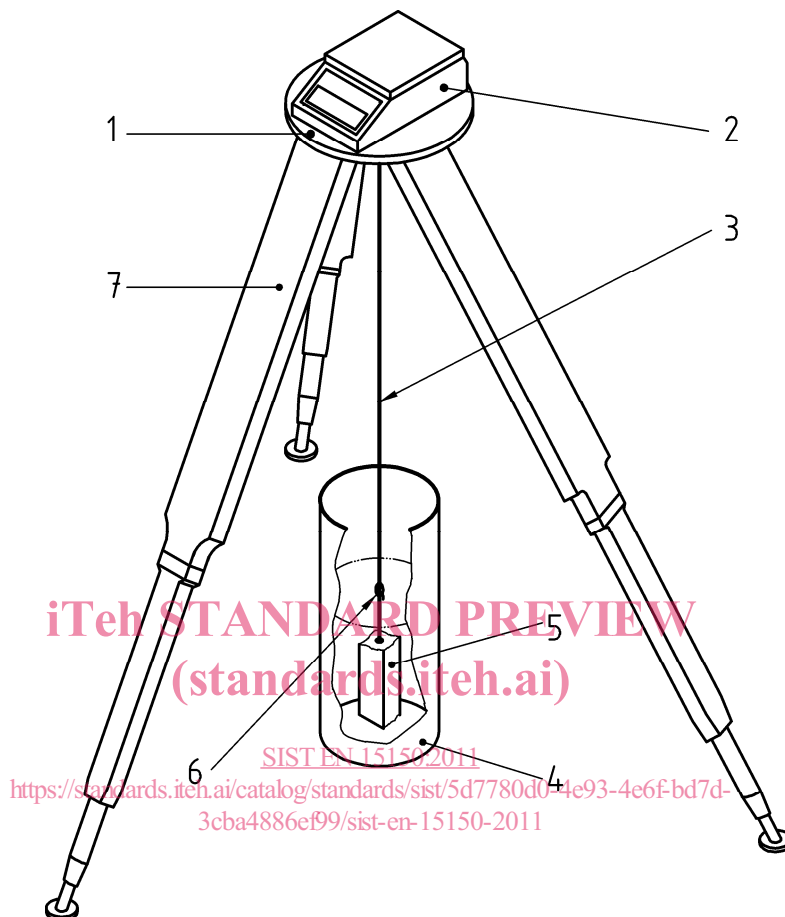

Key

- 1 carrying plate with opening
- 2 balance
- 3 steel string
- 4 liquid container
- 5 test sample (briquette)
- 6 connecting ring or hook
- 7 tripod

Figure 2 — Buoyancy determination rig using a hanging load to a balance (method for briquettes)

7 Sample preparation

7.1 Sampling and sample preparation shall be done in accordance with EN 14778 and EN 14780.

7.2 A total sample weight of 500 g (pellets with a diameter equal to or below 12 mm) or 1 000 g for pellets with a diameter above 12 mm or a minimum of 15 briquettes is required.