
Tekstilije - Metode za določevanje nekaterih aromatskih aminov, izvirajočih iz azo barvil - 3. del: Zaznavanje prisotnosti določenih azo barvil, ki lahko sproščajo 4-aminoazobenzen

Textiles - Methods for determination of certain aromatic amines derived from azo colorants - Part 3: Detection of the use of certain azo colorants which may release 4-aminoazobenzene

Textilien - Verfahren für die Bestimmung bestimmter aromatischer Amine aus Azofarbstoffen - Teil 3: Nachweis der Verwendung gewisser Azofarbstoffe die 4-Aminoazobenzol freisetzen können

Textiles - Méthodes de détermination de certaines amines aromatiques dérivées de colorants azoïques - Partie 3: Détection de l'utilisation de certains colorants azoïques susceptibles de libérer du 4-aminoazobenzène

Ta slovenski standard je istoveten z: EN 14362-3:2012

ICS:

59.080.01 Tekstilije na splošno Textiles in general

SIST EN 14362-3:2012 **en,fr,de**

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN 14362-3:2012

<https://standards.iteh.ai/catalog/standards/sist/94900513-bea7-4ae9-8202-10f2c2b11bc0/sist-en-14362-3-2012>

EUROPEAN STANDARD
NORME EUROPÉENNE
EUROPÄISCHE NORM

EN 14362-3

June 2012

ICS 59.080.01

English Version

**Textiles - Methods for determination of certain aromatic amines
derived from azo colorants - Part 3: Detection of the use of
certain azo colorants, which may release 4-aminoazobenzene**

Textiles - Méthodes de détermination de certaines amines
aromatiques dérivées de colorants azoïques - Partie 3:
Détection de l'utilisation de certains colorants azoïques
susceptibles de libérer du 4-aminoazobenzène

Textilien - Verfahren für die Bestimmung bestimmter
aromatischer Amine aus Azofarbstoffen - Teil 3: Nachweis
der Verwendung gewisser Azofarbstoffe, die 4-
Aminoazobenzol freisetzen können

This European Standard was approved by CEN on 24 May 2012.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: Avenue Marnix 17, B-1000 Brussels

Contents

Page

Foreword.....	3
1 Scope	4
2 Normative references	4
3 General.....	4
4 Principle.....	5
5 Safety precautions.....	5
6 Reagents	5
7 Apparatus	6
8 Procedure	7
9 Evaluation.....	9
10 Test report	10
Annex A (informative) Chromatographic analyses	11
Annex B (normative) Calculation.....	16
Annex C (informative) Reliability of the method.....	18
Annex D (informative) Assessment guide - Interpretation of analytical results	20

[SIST EN 14362-3:2012](https://standards.iteh.ai/catalog/standards/sist/94900513-bea7-4ae9-8202-10f2c2b11bc0/sist-en-14362-3-2012)

<https://standards.iteh.ai/catalog/standards/sist/94900513-bea7-4ae9-8202-10f2c2b11bc0/sist-en-14362-3-2012>

Foreword

This document (EN 14362-3:2012) has been prepared by Technical Committee CEN/TC 248 "Textiles and textile products", the secretariat of which is held by BSI.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by December 2012, and conflicting national standards shall be withdrawn at the latest by December 2012.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

iTeh STANDARD PREVIEW (standards.iteh.ai)

SIST EN 14362-3:2012

<https://standards.iteh.ai/catalog/standards/sist/94900513-bea7-4ae9-8202-10f2c2b11bc0/sist-en-14362-3-2012>

EN 14362-3:2012 (E)**1 Scope**

Azo colorants that are able to form 4-aminoazobenzene, generate under the conditions of EN 14362-1 the amines aniline and 1,4-phenylenediamine. The presence of these 4-aminoazobenzene colorants cannot be reliably ascertained without additional information (e.g. the chemical structure of the colorant used) or without a special procedure.

This part of EN 14362 is supplementary to Part 1 and describes a special procedure to detect the use of certain azo colorants in commodities, which may release 4-aminoazobenzene,

- accessible to reducing agent without extraction, particularly concerning textiles made of cellulose and protein fibres (e.g. cotton, viscose, wool, silk);
- accessible by extracting the fibres (e.g. polyester or imitation leather).

For certain fibre blends both parts of this standard (without or with extraction) may need to be applied.

The procedure detects as well 4-aminoazobenzene (Solvent Yellow 1) which is already available as free amine in commodities without reducing pre-treatment.

The use of certain azo colorants, which may release by reductive cleavage of their azo group(s) one or more of the other aromatic amines listed in the *Regulation (EC) No 1907/2006 of the European Parliament and of the Council on the Registration, Evaluation, Authorisation and Restriction of Chemicals (REACH) as regards Annex XVII*, except 4-aminoazobenzene, cannot be determined quantitatively with this method.

iTech STANDARD PREVIEW
(standards.itech.ai)

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 14362-1:2012, *Textiles — Methods for determination of certain aromatic amines derived from azo colorants — Part 1: Detection of the use of certain azo colorants accessible with and without extracting the fibres*

EN ISO 3696, *Water for analytical laboratory use — Specification and test methods (ISO 3696)*

3 General

Certain azo colorants may release, by reductive cleavage of azo group(s), 4-aminoazobenzene, which is proscribed under *Regulation (EC) No 1907/2006 of the European Parliament and of the Council on the Registration, Evaluation, Authorisation and Restriction of Chemicals (REACH) as regards Annex XVII*.

Table 1 — 4-aminoazobenzene proscribed under Regulation REACH 1907/2006/Annex XVII

No.	CAS number	Index number	EC number	Substance
22	60-09-3	611-008-00-4	200-453-6	4-aminoazobenzene

4 Principle

After selection of a coloured test specimen from the textile article, the test specimen is tested according to the method of the colorant extraction for disperse dyes and/or the method of the direct reduction for the other classes of the dyes (see EN 14362-1).

The textile sample or the residue of the sample extraction is treated with sodium dithionite in an alkaline solution at 40 °C in a closed vessel. 4-aminoazobenzene, which is released in the process, is transferred to a *t*-butyl methyl ether phase by means of liquid-liquid extraction. An aliquot of the *t*-butyl methyl ether phase is used for analysis. The detection and determination of 4-aminoazobenzene can be performed using chromatography (see Annex A).

If 4-aminoazobenzene is detected by one chromatographic method, then confirmation shall be made using one or more alternative methods.

5 Safety precautions

5.1 WARNING — 4-aminoazobenzene is classified as a substance known to be or suspected to be human carcinogen.

Any handling and disposal of these substances shall be in strict accordance with the appropriate national health and safety regulations.

5.2 It is the user's responsibility to use safe and proper techniques in handling materials in this test method. Consult manufacturers for specific details such as material safety data sheets and other recommendations.

5.3 Good laboratory practice should be followed. Wear safety glasses in all laboratory areas and a single-use dust respirator while handling powder colorants.

5.4 Users should comply with any national and local safety regulations.

6 Reagents

Unless otherwise specified, analytical grade chemicals shall be used.

6.1 aqueous sodium dithionite solution, $\rho = 200 \text{ mg/ml}^1$, freshly prepared, to use immediately after resting for one hour in a closed vessel

6.2 sodium hydroxide aqueous solution, $\omega = 2 \text{ \%}^2$)

6.3 *n*-pentane

6.4 methanol

6.5 chlorobenzene

6.6 *t*-butyl methyl ether

6.7 sodium chloride

1) ρ = mass concentration

2) ω = mass portion (% by weight)

EN 14362-3:2012 (E)

6.8 4-aminoazobenzene, highest available defined purity standard

6.9 internal standards for gas chromatography (IS), e.g.:

IS1: benzidine-d8, CAS No.: 92890-63-6

IS2: naphthalene-d8, CAS No.: 1146-65-2

IS3: 2,4,5-trichloroaniline, CAS No.: 636-30-6

IS4: anthracene-d10, CAS No.: 1719-06-8.

6.10 standard solutions

6.10.1 internal standard solution, IS in *t*-butyl methyl ether, $\rho = 10,0 \mu\text{g/ml}$

6.10.2 4-aminoazobenzene calibration solution for checking the experimental procedure and preparation of calibration solutions

4-aminoazobenzene in methanol, $\rho = 500 \mu\text{g/ml}$

6.11 grade 3 water, complying with EN ISO 3696.

7 Apparatus

7.1 reaction vessel (20 ml to 50 ml) of heat-resistant glass, with tight closure

7.2 extraction apparatus, according to Figure 1, consisting of

— coil condenser NS 29/32;

<https://standards.iteh.ai/catalog/standards/sist/94900513-bea7-4ae9-8202-10f27b11bc9/sist-en-14362-3-2012>

— a hook, made from an inert material to hold the specimen in place so that the condensed solvent drips onto the specimen;

— 100 ml round bottom flask NS 29/32;

— heating source.

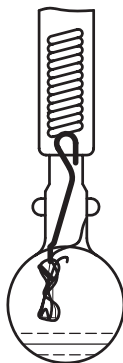


Figure 1 — Apparatus

NOTE Similar apparatus can be used, if the same results are obtained.

7.3 heating source that generates a temperature of $(40 \pm 2) ^\circ\text{C}$

- 7.4 centrifuge**, more than 3000 r/min
- 7.5 vacuum rotary evaporator**
- 7.6 pipettes** in required sizes or variable pipettes
- 7.7 ultrasonic bath**, at least ultrasonic power RMS 160 Watt, with controllable heating
- 7.8 horizontal shaker** with sufficient frequency of 5 s^{-1} , path length 2 cm to 5 cm
- 7.9 instrumental equipment**
- 7.9.1 gas chromatography (GC)** with mass selective detector (MS)
- 7.9.2 high performance liquid chromatography (HPLC)** with gradient elution and diode array detector (DAD) or mass selective detector (MS)
- 7.9.3 thin layer chromatography (TLC)** or high performance thin layer chromatography (HPTLC) equipment, including relevant detection
- 7.9.4 capillary electrophoresis (CE)** with DAD

NOTE A description of the equipment is given in Annex A.

8 Procedure

iTeh STANDARD PREVIEW
(standards.iteh.ai)

8.1 General

Apply this standard to the test specimen that gave a positive result for aniline and 1,4-phenylenediamine or only aniline using EN 14362-1. Choose 8.3 or 8.4 depending of the sample composition.

8.2 Preparation of test specimens

In the case of fabrics with multicoloured patterns, the various colours have to be taken into account separately as far as possible. For commodities consisting of various textile qualities, specimens of the various qualities (in terms of fibre and/or colour) shall be analyzed separately.

Prepare the test specimen by cutting in order to obtain a total mass of 1 g. For specimens to be submitted to colorant extraction (8.3) cut into strips (if apparatus described in 7.2 is used) or cut into small pieces if other apparatus is used or for specimens to be submitted only to reductive cleavage (8.4).

8.3 Colorant extraction for disperse dyes

8.3.1 Extraction of disperse dyes with chlorobenzene

The textile specimen dyed with disperse dyes (see Annex D from EN 14362-1:2012) is kept in the extractor (7.2) for 30 min above 25 ml boiling chlorobenzene. The chlorobenzene extract is allowed to cool down **to room temperature** before detaching it from the extractor.

Concentrate the chlorobenzene extract in the evaporation apparatus (7.5) at a temperature of 45 °C to 60 °C to a small residual quantity. This residue is quantitatively transferred to the reaction vessel with 7 ml methanol (6.4) in total, using an ultrasonic bath to disperse the colorant.

NOTE 1 It is recommended to carry out the transfer in multiple steps; e. g. to add 4 ml of methanol and to dissolve the residue from the glass flask using an ultrasonic bath, then to transfer the suspension quantitatively into the reaction vessel using a pipette, subsequently to rinse three times with 1 ml of methanol and to transfer the solution quantitatively.

EN 14362-3:2012 (E)

NOTE 2 For direct determination of a 4-aminoazobenzene-releasing dispersion colorant (e. g. Disperse Yellow 23) an aliquot of this methanolic solution may be immediately used for analysis by LC-DAD-MS.

8.3.2 Textiles only dyed with disperse dyes

Remove the textile specimen from the extractor, and discard it if it is completely made of fibres dyed with disperse dyes and/or becomes decolourised after extraction.

8.3.3 Textiles dyed with disperse dyes and/or other dyes

Remove the extracted textile specimen from the extractor, if it contains fibres belonging to cases A and/or B (see 8.4 of EN 14362-1:2012). Remove the solvent by washing the specimen with appropriate solvent e.g. n-pentane (6.3) or *t*-butyl methyl ether (6.6) and let it dry. If necessary cut it in small pieces for reductive cleavage. Add the extracted textile specimen to the reaction vessel with the methanolic solution of the dispersed dye (in total 7 ml) for combined reduction.

8.4 Textiles dyed with dyes other than disperse dyes

If the textile specimen contains fibres belonging only to cases A and/or B (see 8.4 of EN 14362-1:2012) put the test specimen directly in a reaction vessel and add 7 ml methanol (6.4).

8.5 Reductive cleavage

A quantity of 9 ml sodium hydroxide solution (6.2) is added to the methanolic solution (8.3.1, 8.3.3 or 8.4). The reaction vessel is tightly closed and shaken vigorously.

Subsequently, 1,0 ml aqueous sodium dithionite solution (6.1) is added for reductive cleavage. The mixture is shaken vigorously and immediately kept without shaking at $(40 \pm 2) ^\circ\text{C}$ for exactly 30 min, whereupon it is cooled to room temperature $20 ^\circ\text{C}$ to $25 ^\circ\text{C}$ within 1 min.

8.6 Separation and concentration of 4-aminoazobenzene

5 ml *t*-butyl methyl ether (6.6) or 5 ml internal standard solution (6.10.1), respectively are added to the reaction solution. Subsequently, 7 g of sodium chloride (6.7) are added and the mixture is shaken in a horizontal way constantly for 45 min; shaking frequency $f = 5 \text{ s}^{-1}$.

NOTE 1 The delay time between cooling down and shaking should not exceed 5 min. For complete phase separation after shaking, it is recommended to centrifuge the mixture.

For subsequent analysis an aliquot of the *t*-butyl methyl ether phase is transferred into an appropriate vial, which is closed immediately. The detection and determination of 4-aminoazobenzene can be performed using the chromatographic techniques listed in 7.9.

NOTE 2 For subsequent analysis it may be necessary to change the solvent or to concentrate the extract from 8.5 and transfer it to another appropriate solvent (e.g. methanol). Removal of the solvent (concentration in the vacuum rotary evaporator, evaporation to dryness) may lead to substantial loss of 4-aminoazobenzene if not performed under controlled conditions.

It is recommended to concentrate the *t*-butyl methyl ether extract to about 1 ml (not to dryness) in a rotary evaporator in a slight vacuum at not more than $50 ^\circ\text{C}$. Then remove the remainder of the solvent very carefully without vacuum by means of a weak flow of inert gas.

If possible avoid changing the solvent, as in the course of the analytical procedure severe losses of analyte may result due to matrix effects.

NOTE 3 Owing to the matrix, 4-aminoazobenzene may exhibit a poor stability. Where delays occur in the work routine, severe losses of analyte may result.

If the complete analysis cannot be performed within 24 h, the specimen is to be kept below -18 °C.

8.7 Calibration solution

8.7.1 Calibration solution for sample preparation without extraction

5 ml *t*-butyl methyl ether (6.6) or 5 ml internal standard solution (6.10.1), respectively are added to 100 µl of the 4-aminoazobenzene calibration solution (6.10.2). This mixture is used for calibration, as the recovery of 4-aminoazobenzene via phase partition according to this procedure is 95% to 100%.

8.7.2 Calibration solution for sample preparation with extraction

100 µl of the 4-aminoazobenzene calibration solution (6.10.2) are added to 6,9 ml methanol (6.4), 9 ml sodium hydroxide solution (6.2), 1 ml water, 7 g sodium chloride (6.7) and 5 ml *t*-butyl methyl ether (6.6) or 5 ml internal standard solution (6.10.1), respectively.

This mixture is shaken in a horizontal way constantly for 45 min; shaking frequency $f = 5 \text{ s}^{-1}$. For subsequent analysis an aliquot is taken out of the *t*-butyl methyl ether phase. The vial for analysis has to be closed immediately.

8.8 Check of the analytical system

8.8.1 Sample preparation without extraction

To check the procedure, 100 µl of the 4-aminoazobenzene calibration solution (6.10.2) are treated according to 8.5.

4-aminoazobenzene recovery rate shall be a minimum of 60 %.

[SIST EN 14362-3:2012](https://standards.iteh.ai/catalog/standards/sist/94900513-bea7-4ae9-8202-10f2c2b11bc0/sist-en-14362-3-2012)

8.8.2 Sample preparation with extraction

To check the procedure, 100 µl of the 4-aminoazobenzene calibration solution (6.10.2) are added to 6,9 ml methanol. This mixture is treated according to 8.5.

4-aminoazobenzene recovery rate shall be a minimum of 60 %.

8.9 Chromatographic analyses

4-aminoazobenzene detection can be performed using the chromatographic techniques listed in 7.9. Other validated methods may be used. If this amine is detected by one chromatographic method, then confirmation shall be made using one or more alternative methods. The result is positive only if both methods give a positive result.

9 Evaluation

9.1 Calculation

The amount of 4-aminoazobenzene is usually calculated by means of a software program. The calculation can also be carried out manually as described in Annex B.

9.2 Reliability of the method

For the reliability of the method see Annex C.