



SLOVENSKI STANDARD

SIST EN ISO 15653:2011

01-november-2011

Kovinski materiali - Preskusna metoda za ugotavljanje kvazistatične lomne žilavosti zvarnih spojev (ISO 15653:2010)

Metallic materials - Method of test for the determination of quasistatic fracture toughness of welds (ISO 15653:2010)

Metallische Werkstoffe - Prüfverfahren zur Bestimmung der quasistatischen Bruchzähigkeit von Schweißverbindungen (ISO 15653:2010)

Matériaux métalliques - Méthode d'essai pour la détermination de la ténacité quasistatique a la rupture des soudures (ISO 15653:2010)

[https://standards.iteh.ai/catalog/standards/sist/58573de3-f87a-4744-bdbd-](https://standards.iteh.ai/catalog/standards/sist/58573de3-f87a-4744-bdbd-261667cc6125/sist-en-iso-15653-2011)

Ta slovenski standard je istoveten z: **EN ISO 15653:2010**

ICS:

25.160.40 Varjeni spoji in vari Welded joints

SIST EN ISO 15653:2011

en,fr,de

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 15653:2011

<https://standards.iteh.ai/catalog/standards/sist/58573de3-f87a-4744-bdbd-261667cc6125/sist-en-iso-15653-2011>

EUROPEAN STANDARD

EN ISO 15653

NORME EUROPÉENNE

EUROPÄISCHE NORM

April 2010

ICS 25.160.40

English Version

Metallic materials - Method of test for the determination of quasistatic fracture toughness of welds (ISO 15653:2010)

Matériaux métalliques - Méthode d'essai pour la détermination de la ténacité quasi statique à la rupture des soudures (ISO 15653:2010)

Metallische Werkstoffe - Prüfverfahren zur Bestimmung der quasistatischen Bruchzähigkeit von Schweißverbindungen (ISO 15653:2010)

This European Standard was approved by CEN on 23 January 2010.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

[SIST EN ISO 15653:2011](https://standards.iteh.ai/catalog/standards/sist/58573de3-f87a-4744-bdbd-261667cc6125/sist-en-iso-15653-2011)

<https://standards.iteh.ai/catalog/standards/sist/58573de3-f87a-4744-bdbd-261667cc6125/sist-en-iso-15653-2011>



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: Avenue Marnix 17, B-1000 Brussels

Contents

Page

Foreword.....3

**iTeh STANDARD PREVIEW
(standards.iteh.ai)**

SIST EN ISO 15653:2011

<https://standards.iteh.ai/catalog/standards/sist/58573de3-f87a-4744-bdbd-261667cc6125/sist-en-iso-15653-2011>

Foreword

This document (EN ISO 15653:2010) has been prepared by Technical Committee ISO/TC 164 "Mechanical testing of metals" in collaboration with Technical Committee CEN/TC 121 "Welding" the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by October 2010, and conflicting national standards shall be withdrawn at the latest by October 2010.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and the United Kingdom.

iTeh STANDARD PREVIEW Endorsement notice (standards.iteh.ai)

The text of ISO 15653:2010 has been approved by CEN as a EN ISO 15653:2010 without any modification.

[SIST EN ISO 15653:2011](https://standards.iteh.ai/catalog/standards/sist/58573de3-f87a-4744-bdbd-261667cc6125/sist-en-iso-15653-2011)

<https://standards.iteh.ai/catalog/standards/sist/58573de3-f87a-4744-bdbd-261667cc6125/sist-en-iso-15653-2011>

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN ISO 15653:2011](#)

<https://standards.iteh.ai/catalog/standards/sist/58573de3-f87a-4744-bdbd-261667cc6125/sist-en-iso-15653-2011>

INTERNATIONAL STANDARD

ISO
15653

First edition
2010-04-15

Metallic materials — Method of test for the determination of quasistatic fracture toughness of welds

*Matériaux métalliques — Méthode d'essai pour la détermination de la
ténacité quasi statique à la rupture des soudures*

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN ISO 15653:2011](https://standards.iteh.ai/catalog/standards/sist/58573de3-f87a-4744-bdbd-261667cc6125/sist-en-iso-15653-2011)

[https://standards.iteh.ai/catalog/standards/sist/58573de3-f87a-4744-bdbd-
261667cc6125/sist-en-iso-15653-2011](https://standards.iteh.ai/catalog/standards/sist/58573de3-f87a-4744-bdbd-261667cc6125/sist-en-iso-15653-2011)



Reference number
ISO 15653:2010(E)

© ISO 2010

PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[SIST EN ISO 15653:2011](https://standards.iteh.ai/catalog/standards/sist/58573de3-f87a-4744-bdbd-261667cc6125/sist-en-iso-15653-2011)

<https://standards.iteh.ai/catalog/standards/sist/58573de3-f87a-4744-bdbd-261667cc6125/sist-en-iso-15653-2011>

**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2010

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Symbols and units	3
5 Principle	3
6 Choice of specimen design, specimen orientation and notch location	4
6.1 Classification of target area for notching	4
6.2 Specimen design	4
6.3 Specimen and crack plane orientation	4
7 Pre-machining metallography	8
7.1 Microstructural assessment of macrosections	8
7.2 Additional requirements for heat-affected zone tests	9
8 Machining	9
8.1 Tolerances on specimen dimensions	9
8.2 Notch placement for through-thickness notched specimens	10
8.3 Notch placement for surface-notched specimens	10
8.4 Notch machining	10
9 Specimen preparation	15
9.1 Fatigue precracking	15
9.2 Side grooving	15
10 Test apparatus, requirements and test procedure	15
11 Post-test metallography	15
11.1 General	15
11.2 Through-thickness notched specimens	16
11.3 Surface-notched specimens	16
11.4 Assessment of pop-in	16
12 Post-test analysis	19
12.1 Choice of tensile properties	19
12.2 K_{Ic}	20
12.3 δ and J	20
12.4 Qualification requirements	20
13 Test report	24
Annex A (informative) Examples of notch locations	25
Annex B (informative) Examples of pre-test and post-test metallography	27
Annex C (normative) Residual-stress modification and precracking technique	29
Annex D (normative) Assessment of pop-in	31
Annex E (informative) Shallow-notched specimen testing	37
Bibliography	41

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 15653 was prepared by Technical Committee ISO/TC 164, *Mechanical testing of metals*, Subcommittee SC 4, *Toughness testing — Fracture (F), Pendulum (P), Tear (T)*.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN ISO 15653:2011](https://standards.iteh.ai/catalog/standards/sist/58573de3-f87a-4744-bdbd-261667cc6125/sist-en-iso-15653-2011)

<https://standards.iteh.ai/catalog/standards/sist/58573de3-f87a-4744-bdbd-261667cc6125/sist-en-iso-15653-2011>

Metallic materials — Method of test for the determination of quasistatic fracture toughness of welds

1 Scope

This International Standard specifies methods for determining fracture toughness in terms of K (stress intensity factor), δ (crack tip opening displacement, CTOD) and J (experimental equivalent of the J -integral) for welds in metallic materials.

This International Standard is complementary to ISO 12135, which covers all aspects of fracture toughness testing of parent metal and which needs to be used in conjunction with this document. This International Standard describes methods for determining point values of fracture toughness. It should not be considered a way of obtaining a valid R -curve (resistance-to-crack-extension curve). However, the specimen preparation methods described in this International Standard could be usefully employed when determining R -curves for welds. The methods use fatigue precracked specimens which have been notched, after welding, in a specific target area in the weld. Methods are described to evaluate the suitability of a weld for notch placement within the target area, which is either within the weld metal or within the weld heat-affected zone (HAZ), and then, where appropriate, to evaluate the effectiveness of the fatigue crack in sampling these areas.

(standards.iteh.ai)

2 Normative references

SIST EN ISO 15653:2011

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 3785, *Metallic materials — Designation of test specimen axes in relation to product texture*

ISO 12135, *Metallic materials — Unified method of test for the determination of quasistatic fracture toughness*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 12135 and the following apply.

3.1

stretch zone width

SZW

increase in crack length associated with crack tip blunting — i.e. prior to the onset of unstable crack extension, pop-in (see 3.3) or slow stable crack extension — and occurring in the same plane as the fatigue precrack

3.2

target area

intended fatigue crack tip position within the weld metal or HAZ

NOTE See 3.7 and 3.9.

ISO 15653:2010(E)**3.3****pop-in**

an abrupt discontinuity in the force versus displacement record, featured as a sudden increase in displacement and, generally, a sudden decrease in force, subsequent to which displacement and force increase to above their values at pop-in

3.4**local compression**

controlled compression applied to specimens in the thickness direction on the unnotched ligament prior to fatigue cracking using hardened steel platens

NOTE See Annex C.

3.5**welding**

an operation in which two or more parts are united by means of heat, friction, pressure or all three of these, in such a way that there is continuity in the nature of the metal between these parts

NOTE Filler metal, the melting temperature of which is of the same order as that of the parent metal, may or may not be used.

3.6**weld**

union of pieces of metal made by welding

3.7**weld metal**

all metal melted during the making of a weld and retained in the weld

3.8**parent metal****base metal**

metal to be joined by welding

iTeh STANDARD PREVIEW
(standards.iteh.ai)
<https://standards.iteh.ai/catalog/standards/sist/58573de3-f87a-4744-bdbd-261667cc6125/sist-en-iso-15653-2011>

3.9**heat-affected zone****HAZ**

zone in the parent metal that is metallurgically affected by the heat of welding

3.10**fusion line****FL**

junction between the weld metal and the parent metal heat-affected zone

3.11**weld positional****WP**

target position for the fatigue crack tip, defined with respect to a reference line

NOTE See Figure A.1 for examples.

3.12**specific microstructure****SM**

target microstructure for the fatigue crack tip

NOTE See Figure A.2 for examples.

3.13**specimen blank**

specimen prepared from weld metal plus parent metal prior to notching

3.14**postweld heat treatment**

heat treatment applied after welding for the purpose of reducing residual stresses or modifying weld properties

4 Symbols and units

For the purposes of this document, the symbols and units given in Table 1 apply in addition to those in ISO 12135.

Table 1 — Symbols and units

Symbol	Unit	Designation
d_1, d_2	mm	Lengths of microstructural features associated with pop-in.
h	mm	Effective weld width, defined as shortest distance between fatigue crack tip and weld fusion line within the central 75 % of the thickness (see Figures 13 and 14).
HV10		Vickers hardness using 10 kg force.
N		Normal to welding direction.
P		Parallel to welding direction.
Q		Weld thickness direction.
$R_{p0,2b}$	MPa	0,2 % offset yield strength of parent metal at the temperature of the fracture test.
$R_{p0,2w}$	MPa	0,2 % offset yield strength of weld metal at the temperature of the fracture test.
R_{mb}	MPa	Tensile strength of parent metal at the temperature of the fracture test.
R_{mw}	MPa	Tensile strength of weld metal at the temperature of the fracture test.
s_1	mm	Distance between crack tip and target area measured in the crack plane (see Figure 12).
s_2	mm	Distance between crack tip and target area measured perpendicular to the crack plane (see Figure 12).
V, V_1, V_2	mm	Crack mouth opening displacement.
X		Direction parallel to primary grain flow of parent metal.
Y		Direction transverse to primary grain flow and to thickness of parent metal.
Z		Direction through thickness of parent metal.
Δa_{pop}	mm	Maximum length of brittle crack extension (beyond SZW) (see 3.1) associated with pop-in.
λ	mm	Length of specific microstructure measured in pre-test or post-test metallography (see Figure B.2).

5 Principle

This International Standard specifies procedures for the determination of fracture toughness on notched-plus-fatigue-cracked specimens taken from welds. It pertains to situations where the crack tip is

- located in relation to a weld feature of interest, referred to as “weld positional” (WP);
- specifically located within a microstructure of interest, referred to as “specific microstructure” (SM).

Metallographic examination of the weld is used to confirm that the target weld feature and/or microstructure is indeed present at the crack tip and in sufficient quantity for testing.

ISO 15653:2010(E)

Specimen geometry and notch orientation are chosen, and a fatigue crack then extended from the specimen's notch tip into the target weld feature or microstructure by applying a controlled alternating force to the specimen. The purpose of the test is to determine weld fracture toughness in the absence of significant welding stresses. To achieve this and to produce a straight-fronted fatigue crack, modifications to the fatigue precracking procedure may be required. These modifications are usually necessary when testing as-welded or partially stress-relieved welds.

The fracture toughness test is performed and evaluated in accordance with ISO 12135, but subject to additional requirements of this test method regarding post-test analysis (see 12.1, 12.2 and 12.3) and qualification (see 12.4).

Post-test metallography is often required to make certain that the crack tip was located in the target weld feature and/or microstructure and to determine the significance of pop-ins.

The sequence of operations is summarized in Figure 1.

6 Choice of specimen design, specimen orientation and notch location

6.1 Classification of target area for notching

A specimen selected for weld positional (WP) testing is intended to test a defined weld region with respect to a reference position (e.g. the weld metal centreline).

A specimen selected for specific microstructure (SM) testing is intended to sample a specific microstructure along the whole or part of the crack front length within the central 75 % of the specimen thickness.

NOTE Some examples of WP and SM notch locations are given in Annex A.

WP weld metal centreline notch locations sampling predominantly grain-refined regions may give misleading (overly high) values of fracture toughness for misaligned two-pass and parallel multi-pass welds. For these welds, it is recommended that the SM notch locations shown in Figures A.2 iv) and A.2 v), respectively, be used.

6.2 Specimen design

Specimen design shall be of compact or single-edge-notched bend configuration as defined in ISO 12135 and may be plain-sided or side-grooved. Bend specimens notched into the plate thickness (see Figures 2, 3 and 4, parent metal specimens XY and YX and weld metal specimens NP and PN) are referred to as through-thickness notched specimens, whilst those notched into the planar surface of the plate (see Figures 2, 3 and 4, parent metal specimens XZ and YZ and weld metal specimens NQ and PQ) are referred to as surface-notched specimens.

NOTE Tolerances on weld specimen dimensions are less stringent than those for testing parent metal (see 8.1).

Test specimens shall have the dimension B or W (see Figure 5) equal to the full thickness of the parent metal adjacent to the weld to be tested (excluding weld overfill).

Testing of sub-sized (i.e. B or $W <$ full thickness in directions Q for weld and Z for parent metal in Figures 2, 3 and 4) and/or side-grooved specimens is permitted, but shall be properly identified as such in the test report. Results from sub-sized and/or side-grooved specimens may differ from those from full-thickness specimens owing to size effects and/or different microstructural regions being tested.

6.3 Specimen and crack plane orientation

Specimen and crack plane orientation relative to the weld and parent metal working directions shall be defined using the identification system described in Figures 2, 3 and 4.

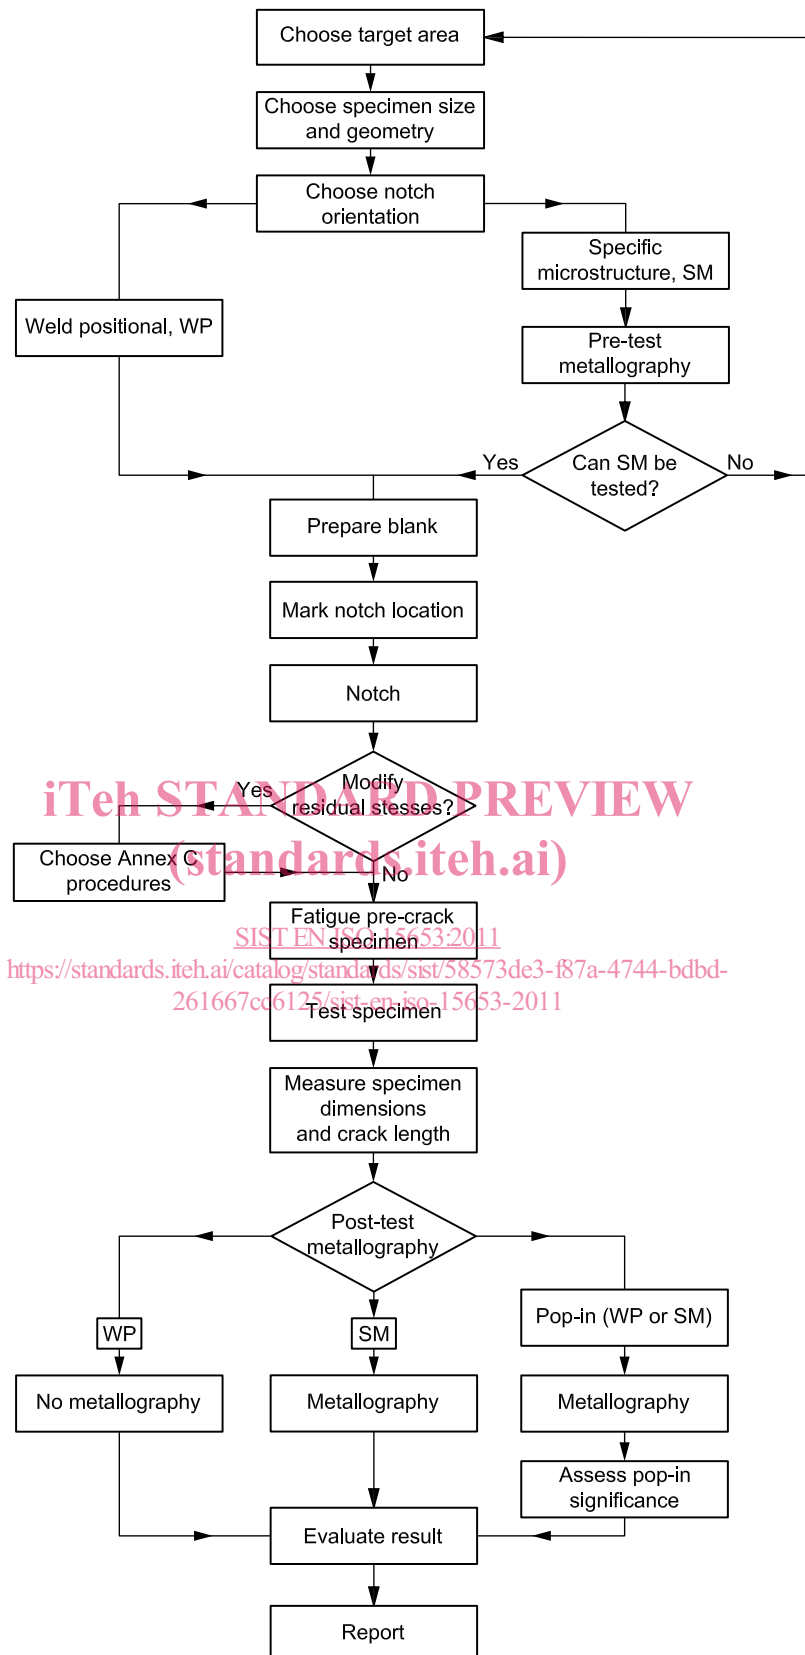


Figure 1 — Flow chart for testing