

INTERNATIONAL STANDARD

ISO 5922

Second edition
2005-02-15

Malleable cast iron

Fonte malléable

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 5922:2005](https://standards.iteh.ai/catalog/standards/sist/76e49fd4-caf0-4620-8c9f-35250e2c0bd9/iso-5922-2005)

<https://standards.iteh.ai/catalog/standards/sist/76e49fd4-caf0-4620-8c9f-35250e2c0bd9/iso-5922-2005>



Reference number
ISO 5922:2005(E)

© ISO 2005

PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 5922:2005](#)

<https://standards.iteh.ai/catalog/standards/sist/76e49fd4-caf0-4620-8c9f-35250e2c0bd9/iso-5922-2005>

© ISO 2005

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Designation	2
5 Order information	3
6 Manufacture	3
7 Mechanical properties	3
8 Sampling	5
9 Test methods	7
10 Retests	7
Annex A (informative) Impact resistance	9
Bibliography	10

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 5922:2005](https://standards.iteh.ai/catalog/standards/sist/76e49fd4-caf0-4620-8c9f-35250e2c0bd9/iso-5922-2005)

<https://standards.iteh.ai/catalog/standards/sist/76e49fd4-caf0-4620-8c9f-35250e2c0bd9/iso-5922-2005>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 5922 was prepared by Technical Committee ISO/TC 25, *Cast iron and pig iron*, Subcommittee SC 1, *Malleable cast iron*.

This second edition cancels and replaces the first edition (ISO 5922:1981), which has been technically revised.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 5922:2005](https://standards.iteh.ai/catalog/standards/sist/76e49fd4-caf0-4620-8c9f-35250e2c0bd9/iso-5922-2005)

<https://standards.iteh.ai/catalog/standards/sist/76e49fd4-caf0-4620-8c9f-35250e2c0bd9/iso-5922-2005>

Malleable cast iron

1 Scope

This International Standard specifies requirements for two types of malleable cast iron, namely whiteheart malleable cast iron and blackheart malleable cast iron, used in the manufacture of castings.

Classification is given for each type of malleable cast iron on the basis of mechanical properties determined on separately cast test pieces.

This International Standard is applicable only to malleable cast iron cast into sand moulds or moulds of comparable thermal diffusivity.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 148, *Steel — Charpy impact test (V-notch)*

ISO 5922:2005

ISO 6506-1, *Metallic materials — Brinell hardness test — Part 1: Test method*

ISO 6892, *Metallic materials — Tensile testing at ambient temperature*

ISO/TR 15931, *Designation system for cast irons and pig irons*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

malleable cast iron

heat-treated iron-carbon alloy, which solidifies in the as-cast condition with a graphite-free structure, referred to as white cast iron, the total carbon content being present in the combined form as cementite (Fe_3C)


3.2

whiteheart malleable cast iron

white cast iron given a heat treatment in a decarburizing atmosphere to produce a material which is partially or entirely decarburized

NOTE The microstructure of whiteheart malleable cast iron is dependent on section size, as described below. Figure 1 shows the microstructural changes depending on the thickness of the material. For the definition of temper carbon, see ISO 945 (graphite form IV).

- a) Small section size = ferrite (+ pearlite + temper carbon);
- b) Large section size, see Figure 1.

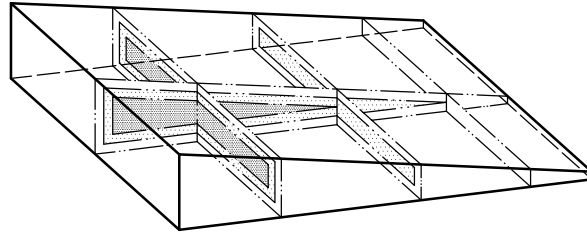

Key




-  core zone: pearlite/ferrite + temper carbon
-  transition zone: pearlite + ferrite + temper carbon
-  rim zone: ferrite

Figure 1 — Microstructure in the core, transition and rim zone

3.3 blackheart malleable cast iron

white cast iron given a non-decarburizing heat treatment

NOTE All of the graphite contained in blackheart malleable cast iron is in the form of temper carbon. For the definition of temper carbon, see ISO 945 (graphite form IV).

iTeh STANDARD PREVIEW

3.3.1 blackheart ferritic malleable cast iron (standards.iteh.ai)

blackheart malleable iron, the microstructure of which has a matrix essentially of ferrite

ISO 5922:2005

3.3.2 blackheart pearlitic malleable cast iron

blackheart malleable iron, the microstructure of which has a matrix, according to the grade specified, of various types of pearlite or other transformation products of austenite

3.4 primary graphite

graphite which occurs in flake form

NOTE Primary graphite is more correctly referred to as eutectic graphite.

4 Designation

The types of malleable cast iron covered by this International Standard shall be designated as follows, in accordance with ISO/TR 15931:

- a) by a reference to this International Standard, i.e. ISO 5922:2005;
- b) by three letters designating the type of malleable cast iron as follows.
 - JMW for whiteheart malleable cast iron,
 - JMB for blackheart malleable cast iron;
- c) by three numerals designating the minimum tensile strength, in newtons per square millimetre, of a 12 mm diameter test piece; these numerals shall be followed by a hyphen (-);

- d) by one or two numerals designating the minimum elongation, as a percentage of a 12 mm diameter test piece.

EXAMPLE The designation of a whiteheart malleable cast iron having a pearlitic matrix structure, a minimum tensile strength of 400 N/mm² and a minimum elongation of 5 %, when measured on a 12 mm diameter test piece, shall be ISO 5922/JMW/400-5.

5 Order information

The following information shall be supplied by the purchaser.

- a) the complete designation of the material;
- b) any special requirements which have to be agreed between the manufacturer and purchaser.

All agreements between the manufacturer and the purchaser shall be made by the time of acceptance of the order.

6 Manufacture

The method of manufacture of malleable cast iron, as well as its chemical composition and heat treatment, shall be left to the discretion of the manufacturer, who shall ensure compliance with the property requirements given in this International Standard for the grade required in the order.

For malleable cast iron to be used in special applications, the chemical composition and any special heat treatment may be the subject of an agreement between the manufacturer and the purchaser at the time of acceptance of the order.

To optimize the impact resistance of all grades specified in Tables 1 and 2, the phosphorus content should not exceed 0,10 %.

7 Mechanical properties

7.1 Tensile strength and elongation

When tested in accordance with 9.1, the values of tensile strength (R_m) and percentage elongation after fracture ($A_{3,4}$) shall be in accordance with the requirements specified in Tables 1 and 2.

NOTE For definitions of R_m and $A_{3,4}$, see ISO 6892.

7.2 0,2 % Proof strength

When requested by the purchaser and agreed at the time of acceptance of the order, 0,2 % proof strength ($R_{p0,2}$) shall be determined in accordance with 9.2, and 0,2 % proof strength values shall be in accordance with the requirements specified in Tables 1 and 2.

NOTE For the definition of $R_{p0,2}$, see ISO 6892.

7.3 Brinell hardness

When requested by the purchaser and agreed at the time of acceptance of the order, Brinell hardness (HBW) shall be determined in accordance with 9.3. Evaluation of the test results may be based on the informative hardness values listed in Tables 1 and 2.

NOTE For definition of HBW, see ISO 6506-1.

7.4 Impact resistance

When the impact resistance test is requested by the purchaser, the method of testing shall be in accordance with 9.4. Evaluation of impact test values shall be the subject of an agreement between the manufacturer and the purchaser at the time of acceptance of the order. Guidance values are given in Annex A, that are obtained by the impact test procedure applied in accordance with ISO 148. The phosphorus content should not exceed 0,10 %.

Table 1 — Mechanical properties of whiteheart malleable cast iron

Designation	Diameter of test piece ^a mm	Tensile strength	Elongation	0,2 % proof strength	Brinell hardness (for information only) HBW max.
		R_m N/mm ² min.	$A_{3,4}$ % min.	$R_{p0,2}$ N/mm ² min.	
ISO 5922/ JMW/350-4	6	270	10	— ^b	230
	9	310	5	—	
	12	350	4	—	
	15	360	3	—	
ISO 5922/ JMW/360-12	6	280	16	— ^b	200
	9	320	15	170	
	12	360	12	190	
	15	370	7	200	
ISO 5922/ JMW/400-5	6	300	12	— ^b	220
	9	360	8	200	
	12	400	5	220	
	15	420	4	230	
ISO 5922/ JMW/450-7	6	330	12	— ^b	220
	9	400	10	230	
	12	450	7	260	
	15	480	4	280	
ISO 5922/ JMW/550-4	6	—	—	— ^b	250
	9	490	5	310	
	12	550	4	340	
	15	570	3	350	

All grades of whiteheart malleable cast iron can be welded, provided correct procedures are employed. Grade JMW/360-12 should be selected for components where strength and avoidance of post-weld heat treatment is particularly required.

(For a wall thickness exceeding 8 mm, a post-weld heat treatment is recommended.)

^a For choosing the diameter of the test piece, see 8.4.

^b Because of the difficulty in determining the proof strength of small test pieces, the values and the method of measurement shall be agreed between the manufacturer and the purchaser at the time of acceptance of the order.

Table 2 — Mechanical properties of blackheart malleable cast iron

Designation	Diameter of test piece ^{a, b} mm	Tensile strength	Elongation	0,2 % proof strength	Brinell hardness (for information only) HBW
		R_m N/mm ² min.	$A_{3,4}$ % min.	$R_{p0,2}$ N/mm ² min.	
ISO 5922/ JMB/275-5 ^c	12 or 15	275	5	—	150 max.
ISO 5922/ JMB/300-6 ^c	12 or 15	300	6	—	150 max.
ISO 5922/ JMB/350-10	12 or 15	350	10	200	150 max.
ISO 5922/ JMB/450-6	12 or 15	450	6	270	150 to 200
ISO 5922/ JMB/500-5	12 or 15	500	5	300	165 to 215
ISO 5922/ JMB/550-4	12 or 15	550	4	340	180 to 230
ISO 5922/ JMB/600-3	12 or 15	600	3	390	195 to 245
ISO 5922/ JMB/650-2	12 or 15	650	2	430	210 to 260
ISO 5922/ JMB/700-2 ^{d, e}	12 or 15	700	2	530	240 to 290
ISO 5922/ JMB/800-1 ^d	12 or 15	800	1	600	270 to 320

^a Of the two diameters given for the test piece, the manufacturer shall have the option of choosing either size, if this is not specified by the purchaser.

^b Where a 6 mm or 9 mm diameter test piece is representative of the relevant wall thickness of a casting, this size of the piece may be used, by agreement between the manufacturer and the purchaser at the time of acceptance of the order. The minimum properties given in this table shall apply.

^c Grades JMB/275-5 and JMB/300-6 are intended particularly for applications in which pressure-tightness is more important than a high degree of strength, ductility or impact resistance.

^d Oil quenched and subsequently tempered.

^e If this grade is air quenched and subsequently tempered, the 0,2 % proof strength shall be a minimum of 430 N/mm².

8 Sampling

8.1 General

Samples shall be made from the same material as that used to produce the casting(s) which they represent. They shall be separately cast in sand moulds, during the same period as when the castings are made.

In all cases, the test pieces shall be heat-treated by the same process as the castings that they represent.