
**Fibre-reinforced plastics — Methods of
producing test plates —**

Part 10:

**Injection moulding of BMC and other
long-fibre moulding compounds —
General principles and moulding of
multipurpose test specimens**

*Plastiques renforcés de fibres — Méthodes de fabrication de plaques
d'essai —*

*Partie 10: Moulage par injection de BMC et d'autres mélanges à mouler
à longues fibres — Principes généraux et moulage d'éprouvettes à
usages multiples*

<https://standards.iteh.ai/catalog/standards/iso/4bb9b94c-6239-4bf8-82ea-1fbbbe3649f3/iso-1268-10-2005>



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

iTeh Standards
(<https://standards.iteh.ai>)
Document Preview

[ISO 1268-10:2005](https://standards.iteh.ai/catalog/standards/iso/4bb9b94c-6239-4bf8-82ea-1fbbbe3649f3/iso-1268-10-2005)

<https://standards.iteh.ai/catalog/standards/iso/4bb9b94c-6239-4bf8-82ea-1fbbbe3649f3/iso-1268-10-2005>

© ISO 2005

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	2
4 Apparatus	7
5 Procedure	10
6 Report on test-specimen preparation	11
Annex A (informative) Examples of runner configurations	12
Annex B (informative) Marking of test specimens	13
Annex C (informative) Example of an injection mould	14
Bibliography	16

iTeh Standards
 (<https://standards.iteh.ai>)
 Document Preview

[ISO 1268-10:2005](https://standards.iteh.ai/catalog/standards/iso/4bb9b94c-6239-4bf8-82ea-1fbbbe3649f3/iso-1268-10-2005)

<https://standards.iteh.ai/catalog/standards/iso/4bb9b94c-6239-4bf8-82ea-1fbbbe3649f3/iso-1268-10-2005>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 1268-10 was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 13, *Composites and reinforcement fibres*.

Together with the other parts (see below), this part of ISO 1268 cancels and replaces ISO 1268:1974, which has been technically revised.

ISO 1268 consists of the following parts, under the general title *Fibre-reinforced plastics — Methods of producing test plates*:

- *Part 1: General conditions*
- *Part 2: Contact and spray-up moulding*
- *Part 3: Wet compression moulding*
- *Part 4: Moulding of prepregs*
- *Part 5: Filament winding*
- *Part 6: Pultrusion moulding*
- *Part 7: Resin transfer moulding*
- *Part 8: Compression moulding of SMC and BMC*
- *Part 9: Moulding of GMT/STC*
- *Part 10: Injection moulding of BMC and other long-fibre moulding compounds — General principles and moulding of multipurpose test specimens*
- *Part 11: Injection moulding of BMC and other long-fibre moulding compounds — Small plates*

Introduction

Many factors in the injection-moulding process can influence the properties of moulded test specimens and hence the measured values obtained when the specimens are used in a test method. The thermal and mechanical properties of such specimens are in fact strongly dependent on the conditions of the moulding process used to prepare the specimens. Exact definition of each of the main parameters of the moulding process is a basic requirement for reproducible and comparable operating conditions.

It is important in defining moulding conditions to consider any influence the conditions may have on the properties to be determined. Thermosets may show differences in orientation and length of anisotropic fillers such as long fibres and in curing. Residual ("frozen-in") stresses in the moulded test specimens may also influence properties. Due to the crosslinking of thermosets, molecular orientation is of less influence on mechanical properties than it is for thermoplastics. Each of these phenomena must be controlled to avoid fluctuation of the numerical values of the measured properties.

The principles described in this part of ISO 1268 are the same as those in ISO 10724-1. Only a few details of the moulds have changed, as has specimen thickness, because of the use of long-fibre reinforcements. It is therefore possible to compare the properties of long-fibre moulding compounds with those of thermosetting powder moulding compounds (PMCs) and thermoplastics.

iTeh Standards (<https://standards.iteh.ai>) Document Preview

[ISO 1268-10:2005](https://standards.iteh.ai/catalog/standards/iso/4bb9b94c-6239-4bf8-82ea-1fbbbe3649f3/iso-1268-10-2005)

<https://standards.iteh.ai/catalog/standards/iso/4bb9b94c-6239-4bf8-82ea-1fbbbe3649f3/iso-1268-10-2005>

Fibre-reinforced plastics — Methods of producing test plates —

Part 10:

Injection moulding of BMC and other long-fibre moulding compounds — General principles and moulding of multipurpose test specimens

1 Scope

This part of ISO 1268 specifies the general principles to be followed while injection moulding test specimens of bulk moulding compound (BMC) and gives details of mould designs for preparing one type of specimen for use in establishing reproducible moulding conditions. Where appropriate, this part of ISO 1268 may be applied to sheet moulding compound (SMC) formulated for injection moulding. Its purpose is to promote uniformity in describing the main parameters of the moulding process and also to establish uniform practice in reporting moulding conditions. The particular conditions required for the reproducible preparation of test specimens which will give comparable results will vary for each material used. These conditions are given in the International Standard for the relevant material or are to be agreed upon between interested parties.

NOTE Tests have shown that mould design is an important factor in the reproducible preparation of test specimens.

This part of ISO 1268 is intended to be read in conjunction with ISO 1268-1.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 472, *Plastics — Vocabulary*

ISO 1268-1, *Fibre-reinforced plastics — Methods of producing test plates — Part 1: General conditions*

ISO 1268-11, *Fibre-reinforced plastics — Methods of producing test plates — Part 11: Injection moulding of BMC and other long-fibre moulding compounds — Small plates*

ISO 2577, *Plastics — Thermosetting moulding materials — Determination of shrinkage*

ISO 3167, *Plastics — Multipurpose test specimens*

ISO 10350-2, *Plastics — Acquisition and presentation of comparable single-point data — Part 2: Long-fibre-reinforced plastics*

ISO 10724-1, *Plastics — Injection moulding of test specimens of thermosetting powder moulding compounds (PMCs) — Part 1: General principles and moulding of multipurpose test specimens*

ISO 10724-2, *Plastics — Injection moulding of test specimens of thermosetting powder moulding compounds (PMCs) — Part 2: Small plates*

ISO 11403-1, *Plastics — Acquisition and presentation of comparable multipoint data — Part 1: Mechanical properties*

ISO 11403-2, *Plastics — Acquisition and presentation of comparable multipoint data — Part 2: Thermal and processing properties*

ISO 11403-3, *Plastics — Acquisition and presentation of comparable multipoint data — Part 3: Environmental influences on properties*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 472 and the following apply.

3.1 mould temperature

T_C
average temperature of the mould cavity surfaces measured after the system has attained thermal equilibrium and immediately after opening the mould

NOTE It is expressed in degrees Celsius (°C).

3.2 temperature of material

T_M
temperature of the plasticized material in a free shot

NOTE 1 It is given by the temperature of the wall of the screw cylinder.

NOTE 2 It is expressed in degrees Celsius (°C).

3.3 pressure on material

p
pressure on the plasticized material in front of the screw at any time during the moulding process (see Figure 1)

NOTE 1 It is expressed in megapascals (MPa).

NOTE 2 The pressure on the material, which is generated hydraulically, can be calculated from the force F_s acting longitudinally on the screw using Equation (1):

$$p = \frac{4 \times 10^3 \times F_s}{\pi \times D^2} \quad (1)$$

where

p is the pressure on the material, in megapascals (MPa);

F_s is the longitudinal force, in kilonewtons (kN), acting on the screw;

D is the screw diameter, in millimetres (mm).

3.4 maximum pressure on the material

p_{\max}
maximum value of the pressure on the material

NOTE It is expressed in megapascals (MPa).

3.5 hold pressure

p_H
pressure on the material during the hold time (see Figure 1)

NOTE It is expressed in megapascals (MPa).

3.6 moulding cycle

complete sequence of operations in the moulding process required for the production of one set of test specimens (see Figure 1)


NOTE It is expressed in seconds (s).

3.7 cycle time

t_T
time required to carry out a complete moulding cycle

NOTE 1 It is expressed in seconds (s).

NOTE 2 The cycle time is the sum of the injection time t_I , the cure time t_{CR} and the mould open time t_O .

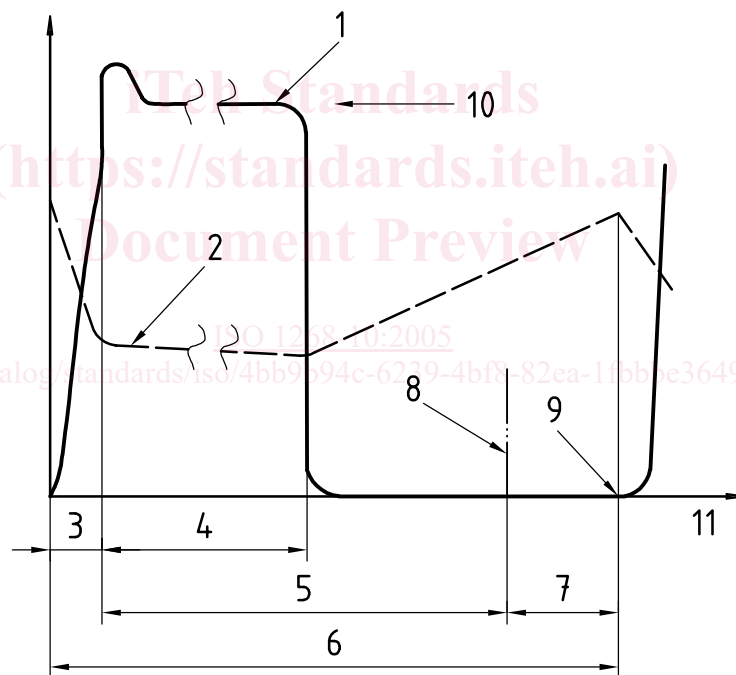

Key

- | | |
|--------------------------------------|-------------------------|
| 1 pressure on material, p | 7 open time, t_O |
| 2 longitudinal position of the screw | 8 mould opening |
| 3 injection time, t_I | 9 mould closing |
| 4 hold time, t_H | 10 hold pressure, p_H |
| 5 cure time, t_{CR} | 11 time |
| 6 cycle time, t_T | |

Figure 1 — Schematic diagram of an injection-moulding cycle, showing the pressure on the material (full line) and the longitudinal position of the screw (dashed line) as a function of time

**3.8
injection time**

t_I
time from the instant the screw starts to move forward until the switchover point between the injection period and the hold period

NOTE It is expressed in seconds (s).

**3.9
cure time**

t_{CR}
time from the end of the injection period until the mould starts to open

NOTE It is expressed in seconds (s).

**3.10
hold time**

t_H
time from the end of the injection period until the hold pressure p_H is released

NOTE It is expressed in seconds (s).

**3.11
mould-open time**

t_O
time from the instant the mould starts to open until the mould is closed and exerts the full locking force

NOTE It is expressed in seconds (s) and includes the time required to remove the mouldings from the mould.

**3.12
cavity**

that part of the hollow space in a mould which produces one specimen

**3.13
two-cavity mould**

mould that contains two identical cavities in a parallel-flow arrangement (see Figure 2)

NOTE Identical flowpath geometries and symmetrical positioning of the cavities in the cavity plate ensure that all test specimens from one shot are equivalent in their properties.