

---

---

**Refractory test piece preparation —  
Gunning refractory panels by the  
pneumatic-nozzle mixing type guns**

*Préparation d'éprouvettes réfractaires — Panneaux réfractaires pour  
gunitage au pistolet mélangeur pneumatique*

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO 20182:2005

<https://standards.iteh.ai/catalog/standards/sist/38fa10a4-7e99-4916-8abd-d753960cade9/iso-20182-2005>



**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO 20182:2005

<https://standards.iteh.ai/catalog/standards/sist/38fa10a4-7e99-4916-8abd-d753960cade9/iso-20182-2005>

© ISO 2005

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

**Contents**

Page

Foreword.....	iv
1 <b>Scope</b> .....	1
2 <b>Normative references</b> .....	1
3 <b>Terms and definitions</b> .....	1
4 <b>Principle</b> .....	2
5 <b>Precision</b> .....	2
6 <b>Apparatus</b> .....	2
7 <b>Sampling</b> .....	3
8 <b>Procedure</b> .....	3
9 <b>Test report</b> .....	4

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO 20182:2005

<https://standards.iteh.ai/catalog/standards/sist/38fa10a4-7e99-4916-8abd-d753960cade9/iso-20182-2005>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 20182 was prepared by Technical Committee ISO/TC 33, *Refractories*.

## iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO 20182:2005](https://standards.iteh.ai/catalog/standards/sist/38fa10a4-7e99-4916-8abd-d753960cade9/iso-20182-2005)

<https://standards.iteh.ai/catalog/standards/sist/38fa10a4-7e99-4916-8abd-d753960cade9/iso-20182-2005>

# Refractory test piece preparation — Gunning refractory panels by the pneumatic-nozzle mixing type guns

**WARNING** — This International Standard may involve hazardous materials, operations and equipment. It does not attempt to address the safety problems associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.

## 1 Scope

This International Standard describes the procedure for the preparation of test panels from refractory materials by gunning through pneumatic-nozzle mixing type guns at ambient temperatures.

**NOTE** The values obtained from test pieces cut from the panel prepared using this method may not correspond with those obtained from test pieces of the same material prepared at a gunning installation site.

It does not apply to plastic gunning mixes, and may not apply to those mixes that contain aggregates that are susceptible to hydration.

It also does not apply to shotcrete type mixes.

## 2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 836, *Terminology for refractories*

ISO 8656-1, *Refractory products — Sampling of raw materials and unshaped products — Part 1: Sampling scheme*

## 3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 836 and the following apply.

### 3.1

#### **gun**

assembly essentially comprising a chamber into which the refractory is added, together with a mechanism that controls the flow of the material through the unit

**NOTE** Depending on the type used, the gun may be open at the top, or a closed pressurized unit.

### 3.2

#### **rebound material**

material that fails to adhere to the surface when being sprayed, and ricochets out of the immediate area

#### 4 Principle

Refractory material is conveyed pneumatically in either a dry or predampened form to the test site, using equipment of the nozzle mixing type. Then water is introduced to the refractory mix at the nozzle and the mixture is projected onto a support plate (see 6.5).

#### 5 Precision

Differences between various types of equipment and in operator techniques may result in variations in the physical properties of the gunned specimens. For referee testing, it is desirable that the same operator use the same equipment to produce test specimens.

#### 6 Apparatus

6.1 **Gun**, of the pneumatic-nozzle mixing type.

6.2 **Air compressor**, capable of supplying a steady airflow at the required pressure and volume.

6.3 **Mixer**, for use where predamping is carried out. The mixer shall be capable of producing a homogeneous mixture of the material to be tested.

6.4 **Hose/nozzle assembly**, comprising a reinforced pneumatic hose and a nozzle assembly suitable for the material being gunned.

6.5 **Gunned-material support plate**, flat, capable of producing a panel having minimum usable dimensions of 300 mm × 300 mm × 80 mm thickness that is suitable for the tests intended to be carried out, after allowance for any material to be cut off as described in Clause 8. The support plate shall have a ledge at its lower edge to prevent panel slipping and may have ledges on the sides and top, and may also incorporate a vertical divider at its centre. The support plate may be made of wood or steel and shall not flex during use. The support plate may be larger than the minimum panel size to allow the edges to be removed from the gunned panel, for example, to remove trapped rebound material at the bottom, and other edge effects. An example of a gunned-material support plate is given in Figure 1. The test report shall state the dimensions of the gunned-material support plate and panel produced.

Dimensions in millimetres

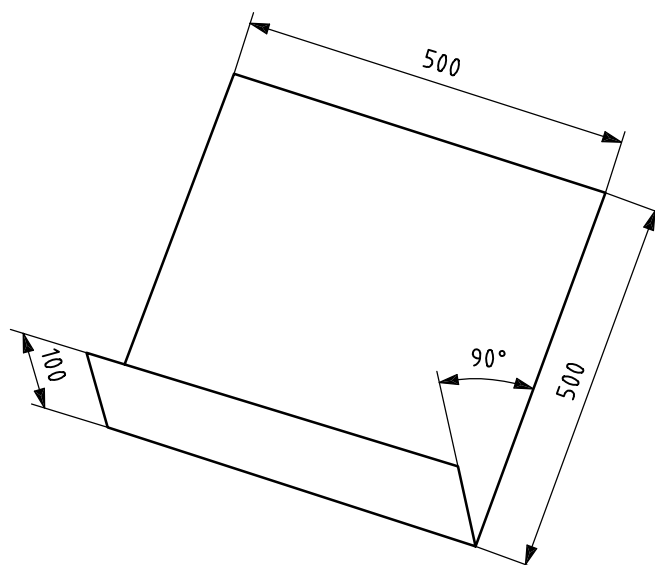


Figure 1 — Example of a gunned-panel support plate

**6.6 Air pressure gauge**, capable of measuring pressures up to 690 kPa, plus or minus 5 % at all pressures.

**6.7 Water-measuring device**, for use if predamping is carried out, capable of measuring the water quantity to the nearest 5 %.

**6.8 Water-pressure gauge**, capable of measuring pressures up to at least 50 kPa greater than the pressure in the supply lines being used and within plus or minus 5 % at all pressures.

**6.9 Miscellaneous tools**, including a trowel and a shovel.

**6.10 Thermometer**, capable of measuring to the nearest 1 °C.

## 7 Sampling

Take the sample for preparation of a test panel in accordance with established sampling principles, such as those given in ISO 8656-1.

The additional volume of material required for sample preparation will depend on the amount left in the apparatus after the gunning operation, the amount of rebound and the amount required to stabilize the gun. The mass of material required will depend on the total volume and the bulk density of the material.

Only full bags of the material to be tested shall be selected and their entire contents shall be used.

## 8 Procedure

**iTeh STANDARD PREVIEW**  
(standards.iteh.ai)

Using Table 1 as a guide, choose the hose diameter appropriate to the particular refractory mix being gunned.

ISO 20182:2005  
<https://standards.iteh.ai/catalog/standards/sist/299-4916-8abd-d753960cade9/iso-20182-2005>

**Table 1 — Feed systems**

Maximum aggregate size in mix mm	Internal diameter of hose mm
< 5	≤ 32
5 to 8	32
> 8	5 × the largest aggregate sizes

The nozzle and the gun are usually held at the same elevation. If this is not the case, record the difference to the nearest metre.

NOTE 1 The water pressure should be greater than 150 kPa above the gunning pressure at the nozzle, possibly requiring the use of a water pump. The watering and nozzle extension will be different for dense and lightweight materials.

Check that the supply water is at 15 °C to 25 °C and that its hardness does not exceed 30 °. Record its temperature to the nearest 1 °C.

NOTE 2 One degree of hardness is equivalent to 10 mg of CaO or 7,14 mg of MgO dissolved in 1 L of water.

Record the ambient temperature and the temperature of the refractory material to the nearest 1 °C. Predampen the material with the manufacturer's recommended amount of water in the mixer, ensuring that the material is used within 20 min of predamping. If there is no recommendation by the manufacturer then, if necessary, predampen in the range 2 % to 5 %, by mass, for dense castables. If there is no predamping recommended by the manufacturer, insulating castables should be predampened as high as possible without causing a stoppage in the gun, hose or nozzle.

Where necessary, to prevent sticking, apply a plate-release agent, such as light oil or grease, to the support plate.

Place the support plate against a rigid surface, typically at an angle of 60° to 80° to the horizontal. Record the angle of inclination and include it in the test report.

Using the minimum amount of water that allows the refractory to adhere to the sprayed surface, adjust the air pressure until the material flows freely from the nozzle. This operation should be performed remote from the support plate.

Holding the nozzle at right angles to the work area and typically 0,5 m to 1 m from it, spray in a circular motion over the full width of the test plate, starting at the bottom of the support plate and working upward, being careful not to entrap rebound material. Continue until the panel's thickness is such that test pieces of the desired size can be cut from the panel, so that all gunned edges are removed in the cutting process.

Interested parties shall agree whether the top surface and edges may be trimmed. The surface shall not be trowelled to obtain a sleek finish.

If a determination of water content is required, take sufficient gunned material, typically 500 g, which is not rebound material.

To minimize moisture loss, either enclose the panel, or cover its surface with an impervious membrane.

Allow the gunned panel to cure at a temperature of 20 °C to 25 °C for 24 h.

NOTE 3 The sample may be stripped after 16 h, provided that it remains in a humid atmosphere (minimum 95 % relative humidity) for a total of 24 h.

Cut test pieces from the gunned panel, with the longest side parallel to the ledge, to a size appropriate to the tests to be carried out, and mark the direction in which the forming/gunning pressure was applied. The cut surface of a test piece shall be at least 1 cm from the exposed edge of the gunned panel. Cut surfaces shall be smooth enough to allow for strength testing if required. The rough, as-gunned faces shall not form part of the test pieces.

NOTE 4 The load in strength tests is applied to test-piece faces cut perpendicular to the direction of gunning.

Dry the samples at 110 °C for 24 h and store for testing. Ensure they do not re-absorb moisture prior to testing.

NOTE 5 For chemically bonded material, a special drying schedule may be required.

Where required, determine the total water content and rebound proportion by methods to be agreed between interested parties.

## 9 Test report

The test report shall include the following information:

- a) all information necessary for identification of the sample tested, including a description of the as-received material, e.g. product name, lot number and production date;
- b) a reference to this International Standard (ISO 20182:2005);
- c) details of the process including:
  - the gun type and operational specifications,
  - the length and diameter of the material hose used,



- the type of nozzle mixing and delivery device,
  - the temperature of the work area, refractory material and water,
  - the mean air pressure measured in the air hose leading to the gun during the gunning operation, to the nearest 10 kPa,
  - the mean water pressure during the gunning operation, to the nearest 10 kPa,
  - the distance from the nozzle to the panel during the major part of the gunning operation, to the nearest 0,2 m,
  - the angle of inclination of the support plate,
  - the difference, if any, in elevation between the nozzle and the gun, to the nearest metre,
  - the quantity of water used for predamping, if applicable, to the nearest 0,5 % by mass,
  - the water hardness, if determined,
  - the dimensions of the gunned panel,
  - the dimensions of the support plate;
- d) if required and determined:
- the total water content of the gunned material, to the nearest 0,1 %,
  - the percentage of rebound material, to the nearest 1 %;
- e) the identity of the operator;
- f) any deviations from the procedure specified;
- g) any unusual features (anomalies) observed during the test, in particular:
- any unusual gunning characteristics, such as surging;
  - any unusual characteristics of the test pieces, such as lamination, segregation, honeycombing;
- h) the date of the test.