



SLOVENSKI STANDARD

SIST EN 14354:2017

01-december-2017

Nadomešča:

SIST EN 14354:2005

SIST EN 14354:2005/AC:2007

Lesne plošče - Furnirane talne obloge

Wood-based panels - Wood veneer floor coverings

Holzwerkstoffe - Furnierte Fußbodenbeläge

Panneaux à base de bois - Revêtements de sol à placage bois

ITEH STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN 14354:2017](#)

Ta slovenski standard je istoveten z: EN 14354:2017

<http://standards.iteh.ai/catalog/standards/sist/en-14354-2017/08f92e64fa12/sist-en-14354-2017>

ICS:

79.080

Polizdelki iz lesa

Semi-manufactures of timber

97.150

Talne obloge

Floor coverings

SIST EN 14354:2017

en,fr,de

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN 14354:2017](#)

<https://standards.iteh.ai/catalog/standards/sist/168152df-270f-4a9c-8d01-08f92e64fa12/sist-en-14354-2017>

EUROPEAN STANDARD

EN 14354

NORME EUROPÉENNE

EUROPÄISCHE NORM

July 2017

ICS 79.080

Supersedes EN 14354:2004

English Version

Wood-based panels - Wood veneer floor coverings

Panneaux à base de bois - Revêtements de sol à placage
bois

Holzwerkstoffe - Furnierte Fußbodenbeläge

This European Standard was approved by CEN on 27 February 2017.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.

[SIST EN 14354:2017](https://standards.iteh.ai/catalog/standards/sist/168152df-270f-4a9c-8d01-08f92e64fa12/sist-en-14354-2017)

<https://standards.iteh.ai/catalog/standards/sist/168152df-270f-4a9c-8d01-08f92e64fa12/sist-en-14354-2017>



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Avenue Marnix 17, B-1000 Brussels

Contents	Page
European foreword.....	5
1 Scope.....	6
2 Normative references.....	6
3 Terms and definitions.....	7
4 Requirements.....	8
4.1 General.....	8
4.2 General requirements.....	8
5 Classification requirements.....	9
5.1 General.....	9
5.2 Classification requirements for elements with lacquered surfaces.....	10
6 Marking and packaging.....	10
6.1 Marking.....	10
6.2 Packaging.....	11
7 Test report.....	11
Annex A (normative) Determination of thickness, length, width, squareness, deviation from edge straightness and cup.....	12
A.1 General.....	12
A.2 Sampling.....	12
A.3 Conditioning.....	12
A.4 Test equipment.....	12
A.5 Procedure.....	13
A.5.1 Determination of thickness t	13
A.5.2 Determination of length l	14
A.5.3 Determination of width w and dimensions of squared elements.....	14
A.5.4 Determination of deviation from squareness q	15
A.5.5 Determination of deviation of edge straightness s	15
A.5.6 Determination of cup f_w	16
A.6 Calculation and expression of results.....	16
A.6.1 Thickness t	16
A.6.2 Width w	16
A.6.3 Length l	16
A.6.4 Deviation from squareness q	16
A.6.5 Deviation from edge straightness s	16
A.6.6 Cup f_w	17
A.7 Test report.....	17

Annex B (normative) Determination of opening and lipping between elements	18
B.1 General	18
B.2 Sampling	18
B.3 Conditioning	18
B.4 Test equipment.....	18
B.5 Procedure	18
B.5.1 Assembling.....	18
B.5.2 Measuring of lipping.....	19
B.5.3 Measuring of openings.....	19
B.5.4 Calculation and expression of results	19
B.6 Test report	19
Annex C (normative) Determination of the elasticity of lacquer.....	20
C.1 General	20
C.2 Sampling	20
C.3 Apparatus	20
C.4 Procedure	20
C.5 Calculation and expression of results	20
C.6 Evaluation of results, elasticity classification	20
Annex D (normative) Determination of the wear resistance using the falling sand method.....	21
D.1 General	21
D.2 Sampling	21
D.3 Conditioning	21
D.4 Apparatus	22
D.4.1 Testing machine.....	22
D.4.2 Grit feeder and accessories.....	22
D.4.3 Additional material or equipment	27
D.5 Procedure	27
D.5.1 General	27
D.5.2 Maintenance of the abrading wheels.....	27
D.5.3 Operation of the abrader	27
D.5.4 Calibration.....	28
D.5.5 Abrasion of test specimen	29
D.6 Expression of results	30
D.7 Test report	30
Annex E (normative) Determination of abrasion resistance using the sand paper method.....	31
E.1 General	31

EN 14354:2017 (E)

E.2	Sampling.....	31
E.3	Conditioning.....	31
E.4	Apparatus.....	32
E.4.1	Testing machine	32
E.4.2	Additional material or equipment.....	35
E.5	Procedure.....	35
E.5.1	General.....	35
E.5.2	Preparation of test specimens and abrasive papers	36
E.5.3	Preparation of abrasive wheels	36
E.5.4	Determination of the abrasion rate of abrasive paper.....	36
E.5.5	Abrasion of test specimen.....	36
E.5.6	Expression of results.....	38
E.5.7	Test report.....	38
Annex F (normative) Determination of the adhesion of the lacquer — Cross cut test.....		39
F.1	General.....	39
F.2	Test equipment.....	39
F.2.1	Cutting tool	39
F.2.2	Spacing guide.....	41
F.2.3	Soft brush	41
F.2.4	Transparent pressure-sensitive adhesive tape	41
F.3	Sampling.....	42
F.4	Test procedure	42
F.4.1	General.....	42
F.4.2	Cutting and removing the lacquer.....	42
F.5	Expression of the results	43
F.6	Test report.....	44
Annex G (normative) Complementary properties		45
Annex H (informative) Guide for evaluation of conformity of product quality		46
H.1	General.....	46
H.2	Terms and definitions	46
H.3	Rules for evaluation of conformity	47
H.3.1	Batch	47
H.3.2	Sampling.....	47
H.3.3	Evaluation of conformity	47
H.4	Sampling report.....	48
Bibliography.....		49

iTech STANDARD PREVIEW
(standards.itech.ai)

[SIST EN 14354:2017](https://standards.itech.ai/catalog/standards/sist/en-14354-2017)

<https://standards.itech.ai/catalog/standards/sist/168152df-270f-4a9c-8d01-08f92e64fa12/sist-en-14354-2017>

European foreword

This document (EN 14354:2017) has been prepared by Technical Committee CEN/TC 112 “Wood-based panels”, the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by January 2018, and conflicting national standards shall be withdrawn at the latest by January 2018.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN 14354:2004.

Compared to EN 14354:2004 the following modifications have been made:

- a) definitions of lacquered and oiled surfaces were introduced;
- b) deletion of requirements on humidity variations as in 4.3;
- c) modifications of classification on wear resistance in Table 2 with two methods of testing;
- d) requirement for the locking strength in Table 2 for the classes 32 and 33;
- e) modified test method for abrasion resistance in Annex D;
- f) new method for abrasion resistance in Annex E;
- g) reference to test according ISO 24339 in Annex G.

This document has been prepared under a mandate given to CEN by the European Commission and the European Free Trade Association.

According to the CEN-CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

EN 14354:2017 (E)**1 Scope**

This European Standard defines terms and specifies requirements and test methods for wood veneer floor coverings with multilayer built up for internal use. It gives guidance for the evaluation of conformity of the products to the requirements of this standard.

This European Standard is not applicable to multilayer parquet elements with a minimum top layer thickness of 2,5 mm. For these products EN 13489 applies.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 319, *Particleboards and fibreboards — Determination of tensile strength perpendicular to the plane of the board*

EN 322, *Wood-based panels — Determination of moisture content*

EN 438-2:2016, *High-pressure decorative laminates (HPL) — Sheets based on thermosetting resins (usually called laminates) — Part 2: Determination of properties*

EN 1534, *Wood flooring — Determination of resistance to indentation — Test method*

EN 13329:2016, *Laminate floor coverings — Elements with a surface layer based on aminoplastic thermosetting resins — Specifications, requirements and test methods*

EN 13442, *Wood flooring and wood panelling and cladding — Determination of the resistance to chemical agents*

EN 16094, *Laminate floor coverings — Test method for the determination of micro-scratch resistance*

EN 60454-2, *Specification for pressure-sensitive adhesive tapes for electrical purposes — Part 2: Methods of test (IEC 60454-2)*

EN ISO 868:2003, *Plastics and ebonite — Determination of indentation hardness by means of a durometer (Shore hardness) (ISO 868:2003)*

EN ISO 10874, *Resilient, textile and laminate floor coverings — Classification (ISO 10874)*

EN ISO 6506-1, *Metallic materials — Brinell hardness test — Part 1: Test method (ISO 6506-1)*

ISO 48, *Rubber, vulcanized or thermoplastic — Determination of hardness (hardness between 10 IRHD and 100 IRHD)*

ISO 7267-2, *Rubber-covered rollers — Determination of apparent hardness — Part 2: Shore-type durometer method*

ISO 24334, *Laminate floor coverings — Determination of locking strength for mechanically assembled panels*

ISO 24339, *Laminate and textile floor coverings — Determination of dimensional variations after exposure to humid and dry climate conditions*

ASTM D 785, *Standard test method for Rockwell hardness of plastics and electrical insulating materials*

FEPA-Standard 42-1, *Grains of fused aluminium oxide, silicon carbide and other abrasive materials for bonded abrasives and for general applications Macrogrits F 4 to F 220*

FEPA-standard 44-1, *Grains of fused aluminium oxide and silicon carbide abrasive materials — Part 1: Determination of bulk density — Macrogrits F and P series*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

wood veneer floor covering

rigid floor covering consisting of a substrate made from a wood-based panel, with a top layer of wood veneer and possibly a backing

3.2

top layer

finished upper wood layer, intended to be the visible side when the floor is installed

3.3

substrate

core material of the wood veneer floor covering

3.4

backing

layer opposite to the top layer

3.5

wood veneer floor covering element

smallest single item identified as the complete product, shaped and machined on its sides to the appropriate dimensions

Note 1 to entry: The element is provided with a suitable system allowing the elements to be assembled together at installation.

3.6

cup

curvature, concave or convex, of the element across the width of the face

3.7

lipping

difference in height, at the edge, between the upper faces of two adjacent and assembled elements when laid on a flat surface

3.8

deviation from edge straightness

concavity or convexity of the edge of the element along the length between the two ends of the element

3.9

wear layer

layer on which wearing occur

ITEH STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN 14354:2017](https://standards.iteh.ai/catalog/standards/sist/168152df-270f-4a9c-8d01-08f92e64fa12/sist-en-14354-2017)

<https://standards.iteh.ai/catalog/standards/sist/168152df-270f-4a9c-8d01-08f92e64fa12/sist-en-14354-2017>

EN 14354:2017 (E)**3.10****lacquered surface**

film-forming coating with a minimum thickness of 20 µm

3.11**oiled surface**

non film forming coating with in general less wear resistance can be provided only by maintenance

Note 1 to entry: These are products containing natural oil, wax or other material for impregnation.

4 Requirements**4.1 General**

All wood veneer floor coverings shall comply with the general requirements given in Table 1. Wood veneer floor coverings with lacquered surface shall comply with the classification requirements given in Table 2. The values given in this Table take account of uncertainties due to variations in the application of finishes and of those described in the test method in Annex D and Annex E.

4.2 General requirements

The nominal dimensions shall be declared by the manufacturer at a given humidity. For appearance for evaluation of conformity, to be used when requested about product quality, the procedure in Annex H may be used.

The wood veneers used for the top layer are hardwood or softwood species and shall be free from decay and insect attack. Variations of colour can occur under the influence of light.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN 14354:2017
<https://standards.iteh.ai/catalog/standards/sist/168152df-270f-4a9c-8d01-08f92e64fa12/sist-en-14354-2017>

Table 1 — General requirements

Characteristics	Requirements	Test methods	
Moisture content H (dispatch from manufacturer)	$5 \% \leq H_{\text{average}} \leq 9 \%$ and $H_{\text{max}} - H_{\text{min}} \leq 3 \%$	EN 322	
Thickness t of an element	$t_{\text{max}} - t_{\text{min}} \leq 0,50 \text{ mm}$ $t_{\text{average}} - t_{\text{nominal}} \leq \pm 0,50 \text{ mm}$	Annex A	
Length l of the top layer in the same package	$l \leq 1\,500 \text{ mm}$: $l_{\text{max}} - l_{\text{min}} \leq 0,50 \text{ mm}$ $l > 1\,500 \text{ mm}$: $l_{\text{max}} - l_{\text{min}} \leq 0,30 \text{ mm/m}$ $l_{\text{average}} - l_{\text{nominal}} \leq 1 \text{ mm}$		
Width w of the top layer in the same package	$w_{\text{max}} - w_{\text{min}} \leq 0,20 \text{ mm}$ $w_{\text{average}} - w_{\text{nominal}} \leq 0,10 \text{ mm}$		
Length l and width w of squared elements $l = w$	$l_{\text{average}} - l_{\text{nominal}} \leq 0,10 \text{ mm}$ $w_{\text{average}} - w_{\text{nominal}} \leq 0,10 \text{ mm}$ $l_{\text{max}} - l_{\text{min}} \leq 0,20 \text{ mm}$ $w_{\text{max}} - w_{\text{min}} \leq 0,20 \text{ mm}$		
Deviation of squareness	$q_{\text{max}} \leq 0,20 \text{ mm}$		
Deviation from edge straightness of the top layer s	$s_{\text{max}} \leq 0,30 \text{ mm/m}$		
Cup f_w in width direction	$f_{w \text{ max}} \leq 0,20 \%$ $f_{w \text{ average}} \leq 0,15 \%$		
Lipping p	$p_{\text{max}} \leq 0,15 \text{ mm}$		Annex B
Opening between elements	$\leq 0,20 \text{ mm}$		
Adhesion of the lacquer ^a	$\leq \text{class 2}$		Annex F
Internal bond of the substrate ^b	$\geq 1,25 \text{ N/mm}^2$	EN 319	
Surface soundness	$\geq 1,00 \text{ N/mm}^2$	EN 13329:2016, Annex D	
max is maximum value min is minimum value			
^a Not applicable for oiled surfaces. ^b For the mechanical assembly systems only (assembly system without glue).			

5 Classification requirements

5.1 General

Veneer floor coverings shall be classified as suitable for different levels of use, according to the performance requirements specified in Table 2, when tested with the methods given therein. Classification shall conform to the scheme specified in EN ISO 10874 (levels 21, 22, 23, 31, 32, 33). The







EN 14354:2017 (E)

use classification defined in the Table 2 had been fixed on the basis of the material (wood veneer) and the linked test methods.

5.2 Classification requirements for elements with lacquered surfaces

The classification requirements for elements with lacquered surfaces are given in Table 2. For the use of this table the producer has to declare which abrasion resistance test method has been used (Annex D or Annex E) and in the case of Annex D the thickness of the top layer.

Table 2 — Classification requirements for elements with lacquered surfaces ex- factory

Class	21	22	23	31	32	33	Test method
Symbol							
Level of use	Domestic			Commercial			
	Moderate	General	Heavy	Moderate	General	Heavy	
Resistance to indentation	$\geq 10 \text{ N/mm}^2$	$\geq 20 \text{ N/mm}^2$		$\geq 30 \text{ N/mm}^2$	$\geq 40 \text{ N/mm}^2$		EN 1534
Thickness swelling	ITd STANDARD PREVIEW (standards.iteh.ai) SIST EN 14354:2017						EN 13329:2016 Annex G
Impact resistance (Elasticity)	EC 0	EC 1		EC 2	EC 3		Annex C
Wear resistance 1,0 mm < top layer < 2,5 mm	800 revolutions			1 500 revolutions	3 000 revolutions		Annex D
Wear resistance Top layer $\leq 1,0$ mm	1 000 revolutions		2 000 revolutions		4 000 revolutions	6 000 revolutions	Annex D
Wear resistance Alternative method	900 revolutions	1 500 revolutions		2 000 revolutions	4 000 revolutions		Annex E
Locking strength	No requirement				Length $\geq 1,0$ KN/m Short side $\geq 2,0$ KN/m		ISO 24334

6 Marking and packaging

6.1 Marking

Wood veneer floor coverings which comply with the requirements of this standard shall have the following information marked by the manufacturer, either on their packaging, or on a label or information sheet included in the packaging.

- product name and number of this document, EN 14354;
- level of use and used abrasion test method (EN 14354:2017, Annex D or E);

- c) wood species of the top layer and thickness of the top layer in the case of use of abrasion method according to EN 14354:2017, Annex D;
- d) nominal dimensions of one element: thickness × width × length in millimetres;
- e) the number of elements contained in a package;
- f) the area in square metres contained in a package;
- g) manufacturer's or supplier's identification.

6.2 Packaging

The product shall be delivered in packages designed to protect the corners, edges and surfaces of the product, under normal conditions of transport and handling. Installation, cleaning and maintenance instructions shall be delivered together with the product.

7 Test report

If a test report is requested, it shall contain at least the following information:

- a) the name and address of the test laboratory;
- b) date of test report;
- c) a reference to this standard; **iTeh STANDARD PREVIEW**
(standards.iteh.ai)
- d) the product tested;
- e) sampling information; [SIST EN 14354:2017
https://standards.iteh.ai/catalog/standards/sist/168152df-270f-4a9c-8d01-08f92e64fa12/sist-en-14354-2017](https://standards.iteh.ai/catalog/standards/sist/168152df-270f-4a9c-8d01-08f92e64fa12/sist-en-14354-2017)
- f) test result;
- g) all deviations from this standard.

Annex A (normative)

Determination of thickness, length, width, squareness, deviation from edge straightness and cup

A.1 General

This annex specifies methods for measuring the thickness, length, width, squareness, deviation from edge straightness and cup of wood veneer floor covering elements.

A.2 Sampling

Take 5 elements at random.

A.3 Conditioning

Elements are measured without conditioning. If requested, the test pieces shall be stabilized to a constant mass in an atmosphere of (23 ± 2) °C and (50 ± 5) % relative humidity. Constant mass is considered to be reached when the results of two successive weighing operations, carried out at an interval of 24 h, do not differ by more than 0,1 % of the mass of the test pieces.

A.4 Test equipment

A.4.1 Micrometer, sliding caliper or any other equivalent tool giving an accuracy of 0,05 mm.

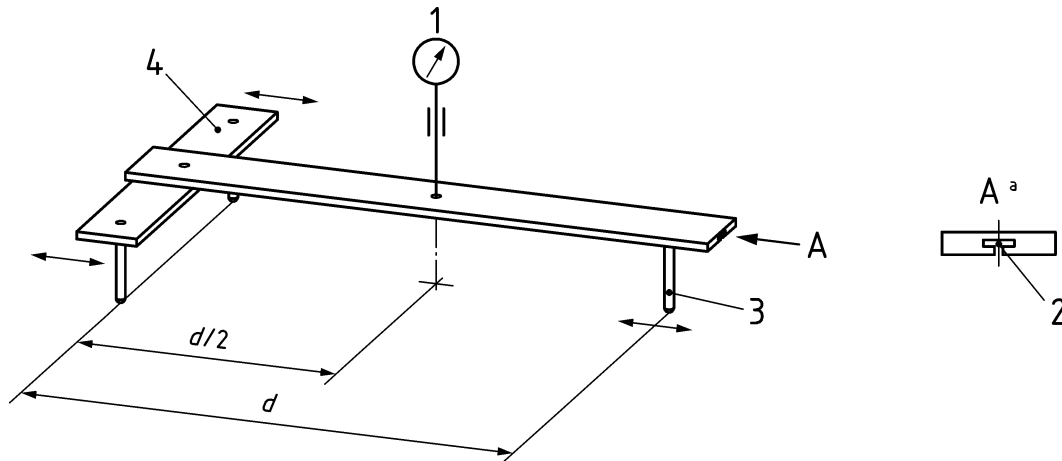
A.4.2 Sliding caliper or any other equivalent tool giving an accuracy of 0,01 mm.

A.4.3 Square arms with lengths of 300 mm and having a maximum angular distortion of 0,02 mm at 300 mm.

A.4.4 Steel ruler of length at least equal to the length of test specimen and having a maximum straightness deviation of 0,05 mm over 1 000 mm.

A.4.5 Apparatus (T-assembly) for measuring width flatness consisting of a dial gauge accurate to $\pm 0,01$ mm with a rounded tip with a radius of $\leq 5,5$ mm, installed centrally in relation to three rounded supports with a radius of ≥ 5 mm. The supports shall be adjustable along a T-shaped assembly of bars to provide the required gauge length. The measurement d shall not be less than the width w of the test specimen minus 10 mm. The tip of the gauge in contact with the face of the test specimen shall apply a force of $(1,0 \pm 0,5)$ N. The mass of the apparatus shall not affect the flatness of the test specimen beyond the limit of the accuracy of the gauge. See Figure A.1 for illustration. The instrument shall be set to zero against a suitable reference plate.

Dimensions in millimetres

**Key**

- a view A enlarged
- 1 dial gauge
- 2 T-groove
- 3 adjustable pin
- 4 adjustable bridge

Figure A.1 — Instrument for measuring the width flatness (Principle)

A.4.6 Steel tape or ruler with an accuracy of $\pm 0,1$ mm up to a length of 1,50 m, and $\pm 0,5$ mm for longer lengths.

A.4.7 Thickness gauges ranging from 0,5 mm to 0,10 mm in steps of 0,01 mm, and from 0,10 mm to 0,50 mm in steps of 0,05 mm.

A.5 Procedure**A.5.1 Determination of thickness t**

Measure the thickness t with a micrometer, or any other device of the equipment described in A.4.1, at a distance of 20 mm from the edges of the top layer, at points located in each corner and in the middle of each long side (only four corner points if the length is ≤ 600 mm), see Figure A.2.