

SLOVENSKI STANDARD oSIST prEN ISO 283:2014

01-september-2014

Naprave za kontinuirni transport - Trakovi tračnih transporterjev - Natezna trdnost pri polni debelini traku, raztezek pri porušitvi in raztezek pri referenčni sili - Preskusna metoda (ISO/DIS 283:2014)

Textile conveyor belts - Full thickness tensile strength, elongation at break and elongation at the reference load - Test method (ISO/DIS 283:2014)

Textilfördergurte - Zugfestigkeit bei voller Gurtdicke, Bruchdehnung und Dehnung bei breitenbezogener Bruchkraft - Prüfverfahren (ISO/DIS 283:2014)

Courroies transporteuses à carcasse textile - Résistance à la traction, allongement à la rupture et allongement sous force de référence en pleine épaisseur - Méthode d'essai (ISO/DIS 283:2014)

Ta slovenski standard je istoveten z: prEN ISO 283 rev

ICS:

53.040.20 Deli za transporterje Components for conveyors

oSIST prEN ISO 283:2014 en

oSIST prEN ISO 283:2014

iTeh STANDARD PREVIEW (standards.iteh.ai)

SIST EN ISO 283:2016

https://standards.iteh.ai/catalog/standards/sist/4e16b5c3-8fba-4d2e-a766-f569f4f643ee/sist-en-iso-283-2016

DRAFT INTERNATIONAL STANDARD ISO/DIS 283

ISO/TC **41**/SC **3** Secretariat: **SAC**

Voting begins on: Voting terminates on:

2014-04-24 2014-09-24

Textile conveyor belts — Full thickness tensile strength, elongation at break and elongation at the reference load — Test method

Courroies transporteuses à carcasse textile — Résistance à la traction, allongement à la rupture et allongement sous force de référence en pleine épaisseur — Méthode d'essai

[Revision of third edition (ISO 283:2007)]

ICS: 53.040.20

iTeh STANDARD PREVIEW (standards.iteh.ai)

SIST EN ISO 283:2016

https://standards.iteh.ai/catalog/standards/sist/4e16b5c3-8fba-4d2e-a766-f569f4f643ee/sist-en-iso-283-2016

ISO/CEN PARALLEL PROCESSING

This draft has been developed within the International Organization for Standardization (ISO), and processed under the **ISO lead** mode of collaboration as defined in the Vienna Agreement.

This draft is hereby submitted to the ISO member bodies and to the CEN member bodies for a parallel five month enquiry.

Should this draft be accepted, a final draft, established on the basis of comments received, will be submitted to a parallel two-month approval vote in ISO and formal vote in CEN.

To expedite distribution, this document is circulated as received from the committee secretariat. ISO Central Secretariat work of editing and text composition will be undertaken at publication stage.

THIS DOCUMENT IS A DRAFT CIRCULATED FOR COMMENT AND APPROVAL. IT IS THEREFORE SUBJECT TO CHANGE AND MAY NOT BE REFERRED TO AS AN INTERNATIONAL STANDARD UNTIL PUBLISHED AS SUCH.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.



Reference number ISO/DIS 283:2014(E)

ISO/DIS 283:2014(E)

iTeh STANDARD PREVIEW (standards.iteh.ai)

SIST EN ISO 283:2016

https://standards.iteh.ai/catalog/standards/sist/4e16b5c3-8fba-4d2e-a766-f569f4f643ee/sist-en-iso-283-2016

Copyright notice

This ISO document is a Draft International Standard and is copyright-protected by ISO. Except as permitted under the applicable laws of the user's country, neither this ISO draft nor any extract from it may be reproduced, stored in a retrieval system or transmitted in any form or by any means, electronic, photocopying, recording or otherwise, without prior written permission being secured.

Requests for permission to reproduce should be addressed to either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office Case postale 56 • CH-1211 Geneva 20 Tel. + 41 22 749 01 11 Fax + 41 22 749 09 47 E-mail copyright@iso.org Web www.iso.org

Reproduction may be subject to royalty payments or a licensing agreement.

Violators may be prosecuted.

Contents		Page
Fore	eword	iv
1	Scope	1
2	Normative references	1
Term	ns and definitions	1
4	Principle	2
5	Apparatus	2
6	Test pieces	3
6.1	Shape and dimensions	
6.2	Method of selection of test pieces	
6.3	Preparation of test pieces	
6.4	Number of test pieces	
6.5	Conditioning of test pieces	8
7	Procedure	8
8	Calculation and expression of results	8
8.1	Tensile strength	8
8.2	Elongation	8
9	Test report (Standards.iteh.ai)	9
Bibli	iography	10

SIST EN ISO 283:2016
https://standards.iteh.ai/catalog/standards/sist/4e16b5c3-8fba-4d2e-a766-f569f4f643ee/sist-en-iso-283-2016

ISO/DIS 283

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 283 was prepared by Technical Committee ISO/TC 41, *Pulleys and belts (including veebelts)*, Subcommittee SC 3, *Conveyor belts*.

This fourth edition cancels and replaces the third edition (ISO 283:2007) which has been technically revised.

SIST EN ISO 283:2016

https://standards.iteh.ai/catalog/standards/sist/4e16b5c3-8fba-4d2e-a766-f569f4f643ee/sist-en-iso-283-2016

Textile conveyor belts — Full thickness tensile strength, elongation at break and elongation at the reference load — Test method

1 Scope

This International Standard specifies a test method for the determination of the full thickness tensile strength in the longitudinal direction and the elongation at the reference force and breaking point of conveyor belts having a textile carcass. The method can also be used for the determination of full thickness tensile strength in the transverse direction and the elongation at the breaking point, for use when the manufacturer is requested by the purchaser to state values for these properties.

This International Standard is not suitable or valid for light conveyor belts as described in ISO 21183-1^[1].

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 7500-1, Metallic materials — Verification of static uniaxial testing machines — Part 1: Tension/compression testing machines — Verification and calibration of the force-measuring system

ISO 18573, Conveyor belts — Test atmospheres and conditioning periods

EN 10002-2, Metallic materials — Tensile testing — Part 2: Verification of the force measuring system of the tensile testing machines

Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

tensile strength

greatest measured force during the tensile test divided by the width of the test piece, expressed in N/mm

3.2

nominal tensile strength

specified minimum value of the tensile strength, expressed in N/mm

ISO/DIS 283

3.3

reference force reference load

one-tenth of the nominal tensile strength in the longitudinal direction multiplied by the width of the test piece in mm, expressed in newtons

EXAMPLE Nominal tensile strength = 1 600 N/mm

One tenth of the nominal tensile strength = 160 N/mm;

Reference force for 25 mm test piece = 25 mm \times 160 N/mm = 4 000 N.

3.4

elongation at break

elongation at the greatest force [load], expressed as the percentage increase in the distance between two reference points

3.5

elongation at the reference force [load]

elongation at the reference force [load] in the longitudinal direction, expressed as the percentage increase in the distance between two reference points

Principle

A test piece, cut from the full thickness of the conveyor belt, is extended under specified conditions using a tensile testing machine, until rupture of the test piece occurs.

Apparatus

- Tensile testing machine, of CRE or CRT type, calibrated to Grade 1 according to ISO 7500-1or
- 5.1 EN 10002-2, and capable of extending the test piece at a constant rate, without interruption, of (100 ± 10) mm/min.
- Device, such as an extensometer, with a measuring length of at least 100 mm and accurate to within 0,1 mm or better, capable of measuring the elongation of the gauge length marked on the test piece. Use of a device that produces a graphical trace throughout the test is preferred.
- Grips, the form of which should prevent any slippage of the test piece during the tensile test. The use of grips with transverse serrations in accordance with Figure 1 is recommended.

Dimensions in millimetres

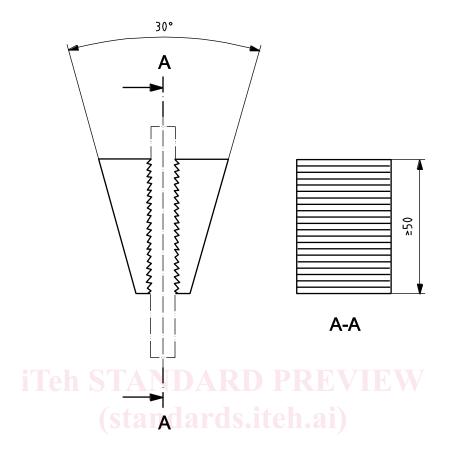


Figure 1 — Grip with transverse serrations

https://standards.iteh.ai/catalog/standards/sist/4e16b5c3-8fba-4d2e-a766-f569f4f643ee/sist-

5.4 Die cutter or power saw, either of the dies with wall profiles as shown in Figure 2 being suitable for cutting the test pieces shown in Figures 3, 4 and 5. Other profiles may be used, but the critical feature is that the cut sides of the test piece are perpendicular to the test piece surfaces.

6 Test pieces

6.1 Shape and dimensions

The shape and dimensions of the test piece shall be in accordance with either Figure 3, 4, 5 or 6.

6.2 Method of selection of test pieces

Test pieces shall be selected parallel, or at right angles, to the axis of the belt, and at not less than 50 mm from the edge of the belt. If test pieces are selected from a sample cut from the belt, no test piece shall be cut with its longitudinal edge less than 12 mm from the edge of the sample. In all cases, the cut or sawn sides of the test piece shall be perpendicular to its surface. No test piece shall contain a ply joint.

For a test piece of type D, draw the form of the test piece on the surface of the belt or sample and from each edge of the sample cut at five places with a power saw up to the drawn lines (see Figure 6).

The type D test piece illustrated in Figure 6 should be limited to the testing of conveyor belts having tensile strengths greater than 2 000 N/mm.

Dimensions in millimetres

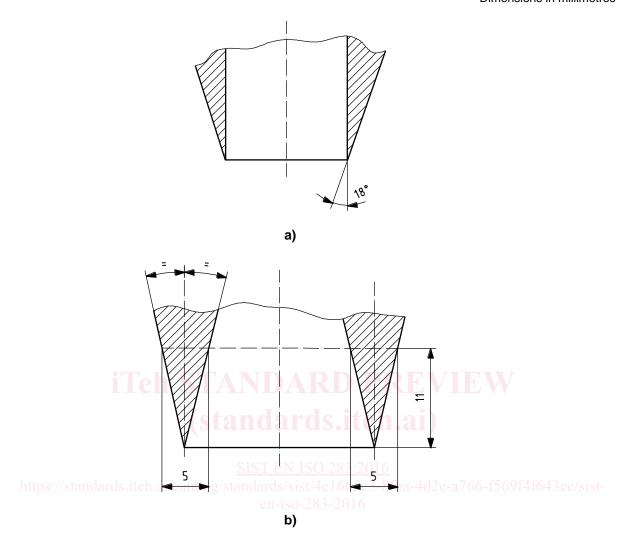


Figure 2 — Suitable die profiles