
Železniške naprave - Zgornji ustroj - Prevzem del - 5. del: Postopki za reprofiliranje tirov na odprti progi, stikal, prehodov in razširjevalnih naprav

Railway applications - Track - Acceptance of works - Part 5: Procedures for rail reprofiling in plain line, switches, crossings and expansion devices

Bahnanwendungen - Oberbau - Abnahme von Arbeiten - Teil 5: Procedure zur Reprofilierung von Schienen in Gleisen, Weichen, Kreuzungen und Schienenauszügen

Applications ferroviaires - Voie - Réception des travaux - Partie 5 : Procédure pour le reprofilage de rails en voie courante, en appareil de voie et en appareil de dilatation

<https://standards.iteh.ai/catalog/standards/sist/d45d292e-bffb-4a12-bd09-02accc65997a/sist-en-13231-5-2018>

Ta slovenski standard je istoveten z: EN 13231-5:2018

ICS:

45.080	Tračnice in železniški deli	Rails and railway components
93.100	Gradnja železnic	Construction of railways

SIST EN 13231-5:2018

en,fr,de

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN 13231-5:2018](#)

<https://standards.iteh.ai/catalog/standards/sist/d45d292e-bffb-4a12-bd09-02acc65997a/sist-en-13231-5-2018>

EUROPEAN STANDARD

EN 13231-5

NORME EUROPÉENNE

EUROPÄISCHE NORM

June 2018

ICS 93.100

English Version

Railway applications - Track - Acceptance of works - Part 5: Procedures for rail reprofiling in plain line, switches, crossings and expansion devices

Applications ferroviaires - Voie - Réception des travaux
- Partie 5 : Procédures pour le reprofilage de rails en
voie courante, en appareil de voie et en appareil de
dilatation

Bahnanwendungen - Oberbau - Abnahme von Arbeiten
- Teil 5: Prozedere zur Schienen-Reprofilierung in
Gleisen, Weichen, Kreuzungen und Schienenauszügen

This European Standard was approved by CEN on 8 February 2018.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Rue de la Science 23, B-1040 Brussels

Contents

	Page
European foreword.....	4
1 Scope	5
2 Normative references	5
3 Terms and definitions	5
4 Basics	7
4.1 Technical Introduction	7
4.2 Background of rail reprofiling	7
4.3 Specific reprofiling strategy	8
5 Rail surface defects	8
5.1 General	8
5.2 Rolling contact fatigue	8
5.2.1 Head check	8
5.2.2 Belgrospi	9
5.2.3 Squats	10
5.2.4 Flaking (Gauge corner cracking)	10
5.2.5 Spalling	11
5.3 Transverse profile deformation	12
5.3.1 Flattened transverse profile	12
5.3.2 Side cutting	12
5.3.3 Lipping	13
5.4 Periodical defects in longitudinal profiles	13
5.4.1 Short pitch corrugation	13
5.4.2 Short wave corrugation	14
5.4.3 Long wave corrugation	16
5.5 Surface damage	17
5.5.1 General	17
5.5.2 Imprints	17
5.5.3 Wheel burns	17
6 Reprofiling procedure	18
6.1 Inspection	18
6.2 Intervention thresholds	18
6.2.1 Longitudinal profile	18
6.2.2 Transverse profile	19
6.2.3 Rolling Contact Fatigue (RCF)	19
6.3 Specification of work	20
6.3.1 Metal removal	20
6.3.2 Target profile	20
6.4 Execution of work	22
6.5 Documentation of work	23
Annex A (informative) Programming of reprofiling work	24
A.1 General reprofiling programme	24
A.1.1 General	24
A.1.2 Reprofiling applications	24
A.1.3 Selection of machine type	25

A.1.4	Combination of reprofiling activities with other track maintenance work	25
A.2	Detailed reprofiling plan	26
Annex B	(informative) Reprofile methods.....	27
B.1	General	27
B.2	Rotating grinding.....	27
B.2.1	Principle of work	27
B.2.2	Performance	28
B.2.3	Results	28
B.2.4	Application.....	28
B.3	Milling.....	29
B.3.1	Principle of work	29
B.3.2	Performance.....	29
B.3.3	Results	30
B.3.4	Application.....	30
B.4	Oscillating grinding.....	30
B.4.1	Principle of work	30
B.4.2	Performance.....	31
B.4.3	Results	31
B.4.4	Application.....	31
B.5	Planing.....	31
B.5.1	Principle of work	31
B.5.2	Performance.....	32
B.5.3	Results	32
B.5.4	Application.....	32
B.6	High speed grinding.....	32
B.6.1	Principle of work	32
B.6.2	Performance.....	33
B.6.3	Results	33
B.6.4	Application.....	34
Annex C	(informative) A reprofiling strategy	35
C.1	General	35
C.2	Specific reprofiling strategy.....	35
C.3	Moving from corrective to preventive reprofiling	35
Annex ZA	(informative) Relationship between this European Standard and the Essential Requirements of EU Directive 2008/57/EC aimed to be covered.....	37
Bibliography	39

EN 13231-5:2018 (E)**European foreword**

This document (EN 13231-5:2018) has been prepared by Technical Committee CEN/TC 256 “Railway applications”, the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by December 2018, and conflicting national standards shall be withdrawn at the latest by December 2018.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN shall not be held responsible for identifying any or all such patent rights.

This document has been prepared under a mandate given to CEN by the European Commission and the European Free Trade Association, and supports essential requirements of EU Directive 2008/57/EC.

For relationship with EU Directive 2008/57/EC, see informative Annex ZA, which is an integral part of this document.

This document is one of the series EN 13231, *Railway applications — Track — Acceptance of works* as listed below:

- *Part 1: Works on ballasted track - Plain line switches and crossings;*
- *Part 3: Acceptance of reprofiling rails in track;*
- *Part 4: Acceptance of reprofiling rails in switches and crossings;*
- *Part 5: Procedures for rail reprofiling in plain line switches, crossings and expansion devices (the present document).*

According to the CEN-CENELEC Internal Regulations, the national standards organisations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

1 Scope

This document specifies the procedure for planning and execution of rail reprofiling work including description of rail surface defects. It concerns work in both plain lines and switches and crossings generally done with machines according to the EN 14033 series and EN 15746 series.

It applies to vignole railway rails of 46 kg/m and above according to EN 13674-1.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 13231-3:2012, *Railway applications — Track — Acceptance of works — Part 3: Acceptance of reprofiling rails in track*

EN 13231-4:2013, *Railway applications — Track — Acceptance of works — Part 4: Acceptance of reprofiling rails in switches and crossings*

3 Terms and definitions

For the purposes of this document the terms and definitions given in EN 13231-3:2012 and EN 13231-4:2013 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>
<https://standards.iteh.ai/catalog/standards/sist/d45d292e-bf1b-4a12-bd09-02acc65997a/sist-en-13231-5-2018>

3.1

anti-head check profile

AHC Profile

rail head profile with a geometry to prevent and reduce head checking

3.2

rolling contact fatigue

RCF

rail damage caused by the complex stresses that are characteristic of rail wheel contact

3.3

head checking

HC

small parallel cracks on the rail head near or on the gauge corner

3.4

Belgrospi

network of cracks developing on the rail head of track with speed greater than 160 km/h affected by short pitch corrugation

3.5

squat

rolling contact fatigue defect whose main characteristics are a blackish patch on rail head, a lateral flow of steel and a collapsed and widened rolling band

EN 13231-5:2018 (E)**3.6****flaking**

surface condition consisting of the gouging of metal on the rail head

3.7**spalling**

cracking and chipping on the top of the rail

Note 1 to entry: Occurs commonly on low rails.

3.8**transverse profile deformation**

plastic metal flow on the rail head

3.9**side cutting**

wear occurring on high rails in small radius curves where wheel flanges contact the rail

3.10**lipping**

plastic metal flow occurring on the rail head under conditions of high axle load and high gross tonnage

3.11**short pitch corrugation**

quasi-periodic irregularities on the running surface

iTeh STANDARD PREVIEW
(standards.iteh.ai)

Note 1 to entry: The wavelength usually is 10 mm to 100 mm. Covering hereby two jointed wavelength according to the EN 13231 series.

[SIST EN 13231-5:2018](https://standards.iteh.ai/catalog/standards/sist/d45d292e-bffb-4a12-bd09-02acc65997a/sist-en-13231-5-2018)

<https://standards.iteh.ai/catalog/standards/sist/d45d292e-bffb-4a12-bd09-02acc65997a/sist-en-13231-5-2018>

3.12**short wave corrugation**

depressions in the running surface which are pronounced

Note 1 to entry: The wavelength usually is 30 mm to 300 mm. Covering hereby two jointed wavelength according to the EN 13231 series.

3.13**long wave corrugation**

irregular unevenness on the running surface

Note 1 to entry: The wavelength usually is 300 mm to 1 000 mm.

3.14**imprint**

damage resulting from a small object which has been pressed into the rail by the wheel

3.15**wheel burn**

abrasive, plastic and thermal damage occurring in zones where trains start to move

Note 1 to entry: Occurs e.g. at signals.

4 Basics

4.1 Technical Introduction

The complexity of vehicle-track interaction generates high stresses at the rail-wheel contact, the severity of which is governed by local track characteristics, vehicle type and other operational conditions. The repeated application of these stresses results in the development of fatigue cracks usually referred to as RCF manifested as head checks, gauge corner cracking, or squats. Although rail metallurgy offers a key mitigation measure against such fatigue degradation, there are no rail steels currently in use that could fully withstand the repeated application of such contact stresses. Furthermore the majority of rails in track today, despite their adequate but lower fatigue resistance, have an appreciable residual life span, which makes it more economic to maintain them in an appropriate manner to extend their life rather than to change them.

Management of rail profile and condition is therefore a prerequisite for safe and cost effective operation of railways. Predictable work – at least in a medium time horizon – organized in a strategic way needs to be defined to extract the maximum benefit from existing technologies and to guide the industry for future development. However, it is essential to ensure that the chosen approach provides enough flexibility to adapt to changing situations in both senses: increased requirements for maintenance due to higher loads and dynamic forces, reduced requirements for maintenance due to lower loads (improved vehicle characteristics) and better performing rails (reduced fatigue development).

The life expectancy of a rail is influenced by its interactions with the other parts of the train-track system. The faster and more frequent train services, higher axle loads and new generations of vehicles with greater primary yaw stiffness have significantly increased the critical track forces that promote more rapid degradation of the rail (and wheel), leading to more frequent and costly maintenance interventions and even rail renewal. Significant research into rail metallurgy has resulted in the development of rail steels with much higher resistance to wear and RCF. Nevertheless rail maintenance by reprofiling is an essential requirement for efficient and safe functioning of railway track. The combination of rail grade selection and maintenance strategy considering local track and traffic characteristics ensures effective control of any kind of rail surface defects.

4.2 Background of rail reprofiling

Reprofiling strategy is a planned maintenance activity usually defined by the infrastructure maintainer. In theory it is independent of available technologies, but in practice it is often influenced by the equipment that is easily accessible to or proposed by the contractors.

Work is programmed depending on damage having reached predetermined intervention thresholds such as corrugation depth, deviation from the transverse profile and depth of cracks.

Alternatively work is executed in cycles which are derived from experience and influenced by availability of machines, track possession times and similar factors such as traffic, usually expressed in mega gross tonnes (MGT), months, seasons, etc. Often work is combined with other maintenance activities (e.g. after rail replacement, after tamping or when the line is closed for other work, etc.).

Before the execution of rail maintenance work, specifications (i.e. the results that need to be achieved) shall be defined for:

- defect repair (metal removal);
- longitudinal profile (tolerance);
- transversal profile (target and tolerance);
- surface condition (roughness, facet widths, etc.).

EN 13231-5:2018 (E)

Rail reprofiling as described in this document refers to rail rectification using currently available technologies such as grinding, milling, planing, etc.

4.3 Specific reprofiling strategy

In addition to the use of the appropriate rail steel grade the consecutive reprofiling cycles are also dependent on other important parameters, such as existing reprofiling capacity (e.g. maximum/minimum metal removal rates, sections lengths, etc.) and available working intervals (possession times, route reprofiling capabilities, etc.). For the development of an optimized reprofiling strategy these parameters shall also be taken into account.

Shorter reprofiling intervals result in smaller metal removal requirements, consequently in such short periods the development of RCF and irregularities such as corrugation and resulting track deterioration is limited.

NOTE For some Infrastructure Managers in Europe, the preferable strategy is preventive cyclic reprofiling with small metal removal requirements applying profiles with moderate gauge corner relief. If the interval between reprofiling cycles is appropriately matched with the initiation and subsequent growth of cracks, metal removal can be adjusted for a one-pass regime which is operationally the best option.

In order to maintain RCF-sensitive sections economically, a certain damage level can be accepted (as intervention threshold or as remaining depth after treatment). However, this damage needs to be kept low enough to be removed pre-emptively and thereby avoiding safety issues. A rail reprofiling strategy requiring metal removal rates of up to 0,6 mm at the critical gauge area and a maximum of 0,2 mm in the centre of the rail head shall be programmed.

Several Infrastructure Managers (IMs) utilize these metal removal specifications to control HC in standard carbon rail (R260) based on reprofiling cycles at 15 MGT for curves and 45 MGT for tangent track. For harder heat treated rails (e.g. R350HT) the intervals may be doubled depending on track and traffic characteristics.

If squats need to be controlled in tangent track due to traffic and vehicle characteristics (stiffness, traction and braking) shorter cycles may be required.

The reprofiling interval and the related average metal removal should depend on actual HC measurements which need to be checked again during reprofiling work. Such a policy optimizes the magnitude of artificial wear by reprofiling and hence prolongs rail life.

5 Rail surface defects

5.1 General

Each irregularity causes a higher dynamic load on the surface of the rail and consequently an impact occurs at each wheel passage. Consequently the rail is subjected to high stresses and the damage often progresses at a significant rate.


Not only is the rail affected but also the whole track system. As the rail cannot always absorb the energy from the impact, the shock load continues further into the track. Local damage to fastenings, pads and sleepers may result. Ultimately the ballast becomes locally overloaded and disturbed and the stability of the track can no longer be ensured.

5.2 Rolling contact fatigue

5.2.1 Head check

Head checking is characterized by small parallel cracks on the rail head near the gauge corner or on the gauge corner (see Figure 1). The exact localization of the head check depends on the contact conditions. It appears mainly on the high rail on large radius curves but can occur on small radius curves or tangent

track. The orientation and periodicity of the cracks depends on rail grade and track geometry. However the cracks are generally oriented from the top of the rail to the gauge in the direction of traffic. In the vertical section through the cracks their orientation is from the top of the rail to the bottom of the rail in the direction of traffic.

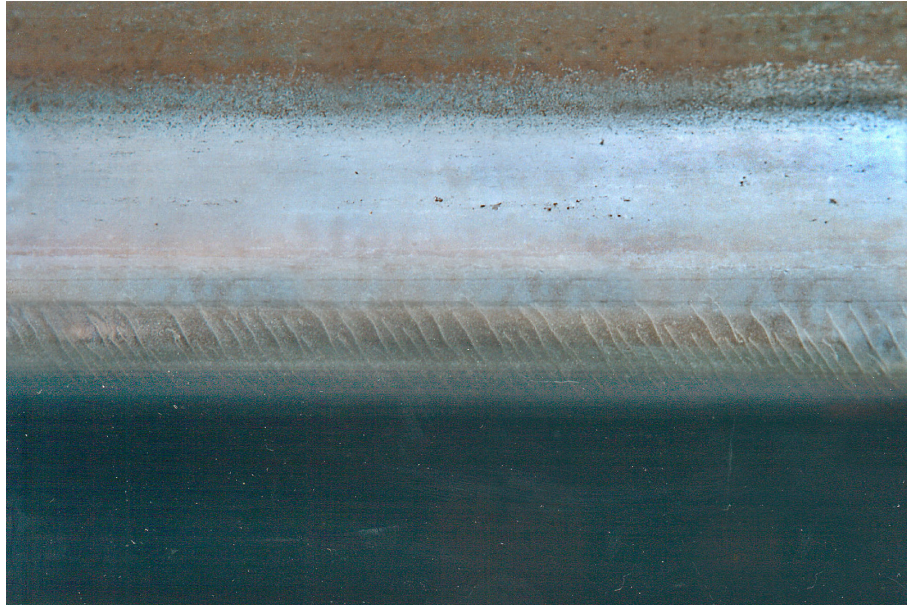

iTeh STANDARD PREVIEW
Figure 1 — Head check
(standards.iteh.ai)

5.2.2 Belgrospi

SIST EN 13231-5:2018

A network of cracks may develop on rail of track speed greater than 160 km/h affected by short pitch corrugation (see Figure 2). The cracks appear at short pitch corrugation with a depth of 0,03 mm. If not removed in time they may grow and develop into squats (see 5.2.3).



Figure 2 — Belgrospi

EN 13231-5:2018 (E)**5.2.3 Squats**

Squat defects (see Figure 3) are rolling contact fatigue defects whose main characteristics are:

- a blackish patch on rail head;
- a lateral flow of steel;
- a collapsed and widened rolling band.

Under this defect a network of cracks grows from two main horizontal cracks and may lead to a severe and unexpected rail breakdown. This network of cracks makes it difficult to analyse the defect.



Figure 3 — Squat

5.2.4 Flaking (Gauge corner cracking)

Flaking is a surface condition consisting of the gouging of metal on the rail head. It is indicated by small chipping and cavities (see Figure 4). It is a progressive horizontal separation on the running surface of rail near the gauge corner with scaling or chipping of small slivers. Flaking should not be confused with shelling as the flaking takes place only on the running surface usually near the gauge corner of the rail and is not as deep as shelling.



Figure 4 — Flaking

5.2.5 Spalling

Spalling (also known as snake skin) appears as a network of cracks on the rail head (see Figure 5) commonly on the low rail of a curve. The cracks are parallel and linked by transverse cracks. The spalling may result in loss of material or in rail delamination.



Figure 5 — Spalling