



# SLOVENSKI STANDARD

## oSIST prEN 10210-3:2016

01-februar-2016

---

### Vročje izdelani votli konstrukcijski profili iz jekla - 3. del: Mere, mejni odstopki in značilnosti profilov

Hot finished structural steel hollow sections - Part 3: Tolerances, dimensions and sectional properties

Warmgefertigte Hohlprofile für den Stahlbau - Teil 3: Grenzabmaße, Masse und statische Werte

Profils creux de construction finis à chaud en aciers - Partie 3 : Tolérances, dimensions et caractéristiques du profil

**Ta slovenski standard je istoveten z: prEN 10210-3**

---

#### **ICS:**

77.140.45	Nelegirana jekla	Non-alloyed steels
77.140.70	Jekleni profili	Steel profiles

**oSIST prEN 10210-3:2016**

**en,fr,de**



EUROPEAN STANDARD  
NORME EUROPÉENNE  
EUROPÄISCHE NORM

**DRAFT**  
**prEN 10210-3**

January 2016

ICS 77.140.75

Will supersede EN 10210-2:2006

English Version

## Hot finished structural steel hollow sections - Part 3: Tolerances, dimensions and sectional properties

Profils creux de construction finis à chaud en aciers -  
Partie 3 : Tolérances, dimensions et caractéristiques du  
profil

Warmgefertigte Hohlprofile für den Stahlbau - Teil 3:  
Grenzabmaße, Masse und statische Werte

This draft European Standard is submitted to CEN members for enquiry. It has been drawn up by the Technical Committee ECISS/TC 103.

If this draft becomes a European Standard, CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

This draft European Standard was established by CEN in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.

Recipients of this draft are invited to submit, with their comments, notification of any relevant patent rights of which they are aware and to provide supporting documentation.

**Warning** : This document is not a European Standard. It is distributed for review and comments. It is subject to change without notice and shall not be referred to as a European Standard.



EUROPEAN COMMITTEE FOR STANDARDIZATION  
COMITÉ EUROPÉEN DE NORMALISATION  
EUROPÄISCHES KOMITEE FÜR NORMUNG

**CEN-CENELEC Management Centre: Avenue Marnix 17, B-1000 Brussels**

<b>Contents</b>	<b>Page</b>
<b>European foreword</b> .....	<b>3</b>
<b>1 Scope</b> .....	<b>4</b>
<b>2 Normative references</b> .....	<b>4</b>
<b>3 Terms and definitions</b> .....	<b>4</b>
<b>4 Symbols</b> .....	<b>5</b>
<b>5 Information to be obtained by the manufacturer</b> .....	<b>6</b>
5.1 <b>Mandatory information</b> .....	<b>6</b>
5.2 <b>Options</b> .....	<b>6</b>
<b>6 Tolerances</b> .....	<b>6</b>
<b>7 Measurement of size and shape</b> .....	<b>8</b>
7.1 <b>General</b> .....	<b>8</b>
7.2 <b>Outside dimensions</b> .....	<b>8</b>
7.3 <b>Thickness</b> .....	<b>8</b>
7.4 <b>Out-of-roundness</b> .....	<b>8</b>
7.5 <b>Concavity and convexity</b> .....	<b>9</b>
7.6 <b>Squareness of sides</b> .....	<b>10</b>
7.7 <b>External corner profile</b> .....	<b>10</b>
7.8 <b>Twist</b> .....	<b>11</b>
7.9 <b>Straightness</b> .....	<b>12</b>
<b>8 Dimensions and sectional properties</b> .....	<b>13</b>
<b>Annex A (normative) Formulae for the calculation of sectional properties</b> .....	<b>14</b>
<b>Annex B (normative) Sectional properties for a limited range of standard sizes</b> .....	<b>19</b>

## European foreword

This document (prEN 10210-3:2016) has been prepared by Technical Committee ECISS/TC 103 “Structural steels other than reinforcements”, the secretariat of which is held by DIN.

This document is currently submitted to the CEN Enquiry.

This document will supersede EN 10210-2:2006.

This European Standard consists of the following parts under the general title 'Hot finished structural steel hollow sections':

- *Part 1: General*
- *Part 2: Technical delivery conditions*
- *Part 3: Tolerances, dimensions and sectional properties*

It forms part of a series of standards on hollow sections together with prEN 10219-1 to prEN 10219-3.

iTeh STANDARD PREVIEW  
(standards.iteh.ai)

SIST EN 10210-2:2019

<https://standards.iteh.ai/catalog/standards/sist/e7ec6b6e-62e6-457a-8c90-92713f61d609/sist-en-10210-2-2019>

## prEN 10210-3:2016 (E)

### 1 Scope

This part of prEN 10210 specifies tolerances for hot finished circular, square, rectangular and elliptical structural hollow sections, manufactured in wall thicknesses up to 120 mm, in the following size ranges:

Circular: Outside diameters up to 2 500 mm

Square: Outside dimensions up to 800 mm x 800 mm

Rectangular: Outside dimensions up to 750 mm x 500 mm

Elliptical: Outside dimensions up to 500 mm x 250 mm

The formulae for calculating sectional properties of sections manufactured to the dimensional tolerances of this standard, to be used for the purposes of structural design, are given in Annex A.

Dimensions and sectional properties for a limited range covering the more common sizes are given in Annex B.

The general conditions are specified in prEN 10210-1 (product characteristics, test methods and performance criteria that apply under the Construction Products Regulations) and the technical delivery conditions in prEN 10210-2.

NOTE The designation of the sections' major axis (yy) and its minor axis (zz) align with the axis designation used for structural design in the structural Eurocodes.

### 2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

prEN 10210-1, *Hot finished structural steel hollow sections - Part 1: General*

prEN 10210-2, *Hot finished structural steel hollow sections - Part 2: Technical delivery conditions*

### 3 Terms and definitions

For the purposes of this document, the terms and definitions given in prEN 10210-1 apply.

## 4 Symbols

For the purposes of this document, the symbols defined in Table 1 apply.

**Table 1 — Symbols and definitions**

Symbol	Unit	Definition
$A$	cm <sup>2</sup>	Cross-sectional area
$A_m$	mm <sup>2</sup>	Area of the surface delimited by the perimeter at mid-thickness
$A_s$	m <sup>2</sup> /m	Superficial area per metre length
$B$	mm	Specified side dimension of a square hollow section. Specified dimension of the shorter side of a rectangular hollow section. Specified outside dimension of an elliptical section on its minor axis
$C_1/C_2$	mm	Length of corner region of a square or rectangular hollow section
$C_t$	cm <sup>3</sup>	Torsional modulus constant
$D$	mm	Specified outside diameter of a circular hollow section
$D_{max}/D_{min}$	mm	The maximum and minimum outside diameter of a circular hollow section measured in the same plane
$e$	mm	Deviation from straightness
$H$	mm	Specified dimension of the longer side of a rectangular hollow section. Specified outside dimension of an elliptical section on its major axis
$I$	cm <sup>4</sup>	Second moment of area
$I_t$	cm <sup>4</sup>	Torsional inertia constant (polar moment of inertia in the case of circular hollow sections only)
$i$	cm	Radius of gyration
$L$	mm	Length
$M$	kg/m	Mass per unit length
$O$	%	Out-of-roundness
$P$	mm	External perimeter of an elliptical hollow section
$R$	mm	External corner radius of a square or rectangular hollow section
$T$	mm	Specified thickness
$U$	mm	Perimeter of an elliptical hollow section at mid-thickness
$V$	mm	Total measured twist
$V_1$	mm	Twist measured at one end of a section
$W_{el}$	cm <sup>3</sup>	Elastic section modulus
$W_{pl}$	cm <sup>3</sup>	Plastic section modulus
$x_1$	mm	Concavity of a side of a square or rectangular hollow section
$x_2$	mm	Convexity of a side of a square or rectangular hollow section
$yy$	—	Axis of cross-section, major axis of a rectangular hollow section
$zz$	—	Axis of cross-section, minor axis of a rectangular hollow section
$\theta$	°	Angle between adjacent sides of a square or rectangular hollow section

**prEN 10210-3:2016 (E)****5 Information to be obtained by the manufacturer****5.1 Mandatory information**

The following mandatory information from this part of prEN 10210 shall be obtained by the manufacturer at the time of enquiry and order:

- a) the dimensions (see Clause 8);
- b) the type of length, length range or length (see Table 3);
- c) for products where the diameter to thickness ration exceeds 100, the agreed tolerance on out-of-roundness.

NOTE This information is included in the list of information to be obtained by the manufacturer contained in prEN 10210-2:2016, Clause 5.

**5.2 Options**

Two options are specified in this part of prEN 10210. In the event that the purchaser does not indicate a wish to implement one of these options at the time of enquiry and order, the manufacturer shall supply in accordance with the basic specification.

Option 3.1 The tolerance on approximate length shall be  $+150_0$  mm (see Table 3).

Option 3.2 Tolerance of external corner radius of 2T maximum at each corner.

**6 Tolerances**

**6.1** Tolerances shall not exceed the values given in Table 2 for shape, straightness and mass, Table 3 for manufacturer's delivered length and Table 4 for the height of the internal and external weld bead of submerged arc welded hollow sections.

**6.2** The internal corners of square and rectangular hollow sections shall be rounded, except in the case of HFW sections for a corner containing the weld, should the weld be located in the corner region..

NOTE The internal corner profile is not specified.



**Table 2 — Tolerances on shape, straightness and mass**

Characteristic	Circular hollow sections	Square rectangular sections and hollow	Elliptical sections hollow
Outside dimensions ( $D$ , $B$ , $H$ )	$\pm 1\%$ with a minimum of $\pm 0,5$ mm and a maximum of $\pm 10$ mm	$\pm 1^a\%$ with a minimum of $\pm 0,5$ mm	
Thickness ( $T$ )	-10 % <sup>b, c</sup>		
Out-of-roundness ( $O$ )	2 % for hollow sections having a diameter to thickness ratio not exceeding 100 <sup>d</sup>	—	
Concavity/Convexity ( $x_1$ , $x_2$ ) <sup>e</sup>	—	1 %	—
Squareness of side ( $\theta$ )	—	$90^\circ \pm 1^\circ$	—
External corner profile ( $C_1$ , $C_2$ or $R$ ) <sup>f</sup>	—	3T maximum at each corner	—
Twist ( $V$ )	—	2 mm <sup>a</sup> plus 0,5 mm/m length <sup>a</sup>	
Straightness ( $e$ )	0,2 <sup>a</sup> % of total length and 3 mm over any 1 m length		
Mass ( $M$ )	-6 %/+8 % on individual delivered lengths		

<sup>a</sup> For elliptical hollow sections of sizes  $H < 250$  mm, the permitted tolerance is twice the value given in this table.

<sup>b</sup> The positive deviation is limited by the tolerance on mass.

<sup>c</sup> For seamless sections thicknesses of less than 10 % but not less than 12,5 % of the nominal thickness may occur in smooth transition areas over not more than 25 % of the circumference.

<sup>d</sup> Where the diameter to thickness ratio exceeds 100, the tolerance on out-of-roundness shall be agreed.

<sup>e</sup> The tolerance on convexity and concavity is independent of the tolerance on outside dimensions.

<sup>f</sup> The sides need not be tangential to the corner arcs.

**Table 3 — Tolerances on manufacturer's delivered length**

Dimensions in millimetres

Type of length <sup>a</sup>	Range of length or length $L$	Tolerance
Random length	$4\ 000 \leq L \leq 16\ 000$ with a range of 2 000 per order item	10 % of sections supplied may be below the minimum for the ordered range but not shorter than 75 % of the minimum range length
Standard length	$4\ 000 \leq L \leq 16\ 000$	$\pm 500$ mm <sup>b</sup>
Exact length	$2\ 000 \leq L \leq 6\ 000$ $6\ 000 < L^c$	$^{+10}_0$ mm $^{+15}_0$ mm

<sup>a</sup> The manufacturer shall establish at the time of enquiry and order the type of length required and the length range or length.

<sup>b</sup> Option 3.1 the tolerance on approximate length is  $^{+150}_0$  mm.

<sup>c</sup> Common lengths available are 6 m and 12 m.

**Table 4 — Tolerance on height of internal and external weld seam for submerged arc welded hollow sections**

Dimensions in millimetres

Thickness, $T$	Maximum weld bead height
$\leq 14,2$	3,5
$> 14,2$	4,8

## prEN 10210-3:2016 (E)

## 7 Measurement of size and shape

### 7.1 General

All external dimensions, including out-of-roundness, shall be measured at a distance from the end of the hollow section of not less than  $D$  for circular sections,  $B$  for square sections or  $H$  for rectangular and elliptical sections, with a minimum of 100 mm.

### 7.2 Outside dimensions

For circular hollow sections the diameter ( $D$ ) and for elliptical hollow sections the outside dimensions ( $B$  and  $H$ ) shall be measured either directly, e.g. using a calliper gauge, or for circular tubes by circumference tape at the discretion of the manufacturer.


The limiting cross-sectional positions for measuring  $B$  and  $H$  for square and rectangular hollow sections are shown in Figure 1.

### 7.3 Thickness

The thickness ( $T$ ) of welded hollow sections shall be measured at a position not less than  $2T$  from the weld.

The limiting cross-sectional positions for measuring the thickness of square and rectangular hollow sections are shown in Figure 1.

NOTE Thickness is normally measured within a distance of half the outside diameter or half the dimension of the longer side from the end of the section.

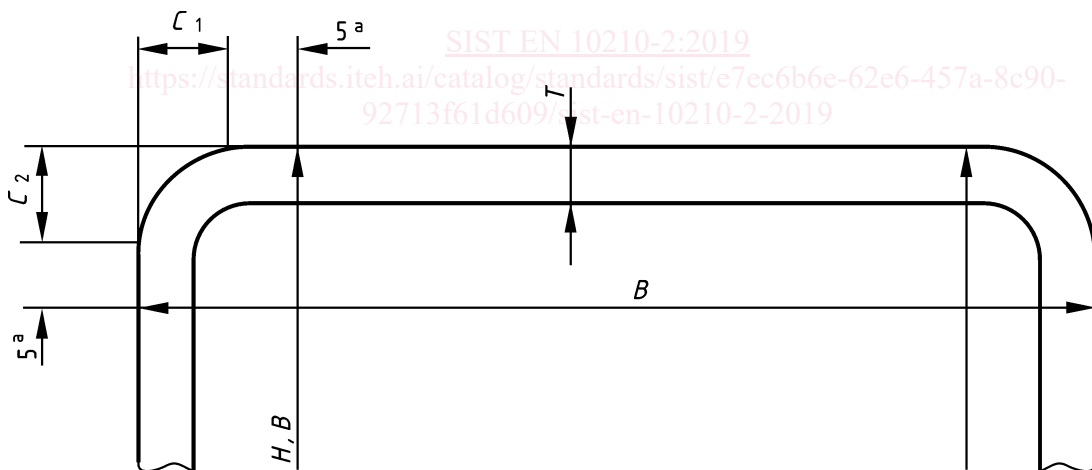

Dimensions in millimetres

<sup>a</sup> This dimension is a maximum when measuring  $B$  or  $H$  and a minimum when measuring  $T$ .

**Figure 1 — Limiting cross-sectional positions for measuring the dimensions  $B$ ,  $H$  and  $T$  for square or rectangular hollow sections**

### 7.4 Out-of-roundness

The out-of-roundness ( $O$ ) of a circular hollow section shall be calculated from the following formula:

$$O(\%) = \frac{D_{\max} - D_{\min}}{D} \times 100$$

### 7.5 Concavity and convexity

The concavity ( $x_1$ ) or the convexity ( $x_2$ ) of the sides of a square or rectangular hollow section shall be measured as shown in Figure 2.

The percentage concavity or convexity shall be calculated as follows:

$$\frac{x_1}{B} \times 100 \% ; \frac{x_2}{B} \times 100 \% ; \frac{x_1}{H} \times 100 \% ; \frac{x_2}{H} \times 100 \%$$

where  $B$  and  $H$  are the dimensions of the sides containing the concavity  $x_1$  or the convexity  $x_2$ .

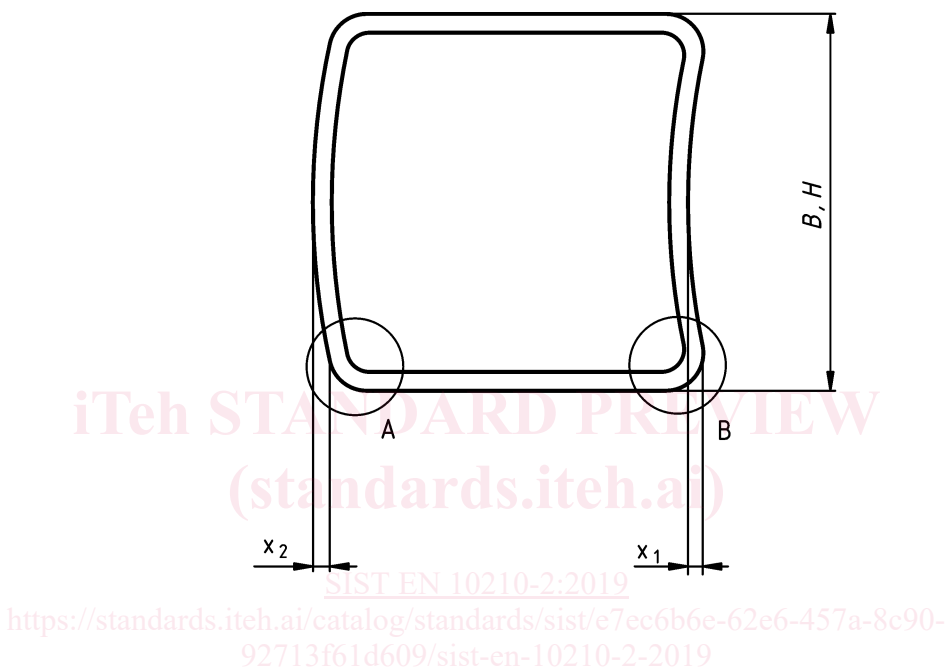


Figure 2 — Measurement of concavity/convexity of square or rectangular hollow sections

## prEN 10210-3:2016 (E)

## 7.6 Squareness of sides

The deviation from squareness of the sides of a square or rectangular hollow section shall be measured as the difference between  $90^\circ$  and  $\theta$  as shown in Figure 3.

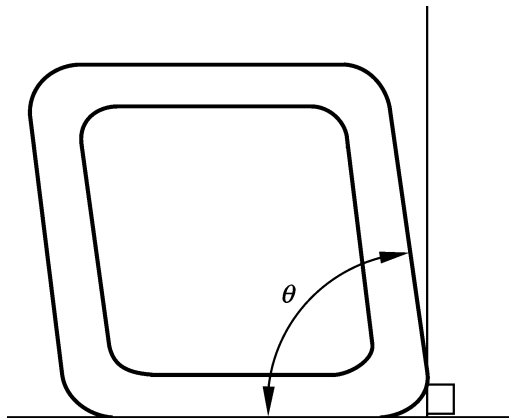


Figure 3 — Squareness of sides of square or rectangular hollow sections

## 7.7 External corner profile

7.7.1 The external corner profile of a square or rectangular hollow section shall be measured according to 7.7.2 or 7.7.3 at the discretion of the manufacturer.

7.7.2 The corner arc shall be measured with a radius gauge.

7.7.3 The distance between the intersection of the flat side and the corner arc and the intersection of the projections of the flat sides to the corner ( $C_1$  and  $C_2$  in Figure 4) shall be measured.

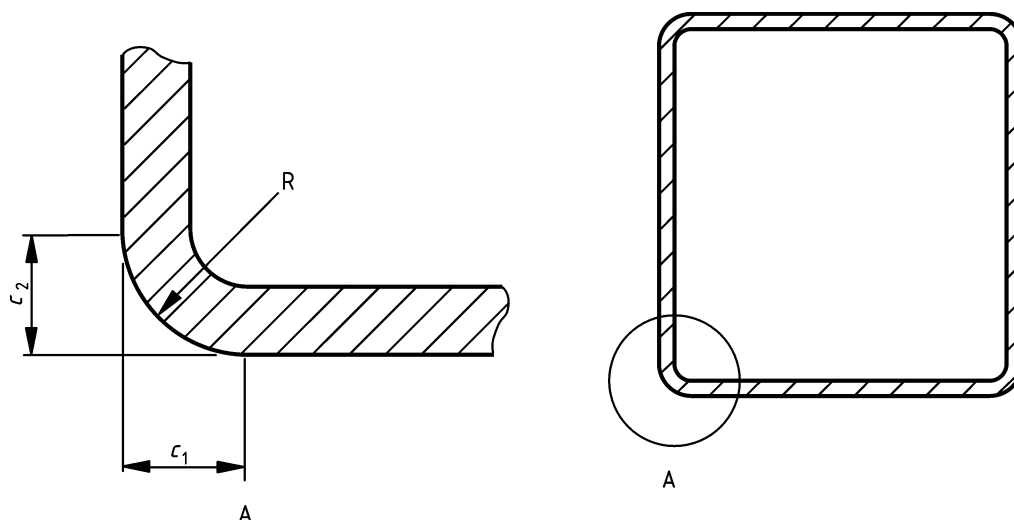


Figure 4 — Outside corner profile of square or rectangular hollow sections

## 7.8 Twist

**7.8.1** The twist ( $V$ ) in a square or rectangular hollow section shall be determined in accordance with 7.8.2 or 7.8.3 at the discretion of the manufacturer. The twist ( $V$ ) in an elliptical hollow section shall be determined in accordance with 7.8.4.

**7.8.2** The hollow section shall be placed on a horizontal surface with one side at one end pressed flat against the surface. At the opposite end of the hollow section, the difference in height of the two lower corners from the horizontal surface (see Figure 5) shall be determined.


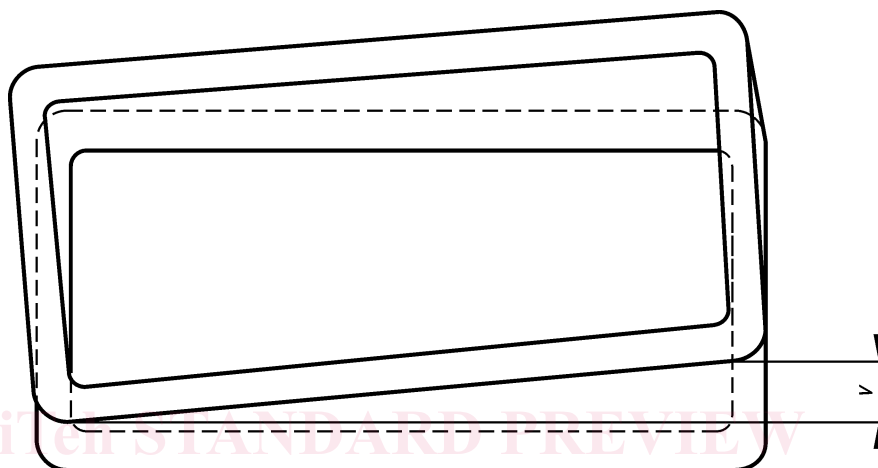


Figure 5 — Twist of square or rectangular hollow sections

**7.8.3** The twist of square and rectangular hollow sections shall be measured with a spirit level and micrometer gauge (screw). The reference length of the spirit level shall be the distance between the intersection of the flat sides and the corner arcs (see Figure 6). The twist  $V$  is the difference between the values  $V_1$  (see Figure 6) measured at each end of the hollow section.

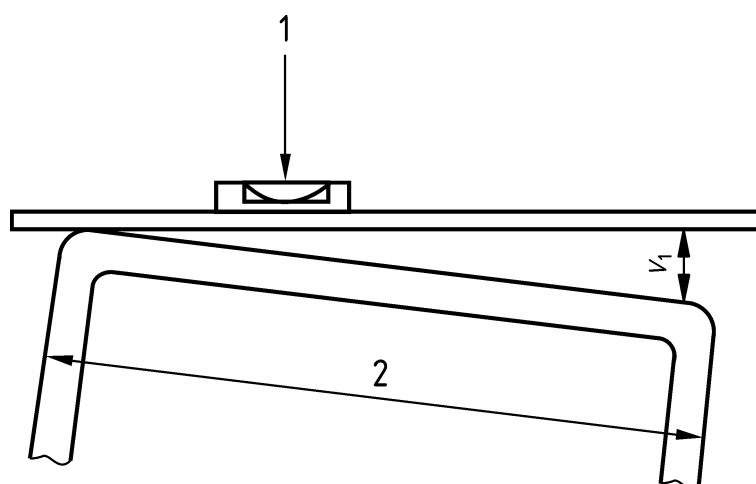

### Key

- 1 spirit level
- 2  $H$  for rectangular sections,  $B$  for square sections

Figure 6 — Measurement of twist of square or rectangular hollow sections