
**Iron ore pellets for blast furnace and
direct reduction feedstocks —
Determination of the crushing strength**

*Boulettes de minerais de fer pour charges de haut fourneaux et
réduction directe — Détermination de la résistance à l'écrasement*

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 4700:2007](#)

<https://standards.iteh.ai/catalog/standards/sist/cc3e24ff-2bd2-44f8-8680-27ccf7ee4037/iso-4700-2007>



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 4700:2007](https://standards.iteh.ai/catalog/standards/sist/cc3e24ff-2bd2-44f8-8680-27ccf7ee4037/iso-4700-2007)

<https://standards.iteh.ai/catalog/standards/sist/cc3e24ff-2bd2-44f8-8680-27ccf7ee4037/iso-4700-2007>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2007

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword.....	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	1
5 Sampling, sample preparation and preparation of test portions	1
6 Apparatus	2
7 Procedure	3
8 Expression of results	4
9 Test report	4
10 Verification	5

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 4700:2007](https://standards.iteh.ai/catalog/standards/sist/cc3e24ff-2bd2-44f8-8680-27ccf7ee4037/iso-4700-2007)

<https://standards.iteh.ai/catalog/standards/sist/cc3e24ff-2bd2-44f8-8680-27ccf7ee4037/iso-4700-2007>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 4700 was prepared by Technical Committee ISO/TC 102, *Iron ore and direct reduced iron*, Subcommittee SC 3, *Physical testing*.

This third edition cancels and replaces the second edition (ISO 4700:1996), which has been revised to homogenise with other physical test standards.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 4700:2007](https://standards.iteh.ai/catalog/standards/sist/cc3e24ff-2bd2-44f8-8680-27ccf7ee4037/iso-4700-2007)
<https://standards.iteh.ai/catalog/standards/sist/cc3e24ff-2bd2-44f8-8680-27ccf7ee4037/iso-4700-2007>

Introduction

This International Standard concerns one of a number of physical test methods that have been developed to measure various physical parameters and to evaluate the behaviour of iron ores, including reducibility, disintegration, crushing strength, apparent density, etc. This method was developed to provide a uniform procedure, validated by collaborative testing, to facilitate comparisons of tests made in different laboratories.

The results of this test should be considered in conjunction with other tests used to evaluate the quality of iron ores as feedstocks for blast furnace and direct reduction processes.

This International Standard may be used to provide test results as part of a production quality-control system, as a basis of a contract, or as part of a research project.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO 4700:2007](https://standards.iteh.ai/catalog/standards/sist/ce3e24ff-2bd2-44f8-8680-27ccf7ee4037/iso-4700-2007)

<https://standards.iteh.ai/catalog/standards/sist/ce3e24ff-2bd2-44f8-8680-27ccf7ee4037/iso-4700-2007>

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 4700:2007

<https://standards.iteh.ai/catalog/standards/sist/ce3e24ff-2bd2-44f8-8680-27ccf7ee4037/iso-4700-2007>

Iron ore pellets for blast furnace and direct reduction feedstocks — Determination of the crushing strength

CAUTION This International Standard may involve hazardous operations and equipment. This standard does not purport to address all of the safety issues associated with its use. It is the responsibility of the user of this International Standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to its use.

1 Scope

This International Standard specifies a method to provide a measure of the compressive load attained to cause breakage of pellets.

This International Standard is applicable to hot bonded pellets.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 3082:2000¹⁾, *Iron ores — Sampling and sample preparation procedures*

ISO 11323:2002, *Iron ore and direct reduced iron — Vocabulary*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 11323 apply.

4 Principle

A single pellet of a specific size range is compressed at a specific speed. The procedure is repeated on all pellets in the test portion. The crushing strength is calculated as the arithmetic mean of all the measurements obtained.

5 Sampling, sample preparation and preparation of test portions

5.1 Sampling and sample preparation

Sampling of a lot and preparation of a test sample shall be in accordance with ISO 3082.

The size range for pellets shall be – 12,5 mm + 10,0 mm.

1) Under revision to incorporate ISO 10836, *Iron ores — Method of sampling and sample preparation for physical testing*.

A test sample of at least 1 kg, on a dry basis, of sized pellets shall be obtained.

Oven-dry the test sample to constant mass at $105\text{ °C} \pm 5\text{ °C}$ and cool it to room temperature before testing.

NOTE Constant mass is achieved when the difference in mass between two subsequent measurements becomes less than 0,05 % of the initial mass of the test sample.

5.2 Preparation of test portions

One test portion comprising at least 60 pellets, as agreed upon at the time of order, shall be taken from the test sample by random selection.

NOTE A method of determining the exact number of pellets to obtain a specific precision in the test results is to use the following equation:

$$n = \left(\frac{2\sigma}{\beta} \right)^2$$

where

n is the number of pellets;

σ is the standard deviation, in newtons, derived from several experiments;

β is the required precision, in newtons, for 95 % confidence levels.

ITEH STANDARD PREVIEW
(standards.iteh.ai)

6 Apparatus

6.1 General

[ISO 4700:2007](https://standards.iteh.ai/catalog/standards/sist/cc3e24ff-2bd2-44f8-8680-27ccf7ee4037/iso-4700-2007)

<https://standards.iteh.ai/catalog/standards/sist/cc3e24ff-2bd2-44f8-8680-27ccf7ee4037/iso-4700-2007>

The test apparatus shall comprise:

- a) ordinary laboratory equipment, such as an oven, hand tools and safety equipment;
- b) loading unit;
- c) load transmission system;
- d) load indicator or recorder.

6.2 Loading unit, formed by two compressive flat platens made of steel, installed in mutual parallel planes. The surface of the platens that will be in contact with the sample shall be made of surface-hardened steel. A device capable of setting the speed of the compressive platen between 10 mm/min and 20 mm/min over the entire test period shall be used.

NOTE If the platen speed is not constant during the test cycle, results may differ depending upon the test machine used. More uniform results may be obtained using a test machine that applies a constant load increase.

6.3 Load transmission system, which shall be either a load cell or a lever. The capacity of the load cell for transmission of the applied load to the indicating unit shall be at least 10 kN.

6.4 Load indicator or recorder, which shall be either an electric indicator (digital read-out device, recording chart, meter with needle rider or other suitable device) for the load-cell type, or a mechanical indicator (gauge equipped with a needle rider or other suitable device) for the lever type. When using a load cell, the chart-recorder pen-response time shall be 1,0 s or less for a full-scale deflection. The minimum graduation shall be 1/100 of the full scale. The compression device shall be calibrated regularly.

7 Procedure

7.1 Number of determinations for the test

Carry out the test on 60 or more single pellets (see the Note in 5.2).


7.2 Load application

Place a test piece (single pellet) at the approximate centre of the surface-hardened portion of the lower platen. Apply the load at a constant platen speed between 10 mm/min and 20 mm/min throughout the test period.

The test is complete when

- either the load falls to a value of 50 % or more of the maximum load recorded (see Figure 1),
- or the platen gap has reduced to 50 % of the initial mean test-piece diameter (see Figure 2).

In either case, the crushing strength is the maximum load attained in the test.

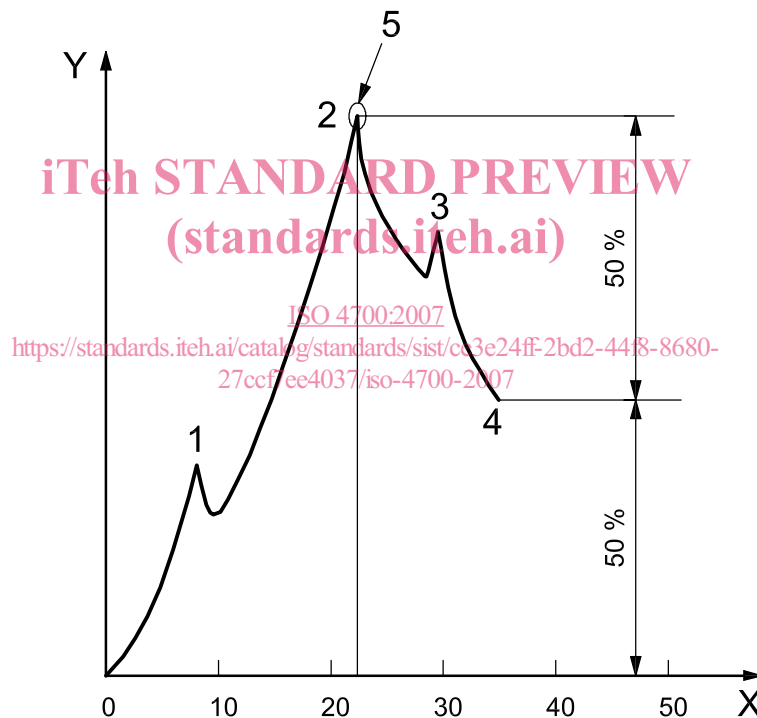

Key

- X contraction, %
- Y load
- 1 1st peak
- 2 2nd peak
- 3 3rd peak
- 4 stop
- 5 strength

Figure 1 — Measurement of crushing strength as explained in Example 1 in the procedure