
**Road vehicles — Wheels — Nut seat
strength tests**

Véhicules routiers — Roues — Essai de résistance des sièges d'écrou

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 15172:2005](https://standards.iteh.ai/catalog/standards/sist/5fdb8d47-37a5-4ef9-a121-82bfdfefbf03/iso-15172-2005)

<https://standards.iteh.ai/catalog/standards/sist/5fdb8d47-37a5-4ef9-a121-82bfdfefbf03/iso-15172-2005>



Reference number
ISO 15172:2005(E)

PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 15172:2005](https://standards.iteh.ai/catalog/standards/sist/5fdb8d47-37a5-4ef9-a121-82bfdfefbf03/iso-15172-2005)

<https://standards.iteh.ai/catalog/standards/sist/5fdb8d47-37a5-4ef9-a121-82bfdfefbf03/iso-15172-2005>

© ISO 2005

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 15172 was prepared by Technical Committee ISO/TC 22, *Road vehicles*, Subcommittee SC 19, *Wheels*.

iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 15172:2005

<https://standards.iteh.ai/catalog/standards/sist/5fdb8d47-37a5-4ef9-a121-82bfdfefbf03/iso-15172-2005>

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 15172:2005

<https://standards.iteh.ai/catalog/standards/sist/5fdb8d47-37a5-4ef9-a121-82bfdfefbf03/iso-15172-2005>

Road vehicles — Wheels — Nut seat strength tests

1 Scope

This International Standard specifies a test method to evaluate the strength of the nut seat of wheels intended for use on passenger cars, light trucks and multi-purpose vehicles. While this test ensures the minimum strength of the nut seat, the wheel must also have a degree of flexibility to allow torque retention. This test evaluates the axial strength of the nut seat. In addition, the informative annex provides recommended bearing area to ensure enough strength for the rotational force in tightening a nut against the nut seat.

2 Test procedures

2.1 General

The principle of this test is to apply an axial load to the nut seat and determine permanent deformation of the nut seat. An additional test to measure yield strength is also specified.


2.2 Wheels for test

Use only fully processed wheels including all coatings representative of production parts intended for the vehicle.

<https://standards.iteh.ai/catalog/standards/sist/5fdb8d47-37a5-4ef9-a121-82bfd1efbf03/iso-15172-2005>

2.3 Test equipment

The test equipment shall be capable of supporting the complete wheel mounting area with a rigid flat surface which is dimensionally representative of the vehicle hub (see Figure 1). The equipment shall provide a hardened (R_c 45 min) punch or load applicator with a shape designed to match the seat face and the fastener contact area representative of that specified for the wheel. The punch or load applicator shall provide a measured, non-rotational axial force of F (the maximum load obtained in the bolt when the nut is tightened to the maximum recommended torque) perpendicular to the plane of the supporting surface. F shall depend on the type of fastener used to fix the wheel on the hub. Only one nut seat of a wheel shall be loaded at a time. In addition to the loading mechanism, devices to measure nut seat deformation or punch travel shall be required.

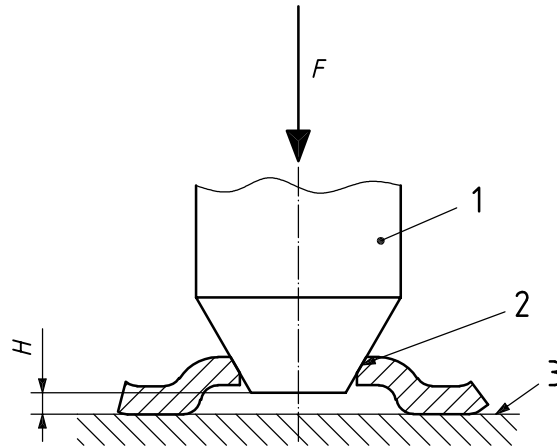

Key

- F measured axial force
- H nut seat height
- 1 hardened punch
- 2 nut/bolt seat
- 3 supporting surface

Figure 1 — Test nomenclature and loading fixture

iTech STANDARD PREVIEW
(standards.iteh.ai)

2.4 Strength test procedures

2.4.1 Deformation test method

The deformation test shall be carried out as follows: <http://standards.iteh.ai/catalog/standards/sist/5fdb8d47-37a5-4ef9-a121-82bfdfefbf03/iso-15172-2005>

- a) Insert the test wheel in the loading device and align the punch with the nut seat.
- b) Apply the load F_0 ($0,6 \times F$) to the nut seat and measure the nut seat height (H_0).
- c) Apply a load (F) and hold for 15 s.
- d) Reduce the load to F_0 and measure the nut seat height (H_1).
- e) Repeat steps c) and d) five times and measure the nut seat height (H_n) at F_0 load each time.
- f) Repeat steps a) through e) on each nut seat of the wheel. The entire procedure is repeated on additional wheels if necessary.

Performance requirements shall be as follows:

- a) The nut seat shall not have newly formed cracks.
- b) The nut seat height change ($H_1 - H_0$) after the first cycle shall not exceed 0,6 mm.
- c) The fifth nut seat height change ($H_5 - H_0$) shall not exceed 0,80 mm.


2.4.2 Yield strength test method

Insert a new test wheel on the loading device and align the load applicator with the nut seat. Apply the load to the individual nut boss until complete collapse. Record the maximum load prior to collapse. Test each nut seat, but do not perform tests on adjacent nut bosses. Therefore, two or more new wheels shall be required to completely evaluate the wheel.

Annex A (informative)

Bearing surface recommendation

The repeatability of the yield strength test and deformation test is optimum when the following criteria is met or exceeded. This recommendation uses the applied stresses to predict yielding at a critical value given by the maximum shear stress (Tresca) criterion. At the critical value, the sum of the applied stresses from the stud tension and nut torque equal the yield point of the nut seat material. The applied stresses are a conservative approximation for the principal stresses. It is important to note that stud tension creates a compressive stress on the nut seat.

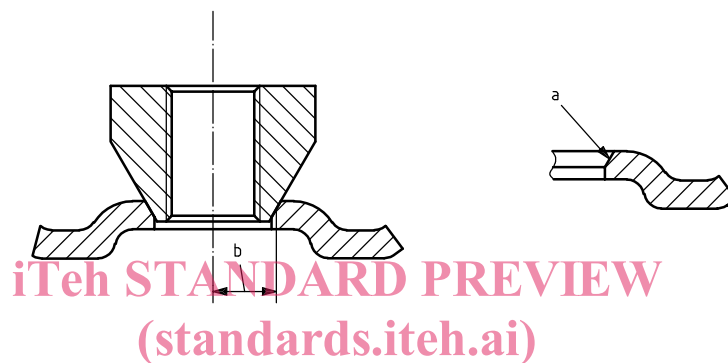

- a Bearing surface.
b Mean radius.

ISO 15172:2005
<https://standards.iteh.ai/catalog/standards/sist/56fb8d47-37a5-4a99-a121-82bdfefbf03/iso-15172-2005>
Figure A.1 — Nomenclature for mean radius and bearing area

The tables below give example values of B_s for typical assumed properties. Use the following formula to calculate bearing surface areas for wheels made from materials with other properties:

$$B_s = [T_s + (T_q/R)]/Y$$

where

- B_s is the bearing surface;
 T_s is the stud tension;
 T_q is the applied torque;
 R is the mean radius of nut seat;
 Y is the yield strength of the material.

Table A.1 — Calculated steel wheel minimum bearing surface using stress differentials (sq. mm)

Stud Tension (N)	Applied Torque (Nm)							
	90	100	110	120	130	140	150	160
12 000	92,7	97,5	102,3	107,0	111,8	116,6	121,3	126,1
16 000	109,3	114,1	118,9	123,6	128,4	133,2	137,9	142,7
20 000	125,9	130,7	135,5	140,2	145,0	149,8	154,5	159,3
24 000	142,5	147,3	152,0	156,8	161,6	166,4	171,1	175,9
28 000	159,1	163,9	168,6	173,4	178,2	183,0	187,7	192,5

This calculation assumes a minimum yield of 241 Mpa and a mean nut seat diameter of 17,4 mm to represent typical low carbon steels.

Table A.2 — Calculated aluminum wheel minimum bearing surface using stress differentials (sq. mm)

Stud Tension (N)	Applied Torques (Nm)							
	90	100	110	120	130	140	150	160
12 000	185,0	194,1	203,2	212,3	221,4	230,5	239,6	248,7
16 000	219,3	228,4	237,5	246,6	255,7	264,8	273,9	283,1
20 000	253,6	262,7	271,9	281,0	290,1	299,2	308,3	317,4
24 000	288,0	297,1	306,2	315,3	324,4	333,5	342,6	351,7
28 000	322,3	331,4	340,5	349,6	358,7	367,8	377,0	386,1

This calculation assumes a minimum yield of 116,5 Mpa and a mean nut seat diameter of 18,85 mm to represent typical aluminum wheels.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 15172:2005

<https://standards.iteh.ai/catalog/standards/sist/5fdb8d47-37a5-4ef9-a121-82bfdfefbf03/iso-15172-2005>