

---

---

**Laminated veneer lumber (LVL) —  
Specifications**

*Lamibois (LVL) — Spécifications*

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[ISO 18776:2008](https://standards.iteh.ai/catalog/standards/sist/3084c5d7-34d9-4803-93e0-f214994fe4b/iso-18776-2008)

<https://standards.iteh.ai/catalog/standards/sist/3084c5d7-34d9-4803-93e0-f214994fe4b/iso-18776-2008>



**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO 18776:2008

<https://standards.iteh.ai/catalog/standards/sist/3084c5d7-34d9-4803-93e0-f214994fe4b/iso-18776-2008>



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2008

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

Page

Foreword.....	iv
<b>1</b> <b>Scope</b> .....	<b>1</b>
<b>2</b> <b>Conformance</b> .....	<b>1</b>
<b>2.1</b> <b>Quality system requirements</b> .....	<b>1</b>
<b>2.2</b> <b>Manufacturing specifications</b> .....	<b>1</b>
<b>3</b> <b>Normative references</b> .....	<b>2</b>
<b>4</b> <b>Terms and definitions</b> .....	<b>2</b>
<b>5</b> <b>Materials</b> .....	<b>3</b>
<b>5.1</b> <b>Veneer</b> .....	<b>3</b>
<b>5.1.1</b> <b>General</b> .....	<b>3</b>
<b>5.1.2</b> <b>Species</b> .....	<b>3</b>
<b>5.1.3</b> <b>Thickness</b> .....	<b>3</b>
<b>5.1.4</b> <b>Quality</b> .....	<b>3</b>
<b>5.1.5</b> <b>Jointing</b> .....	<b>4</b>
<b>5.2</b> <b>Adhesives</b> .....	<b>4</b>
<b>6</b> <b>Bonding quality</b> .....	<b>4</b>
<b>7</b> <b>Lay-up (arrangement of veneers)</b> .....	<b>4</b>
<b>8</b> <b>Dimensions, shape and tolerances</b> .....	<b>4</b>
<b>8.1</b> <b>Dimensions</b> .....	<b>4</b>
<b>8.2</b> <b>Shape</b> .....	<b>5</b>
<b>8.3</b> <b>Tolerances</b> .....	<b>5</b>
<b>8.3.1</b> <b>Dimensions</b> .....	<b>5</b>
<b>8.3.2</b> <b>Shape</b> .....	<b>6</b>
<b>9</b> <b>Determination of properties</b> .....	<b>6</b>
<b>9.1</b> <b>Physical properties</b> .....	<b>6</b>
<b>9.2</b> <b>Mechanical properties</b> .....	<b>6</b>
<b>9.2.1</b> <b>General</b> .....	<b>6</b>
<b>9.2.2</b> <b>Structural applications</b> .....	<b>6</b>
<b>9.3</b> <b>Supplementary properties</b> .....	<b>6</b>
<b>10</b> <b>Preservative and chemical treatments</b> .....	<b>7</b>
<b>10.1</b> <b>Natural or conferred biological durability</b> .....	<b>7</b>
<b>10.2</b> <b>Effect of chemical treatments</b> .....	<b>7</b>
<b>11</b> <b>Formaldehyde release</b> .....	<b>7</b>
<b>12</b> <b>Marking (identification)</b> .....	<b>7</b>
<b>Annex A</b> (normative) <b>Veneer quality</b> .....	<b>9</b>
<b>Annex B</b> (normative) <b>Panel construction (Veneer arrangement)</b> .....	<b>10</b>
<b>Annex C</b> (informative) <b>Properties to be determined depending on end use</b> .....	<b>11</b>
<b>Annex D</b> (informative) <b>Supplementary properties</b> .....	<b>12</b>
<b>Bibliography</b> .....	<b>13</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 18776 was prepared by Technical Committee ISO/TC 89, *Wood-based panels*, Subcommittee SC 3, *Plywood*.

## iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 18776:2008

<https://standards.iteh.ai/catalog/standards/sist/3084c5d7-34d9-4803-93e0-f214994fe4b/iso-18776-2008>

# Laminated veneer lumber (LVL) — Specifications

## 1 Scope

This International Standard specifies the requirements for Laminated Veneer Lumber (LVL) for general purposes and structural applications, in dry, tropical-dry/humid or high humidity/exterior conditions. Laminated Veneer Lumber (LVL) is a general description for an assembly of veneers laminated with an adhesive in which the grain direction of the outer veneers and most other veneers is in the longitudinal direction.

This International Standard specifies requirements for

- the quality of veneers,
- bond durability,
- tolerances on dimensions, and
- structural characterization.

Characteristic values, to be used for design purposes, are based on testing and evaluation of laminated veneer lumber.

ISO 18776:2008

<https://standards.iteh.ai/catalog/standards/sist/3084c5d7-34d9-4803-93e0-f214994fe4b/iso-18776-2008>

## 2 Conformance

### 2.1 Quality system requirements

Products conforming to this International Standard shall be manufactured to a formalised manufacturing specification covering all relevant process variables under a quality system which includes

- in-plant process quality control and internal auditing procedures, and
- external auditing of plant process control and end-product quality.

The system shall be consistent with the requirements of ISO/IEC Guide 65.

### 2.2 Manufacturing specifications

The manufacturing specifications shall set the limits on all variables that affect or correlate with final product properties, including

- a) materials (see Clause 5),
- b) bonding quality (see Clause 6),
- c) lay-up (construction) (see Clause 7),
- d) manufacturing process, and
- e) secondary processes and treatment (see, for example, Clause 10).

NOTE The above list is not necessarily exhaustive.

### 3 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO/IEC Guide 65, *General requirements for bodies operating product certification systems*

ISO 2074, *Plywood — Vocabulary*

ISO 9427, *Wood-based panels — Determination of density*

ISO 12460-1, *Wood-based panels — Determination of formaldehyde release — Part 1: Formaldehyde emission by the 1-cubic-metre chamber method*

ISO 12460-2, *Wood-based panels — Determination of formaldehyde release — Part 2: Small-scale chamber method*

ISO 12460-3, *Wood-based panels — Determination of formaldehyde release — Part 3: Gas analysis method*

ISO 12460-4, *Wood-based panels — Determination of formaldehyde release — Part 4: Dessicator method*

ISO 12466-1, *Plywood — Bonding quality — Part 1: Test methods*

ISO 12466-2, *Plywood — Bonding quality — Part 2: Requirements*

ISO 16978, *Wood-based panels — Determination of modulus of elasticity in bending and of bending strength*

ISO 16979, *Wood-based panels — Determination of moisture content*

ISO 21887, *Durability of wood and wood-based products — Use classes*

ISO 27567, *Laminated veneer lumber — Measurement of dimensions and shape — Method of test*

### 4 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 2074 and the following apply.

#### 4.1

#### **laminated veneer lumber**

#### **LVL**

product made of an assembly of veneers, laminated with an adhesive, in which the grain direction of the outer veneers and most other veneers are parallel and run in the longitudinal direction

#### 4.2

#### **dry conditions**

conditions in which the LVL attains an equilibrium moisture content not exceeding 12 % except for only a few weeks per year (e.g. ambient temperature of 20 °C and relative humidity of 65 %)

NOTE 1 LVL, suitable for use in these conditions, is considered as suitable for use in biological-use class 1 of ISO 21887.

NOTE 2 LVL, under these conditions, is appropriate for dry internal applications, excluding any extended direct exposure to water.

**4.3****tropical-dry/humid conditions**

conditions in which the LVL attains an equilibrium moisture content not exceeding 18 %, except for only a few weeks per year (e.g. ambient temperature of 30 °C and relative humidity of 85 %)

NOTE 1 LVL, suitable for use in these conditions, is considered as suitable for use in biological-use class 1 and class 2 of ISO 21887.

NOTE 2 LVL, under these conditions, is appropriate for protected external applications (e.g. behind cladding or under roof coverings), but is also capable of resisting weather exposure for short periods (e.g. when exposed during the construction). It is also suitable for interior situations where the service moisture condition is raised above the humidity of dry conditions.

**4.4****high humidity/exterior conditions**

conditions leading to higher equilibrium moisture content than in tropical-dry/humid conditions or prolonged exposure to weather

NOTE LVL, suitable for use in these conditions, is considered as suitable for use in biological-use class 1, 2 and 3 of ISO 21887.

**4.5****structural use**

load-bearing application for which predictable and reliable material structural-design properties are required

**5 Materials**

**iTeh STANDARD PREVIEW**  
(standards.iteh.ai)

The following characteristics shall form part of the manufacturing specifications:

**5.1 Veneer**

[ISO 18776:2008  
https://standards.iteh.ai/catalog/standards/sist/3084c5d7-34d9-4803-93e0-f214994fe4b/iso-18776-2008](https://standards.iteh.ai/catalog/standards/sist/3084c5d7-34d9-4803-93e0-f214994fe4b/iso-18776-2008)

**5.1.1 General**

The following requirements apply at the time of pressing:

The species, species group, mechanical property group or predictor shall be identified.

NOTE The notional veneer stiffnesses obtained via calibrated electronic or other techniques, such as sound waves, are considered as acceptable predictors.

In LVL for structural use, the position of veneers in the assembly/construction shall be identified (see Annex B).

**5.1.2 Species**

Any wood species is permitted.

**5.1.3 Thickness**

Unless otherwise stated, veneer thickness shall be a maximum of 6,0 mm.

Other thicknesses are permitted, provided they meet the structural and serviceability requirements for the intended application.

**5.1.4 Quality**

The minimum quality (grade) of each face, back and inner ply shall be specified in accordance with Annex A.

### 5.1.5 Jointing

Edge joints parallel to the grain are permitted, either glued or unglued.

End joints shall be defined in the manufacturing specification in regard to the type of joint (i.e. scarfed, crushed, butt or other) and the geometrical distribution and frequency of joints.

### 5.2 Adhesives

The adhesive, in combination with the veneers used, shall provide a bond of the strength, durability and integrity necessary to meet the requirements for the bond type as specified in Clause 6.

## 6 Bonding quality

The bonding quality shall be established in accordance with ISO 12466-1 (Chisel test) and ISO 12466-2.

NOTE Awaiting a new document, specifically for LVL (ISO/AWI 10033).

## 7 Lay-up (arrangement of veneers)

The lay-up (arrangement) of veneers within the LVL construction, including the type and frequency of end joints, shall be specified in accordance with Annex B.

iTeh STANDARD PREVIEW  
(standards.iteh.ai)

## 8 Dimensions, shape and tolerances

Unless stated otherwise by the contract, dimensions and tolerances apply at a moisture content of  $(10 \pm 4) \%$ .

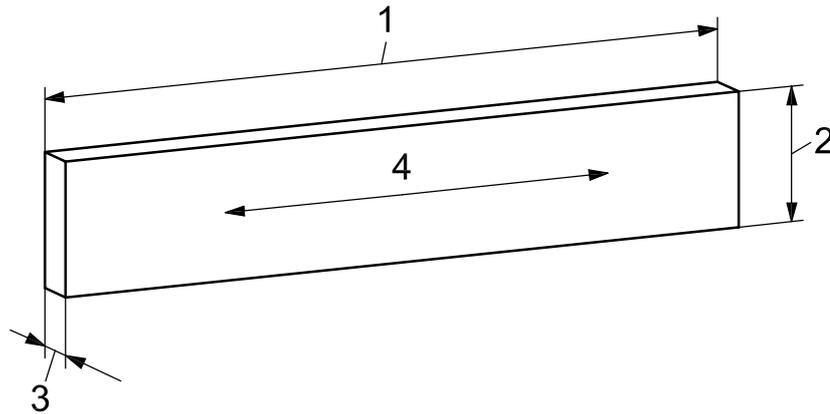
<https://standards.iteh.ai/catalog/standards/sist/3084c5d7-34d9-4803-93e0->

The moisture content shall be measured in accordance with ISO 16979.

### 8.1 Dimensions

Length, width and thickness, measured in accordance with ISO 27567, shall be specified, where:

- length is defined as the dimension in the direction along the grain of the majority of veneers in the LVL;
- width is defined as the dimension in the plane of the LVL normal to the length;
- thickness is defined as the dimension, through the LVL, normal to the length and width.

**Key**

- 1 length
- 2 width
- 3 thickness
- 4 major grain direction

**Figure 1 — Dimensions of LVL****8.2 Shape**

Requirements for twist, spring, bow, squareness of section and cupping shall be specified.

Twist, spring, bow, squareness of section and cupping are defined in ISO 27567.

**8.3 Tolerances**

ISO 18776:2008

[https://standards.iteh.ai/catalog/standards/sist/3084c5d7-34d9-4803-93e0-](https://standards.iteh.ai/catalog/standards/sist/3084c5d7-34d9-4803-93e0-4214994634b/iso-18776-2008)

[4214994634b/iso-18776-2008](https://standards.iteh.ai/catalog/standards/sist/3084c5d7-34d9-4803-93e0-4214994634b/iso-18776-2008)

Unless otherwise stated by the contract, the dimensions of LVL measured in accordance with ISO 27567 shall not differ from specified/declared dimensions, by more than the tolerances given in 8.3.1 and 8.3.2.

**8.3.1 Dimensions**

Tolerances on dimensions are given in Table 1:

**Table 1 — Tolerances on dimensions**

Dimension	Tolerances
Thickness ( $t$ )	$\pm 5\%$
Width ( $b$ ) —	$\pm 1\%$
Length ( $L$ )	$\begin{matrix} +2 \\ 0 \end{matrix}\%$