
**Plastics — Use of polyethylene reference
specimens (PERS) for monitoring
laboratory and outdoor weathering
conditions**

*Plastiques — Utilisation d'éprouvettes de référence en polyéthylène
pour l'évaluation des conditions de vieillissement climatique*

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO/TR 19032:2006

<https://standards.iteh.ai/catalog/standards/sist/3fce304f-9a42-4977-9a30-84ec2c37b4df/iso-tr-19032-2006>



Reference number
ISO/TR 19032:2006(E)

PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO/TR 19032:2006

<https://standards.iteh.ai/catalog/standards/sist/3f9e304f-9a42-4977-9a30-84ec2c37b4df/iso-tr-19032-2006>

© ISO 2006

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword.....	iv
Introduction	v
1 Scope	1
2 Background information	1
3 Material	1
3.1 Preparation of PERS.....	1
4 Procedure	2
4.1 Method for measuring the carbonyl index of PERS.....	2
4.2 Round Robin Test of laboratory light-source exposure devices with PERS	3
4.2.1 Xenon-arc-lamp exposure.....	3
4.2.2 Open-flame carbon-arc-lamp exposure.....	3
4.2.3 Fluorescence lamp exposure	4
4.3 Outdoor exposure test of PERS	4
4.4 Consistency of laboratory light-source exposure devices	5
5 Results and discussion.....	6
5.1 Result of RRT of laboratory light-source exposure devices with PERS.....	6
5.1.1 Xenon-arc-lamp exposure.....	6
5.1.2 Open-flame carbon-arc-lamp exposure.....	10
5.1.3 Fluorescent lamp exposure	10
5.2 Characterizing the conditions of outdoor exposure test site	11
5.3 Examples of correlation between outdoor exposure test and laboratory light-source exposure test using PERS	12
5.4 Control limit of particular laboratory light-source exposure apparatus	13
6 Conclusion	14
6.1 Results of RRT	14
6.2 Outdoor exposure of PERS	15
6.3 Correlation between outdoor and xenon-arc-lamp exposure for PERS	15
6.4 Consistency of laboratory light-source exposure devices	15
Bibliography	16

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

In exceptional circumstances, when a technical committee has collected data of a different kind from that which is normally published as an International Standard ("state of the art", for example), it may decide by a simple majority vote of its participating members to publish a Technical Report. A Technical Report is entirely informative in nature and does not have to be reviewed until the data it provides are considered to be no longer valid or useful.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO/TR 19032 was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 6, *Ageing, chemical and environmental resistance*.

<https://standards.iteh.ai/catalog/standards/sist/3f9e304f-9a42-4977-9a30-84ec2c37b4df/iso-tr-19032-2006>

Introduction

The method described in this Technical Report demonstrates the use of polyethylene reference specimens (hereafter called PERS) for monitoring conditions in weathering tests used for plastics. The PERS has double bonds in its molecular structure, which are easily oxidized to produce carbonyl groups. The change in carbonyl index of PERS is produced by the combined effects of ultraviolet (UV) and temperature. Therefore, the carbonyl groups proportionally increase, depending on the received UV and temperature. Based on this relationship, the effect of UV radiation and temperature on PERS can be expressed quantitatively. For laboratory-accelerated exposures, PERS is also sensitive to changes in the chamber air temperature. The effect of moisture was not determined in the study.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO/TR 19032:2006](https://standards.iteh.ai/catalog/standards/sist/3f9e304f-9a42-4977-9a30-84ec2c37b4df/iso-tr-19032-2006)

<https://standards.iteh.ai/catalog/standards/sist/3f9e304f-9a42-4977-9a30-84ec2c37b4df/iso-tr-19032-2006>

iTeh STANDARD PREVIEW **(standards.iteh.ai)**

ISO/TR 19032:2006

<https://standards.iteh.ai/catalog/standards/sist/3fce304f-9a42-4977-9a30-84ec2c37b4df/iso-tr-19032-2006>

Plastics — Use of polyethylene reference specimens (PERS) for monitoring laboratory and outdoor weathering conditions

1 Scope

This Technical Report describes a method that demonstrates the use of polyethylene reference specimens (PERS) for monitoring laboratory and outdoor conditions in weathering tests used for plastics.

2 Background information

Degradation of plastics in an outdoor environment is mainly influenced by the ultraviolet radiation received, environmental temperature, moisture, etc. Especially in photo-oxidation induced from ultraviolet radiation, temperature plays a very important role. Measuring the ultraviolet radiation during the exposure period is useful for comparison of the result of the exposure test, but it is not enough to compare the exposure results. Therefore, it is very important to find some index that can be used to evaluate the complex effect of received ultraviolet radiation and environmental temperature. The PERS is used to characterize the level of combined effect of ultraviolet radiation and temperature, and its characteristic proportionally increases depending on the UV radiation and temperature received.

3 Material

ISO/TR 19032:2006

<https://standards.iteh.ai/catalog/standards/sist/3fce304f-9a42-4977-9a30-8c2c3784d18c/iso-tr-19032-2006>

PERS is high-density polyethylene polymerized using molybdenum dioxide as a catalyst, containing the trans-form vinylene group. Other basic properties are as follows:

- absorbance ratio of trans-form vinylene group to methylene group: 1,0 to 1,3;
- melt flow rate (2,16 kg, 190 °C): 0,2 to 0,4 g/10 min;
- density: 950 to 965 kg/m³;
- thickness: (0,2 ± 0,02) mm.

3.1 Preparation of PERS

After kneading for 5 min the material between two rolls whose surfaces are heated at 150 °C to 170 °C, cut into small pieces of 0,4 g to 0,5 g.

After pre-heating for 90 s in a compression moulding machine whose surface is heated at 160 °C to 180 °C, compress the material for 60 s, cool in a compression moulding machine whose surface temperature is 30 °C to 40 °C, for 60 s, and prepare the press sheet of the thickness mentioned above.

NOTE PERS can be obtained from the following organization:

Japan Weathering Test Center
1-3-7 Shibakoen Minatoku Tokyo Japan

4 Procedure

4.1 Method for measuring the carbonyl index of PERS

An infrared (IR) spectrophotometer should be used as the measuring apparatus.

Measure the infrared absorption spectra after irradiation, in the range of $2\,200\text{ cm}^{-1}$ to $1\,600\text{ cm}^{-1}$. In this case, use for the scanning speed the same method as for a quantitative analysis.

The carbonyl index is determined in accordance with the following equation, based upon infrared absorbance spectra of exposed PERS. Absorbance at near $2\,020\text{ cm}^{-1}$ peak is employed as an internal standard to correct for sample film thickness, while absorbance at near $1\,715\text{ cm}^{-1}$ peak is used to indicate carbonyl group content. A typical diagram of IR absorbance is shown in Figure 1.

$$A_r = \frac{A_{1\,715}}{A_{2\,020}}$$

where

A_r is the absorbance ratio (carbonyl index);


$A_{1\,715}$ is the absorbance at near $1\,715\text{ cm}^{-1}$ ($I - I_0$);

$A_{2\,020}$ is the absorbance at near $2\,020\text{ cm}^{-1}$ ($I - I_0$);

I_0 is the absorbance measured by the base-line method at individual wave number;

I is the absorbance at the peak of individual wave number.

ISO/TR 19032:2006
<https://standards.iteh.ai/catalog/standards/sist/3fce304f-9a42-4977-9a30-84ec2c37b4df/iso-tr-19032-2006>

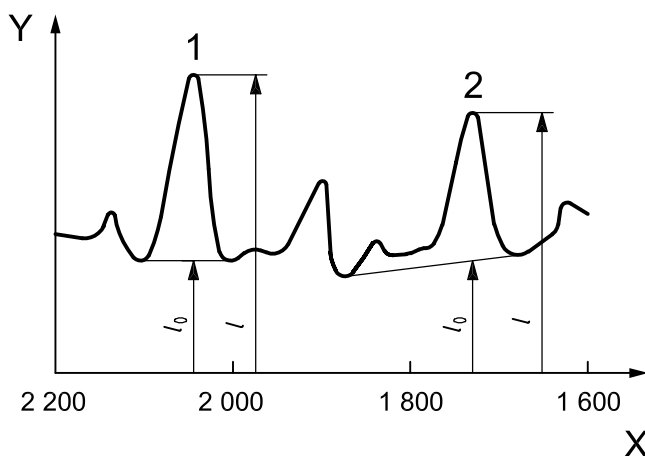

Key

Y absorbance

X wavenumber (cm^{-1})

1 peak near $2\,020\text{ cm}^{-1}$

2 peak near $1\,715\text{ cm}^{-1}$

Figure 1 — IR absorbance diagram showing base line and peak absorbance

4.2 Round Robin Test of laboratory light-source exposure devices with PERS

It is well known that the degradation of plastics materials or products used outdoors will occur by the combined effect of ultraviolet radiation and temperature, or other factors. It is also recognized that the reproducibility in the laboratory light-source exposure test will vary with the change in ultraviolet spectrum distributions and the chamber temperatures caused by deterioration of lamps and filters with operating time, even if ultraviolet radiation and black standard temperature (BST) or black panel temperature (BPT) are under constant conditions.

Since the PERS can quantitatively evaluate, as carbonyl index, the combined effect of UV radiation and temperature, the carbonyl index obtained can reflect changes in a given environment.

In order to verify the repeatability and reproducibility of the specimens and exposure test, the Round Robin Test (hereafter called RRT) using the PERS by laboratory light-source exposure devices in ISO/TC 61/SC 6/WG 2 was conducted.

4.2.1 Xenon-arc-lamp exposure

The test conditions were according to ISO 4892-2^[1]. The conditions are shown in Table 1. It was not requested to control the chamber temperature, but participants were requested to report this temperature.

Each participant was provided with 4 sets of PERS that were mounted in 150 mm × 70 mm plastics holders. One set of holders consists of 3 pieces of PERS.

Table 1 — Exposure conditions for xenon-arc lamp

Filter	daylight filter
Irradiance	0,5 W/(m ² ·nm) at 340 nm or 60 W/m ² (300 to 400 nm)
BST or BPT	(65 ± 3) °C for BST or (63 ± 3) °C for BPT
Chamber temperature	Arbitrary
Water spray	102 min of light only followed by 18 min of light plus water spray
Humidity	(50 ± 5) %
Period	24 h, 48 h, 72 h and 96 h

4.2.2 Open-flame carbon-arc-lamp exposure

The test conditions were according to ISO 4892-4^[2]. The conditions are shown in Table 2. The chamber temperature was not specified, but participants were requested to report this temperature.

Each participant was provided with 4 sets of PERS that were mounted in 150 mm × 70 mm plastics holders. One set of holders consists of 3 pieces of PERS.

Table 2 — Exposure conditions for open-flame carbon-arc lamp

Filter	Type 1 (Type 1 known as Corex 7058 filter)
BST or BPT	(65 ± 3) °C for BST or (63 ± 3) °C for BPT
Chamber temperature	Arbitrary
Water spray	102 min light only followed by 18 min of light plus water spray
Humidity	(50 ± 5) %
Period	24 h, 48 h, 72 h and 96 h

4.2.3 Fluorescence lamp exposure

The test conditions were according to ISO 4892-3 [3]. The conditions are shown in Table 3. Irradiance was not specified at any intensity.

Each participant was provided with 4 sets of PERS that were mounted in 150 mm × 70 mm plastics holders. One set of holders consists of 3 pieces of PERS.

Table 3 — Exposure conditions for fluorescent lamp

Lamp type	UVA340
Irradiance	Arbitrary
Mode	Mode 1: 4 h of dry UV exposure followed by 4 h of condensation
BPT	(63 ± 3) °C at UV exposure and (50 ± 3) °C at condensation
Period	8 h, 24 h, 32 h and 48 h

After each sample had been exposed for each exposure period, the carbonyl index was determined, based upon the method described in 4.1.

4.3 Outdoor exposure test of PERS

The result of the outdoor exposure test varies, even if it is conducted in the same place, because of differences due the seasonal climate changes. Although it is useful to measure the amount of ultraviolet radiation for comparison of exposure tests, it is not enough in the comparison only to consider the amount of ultraviolet radiation, because plastics are influenced not only by ultraviolet radiation but by temperature or by moisture. Since PERS is influenced by the combined effect of ultraviolet radiation and temperature, PERS were exposed in various places where the climate was different.

Six locations in different climates and different countries were selected: Sapporo, Choshi, Miyakojima (Japan), Serpong, Bandung (Indonesia) and Phoenix (USA). Locations and exposure angles are shown in Table 4.

Table 4 — Locations and exposure angles

Exposure site	Exposure angle	Latitude
Sapporo (Japan)	45° South	43° 03' N
Choshi (Japan)	30° South	35° 43' N
Miyakojima (Japan)	20° South	24° 44' N
Serpong (Indonesia)	5° ^a South and north	6° 15' S
Phoenix (USA)	34° South	33° 54' N
^a From November to February, the samples face south; and from March to October, they face north.		

The conditions of the outdoor exposure test are based on ISO 877 [4]. Three pieces of PERS were exposed for 1 month. By replacing exposed PERS with new ones, the exposure test was repeated in the following months successively. The exposure test was repeated successively for more than 24 months.

The practical procedure of the outdoor exposure test is shown below.

- 1) The conditions of the outdoor exposure test are based on ISO 877.
- 2) Prepare a minimum of three PERS and expose them for 1 month. It is desirable to expose them at the beginning of a calendar month, in order to evaluate the condition of the month.
- 3) By replacing exposed PERSs with new ones, the exposure test is repeated in the following months successively.
- 4) The exposure test is repeated successively for at least 12 months.
- 5) The accumulated value of the carbonyl index for each month will be adopted for the index of combined effect of UV radiation and temperature at the site of exposure.

4.4 Consistency of laboratory light-source exposure devices

It is recognized that changes in the characteristics of lamps and filters with time, and changes in the chamber temperature of laboratory light-source exposure devices, influence the reproducibility and repeatability of test results, even if the test is operated under constant conditions of ultraviolet radiation and BST or BPT.

Since the carbonyl index of a polyethylene reference specimen is proportional to the environment where ultraviolet radiation and temperature are compounded, consistency of the exposure environment could be monitored with this reference material.

In order to verify the correct operation of a particular xenon-arc-lamp device, the control limit was determined by PERS.

<https://standards.iteh.ai/catalog/standards/sist/3f9e304f-9a42-4977-9a30-84ec2c37b4df/iso-tr-19032-2006>

The test conditions were according to ISO 4892-2. For different operating times of lamp and filters, exposure was repeated three times.

The practical procedure was carried out as follows.

- 1) The conditions of the laboratory light-source exposure test are based on ISO 4892.
- 2) PERS should be irradiated for about 100 h. The number of PERSs should not be less than three.
- 3) Carbonyl indices are measured after removal from exposure.
- 4) Repeat 1) to 3), at three different times.
- 5) Calculate the standard deviation “S” of each exposure.
- 6) Calculate the repeatability standard deviation “S_r”.

$$S_r = \sqrt{\frac{\sum S^2}{3}}$$

- 7) Calculate the control limit “CL” of this apparatus.

$$CL = \text{total average value} \pm (2 \times S_r)$$