

---

---

**Adhesives — Determination of  
temperature dependence of shear  
strength**

*Adhésifs — Détermination de la résistance au cisaillement en fonction  
de la température*

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[ISO 19212:2006](https://standards.iteh.ai/catalog/standards/sist/33efdf6d-737d-4844-9c63-62dbb66ed983/iso-19212-2006)

<https://standards.iteh.ai/catalog/standards/sist/33efdf6d-737d-4844-9c63-62dbb66ed983/iso-19212-2006>



**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO 19212:2006

<https://standards.iteh.ai/catalog/standards/sist/33efdf6d-737d-4844-9c63-62dbb66ed983/iso-19212-2006>

© ISO 2006

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

## Contents

Page

1	Scope .....	1
2	Normative references .....	1
3	Terms and definitions .....	1
4	Methods of test for shear strength .....	2
4.1	Test method for metals .....	2
4.2	Test method for wood .....	2
5	Test atmosphere .....	2
6	Sampling and handling of adhesives .....	2
7	Kinds of adhesive and surface preparation of adherends .....	2
8	Preparation of test specimens .....	2
8.1	Metal adherends .....	2
8.2	Wood adherends .....	2
9	Procedure .....	2
10	Expression of results .....	3
10.1	Plot of shear strength versus temperature .....	3
10.2	Failure patterns .....	3
11	Test report .....	3
Annex A (informative)	Practical information on the test method .....	5
Bibliography	.....	7

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 19212 was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 11, *Products*.

## iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO 19212:2006](https://standards.iteh.ai/catalog/standards/sist/33efdf6d-737d-4844-9c63-62dbb66ed983/iso-19212-2006)

<https://standards.iteh.ai/catalog/standards/sist/33efdf6d-737d-4844-9c63-62dbb66ed983/iso-19212-2006>

# Adhesives — Determination of temperature dependence of shear strength

**SAFETY STATEMENT** — Persons using this document should be familiar with normal laboratory practice, if applicable. This document does not purport to address all of the safety problems, if any, associated with its use. It is the responsibility of the user to establish appropriate safety and health practices and to ensure compliance with any regulatory requirements.

## 1 Scope

This International Standard specifies methods for determining the temperature dependence of the shear strength of the adhesive or adhesive bond in adhesively bonded products.

## 2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 291, *Plastics — Standard atmospheres for conditioning and testing*

ISO 472, *Plastics — Vocabulary*

ISO 4587, *Adhesives — Determination of tensile lap-shear strength of rigid-to-rigid bonded assemblies*

ISO 6238, *Adhesives — Wood-to-wood adhesive bonds — Determination of shear strength by compressive loading*

ISO 10365, *Adhesives — Designation of main failure patterns*

ISO 15605, *Adhesives — Sampling*

ISO 17212, *Structural adhesives — Guidelines for the surface preparation of metals and plastics prior to adhesive bonding*

## 3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 472 and the following apply.

### 3.1

#### **temperature dependence of shear strength in adhesive bonds**

property capable of being measured by determining the shear strength of test specimens at various temperatures and recording the changes

## 4 Methods of test for shear strength

### 4.1 Test method for metals

For adherends made of metal, the shear strength shall be determined in accordance with ISO 4587.

### 4.2 Test method for wood

For adherends made of wood, the shear strength shall be determined in accordance with ISO 6238.

## 5 Test atmosphere

The specimens shall be conditioned and tested in one of the standard atmospheres specified in ISO 291.

## 6 Sampling and handling of adhesives

The method used for sampling and for handling the adhesives shall be in accordance with ISO 15605.

## 7 Kinds of adhesive and surface preparation of adherends

See ISO 17212.

iTeh STANDARD PREVIEW

## 8 Preparation of test specimens (standards.iteh.ai)

### 8.1 Metal adherends

<https://standards.iteh.ai/catalog/standards/sist/33efdf6d-737d-4844-9c63-62dbb66ed983/iso-19212-2006>

The test joints may be prepared either individually or from adhesively bonded panels, in each case following the procedure specified in ISO 4587. Surface treatment of the adherends and application and curing of the adhesive shall be in accordance with the adhesive manufacturer's instructions.

Whether prepared individually or cut from adhesively bonded panels, the shape and dimensions of the specimens shall be as specified in ISO 4587.

For each test temperature (see Clause 9), the number of specimens tested shall be at least five.

### 8.2 Wood adherends

The test joints may be prepared either individually or from adhesively bonded blocks, in each case following the procedure specified in ISO 6238. Surface treatment of the adherends and application and curing of the adhesive shall be in accordance with the adhesive manufacturer's instructions.

Whether prepared individually or cut from adhesively bonded blocks, the shape and dimensions of the specimens shall be as specified in ISO 6238.

For each test temperature (see Clause 9), the number of specimens tested shall be at least 12 and, when they are cut from adhesively bonded blocks, they shall come from at least three blocks.

## 9 Procedure


Immediately after being conditioned for 168 h (or 48 h in the case of heat-cured adhesives) in one of the atmospheres specified in ISO 291, specimens shall be tested in accordance with Clause 4 in the same atmosphere as used for conditioning.

In addition, specimens shall be tested at temperatures selected from the following:  $(-40 \pm 3)^\circ\text{C}$ ,  $(-20 \pm 3)^\circ\text{C}$ ,  $(0 \pm 2)^\circ\text{C}$ ,  $(40 \pm 2)^\circ\text{C}$ ,  $(60 \pm 2)^\circ\text{C}$ ,  $(80 \pm 2)^\circ\text{C}$ ,  $(100 \pm 2)^\circ\text{C}$ ,  $(120 \pm 2)^\circ\text{C}$ ,  $(140 \pm 2)^\circ\text{C}$ ,  $(160 \pm 2)^\circ\text{C}$  and  $(180 \pm 2)^\circ\text{C}$ , the additional conditioning time at each temperature being 10 min for metals and 24 h for wood. It is not necessary to control the humidity when testing at these temperatures.

## 10 Expression of results

### 10.1 Plot of shear strength versus temperature

Plot adhesive shear strength versus temperature using the results from Clause 9. Figure 1 shows an example of a typical plot.

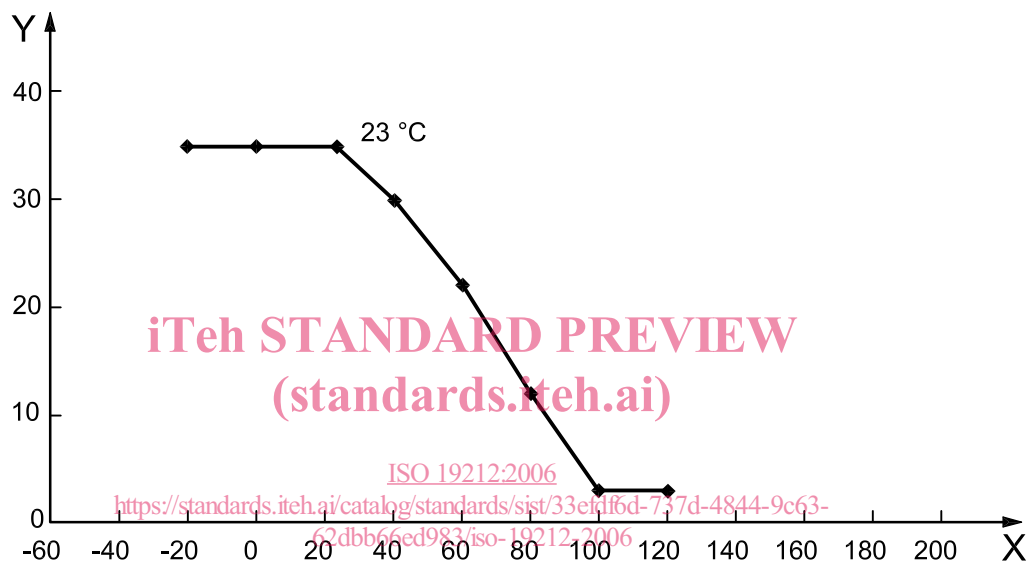

#### Key

- X temperature ( $^\circ\text{C}$ )  
Y shear strength (MPa)

Figure 1 — Typical plot of shear strength versus temperature

### 10.2 Failure patterns

Classify failure patterns in accordance with ISO 10365.

## 11 Test report

The test report shall include the following particulars:

- a reference to this International Standard;
- all details necessary for complete identification of the adhesive tested, including type, source, manufacturer's code number, batch or lot number, physical form, etc.;
- the shape and dimensions of the adherends, as well as the material of which they are made, their surface preparation and any other necessary information on them;
- the method used to apply the adhesive to the adherends, the drying and pre-cure conditions (if relevant), the curing time or setting time, and the bonding procedure used (including the bonding temperature and pressure);

## ISO 19212:2006(E)

- e) the average thickness of the bond after bonding and the method used to determine the thickness;
- f) details of test specimen preparation, the shape and dimensions of the test specimens, their number and construction, the atmosphere in which they were conditioned before testing and the atmosphere in which they were tested;
- g) the test speed (or the rate of loading in the case of constant rate of load application);
- h) the shear strength of each test specimen tested at each temperature, the mean shear strength and the standard deviation from the mean, and the plot of adhesive strength versus temperature;
- i) the failure patterns, classified in accordance with ISO 10365;
- j) details of any deviations from the specified procedure and of any incidents which may have affected the results;
- k) the date of testing.

## iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 19212:2006

<https://standards.iteh.ai/catalog/standards/sist/33efdf6d-737d-4844-9c63-62dbb66ed983/iso-19212-2006>



## Annex A (informative)

### Practical information on the test method

#### A.1 General

This International Standard is relevant to adhesives that are used for the manufacture of products which are utilized in the interior of buildings. For these applications, a knowledge of the dependence of the adhesive strength on temperature is a useful indicator of the durability of the adhesive, and a measure of the temperature dependence of shear strength is an important aid in design and material selection.

This annex gives practical information relating to this standard, including background information on the method used as well as the reasons why this method was preferred to other methods.

There are three commonly used ways of determining the dependence of adhesive strength on temperature:

- a) by determination of the temperature dependence of the adhesive bond (i.e. the measurement of the adhesive strength at different temperatures)<sup>[1]</sup>;
- b) by determination of the thermal-degradation properties of the bond;
- c) by determination of the temperature dependence of the creep properties of the bond<sup>[2]</sup>.

This International Standard uses approach a).

#### A.2 Background information

ISO 19212:2006

[https://standards.iteh.ai/catalog/standards/sist/33efdf6d-737d-4844-9c63-](https://standards.iteh.ai/catalog/standards/sist/33efdf6d-737d-4844-9c63-62db66ed983/iso-19212-2006)

[62db66ed983/iso-19212-2006](https://standards.iteh.ai/catalog/standards/sist/33efdf6d-737d-4844-9c63-62db66ed983/iso-19212-2006)

##### A.2.1 Test methods not considered appropriate for this International Standard

###### A.2.1.1 Determination of adhesive strength at the glass-transition temperature

Since the mechanical properties of an adhesive change most rapidly at temperatures in the region of the adhesive's glass-transition temperature  $T_g$  [3], [4], [5], consideration has been given to characterizing temperature dependence by presenting strength results at  $T_g$ . Following experimental studies in which differential scanning calorimetry (DSC) and thermomechanical analysis (TMA) were employed to measure  $T_g$ , this approach was considered unsatisfactory for the following reasons:

- a) Some adhesives, such as epoxy resins and urethane resins, show extreme changes in adhesive strength around  $T_g$ , whereas others do not. This difference in behaviour is due to the fact that each resin has different softening properties.
- b) In the case of emulsion resins, it is very difficult to measure  $T_g$  because of the effects of the emulsifying agent and the solvent.
- c) The reproducibility of determinations at  $T_g$  is problematic because the value of  $T_g$  depends on the method used to measure it, such as DSC, TMA or differential thermal analysis (DTA), as well as on the operator carrying out the measurement and the measurement conditions (rate of heating).

###### A.2.1.2 Classification of adhesives by temperature dependence

Next, a method for classifying adhesives by measuring the reduction in strength at an elevated temperature was explored.

The adhesive strength of adhesively bonded products, or parts of such products, was measured at 23 °C and at a higher temperature between 23 °C and 100 °C. The adhesives were then classified into four types