

---

---

**Binders for paints and varnishes — Gum  
rosin — Gas-chromatographic analysis**

*Liants pour peintures et vernis — Gomme-résine — Analyse par  
chromatographie en phase gazeuse*

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[ISO 19334:2006](https://standards.iteh.ai/catalog/standards/sist/d22a85e4-f9c5-43d7-9288-4c5d8fcad85b/iso-19334-2006)

<https://standards.iteh.ai/catalog/standards/sist/d22a85e4-f9c5-43d7-9288-4c5d8fcad85b/iso-19334-2006>



**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO 19334:2006

<https://standards.iteh.ai/catalog/standards/sist/d22a85e4-f9c5-43d7-9288-4c5d8fcad85b/iso-19334-2006>

© ISO 2006

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 19334 was prepared by Technical Committee ISO/TC 35, *Paints and varnishes*, Subcommittee SC 10, *Test methods for binders for paints and varnishes*.

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[ISO 19334:2006](https://standards.iteh.ai/catalog/standards/sist/d22a85e4-f9c5-43d7-9288-4c5d8fcad85b/iso-19334-2006)

<https://standards.iteh.ai/catalog/standards/sist/d22a85e4-f9c5-43d7-9288-4c5d8fcad85b/iso-19334-2006>

## Introduction

Gum rosins are important commercial materials, primarily composed of rosin acids, but also containing some neutral material. For many applications, it is necessary to know the level of the individual rosin acids present in these products. Gas chromatography has proven to be a useful tool for such determinations (see ASTM D 509, *Standard Test Methods of Sampling and Grading Rosin*), and capillary chromatography, specified in these test methods, is considered to be the most effective gas-chromatographic technique currently available.

Due to hydrogen bonding, unmodified rosin acids cannot be volatilized at atmospheric pressure without undergoing decomposition. So, it is necessary to convert the free acids to more volatile and more stable methyl esters prior to chromatographic separation.

This standard describes one way to prepare methyl esters. The classic method is through the use of diazomethane, but diazomethane is a hazardous and toxic material, and so is no longer the preferred agent.

Trimethylphenylammonium hydroxide (TMPAH) and tetramethylammonium hydroxide (TMAH) are satisfactory methylating agents as both produce results that are very similar to those of diazomethane, but without the hazards that are associated with diazomethane.

*N,N*-dimethylformamide dimethyl acetal (DMF-DMA) gives results comparable to those obtained with TMPAH and TMAH and is easy and safe to use. However, the reagent is moisture-sensitive, requiring samples to be free of any significant levels of water.

This International Standard specifies a method using TMAH.

[ISO 19334:2006](https://standards.iteh.ai/catalog/standards/sist/d22a85e4-f9c5-43d7-9288-4c5d8fcad85b/iso-19334-2006)

<https://standards.iteh.ai/catalog/standards/sist/d22a85e4-f9c5-43d7-9288-4c5d8fcad85b/iso-19334-2006>

# Binders for paints and varnishes — Gum rosin — Gas-chromatographic analysis

## 1 Scope

This International Standard specifies a gas-chromatographic method for determining the amounts of certain rosin acids in gum rosin using capillary gas-chromatographic separation of the volatile methyl esters of these acids. It is intended primarily to permit the identification of gum rosin from specific species of pine trees. It is not designed for the quantitative analysis of gum rosin. If such analyses are required, the internal-standard technique specified in ASTM D 5974 should be used.

## 2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

GB 8145, *Gum rosin — Test methods of rosin*

ASTM D 509, *Standard Test Methods of Sampling and Grading Rosin*

Naval Stores Act of 1923 (42 Stat 1435.7, USC 91-99) as amended in 1951

<https://standards.iteh.ai/catalog/standards/sist/d22a85e4-f9c5-43d7-9288-4c5d8fcad85b/iso-19334-2006>

## 3 Sampling

Take a representative sample following the procedures specified in GB 8145, ASTM D 509 or the Naval Stores Act of 1923 (42 Stat 1435.7, USC 91-99) as amended in 1951.

NOTE Rosin samples need to be freshly broken from a larger mass to ensure the results are not affected by air oxidation of the rosin.

## 4 Preparation of methyl esters

### 4.1 Apparatus

#### 4.1.1 Gas chromatograph

Use an instrument equipped with a flame-ionization detector (FID) that can be operated under the conditions given in 5.1.

#### 4.1.2 Column

The recommended (referee) column is a fused-silica BDS column 25 m in length, 0,32 mm in internal diameter and with a 0,20  $\mu\text{m}$  film thickness, which gives separation equivalent to or better than that shown in Figures 1 to 3.

If other columns are used, the operating conditions shall be chosen such that the separation obtained is equivalent to or better than that shown in Figures 1 to 3.

## 4.2 Reagents and materials

Reagent-grade chemicals should preferably be used in all analyses. If other grades are used, it shall be first ascertained that the reagent concerned is of sufficiently high purity to permit its use without lessening the accuracy of the determination.

**4.2.1 Tetramethylammonium hydroxide (TMAH) solution**, 24 % in methanol, CAS No. 75-59-2.

**4.2.2 Tetramethylammonium hydroxide (TMAH) solution**, 6 % in methanol. Dilute 25 ml of the reagent described in 4.2.1 with 75 ml of methanol.

**4.2.3 Phenolphthalein solution**, 1 % (mass per volume) in methanol.

**4.2.4 Methanol**, anhydrous.

**4.2.5 Toluene** (optional).

## 4.3 Procedure

Weigh approximately 50 mg of the sample into a suitable vial, and dissolve it in 0,5 ml to 3,0 ml of methanol. Add 2 or 3 drops of phenolphthalein indicator solution, and titrate to a pink colour (pH 7,8 to 8,1) with the 6 % solution of TMAH. When the solution is injected into the heated injection port of the chromatograph, the tetramethylammonium salts are pyrolyzed to methyl esters.

NOTE For solid rosin, 2 or 3 drops of toluene may be added to the vial prior to the addition of TMAH, to assist in dissolving the sample.

STANDARD PREVIEW  
(standards.iteh.ai)

## 5 Gas-chromatographic analysis

ISO 19334:2006

[https://standards.iteh.ai/catalog/standards/sist/d22a85e4-f9c5-43d7-9288-](https://standards.iteh.ai/catalog/standards/sist/d22a85e4-f9c5-43d7-9288-4c5d8fcad85b/iso-19334-2006)

### 5.1 Set-up of gas chromatograph (GC)

[4c5d8fcad85b/iso-19334-2006](https://standards.iteh.ai/catalog/standards/sist/d22a85e4-f9c5-43d7-9288-4c5d8fcad85b/iso-19334-2006)

Set the GC conditions so that they are approximately as follows (see also last paragraph in this subclause):

Column temperature: 195 °C, isothermal

Injection port temperature: 300 °C

Injection port liner: glass splitter

Detector temperature: 280 °C

Carrier gas: hydrogen or helium

Linear flow rate: 40 cm/s

Split ratio: 40 to 1

Detector: FID

hydrogen: 50 kPa

air: 100 kPa

These are typical operating conditions for an instrument using a BDS column. The particular equipment used shall be adjusted in accordance with the manufacturer's instructions to optimize its performance. Ongoing adjustment of operating temperature and flow rate may be necessary to maintain optimum performance of the column due to ageing.

## 5.2 Analysis

Inject 0,5 µl to 1,0 µl of the test sample prepared in 4.3.

NOTE Dilution of the sample with additional solvent may be necessary to obtain injections that do not overload the column or detector.

## 5.3 Calculation

Sum the areas of the individual peaks, exclusive of the solvent peak, to obtain the total peak area.

Calculate the relative percentage of each rosin acid methyl ester present, uncorrected for the amount of polymeric materials present, using the equation:

$$\text{Rosin acid (\%)} = \frac{A \times 100}{A_{\text{Tot}}}$$

where

$A$  is the peak area for the rosin acid methyl ester being determined;

$A_{\text{Tot}}$  is the sum of the areas of all the rosin acid methyl ester peaks.

NOTE See Figures 1 to 3 for typical chromatograms of selected gum rosins and Table 1 for the compositions determined from these and other such chromatograms.

(standards.iteh.ai)

## 6 Test report


The test report shall contain at least the following information:

- all details necessary to identify the product tested;
- a reference to this International Standard (ISO 19334:2006);
- the area percent of individual rosin acids to the nearest 0,1 %;
- by comparison with Table 1 and Figures 1 to 3, the identity of the gum rosin;
- any deviation from the test method specified;
- the date of the test.

**Table 1 — Typical contents of characteristic rosin acids in gum rosins from pine species**  
(determined by the gas-chromatographic method specified in this International Standard)

Rosin acid	<i>Pinus massoniana</i> %	<i>Pinus merkusii</i> %	<i>Pinus elliottii</i> %	<i>Pinus pinaster</i> %	<i>Pinus caribaea</i> %	<i>Pinus simoa</i> %	Relative retention time
Communic	0	0	5	0	1	0	0,588
Palustric	25	20	19	19	22	20	0,634
Isopimaric	2	15	17	5	8	4	0,664
Abietic	35	35	23	38	35	41	0,967
Dehydroabietic	4	5	5	6	7	4	1,000
Neoabietic	16	5	20	16	17	18	1,092
Mercusic	0	7	0	0	0	0	1,514

NOTE Capillary gas-liquid chromatography (GLC). Labelled peaks eluted as methyl esters. Conversion of rosin acids to their methyl derivatives by means of tertamethylammonium hydroxide (TMAH) procedure. Column: fused-silica BDS,  $l = 25$  m,  $d = 0,32$  mm, film thickness = 0,2 µm,  $T = 195$  °C (isothermal), carrier gas H<sub>2</sub> at 50 kPa

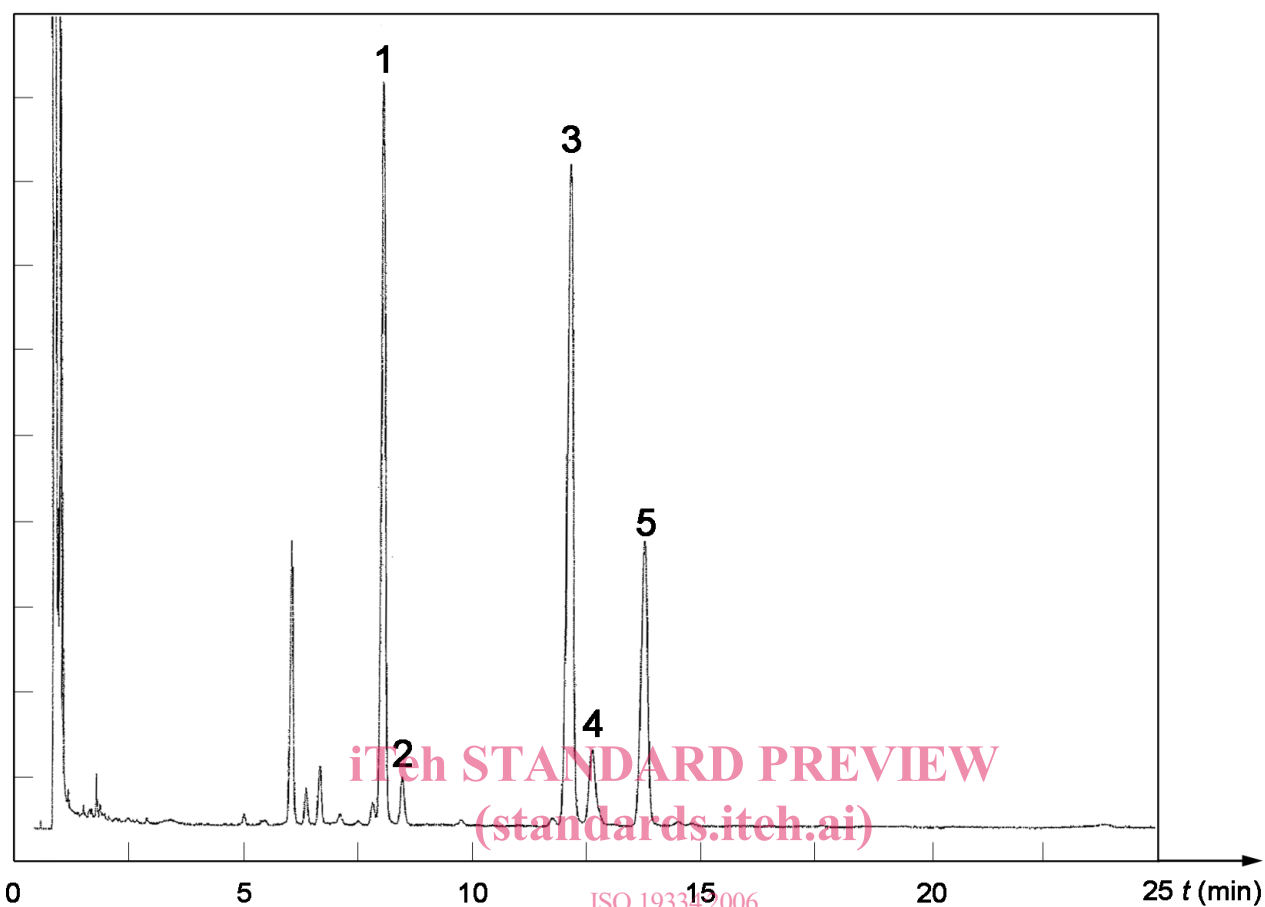

ISO 19334:2006  
<https://standards.itech.ai/catalog/standards/sist/d22a85e4-f9c5-43d7-9288-4c5d8fcad85b/iso-19334-2006>

- Key**
- 1 palustric acid
  - 2 isopimaric acid
  - 3 abietic acid
  - 4 dehydroabietic acid
  - 5 neoabietic acid

**Figure 1 — Chromatogram of rosin acid methyl esters from *Pinus massoniana* rosin**



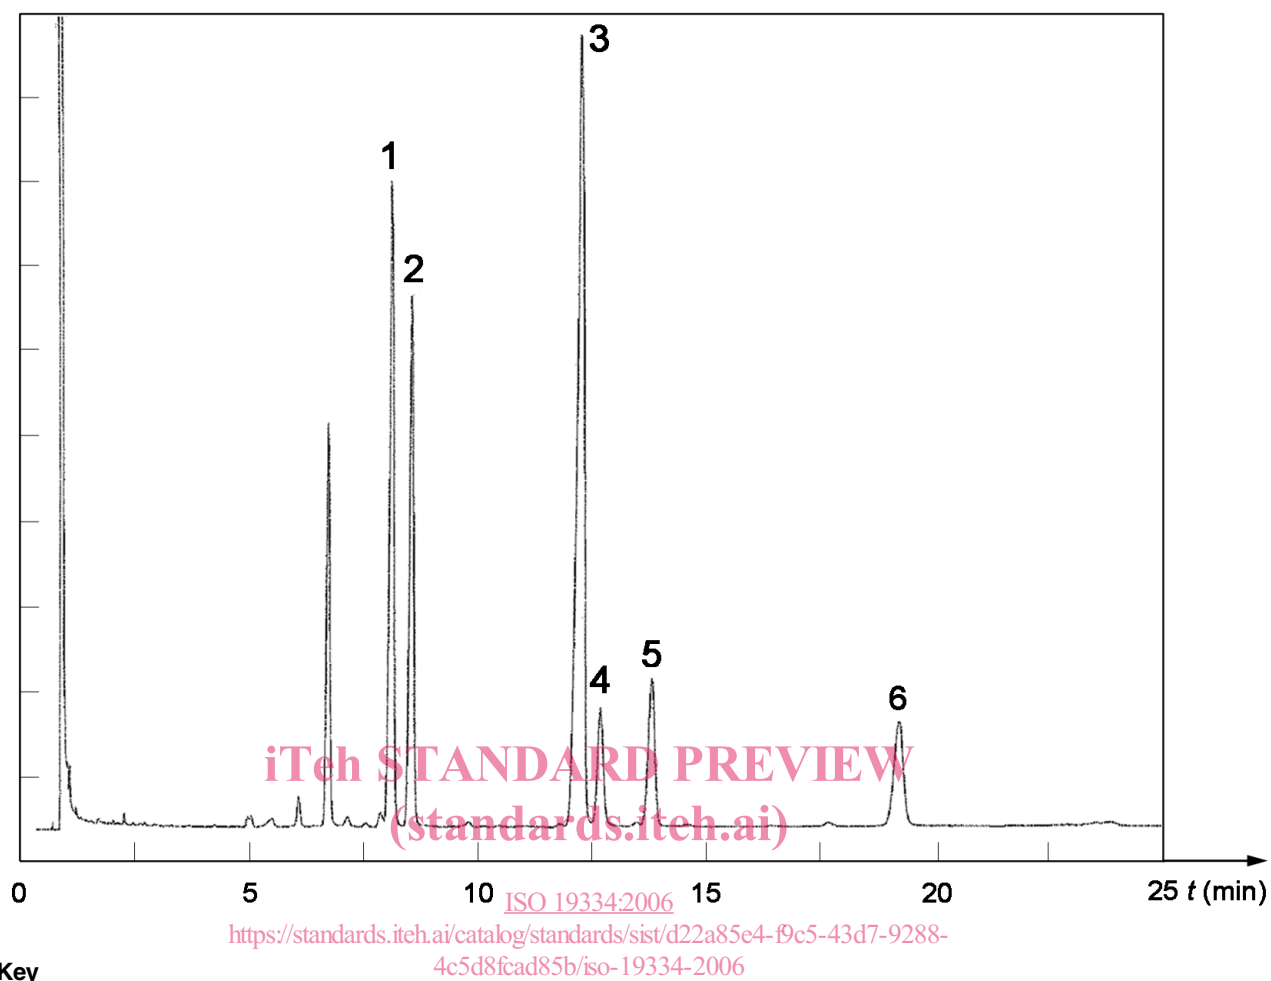


Figure 2 — Chromatogram of rosin acid methyl esters from *Pinus merkusii* rosin