
**Tubeless tyres — Valves and
components — Test methods**

*Pneumatiques sans chambre — Valves et composants — Méthodes
d'essai*

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 14960:2004](https://standards.iteh.ai/catalog/standards/sist/481773ed-4217-4269-aa5f-60d0fb3139a5/iso-14960-2004)

[https://standards.iteh.ai/catalog/standards/sist/481773ed-4217-4269-aa5f-
60d0fb3139a5/iso-14960-2004](https://standards.iteh.ai/catalog/standards/sist/481773ed-4217-4269-aa5f-60d0fb3139a5/iso-14960-2004)



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 14960:2004

<https://standards.iteh.ai/catalog/standards/sist/481773ed-4217-4269-aa5f-60d0fb3139a5/iso-14960-2004>

© ISO 2004

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Test set-up	1
4.1 Test valve description	1
4.2 Test fixtures	2
4.3 Installation	2
5 Test methods and performance requirements	2
5.1 Adhesion	2
5.1.1 Test procedure	2
5.1.2 Performance requirements	3
5.2 Valve core seal	3
5.2.1 Valve core specifications	3
5.2.2 Room temperature test	3
5.2.3 Low temperature test	3
5.2.4 High temperature test	4
5.3 Valve cap seal — Room temperature test (optional, for sealing caps only)	4
5.3.1 Test procedure	4
5.3.2 Performance requirement	4
5.4 Valve-to-rim seal	4
5.4.1 Principal	4
5.4.2 Low temperature test	4
5.4.3 High temperature test	6
5.5 Installation tests	7
5.5.1 Force to seat	7
5.5.2 Force to pull out	7
5.6 Burst	8
5.6.1 Test hole diameter and plate thickness	8
5.6.2 Test procedure	8
5.6.3 Performance requirement	8
5.7 Ozone resistance	8
5.7.1 Test hole diameter and plate thickness	8
5.7.2 Test procedure	8
5.7.3 Performance requirement	9
5.8 Flexing resistance	9
5.8.1 Test hole diameter and plate thickness	9
5.8.2 Test procedure	9
5.8.3 Performance requirement	9
Bibliography	10

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 14960 was prepared by Technical Committee ISO/TC 31, *Tyres, rims and valves*, Subcommittee SC 9, *Valves for tube and tubeless tyres*.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO 14960:2004](https://standards.iteh.ai/catalog/standards/sist/481773ed-4217-4269-aa5f-60d0fb3139a5/iso-14960-2004)

<https://standards.iteh.ai/catalog/standards/sist/481773ed-4217-4269-aa5f-60d0fb3139a5/iso-14960-2004>

Tubeless tyres — Valves and components — Test methods

1 Scope

This International Standard specifies test methods and performance requirements for snap-in tubeless tyre valves and their components, intended for, but not limited to, highway applications.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 3911, *Wheel and rims for pneumatic tyres — Vocabulary, designation and marking*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 3911 and the following apply.

3.1

snap-in valve

tyre valve having a rigid housing adhered to a resilient body designed to retain and seal the valve in the rim hole

3.2

unused valve

snap-in valve that has completed final manufacturing processing at least 24 h previously, which has not been subjected to any test or service and which has been stored for no longer than 4 months in the dark at ambient temperature, in an optimal and non-aggressive environment

NOTE Rubber compounds can change characteristics during their life expectancy.

3.3

aged valve

unused valve that has been subjected to 100 ± 3 °C for a minimum of 4 h in circulating hot air and cooled at 20 °C to 26 °C for a minimum of 4 h

4 Test set-up

4.1 Test valve description

A snap-in valve unit free of rubber in the air passage, having no rubber or cement above the second thread on the housing, and without flow cracks, blisters, voids, or other moulding defects; its mould parting line flash should not exceed 1,3 mm in height or 0,15 mm in thickness at the outer edge.

4.2 Test fixtures

Break both edges on both sides of the valve hole, to form either a 45° chamfer of 0,3 mm to 0,4 mm or such that they are rounded with a radius of 0,3 mm to 0,4 mm. Emery cloth or suitable tooling should be used for this purpose. It is also recommended that the material of the test fixture be representative of the material of the actual rim.

NOTE The primary external seal of a snap-in valve in a valve hole is obtained from the rubber compression of the valve body onto the internal surface of the valve hole. Secondary external sealing can be present by the contact of the remainder of the valve body exterior to the surface of the material around the valve hole. Either or both of these seals may be affected by the compound curvatures in the wheel rims and by stock thickness.

The dimensions of the test fixtures shall be in accordance with Table 1.

Table 1 — Test Fixtures

Dimensions in millimetres

Test(s) (subclause)	Rim hole			
	Nominal diameter 11,3		Nominal diameter 15,7	
	Test hole diameter	Plate thickness	Test hole diameter	Plate thickness
Valve-to-rim seal (5.4)	11,7 ⁰ _{-0,05}	1,8 ± 0,05	16,1 ⁰ _{-0,05}	1,8 ± 0,05
Installation (5.5)	11,3 ^{+0,05} ₀	3,5 ± 0,05	15,7 ^{+0,05} ₀	3,5 ± 0,05
Ozone resistance (5.7)	11,3 ^{+0,05} ₀	3,5 ± 0,05	15,7 ^{+0,05} ₀	3,5 ± 0,05
Burst or unseating (5.6)	11,7 ⁰ _{-0,05}	1,8 ± 0,05	16,1 ⁰ _{-0,05}	1,8 ± 0,05
Flexing resistance (5.8)	11,7 ⁰ _{-0,05}	1,8 ± 0,05	16,1 ⁰ _{-0,05}	1,8 ± 0,05

4.3 Installation

All valves, wetted with clean water as a lubricant, shall be installed in a test fixture in accordance with 4.2 by applying a valve insertion force to the end of the valve metal insert or a valve traction force to the mouth of the valve, perpendicular to the plane of the valve mounting hole and directly through the centre of the valve mounting hole.

However, no valve assembly shall be tested which has damage resulting from installation.

A valve shall be considered properly seated when the entire indicator ring is observed to be through the rim or valve mounting hole fixture.

After installation, valve assemblies shall be thoroughly dried in the sealing area before continuing testing.

5 Test methods and performance requirements

5.1 Adhesion

5.1.1 Test procedure

- a) Make two axial and parallel cuts, 180° apart, through the full thickness of the rubber cover down the entire length of the valve.

- b) Pull each side of the button base away from the insert, towards the cap thread end at (150 ± 15) mm/min with a traction machine or manually, using pliers.

The test shall be conducted at (23 ± 5) °C.

5.1.2 Performance requirements

Any separation between brass and rubber, brass and cement, or cement and rubber, in excess of 41 mm² on each valve shall be considered as a failure.

Any separation creating a strip along the complete valve axis direction shall be considered as a failure.

5.2 Valve core seal

5.2.1 Valve core specifications

Valve cores installed in snap-in valve assemblies (see Figure 1) shall have a pin height tolerance of $+0,25$ mm, relative to the valve mouth, and a standard torque of $-0,90$

- 0,40 N·m to 0,50 N·m with metallic sealing, or
- 0,17 N·m to 0,34 N·m for a non-metallic gasket.

5.2.2 Room temperature test

5.2.2.1 Test procedure

- a) Immerse the valve assembly vertically in clean water at (23 ± 5) °C not more than 100 mm below the surface of the water (see Figure 1).
- b) Check for leakage using the following test air pressures:
- for a cup gasket seal, apply a pressure of 35 kPa;
 - for a barrel seal, apply a pressure of 475 kPa.

5.2.2.2 Performance requirement

Leakage shall be at a rate inferior to 0,2 cm³/min; alternatively, no bubble shall be detached during the test time of 1 min.

5.2.3 Low temperature test

5.2.3.1 Test procedure

- a) Depress and release the valve core pin once after a 24 h minimum exposure at (-40 ± 3) °C; maintain assembly pressure at (180 ± 15) kPa. See Figure 1.
- b) Check for leakage with ethanol or methanol at (-40 ± 3) °C, 25 mm above the valve mouth, with the assembly still pressurised to 180 kPa.
- c) Begin leak detection after a 1 min soak period.

5.2.3.2 Performance requirement

Leakage shall be at a rate inferior to 0,2 cm³/min; alternatively, no bubble shall be detached during the test time of 1 min.

5.2.4 High temperature test

5.2.4.1 Test procedure

- a) Depress and release the valve core pin once after a 48 h minimum soak period at (100 ± 3) °C; maintain assembly pressure at (600 ± 15) kPa. See Figure 1.
- b) Check for leakage with (66 ± 3) °C clean water at not more than 50 mm above the valve mouth, with the assembly still pressurised to 600 kPa.

5.2.4.2 Performance requirement

Leakage shall be at a rate inferior to 0,2 cm³/min; alternatively, no bubble shall be detached during the test time of 1 min.

5.3 Valve cap seal — Room temperature test (optional, for sealing caps only)

5.3.1 Test procedure

- a) Screw the cap with a sealing gasket at 0,15 N·m to 0,20 N·m torque on a valve without a core.
- b) Immerse the valve assembly vertically in clean water at (23 ± 5) °C not more than 100 mm below the surface of the water (see Figure 1).
- c) Check for leakage using a 475 kPa test pressure.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 14960:2004

<http://standards.iteh.ai/standards/sist/481773ed-4217-4269-aa5f-60d0fb3139a5/iso-14960-2004>

5.3.2 Performance requirement

Leakage shall be at a rate inferior to 0,2 cm³/min; alternatively, no bubble shall be detached during the test time of 1 min.

5.4 Valve-to-rim seal

5.4.1 Principal

Temperature tests are performed to subject the test valve to extremes in temperature. The flexing of the valve simulates possible operational conditions.

The same valve and assembly, as shown in Figure 2, may be used for both tests, provided the low temperature test is conducted first.

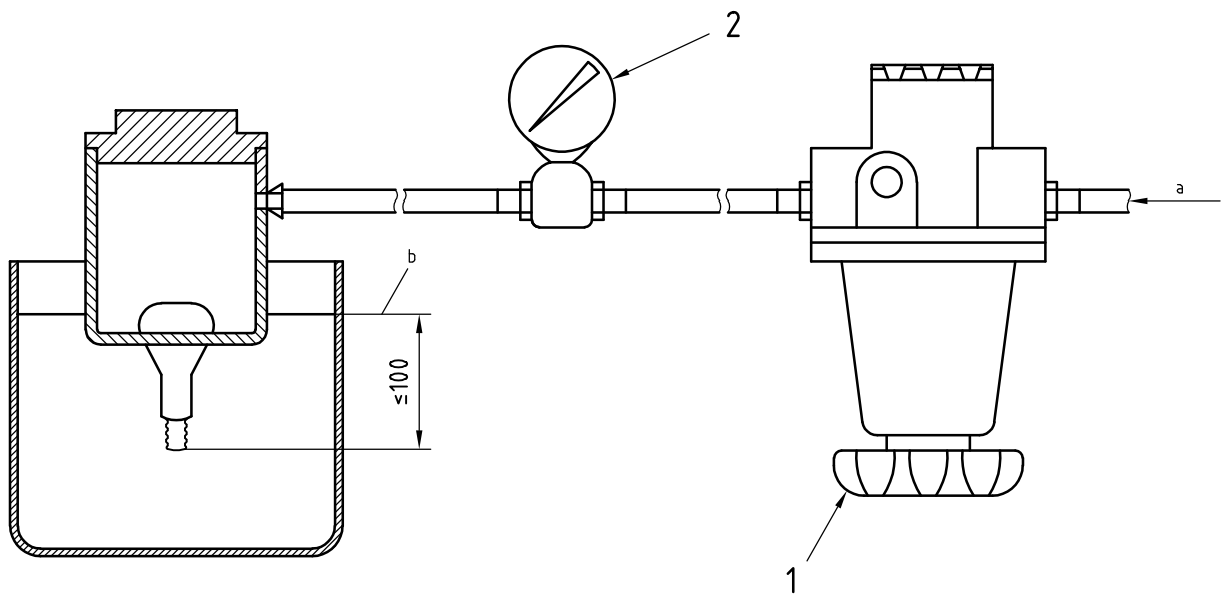
5.4.2 Low temperature test

5.4.2.1 Test hole dimensions

The test holes shall have the following dimensions, in millimetres:

- 11,7⁰_{-0,05} in diameter and 1,8 ± 0,05 thick;
- 16,1⁰_{-0,05} in diameter and 1,8 ± 0,05 thick.

Dimensions in millimetres

**Key**

- 1 regulator
- 2 gauge
- a Air supply.
- b Liquid level.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

Figure 1 — Valve seal test set-up

[ISO 14960:2004](https://standards.iteh.ai/catalog/standards/sist/481773ed-4217-4269-aa5f-60d0fb3139a5/iso-14960-2004)

5.4.2.2 Test procedure

- a) Mount the test valve on a test plate in accordance with 4.2 and 4.3.
- b) Expose the assembly to a temperature of $(-40 \pm 3)^\circ\text{C}$ for 24 h minimum to ensure the valve seal area is at the test temperature, while applying a test pressure of (180 ± 15) kPa.
- c) Immerse the valve assembly, still pressurised to (180 ± 15) kPa, with the valve mouth upwards, in ethanol or methanol at $(-40 \pm 3)^\circ\text{C}$, and with the valve button not more than 100 mm below the surface of the liquid (see Figure 2).
- d) Flex the immersed valve to an angle of $25^\circ \pm 3^\circ$ with respect to the axis of the valve mounting hole. Revolve the cap end of the valve one complete turn around the axis of the mounting hole, executing this single revolution at a uniform rate, without the application of torque to the valve body and within 15 s to 45 s.
- e) Place the assembly in a refrigerator at $(-40 \pm 3)^\circ\text{C}$; maintain the pressure at (180 ± 15) kPa.
- f) Repeat steps c) to e) of the procedure at minimum intervals of 0,5 h a total of five times.

5.4.2.3 Performance requirements

Leakage shall be at a rate inferior to $0,2 \text{ cm}^3/\text{min}$; alternatively, no bubble shall be detached during the test time of 1 min at the rim seal before, during or after revolving and flexing the valve.

NOTE Air inclusions during installation are not considered.