

---

---

**Destructive tests on welds in metallic  
materials — Cold cracking tests for  
weldments — Arc welding processes —**

**Part 2:  
Self-restraint tests**

iTeh STANDARD PREVIEW

(standards.iteh.ai)  
*Essais destructifs des soudures sur matériaux métalliques — Essais de  
fissuration à froid des assemblages soudés — Procédés de soudage à  
l'arc —*

*Partie 2: Essais sur éprouvette auto-bridée*

<https://standards.iteh.ai/catalog/standards/sist/ecb1a0ca-b759-42b7-8fdc-5dbbdf7a673/iso-17642-2-2005>



**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

**iTeh STANDARD PREVIEW  
(standards.iteh.ai)**

[ISO 17642-2:2005](#)

<https://standards.iteh.ai/catalog/standards/sist/ecb1a0ca-b759-42b7-8fdc-5dbbdf7a673/iso-17642-2-2005>

© ISO 2005

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 17642-2 was prepared by the European Committee for Standardization (CEN) in collaboration with Technical Committee ISO/TC 44, *Welding and allied processes*, Subcommittee SC 5, *Testing and inspection of welds*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

Throughout the text of this document, read “...this European Standard...” to mean “...this International Standard...”.

[ISO 17642-2:2005](https://standards.iteh.ai/)

ISO 17642 consists of the following parts, under the general title *Destructive tests on welds in metallic materials — Cold cracking tests for weldments* — Arc welding processes:

- *Part 1: General*
- *Part 2: Self-restraint tests*
- *Part 3: Externally loaded tests*

Annex ZA provides a list of corresponding International and European Standards for which equivalents are not given in the text.

**Contents**

page

|   |           |
|---|-----------|
| Foreword.....   | v         |
| <b>1 Scope .....</b>  | <b>1</b>  |
| <b>2 Normative references .....</b>   | <b>1</b>  |
| <b>3 Terms and definitions .....</b>  | <b>1</b>  |
| <b>4 Designation and symbols .....</b>  | <b>2</b>  |
| <b>5 Principle.....</b>   | <b>2</b>  |
| 5.1 General.....  | 2         |
| 5.2 Qualitative evaluation.....   | 2         |
| 5.3 Quantitative evaluation .....   | 2         |
| <b>6 Test.....</b>  | <b>3</b>  |
| 6.1 CTS-test .....  | 3         |
| 6.1.1 Dimensions of the test pieces .....   | 3         |
| 6.1.2 Preparation of the test pieces .....  | 3         |
| 6.1.3 Anchor welds .....  | 4         |
| 6.1.4 Test welds.....   | 5         |
| 6.1.5 Test results .....  | 7         |
| 6.2 <b>TEKKEN-test (Y-groove) and Lehigh test (U-groove).....</b>   | <b>9</b>  |
| 6.2.1 General.....  | 9         |
| 6.2.2 Dimensions of the test pieces .....   | 9         |
| 6.2.3 Preparation of the test pieces .....  | 10        |
| 6.2.4 Anchor welds .....  | 10        |
| 6.2.5 Test welds.....   | 10        |
| 6.2.6 Test results.....   | 13        |
| <b>7 Test report (CTS, Y and U groove).....</b>   | <b>16</b> |
| <b>Annex A (informative) Test report for CTS test.....</b>  | <b>17</b> |
| <b>Annex B (informative) Test report for Y- or U-joint (TEKKEN) weld cracking test .....</b>                                  | <b>18</b> |
| <b>Annex ZA (normative) Normative references to International publications with their relevant European publication .....</b> | <b>19</b> |

STANDARD PREVIEW  
(standards.itech.ai)

ISO 17642-2:2005  
<https://standards.itech.ai/catalog/standards/sist/ecb1a0ca-b759-42b7-8fdc-3db6d17a3797/iso-17642-2-2005>

## Foreword

This document (EN ISO 17642-2:2005) has been prepared by Technical Committee CEN/TC 121 "Welding", the secretariat of which is held by DIN, in collaboration with Technical Committee ISO/TC 44 "Welding and allied processes".

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by September 2005, and conflicting national standards shall be withdrawn at the latest by September 2005.

EN ISO 17642 consists of the following parts, under the general title *Destructive tests on welds in metallic materials - Cold cracking tests for weldments - Arc welding processes*:

- Part 1: General
- Part 2: Self-restraint tests
- Part 3: Externally loaded tests

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

**(standards.iteh.ai)**

[ISO 17642-2:2005](https://standards.iteh.ai/catalog/standards/sist/ecb1a0ca-b759-42b7-8fdc-5dbbdf7a673/iso-17642-2-2005)

<https://standards.iteh.ai/catalog/standards/sist/ecb1a0ca-b759-42b7-8fdc-5dbbdf7a673/iso-17642-2-2005>

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO 17642-2:2005

<https://standards.iteh.ai/catalog/standards/sist/ecb1a0ca-b759-42b7-8fdc-5dbbdf7a673/iso-17642-2-2005>

## 1 Scope

This standard specifies the sizes of the test pieces, the specimens and the procedures for carrying out self-restraint cold cracking tests by:

- CTS(Controlled Thermal Severity)-test
- Tekken (Y-groove) or Lehigh (U-groove) test

in order to obtain information about the cold cracking sensitivity during welding.

This standard applies primarily but not exclusively to C-Mn and low alloy steels.

## 2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 1043-1:1995, *Destructive tests on welds in metallic materials — Hardness testing — Part 1: Hardness test on arc welded joints*

EN 1321, *Destructive tests on welds in metallic materials — Macroscopic and microscopic examination of welds*

EN ISO 3690, *Welding and allied processes - Determination of hydrogen content in ferritic arc weld metal (ISO 3690:2000)*

[ISO 17642-2:2005](https://standards.iteh.ai/catalog/standards/sist/ech1a0ca-b759-42b7-8f1c-3dbbdf267350/iso-17642-2-2005)

EN ISO 17642-1:2004, *Destructive tests on welds in metallic materials - Cold cracking tests for weldments - Arc welding processes - Part 1: General (ISO 17642-1:2004)*

## 3 Terms and definitions

For the purposes of this document, the terms and definitions given in EN ISO 17642-1:2004 apply.

## 4 Designation and symbols

The following designations and symbols given in Table 1 apply.

**Table 1 — Designation and symbols**

| Symbol | Designation                               | Unit |
|--------|---|------|
|        | CTS-test                                  |      |
| $t$    | material thickness                        | mm   |
| $L_V$  | leg length vertical                       | mm   |
| $L_H$  | leg length horizontal                     | mm   |
| $L$    | length of the test bead                   | mm   |
|        | Tekken or Lehigh test (Y and U-groove)    |      |
| $t$    | material thickness                        | mm   |
| $g$    | root gap                                  | mm   |
| $W$    | diameter of drilled hole and groove width | mm   |
| $C_f$  | crack ratio for surface cracks            | %    |
| $C_r$  | crack ratio for root cracks               | %    |
| $C_s$  | crack ratio for cracks in sections        | %    |
| $l_f$  | length of surface crack                   | mm   |
| $l_r$  | length of root crack                      | mm   |
| $H_C$  | height root crack                         | mm   |
| $H$    | minimum thickness of test bead            | mm   |
| $L$    | length of the test bead                   | mm   |

## 5 Principle

ISO 17642-2:2005

<https://standards.iteh.ai/catalog/standards/sist/ecb1a0ca-b759-42b7-8fdc-5dbbdf7a673/iso-17642-2-2005>

### 5.1 General

The self-restraint cold cracking tests are designed to assess the cold cracking sensitivity of the parent materials and the arc welding consumables. The test consists of depositing a weld bead on a test sample made of two plates with pre-defined conditions and to examine transverse cut faces of the weld with a view to detect possible cracks either in the weld metal or in the heat affected zone.

This test procedure essentially applies to metal arc welding with covered electrodes and semi-automatic gas metal arc welding using solid and tubular wires. In general this method is not used for high current processes such as submerged-arc welding.

### 5.2 Qualitative evaluation

When using well determined welding conditions for welding a given material, a single evaluation test is performed. In the case of the CTS-test, the two test welds are examined.

### 5.3 Quantitative evaluation

When aiming at determining the cracking limit, a series of tests shall be performed. The no crack test shall be repeated, on the contrary, other tests shall be performed.




## 6 Test

### 6.1 CTS-test

#### 6.1.1 Dimensions of the test pieces

The dimensions of the test piece shall be in accordance with Figure 1.

Dimensions in millimetres

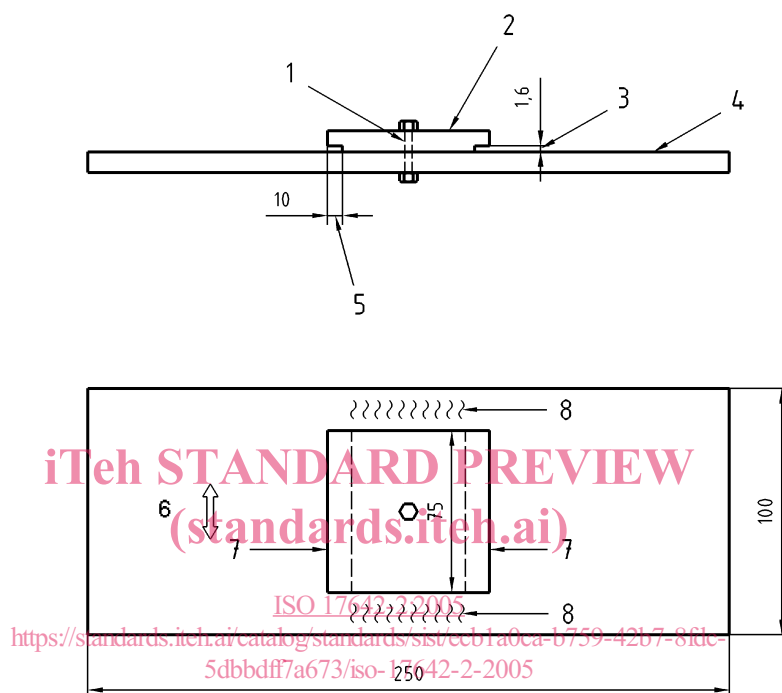

#### Key

- 1 Clearance hole 13 mm diameter
- 2 Top plate
- 3 Root notch gap
- 4 Bottom plate
- 5 Root notch depth
- 6 Preferred principal rolling direction
- 7 Test welds
- 8 Anchor welds

Figure 1 — CTS test

#### 6.1.2 Preparation of the test pieces

All test pieces shall be prepared from those parent materials which are actually to be welded with the welding consumables to be tested (see Figure 2).

Machine the test material for the pieces by sawing, milling or grinding. Ensure that surfaces to be welded are milled or ground finish. Take care to minimize heating and deformation in the material during machining.

Use the general arrangement of the test piece shown in Figure 1 and the tolerances and surface finish requirements given in Table 2.

**Table 2 — CTS test piece dimensions/conditions and tolerances**

| Dimension/conditions                      | Values  |
|---|---|
| Material thickness, <i>t</i><br>Top block | 6 mm min.<br>(75 ± 1) mm x (75 ± 1) mm x <i>t</i> |
| Bottom block                              | (250 ± 3) mm x (100 ± 3) mm x <i>t</i>            |
| Root notch<br>depth<br>gap                | (10 ± 0,5) mm<br>(1,6 ± 0,10) mm                  |
| Torque on bolt                            | (100 ± 5) N·m                                     |
| Surface finish on mating faces            | 3,2 μm R <sub>a</sub> max.                        |
| Surface finish on area to be welded       | 6,3 μm R <sub>a</sub> max.                        |
| Mating face gap                           | 0,05 mm max.                                      |

Top and bottom blocks shall both have the same thickness. Top blocks shall be machined and bottom blocks may be machined or flame cut. Both blocks shall be of the same material.

In those exceptional circumstances where it is impossible to machine both blocks from the test material, the top block shall be from the material under test and the bottom block from a material of equivalent yield strength. It is important that the susceptibility of the bottom block to HAZ hydrogen cracking is less than that of the test material.

Where the principal rolling direction of the plate can be determined, arrange the rolling directions of the top and bottom plates to be the same (see Figure 1).

Ensure that the surfaces to be welded are ground smooth and free from scale, rust, oil, grease and other contaminants.

Use a bolt with a 12 mm diameter for assembling the blocks. Degrease the bolt, a suitable plain nut and any washers to be used prior to use. Do not use nuts and bolts treated by plating processes. Insert the bolt through the top and bottom blocks, add the nut and washers and tighten to the required torque (see Table 2). Check the torque value prior to all welding operations and adjust as necessary.

**6.1.3 Anchor welds**

Make the anchor welds (shown in Figure 1) with a welding consumable with a yield strength equal to or greater than the yield strength of the material under test, up to parent material yield strength of 895 N/mm<sup>2</sup>.

NOTE Where the yield strength of the parent material exceeds 895 N/mm<sup>2</sup>, the consumable selected can have a yield strength less than that of the parent material (but greater than 895 N/mm<sup>2</sup>) and /or austenitic stainless steel weld deposit can be used.

Start and finish the anchor fillet welds 10 mm (± 3 mm) from the corners of the top plate and make them the following throat sizes:

- up to 15 mm plate thickness: (6 ± 1) mm;
- plate thickness 15 mm and over: (13 ± 1) mm.

Deposit the welds with a procedure to avoid hydrogen cracking, using preheat, interpass and post-heating control as necessary.

Dry all consumables used for anchor welds in accordance with the manufacturers' recommendations to give the lowest possible hydrogen levels.

Check the torque on the bolt and tighten the bolt where necessary. Leave the assembly for 12 h before test welding.

## 6.1.4 Test welds


### 6.1.4.1 Preheating

When the test piece is to be preheated, place the assembly in an oven and leave it for sufficient time to ensure even and thorough heating. Set the oven at a higher temperature than required for the test in order to allow for cooling of the assembly during transfer and set-up.

Prior to any welding, check the temperature of the test blocks using a calibrated surface pyrometer or thermocouple. Where the tests demand a specific preheat temperature, welding should not be commenced until the required temperature is achieved. Temperatures of the top and bottom blocks in the test area shall not differ by more than 5 °C.

### 6.1.4.2 Deposition

A jig should be used to position the assembly. The position of the electrode/wire with respect to the test block (see Figure 2) shall be such that the deposited test welds are symmetrically in the flat positions across the full width of the block in a single direction and in a single pass. Ensure that the test weld does not extend beyond the ends of the block.

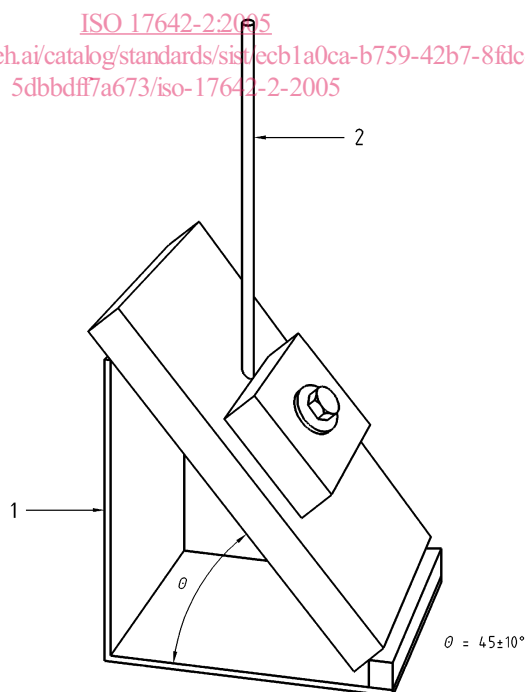

#### Key

- 1 Test jig
- 2 Welding consumable

Figure 2 — Jig used to position test assembly