
Plastics — Compression moulding of test specimens of thermoplastic materials

Plastiques — Moulage par compression des éprouvettes en matières thermoplastiques

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 293:2004

<https://standards.iteh.ai/catalog/standards/sist/afa54b6d-55a8-4f8c-b652-c07ecd32e9b5/iso-293-2004>



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 293:2004

<https://standards.iteh.ai/catalog/standards/sist/afa54b6d-55a8-4f8c-b652-c07ecd32e9b5/iso-293-2004>

© ISO 2004

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

	Page
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Apparatus	2
5 Procedure	4
6 Inspection of the moulded specimens or sheets	6
7 Specimen preparation report	6

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 293:2004](https://standards.iteh.ai/catalog/standards/sist/afa54b6d-55a8-4f8c-b652-c07ecd32e9b5/iso-293-2004)

<https://standards.iteh.ai/catalog/standards/sist/afa54b6d-55a8-4f8c-b652-c07ecd32e9b5/iso-293-2004>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 293 was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 9, *Thermoplastic materials*.

This third edition cancels and replaces the second edition (ISO 293:1986), of which it constitutes a minor revision intended, above all, to update the normative references (Clause 2).

iTeh STANDARD PREVIEW
(standards.iteh.ai)
ISO 293:2004
<https://standards.iteh.ai/catalog/standards/sist/afa54b6d-55a8-4f8c-b652-c07ecd32e9b5/iso-293-2004>

Introduction

For reproducible test results, specimens with a defined state are required. In contrast to injection moulding, the aim of compression moulding is to produce test specimens and sheets for machining or stamping of test specimens that are homogeneous and isotropic.

In the process of compression moulding, mixing of material takes place on a negligible scale. Granules and powders fuse only at their surfaces and preforms (milled sheets) are only partially softened.

Isotropic and homogeneous specimens can, therefore, only be obtained when the moulding material is itself homogeneous and isotropic. This has to be considered when processing multiphase materials, such as ABS, which retain their internal structure.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO 293:2004](https://standards.iteh.ai/catalog/standards/sist/afa54b6d-55a8-4f8c-b652-c07ecd32e9b5/iso-293-2004)

<https://standards.iteh.ai/catalog/standards/sist/afa54b6d-55a8-4f8c-b652-c07ecd32e9b5/iso-293-2004>

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 293:2004

<https://standards.iteh.ai/catalog/standards/sist/afa54b6d-55a8-4f8c-b652-c07ecd32e9b5/iso-293-2004>

Plastics — Compression moulding of test specimens of thermoplastic materials

1 Scope

This International Standard specifies the general principles and the procedures to be followed with thermoplastics in the preparation of compression-moulded test specimens, and sheets from which test specimens may be machined or stamped.

In order to obtain mouldings in a reproducible state, the main steps of the procedure, including four different cooling methods, are standardized. For each material, the required moulding temperature and cooling methods are as specified in the appropriate International Standard for the material or as agreed between the interested parties.

The procedure is not recommended for reinforced thermoplastics.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 293:2004

<https://standards.iteh.ai/catalog/standards/sist/afa54b6d-55a8-4f8c-b652->

ISO 286-1, *Geometrical product specifications (GPS) — ISO coding system for tolerances of linear sizes — Part 1: Bases of tolerances and fits*

ISO 4287, *Geometrical Product Specifications (GPS) — Surface texture: Profile method — Terms, definitions and surface texture parameters*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

moulding temperature

temperature of the mould or the press during the preheating and moulding time, measured in the nearest vicinity to the moulded material

3.2

demoulding temperature

temperature of the mould or the press platens at the end of the cooling time, measured in the nearest vicinity to the moulded material

NOTE For positive moulds, holes are normally drilled in the mould for measuring the temperatures defined in 3.1 and 3.2.

3.3

preheating time

time required to heat the material in the mould up to the moulding temperature while maintaining the contact pressure

3.4
moulding time

time during which full pressure is applied while maintaining the moulding temperature

3.5
average cooling rate (non-linear)

rate of cooling by a constant flow of the cooling fluid, calculated by dividing the difference between moulding and demoulding temperatures by the time required to cool the mould to the demoulding temperature

NOTE The average cooling rate is usually expressed in degrees Celsius per minute.

3.6
cooling rate

constant rate of cooling in a defined temperature range obtained by controlling the flow of the cooling fluid in such a way that over each 10 min interval the deviation from this specified cooling rate does not exceed the specified tolerance

NOTE The cooling rate is usually expressed in degrees Celsius per hour.

4 Apparatus

4.1 Moulding press

The press shall have a clamping force capable of applying a pressure (conventionally given as the ratio of the clamping force to the area of the mould cavity) of at least 10 MPa.

The pressure shall be maintained to within 10 % of the specified pressure during the moulding cycle.

The platens shall be capable of
a) being heated to at least 240 °C;

b) being cooled at a rate given in Table 1.

The difference between the temperatures of any points of the mould surfaces shall not vary by more than ± 2 °C during heating and ± 4 °C during cooling.

When the heating and cooling system is incorporated in the mould, it shall comply with the same conditions.

The platens or mould shall be heated either by high-pressure steam, by a heat-conducting fluid in an appropriate channel system, or by using electric heating elements. The platens or mould are cooled by a heat-conducting fluid (usually cold water) in a channel system.

For quench cooling (see method C in Table 1), two presses shall be used, one for heating during moulding and the other for cooling.

For a specified cooling method, the flow rate of the heat-conducting fluid shall be predetermined in a test without any material in the mould.

The temperature may be continuously controlled in the centre between the upper and lower platen of the press.

4.2 Moulds

4.2.1 General

The characteristics of the test specimens prepared by using different types of moulds are not the same. In particular, the mechanical properties depend on the pressure applied to the material during cooling.

In general, two types of moulds, “flash moulds” (see Figure 1) and “positive moulds” (see Figure 2), are used for compression moulding test specimens of thermoplastics.



Figure 1 — Types of flash (“picture frame”) moulds

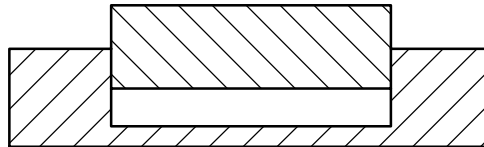


Figure 2 — Positive-type mould

Flash moulds permit excess moulding material to be squeezed out and do not exert moulding pressure on the moulding material during cooling. They are particularly convenient for preparing test specimens or panels of similar thickness or comparable levels of low internal stress.

With positive moulds, the full moulding pressure, neglecting friction, is exerted on the material during cooling. The thickness, stress and density of the resulting mouldings depend on mould construction, size of material charge and the moulding and cooling conditions. This type of mould produces consolidated test specimens with moulded surfaces and is therefore particularly suitable for obtaining flat surfaces or suppressing the formation of voids within test specimens.

ISO 293:2004

<https://standards.iteh.ai/catalog/standards/sist/afa54b6d-55a8-4f8c-b652-c07ecd32e9b5/iso-293-2004>

4.2.2 Fabrication

The moulds shall be made of materials capable of withstanding the moulding temperature and pressure. The surfaces in contact with the material shall be polished to obtain good surface conditions on the specimens (recommended surface roughness $0,16Ra$, see ISO 4287). Specimen removal can be made easier by chromium plating these surfaces. For specimens of small dimensions, a 2° taper is strongly recommended.

Blind holes may be drilled in the mould so that temperature can be measured in the vicinity of the moulded material by using thermocouples or mercury thermometers.

Depending on the performance of the press (see 4.1), the moulds may have built-in heating and/or cooling devices similar to those described for the press platens.

An alloy steel, resistant to mechanical shock and heat-treated to provide a tensile strength of 2 200 MPa, will generally be satisfactory for the moulds. However, in the special case of PVC moulding materials, the use of martensite stainless steel treated to provide a tensile strength of 1 050 MPa is recommended.

4.2.3 Types

4.2.3.1 General

The type of mould used shall be capable of producing test specimens of the types and states specified in the appropriate International Standard for the material or shall be agreed upon between the interested parties.