
**Light conveyor belts — Determination of
the maximum tensile strength**

*Courroies transporteuses légères — Détermination de la résistance
maximale à la traction*

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 21180:2005

<https://standards.iteh.ai/catalog/standards/sist/4d577755-c863-4430-84dc-990e48e05b81/iso-21180-2005>



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 21180:2005

<https://standards.iteh.ai/catalog/standards/sist/4d577755-c863-4430-84dc-990e48e05b81/iso-21180-2005>

© ISO 2005

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 21180 was prepared by Technical Committee ISO/TC 41, *Pulleys and belts (including veebelts)*, Subcommittee SC 3, *Conveyor belts*.

This International Standard is based on EN 1722:1999, prepared by CEN/TC 188.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 21180:2005
<https://standards.iteh.ai/catalog/standards/sist/4d577755-c863-4430-84dc-990e48e05b81/iso-21180-2005>

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 21180:2005

<https://standards.iteh.ai/catalog/standards/sist/4d577755-c863-4430-84dc-990e48e05b81/iso-21180-2005>

Light conveyor belts — Determination of the maximum tensile strength

1 Scope

This International Standard specifies a test method for the determination of the maximum tensile strength of light conveyor belts according to ISO 21183-1, or of other conveyor belts where ISO 283 is not applicable.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 283¹⁾, *Textile conveyor belts — Full thickness tensile strength, elongation at break and elongation at the reference load — Test method*

ISO 7500-1:2004, *Metallic materials — Verification of static uniaxial testing machines — Part 1: Tension/compression testing machines — Verification and calibration of the force-measuring system*

ISO 18573:2003, *Conveyor belts — Test atmospheres and conditioning periods*

ISO 21183-1, *Light conveyor belts — Part 1: Principal characteristics and applications*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

tensile load

force per unit of belt width, expressed in newtons per millimetre

NOTE 1 In light conveyor belt technology, the definition of tensile load deviates from that commonly used. It is measured in force per unit of belt width in newtons per millimetre, whilst normally it is defined as a stress, i.e. a force per unit of cross section, in newtons per square millimetre.

NOTE 2 In light conveyor belt technology, the symbol for the tensile load is k and the maximum tensile strength is designated as k_{\max} , expressed in newtons per millimetre

NOTE 3 In EN 10002-1:2001, the symbol k is used to represent the coefficient of proportionality.

1) To be published. (Revision of ISO 283-1:2000)

4 Symbols

The following symbols are used in this document (see also Figure 1):

F_{break} is the tensile force in the test piece at break, in newtons;

F_{max} is the maximum tensile force in the test piece, in newtons;

NOTE F_{max} and F_{break} can be the same but are not necessarily so.

k_{max} is the value of F_{max} divided by the width, in millimetres, of the narrowest part of the test piece at the start of the test

Δl is the actual increase in length of the test piece between the jaws, in millimetres, during the test

Δl_{break} is the increase in length of the test piece between the jaws, in millimetres, taken at F_{break}


Δl_{max} is the increase in length of the test piece between the jaws, in millimetres, taken at F_{max}

Δl_{m} is the increase in length of the distance between the datum marks (see 7.4), in millimetres

ε_{max} is the value of Δl_{max} or Δl_{m} divided by the initial length of the test piece or the initial distance between the datum marks and expressed in percent.

iTeh STANDARD PREVIEW

(standards.iteh.ai)

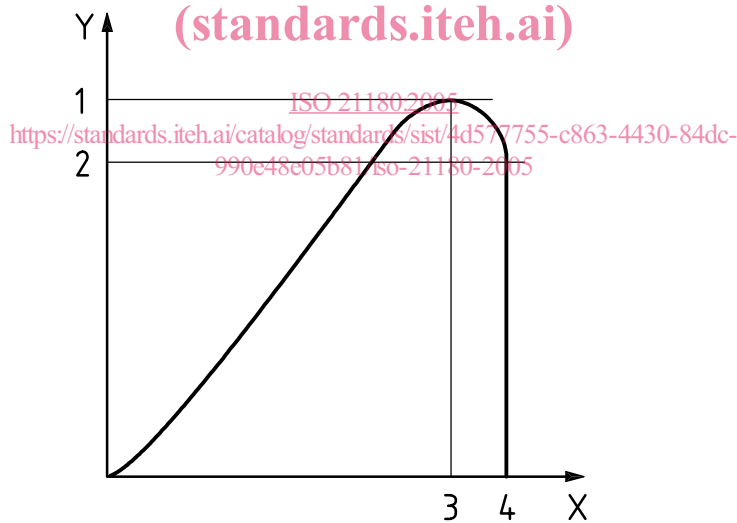

Key

X tensile force, F , N

Y elongation of test piece, Δl , mm

1 F_{max}

2 F_{break}

3 Δl_{max}

4 Δl_{break}

Figure 1 — Dynamometer graph

5 Principle

A test piece, cut from the full thickness of the conveyor belt in the longitudinal direction, is tested and the tensile force recorded as a function of the belt elongation. From that graph, the maximum tensile strength is determined by calculation.

6 Apparatus


6.1 Tensile testing machine (dynamometer), capable of applying a load suitable for the maximum tensile strength of the test piece and with a force-measuring system in accordance with ISO 7500-1:2004, Class of machine 3 or better (e.g. Class of machine 2).

7 Test pieces

7.1 Shape and dimensions

The test pieces shall be cut from the full thickness of the conveyor belt in the longitudinal direction. Their shape and dimensions shall be in accordance with Figure 2. The test pieces shall not be tested sooner than five days after manufacture.

Dimensions in millimetres

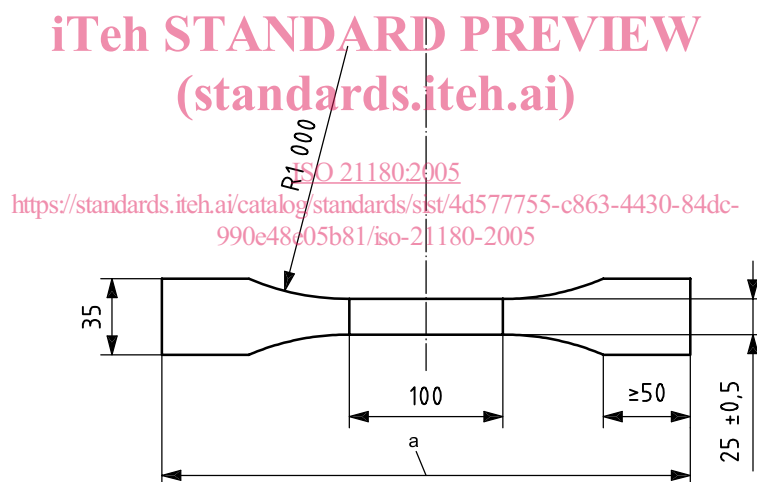

^a 220 + (2 × length of a jaw).


Figure 2 — Shape and dimensions of test piece

For certain types of belt construction, the shape of the test pieces illustrated in Figure 2 may produce abnormal and unequal stress distributions in the threads, causing systematic slip in the grips, giving misleading results. Under such circumstances the test may be conducted using test pieces of a different shape (see, for example, ISO 1421 and ISO 13941-1).

7.2 Number and selection

Five test pieces shall be taken in the longitudinal direction of the conveyor belt.

The test pieces shall be selected in accordance with Figure 3.

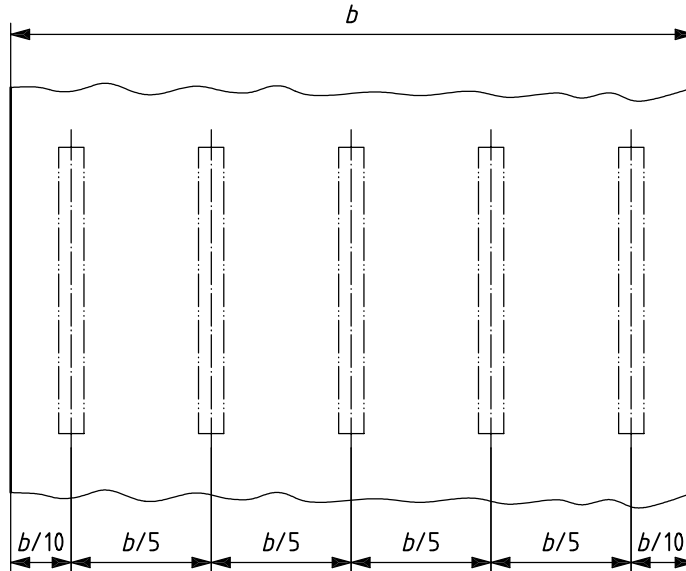

iTeh STANDARD PREVIEW

Figure 3 — Distribution of test piece selection

ISO 21180:2005

<https://standards.iteh.ai/catalog/standards/sist/4d577755-c863-4430-84dc-990e48e05b81/iso-21180-2005>

7.3 Conditioning

Before testing, condition the test pieces in accordance with ISO 18573:2003, Atmosphere B, for 24 h, except that, if the light conveyor belt consists of materials with a high absorption of moisture, e.g. cotton or polyamide, condition the test pieces for 48 h.

7.4 Preparation

On the longitudinal axis of the test piece, draw two datum marks equidistant from the centre and $(100 \pm 0,5)$ mm apart (see Figure 2).

8 Procedure

Place the ends of the test piece between the jaws of the tensile testing machine (6.1) such that the test piece is straight without using force. Ensure that the free length between the jaws is $220 \text{ mm} \pm 5 \text{ mm}$ and that there is no slippage of the test piece in the jaws during the test.

Slippage can be minimized by rubbing rosin on the portion of the test piece that will be in the jaws, removing any excess rosin and enclosing both sides of the rosin-coated test piece with coarse emery cloth. The emery cloth should be folded over the ends of the test piece with the coarse side of the cloth next to the rosin-coated surfaces.

Exert a continuous (uninterrupted) tensile stress on the test piece, at a rate of (100 ± 10) mm/min.

Record the tensile force as a function of the belt elongation. Continue at least until the maximum tensile force F_{\max} is reached or, optionally, until breakage occurs. If testing until breakage occurs, observe whether the break occurs between the two datum marks on the test piece. If any test pieces break outside this central portion or if they slip in the jaws, do not take these results into account when calculating the mean but repeat the test using new test pieces.

9 Calculation and expression of results

Read the maximum tensile force, F_{\max} , from the graph as shown in Figure 1.

Divide F_{\max} by the smallest width of the test piece (25 mm), thus giving the maximum tensile strength k_{\max} :

$$k_{\max} = \frac{F_{\max}}{25 \text{ mm}} \text{ N/mm}$$

If required, calculate the elongation ε_{\max} taking place at F_{\max} from Δl_m (in millimetres) and record it as a percentage as follows:

$$\varepsilon_{\max} = \frac{\Delta l_m}{100 \text{ mm}} \times 100 \%$$

If no measuring device for Δl_m (in millimetres) is available, ε_{\max} may also be calculated from Δl_{\max} as follows:

$$\varepsilon_{\max} = \frac{\Delta l_{\max}}{220 \text{ mm}} \times 100 \%$$

However, this method has the disadvantage that the result is influenced by the different widths of the test piece (25 mm to 35 mm) and is only correct if there has been no slippage of the test piece in the jaws of the apparatus.

If the test was continued until breakage occurred, k_{break} and $\varepsilon_{\text{break}}$ may analogously be determined from F_{break} .

Calculate the individual k_{\max} values of all five test pieces and take the arithmetical mean of the five values. Use the same procedure for the calculation of ε_{\max} , if required. Determine the values for the breaking conditions in the same way, if applicable.

10 Test report

The test report shall include the following information:

- a) a complete designation of the tested conveyor belt material and the manufacturing date;
- b) reference to this International Standard;
- c) test room temperature and relative humidity;
- d) conditioning period;
- e) results of the test in accordance with Clause 9;
- f) date of test.