



Standard Test Method for Measurement of Load-Carrying Capacity of Lubricating Grease (Timken Method)¹

This standard is issued under the fixed designation D 2509; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

This test method was adopted as an ASTM-IP Standard.

1. Scope

1.1 This test method covers the determination of the load-carrying capacity of lubricating greases by means of the Timken Extreme Pressure Tester.

1.2 The values stated in SI units are to be regarded as the standard. The values given in parentheses are for information only.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.* For specific precautionary statements see Note 1, Note 2, and Note 4.

2. Referenced Documents

2.1 ASTM Standards:

D 235 Specification for Mineral Spirits (Petroleum Spirits) (Hydrocarbon Dry Cleaning Solvent)²

D 329 Specification for Acetone²

3. Terminology

3.1 Definitions:

3.1.1 *load-carrying capacity, of a lubricating grease, n*—the maximum load or pressure that can be sustained by a lubricating grease without failure of the sliding contact surfaces as evidenced by seizure or welding.

3.1.1.1 *Discussion*—The values of load carrying capacity of a lubricating grease vary according to test method.

3.1.2 *scoring, in tribology, n*—a severe form of wear characterized by the formation of extensive grooves and scratches in the direction of sliding.

3.1.2.1 *Discussion*—When the lubricant film is substantially maintained, a smooth scar is obtained on the test block, but

when there is a breakdown of the lubricant film, scoring or surface failure of the test block takes place as shown in Fig. 1.³ In its simplest and recognized form, scoring is characterized by a wide scar on the test block and by the transfer of metal from the test block to the contacting surface of the test cup. The form of surface failure more usually encountered, however, consists of a comparatively smooth scar, which shows local damage that usually extends beyond the width of the scar. Scratches or striations that occur in an otherwise smooth scar and that do not extend beyond the width of the scar are not considered scoring in this test method.

3.1.3 *seizure or welding, n*—localized fusion of rubbing metal, usually indicated by streaks of transferred metal, increased friction and wear, or unusual noise and vibration.

3.1.4 *wear, n*—the removal of metal from a rubbing surface by mechanical action, or by a combination of mechanical and chemical actions.

3.2 Definitions of Terms Specific to This Standard:

3.2.1 *OK value, n*—the maximum mass (weight) added to the load lever mass (weight) pan, at which no scoring or seizure occurs.

3.2.2 *score value, n*—the minimum mass (weight) added to the load lever mass (weight) pan, at which scoring or seizure occurs.

4. Summary of Test Method

4.1 The tester is operated with a steel test cup rotating against a steel test block. The rotating speed is 123.71 ± 0.77 m/min (405.88 ± 2.54 ft/min) which is equivalent to a spindle speed of 800 ± 5 rpm. Grease samples are brought to and applied at $24 \pm 6^\circ\text{C}$ ($75 \pm 10^\circ\text{F}$).

4.2 Two determinations are made: the minimum load (score value) that will rupture the lubricant film being tested between the rotating cup and the stationary block and cause abrasion; and the maximum load (OK value) at which the rotating cup will not rupture the lubricant film and cause abrasion between

¹ This method is under the jurisdiction of ASTM Committee D02 on Petroleum Products and Lubricants and is the direct responsibility of Subcommittee D02.G on Lubricating Grease.

Current edition approved Feb. 15, 1993. Published May 1993. Originally published as D 2509 – 66 T. Last previous edition D 2509 – 91.

² *Annual Book of ASTM Standards*, Vol 06.04.

³ Glossy prints of Fig. 1 are available from ASTM. Request Adjunct No. ADJD2509.

ASTM D 2509



FIG. 1 Test Blocks Showing Various Types of Scar

the rotating cup and the stationary block.

5. Significance and Use

5.1 The test method is used widely for specification purposes and is used to differentiate between greases having low, medium, or high levels of extreme pressure characteristics. The results may not correlate with results from service.

6. Apparatus and Materials

6.1 *Timken Extreme Pressure Tester*, described in detail in Annex A1 and illustrated in Fig. 2.

6.2 *Sample Feed Devices*, for supplying the test specimens with grease are described in Annex A1.

6.3 *Loading Mechanism*, for applying and removing the load mass (weight) without shock at the uniform rate 0.91 to 1.36 kg/s (2 to 3 lb/s). A detailed description is given in Annex A1.

6.4 *Test Cups*,⁴ of carburized steel, having a Rockwell Hardness C Scale Number of 58 to 62, or a Vickers Hardness Number of 653 to 746. The cups have a width of 13.06 ± 0.05 mm (0.514 ± 0.002 in.), a perimeter of 154.51 ± 0.23 mm (6.083 ± 0.009 in.), a diameter of $49.22 +0.025, -0.127$ mm ($1.938 +0.001, -0.005$ in.), and a maximum radial run-out of 0.013 mm (0.0005 in.). The axial surface roughness should lie between 0.51 and 0.76 μm (20 and 30 $\mu\text{in.}$) C.L.A.

6.5 *Test Blocks*⁵ with test surfaces 12.32 ± 0.10 mm (0.485 ± 0.004 in.) wide and 19.05 ± 0.41 mm (0.750 ± 0.016 in.)

long, of carburized steel, having a Rockwell Hardness C Scale Number of 58 to 62, or a Vickers Hardness Number of 653 to 746. Each block is supplied with four ground faces and the surface roughness should lie between 0.51 and 0.76 μm (20 and 30 $\mu\text{in.}$) C.L.A.

6.6 *Microscope*,⁶ low-power (50 \times to 60 \times), having sufficient clearance under objective to accommodate the test block. It should be fitted with a filar micrometer so that the scar width may be measured with an accuracy of ± 0.05 mm (± 0.002 in.).

6.7 *Timer*, graduated in minutes and seconds.

7. Reagents

7.1 *Acetone*, conforming to Specification D 329.

NOTE 1—**Warning:** Extremely flammable. Vapors can cause flash fire.

7.2 *Stoddard Solvent*, conforming to Specification D 235. (White Spirit conforming to British Standard 245, Type I, is considered a functionally equivalent material.)

NOTE 2—**Warning:** Combustible. Vapor harmful.

8. Preparation of Apparatus

8.1 Clean the apparatus with Stoddard solvent (**Warning**—See Note 2.) and acetone (**Warning**—See Note 1.) and blow dry. Shield the sump outlet and disconnect the oil pump to eliminate wear on the unused pump. Replace the oil reservoir with the grease feed device.

8.2 Select a new test cup and block, wash with Stoddard solvent, and dry with a clean soft cloth or paper. Immediately

⁴ Available from the Falex Corp. 1020 Airpark Dr., Sugar Grove, IL 60554 under Part No. F-25061.

⁵ Available from Falex Corp. under Part No. F-25001.

⁶ Falex Corp. is a satisfactory source of supply.

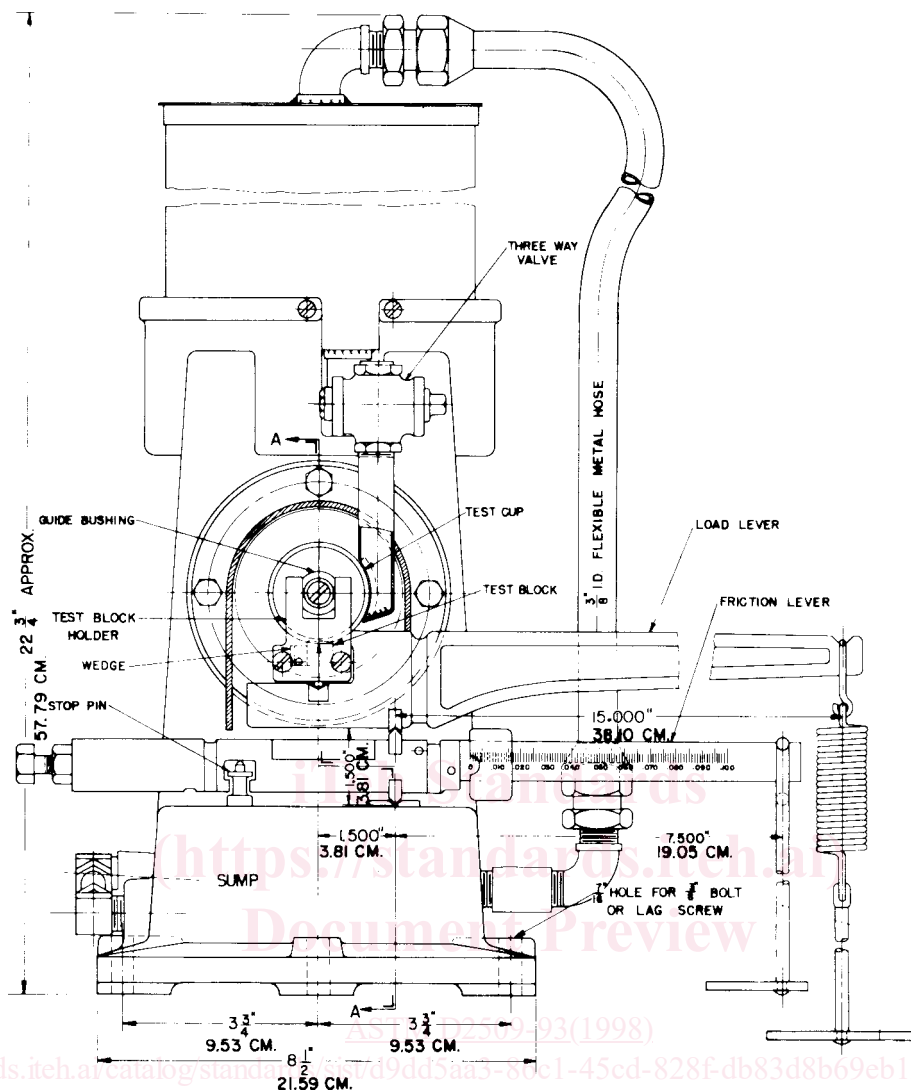


FIG. 2 Timken Tester

before use rinse the test cup and block with acetone and blow them dry. Do not use solvents such as carbon tetrachloride or others that may inherently possess load-carrying properties which may affect the results.

8.3 Assemble the tester carefully (Fig. 3), placing the test cup on the spindle and making certain that it is well seated, drawing it up firmly but avoiding possible distortion from excessive tightening (Note 3). Place the test block in the test block holder and adjust the levers so that all the knife edges are in proper alignment. Exercise special care in placing the stirrup of the spring-weight platform assembly (selection of which will depend on the loading device) in the groove of the load-lever arm to avoid premature shock to the test block when the load is applied. To ensure the test block, test block holder, and lever arms are properly aligned and seated, coat the test block and test cup with the grease to be tested, and rotate the machine slowly for a few revolutions either by hand or by suitable control mechanism. If the parts are in alignment, the grease will be wiped off the cup over its entire width.

NOTE 3—At this point it is recommended that a dial indicator be used to check that the radial run-out of the cup *in situ* does not exceed 0.001 in.

(0.025 mm) total indicator movement.


9. Procedure

9.1 Bring the grease to $24 \pm 6^\circ\text{C}$ ($75 \pm 10^\circ\text{F}$). Fill the grease-feeding device with grease, avoiding the inclusion of air bubbles. Apply a film of grease to the test cup and block and thoroughly grease the guide bushing with the test grease. Do not heat the grease.

9.2 Apply the grease at $25 \pm 6^\circ\text{C}$ ($75 \pm 10^\circ\text{F}$) to the test block through the grease-feed mechanism at the uniform rate of $45 \pm 9 \text{ g/min}$ ($0.1 \pm 0.02 \text{ lb/min}$). Start the motor and run for 30 s to break-in. If the equipment used is equipped with acceleration control, start the motor and increase the spindle speed gradually to achieve $800 \pm 5 \text{ rpm}$ after 15 s. Run for a further 15 s to complete the break-in.

9.3 After the break-in period of 30 s, start the timer and apply at 8.9 to 13.3 N/s (2 to 3 lbf/s), a load of 133.4 N (30 lbf). (A starting load of 133.4 N (30 lbf/s) is recommended. The load lever arm, spring, and mass (weight) carrier assembly are not considered part of the applied load.) Then allow the machine to run at $800 \pm 5 \text{ rpm}$ for 10 min \pm 15 s after load

ASTM D 2509

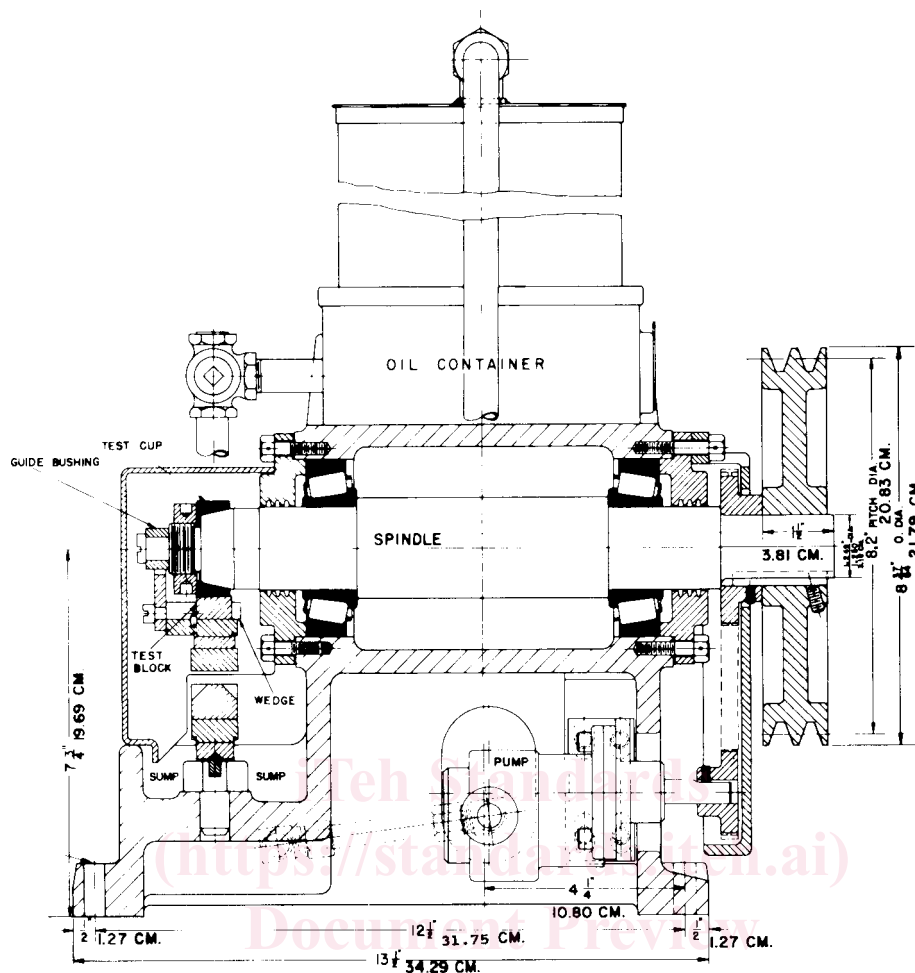

SECTION "A-A"
FIG. 2 (continued)

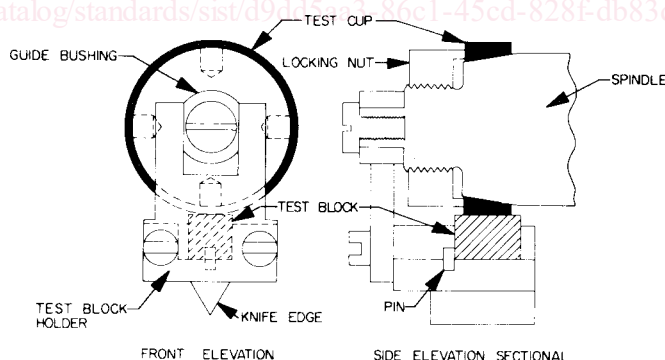


FIG. 3 Assembly of Tester Showing Test Pieces

application is initiated, unless a score is detected before that period. Excessive noise and fluctuations in the spindle speed indicate scoring of the test components. Stop the machine at once, turn off the supply of grease lubricant, and remove the load.

9.4 If, after the load has been applied, scoring is evident by vibration or noise, stop the tester at once, remove the load, and turn off the flow of lubricant. Since the excessive heat developed with deep scoring may alter the surface characteristics of the entire block, discard the test block.

NOTE 4—**Warning:** The machine and test pieces may be hot at this point and care should be exercised in their handling.

9.5 If no scoring is detected, allow the tester to run for 10 min ± 15 s from the start of the application of the load. At the end of the 10 min ± 15 s period, reverse the loading device and remove the load from the lever arm. Turn off the motor, allow the spindle to come to rest, then turn off the flow of grease. Remove the load lever and inspect the condition of the test block surface. The lubricant has failed at the imposed load if the wear scar indicates any scoring or welding.