

SLOVENSKI STANDARD
oSIST prEN 12681-1:2016
01-maj-2016

Livarstvo - Radiografsko preskušanje - 1. del: Filmske tehnike

Founding - Radiographic testing - Part 1: Film techniques

Gießereiwesen - Durchstrahlungsprüfung - Teil 1: Filmtechniken

Fonderie - Contrôle par radiographie - Partie 1 : Techniques à l'aide de films

Ta slovenski standard je istoveten z: prEN 12681-1

<https://standards.iteh.ai/catalog/standards/sist/b748d01b-3dca-4b0e-8ff1-3ebc1a70863d/sist-en-12681-1-2018>

ICS:

77.040.20	Neporušitveno preskušanje kovin	Non-destructive testing of metals
-----------	---------------------------------	-----------------------------------

oSIST prEN 12681-1:2016

en,fr,de

EUROPEAN STANDARD
NORME EUROPÉENNE
EUROPÄISCHE NORM

DRAFT
prEN 12681-1

March 2016

ICS 77.040.20

Will supersede EN 12681:2003

English Version

Founding - Radiographic testing - Part 1: Film techniques

Fonderie - Contrôle par radiographie - Partie 1 :
Techniques à l'aide de films

Gießereiwesen - Durchstrahlungsprüfung - Teil 1:
Filmtechniken

This draft European Standard is submitted to CEN members for enquiry. It has been drawn up by the Technical Committee CEN/TC 190.

If this draft becomes a European Standard, CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

This draft European Standard was established by CEN in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.

Recipients of this draft are invited to submit, with their comments, notification of any relevant patent rights of which they are aware and to provide supporting documentation.

Warning : This document is not a European Standard. It is distributed for review and comments. It is subject to change without notice and shall not be referred to as a European Standard.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Avenue Marnix 17, B-1000 Brussels

Contents

Page

European foreword.....	4
Introduction	5
1 Scope.....	6
2 Normative references.....	6
3 Terms and definitions	7
4 Symbols and abbreviations	8
5 Classification of radiographic techniques.....	9
6 Requirements.....	9
6.1 General preparations.....	9
6.1.1 Protection against ionizing radiation.....	9
6.1.2 Surface preparation and stage of manufacture.....	9
6.2 Agreements	9
6.3 Personnel qualification.....	10
7 Test arrangements.....	10
7.1 General.....	10
7.2 Single wall radiography of plane areas.....	10
7.3 Single wall radiography of curved areas	10
7.4 Double wall radiography of plane and curved areas	10
7.5 Choice of test arrangements for complex geometries	11
7.6 Acceptable test area dimensions.....	11
8 Choice of tube voltage and radiation source	16
8.1 X-ray devices up to 1 000 kV	16
8.2 Other radiation sources.....	17
9 Film systems and metal screens	17
10 Reduction of scattered radiation.....	19
10.1 Metal filters and collimators.....	19
10.2 Interception of backscattered radiation.....	19
11 Source-to-object distance.....	20
12 Optical density <i>D</i> of radiograph	22
13 Film processing and viewing.....	22
13.1 Processing.....	22
13.2 Film viewing conditions.....	22
14 Techniques for increasing the covered thickness range	23
14.1 General.....	23
14.2 Multiple film technique.....	23
14.3 Contrast decreasing by higher radiation energy	24
14.4 Contrast decreasing by beam hardening.....	24
14.5 Contrast decreasing by thickness equalization.....	25

15	Radiographs.....	25
15.1	Identification of radiograph, test area, film position plan.....	25
15.2	Marking of the test areas	25
15.3	Overlap of films	25
16	Verification of image quality	25
17	Influence of crystalline structure	26
18	Acceptance criteria	26
18.1	General	26
18.2	Severity levels	26
18.3	Wall section zones	26
19	Test report	27
	Annex A (normative) Minimum image quality values.....	29
	Annex B (normative) Severity levels for steel castings.....	32
	Annex C (normative) Severity levels for iron castings	35
	Annex D (normative) Severity levels for aluminium alloy and magnesium alloy castings.....	38
	Annex E (normative) Severity levels for copper alloy castings.....	42
	Annex F (normative) Severity levels for titanium and titanium alloy castings.....	44
	Annex G (informative) Significant technical changes between this European Standard and the previous edition.....	46
	Bibliography	47

SIST EN 12681-1:2018

<https://standards.iteh.ai/catalog/standards/sist/b748d01b-3dca-4b0e-8ff1-3ebc1a70863d/sist-en-12681-1-2018>

prEN 12681-1:2016 (E)**European foreword**

This document (prEN 12681-1:2016) has been prepared by Technical Committee CEN/TC 190 “Foundry Technology”, the secretariat of which is held by DIN.

This document is currently submitted to the CEN Enquiry.

This document will supersede EN 12681:2003.

Within its programme of work, Technical Committee CEN/TC 190 requested CEN/TC 190/WG 10 “Inner defects” to revise and to split the following standard:

EN 12681:2003, *Founding — Radiographic testing*

into:

- prEN 12681-1, *Founding — Radiographic testing — Part 1: Film techniques* (replacement for EN 12681:2003)
- prEN 12681-2, *Founding — Radiographic testing — Part 2: Techniques with digital detectors* (new issue and part of EN 12681:2003)

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN 12681-1:2018

<https://standards.iteh.ai/catalog/standards/sist/b748d01b-3dca-4b0e-8ff1-3ebc1a70863d/sist-en-12681-1-2018>

Introduction

Radiography can be used to detect internal discontinuities in a casting. The discontinuities can be gas holes, non-metallic inclusions, shrinkage, cracks, inserts or chills or inclusions that have lower or higher densities than the parent metal. This European Standard gives acceptance criteria through severity levels.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN 12681-1:2018

<https://standards.iteh.ai/catalog/standards/sist/b748d01b-3dca-4b0e-8ff1-3ebc1a70863d/sist-en-12681-1-2018>

1 Scope

This European Standard gives specific procedures for industrial X-ray and gamma radiography for discontinuity detection purposes, using NDT (Non-destructive testing) film techniques. This part of EN 12681 specifies the requirements for film radiographic testing of castings.

Films after exposure and processing become radiographs with different area of optical density. Radiographs are viewed and evaluated using industrial radiographic illuminators.

This part of EN 12681 specifies the recommended procedure for the choice of operating condition selection and radiographic practice.

These procedures are applicable to castings produced by any casting process, especially for steel, cast iron, aluminium, cobalt, copper, magnesium, nickel, titanium, zinc and any alloys of them.

NOTE This European Standard complies with EN ISO 5579.

This part of this European Standard does not apply to:

- radiographic testing of castings for aerospace applications (see prEN 2002-21);
- radiographic testing of welded joints (see EN ISO 17636-1);
- radiography with digital detectors (see prEN 12681-2);
- radiosopic testing (see EN 13068, all parts).

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 12543, *Non-destructive testing — Characteristics of focal spots in industrial X-ray systems for use in non-destructive testing (all parts)*

EN 12679, *Non-destructive testing - Determination of the size of industrial radiographic sources - Radiographic method*

EN 25580, *Non-destructive testing - Industrial radiographic illuminators - Minimum requirements (ISO 5580:1985)*

EN ISO 5579:2013, *Non-destructive testing - Radiographic testing of metallic materials using film and X-ray or gamma rays - Basic rules (ISO 5579:2013)*

EN ISO 9712, *Non-destructive testing - Qualification and certification of NDT personnel (ISO 9712)*

EN ISO 11699-1, *Non-destructive testing - Industrial radiographic film - Part 1: Classification of film systems for industrial radiography (ISO 11699-1)*

EN ISO 11699-2, *Non-destructive testing - Industrial radiographic films - Part 2: Control of film processing by means of reference values (ISO 11699-2)*

EN ISO 19232-1, *Non-destructive testing - Image quality of radiographs - Part 1: Determination of the image quality value using wire-type image quality indicators (ISO 19232-1)*

EN ISO 19232-2, *Non-destructive testing - Image quality of radiographs - Part 2: Determination of the image quality value using step/hole-type image quality indicators (ISO 19232-2)*

EN ISO 19232-4, *Non-destructive testing - Image quality of radiographs - Part 4: Experimental evaluation of image quality values and image quality tables (ISO 19232-4)*

ISO 5576, *Non-destructive testing — Industrial X-ray and gamma-ray radiology — Vocabulary*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 5576, EN ISO 5579 and the following apply.

3.1

wall thickness

t

thickness as measured on the casting

3.2

nominal wall thickness

t_n

thickness as specified on the drawing

3.3

penetrated thickness

w

thickness of material in the direction of the radiation beam calculated on the basis of the real thicknesses of all penetrated walls

3.4

source size

d

size of the radiation source or focal spot size

[SOURCE: EN ISO 5579:2013, definition 3.4]

3.5

object-to-film distance

b

largest (maximum) distance between the source side of the radiographed part of the test object and the film surface measured along the central axis of the radiation beam

3.6

source-to-object distance

f

distance between the source of radiation and the source side of the test object, most distant from the film, measured along the central axis of the radiation beam

prEN 12681-1:2016 (E)

3.7

source-to-film distance**SFD**

distance between the source of radiation and the film measured in the direction of the beam

Note 1 to entry: $SFD = f + b$

where

f source-to-object distance;

b object-to-film distance.

[SOURCE: EN ISO 5579:2013, definition 3.5, modified – description in words presented as formula]

4 Symbols and abbreviations

For the purposes of this document, the symbols and abbreviations given in Table 1 apply.

Table 1 — Symbols and abbreviations

symbol or abbreviation	Term	Clause, Figure, Annex
b	object-to-film distance	3.5
d	source size	3.4
D	optical density of film	Clause 12 14.2 Clause 16 Figure 15
f	source-to-object distance	3.6
F	Film	Figure 1
IQI	image quality indicator	Clause 16 Annex A
S	source of radiation	Figure 1
SFD	source-to film-distance	3.7
t	wall thickness	3.1 Figure 1
t_n	nominal wall thickness	3.2 Annexes B to F
w	penetrated thickness	3.3

5 Classification of radiographic techniques

The radiographic techniques are divided into two classes:

- Class A: basic techniques;
- Class B: improved techniques.

It is recommended to perform the testing according to class A, if not otherwise specified in the order. Class B techniques will be used when class A might be insufficiently sensitive.

If, for technical or industrial reasons, it is not possible to meet one of the conditions specified for class B, such as the type of radiation source or the source-to-object distance f , it may be agreed by contracting parties that the condition selected may be what is specified for class A. In film radiography the loss of sensitivity shall be compensated by an increase of minimum optical density to 3,0 or by selection of a two class better film system. The other conditions for class B remain unchanged, especially the image quality achieved. Because of the better sensitivity compared to class A, the test specimen may be regarded as being examined to class B. This does not apply if the special SFD reductions as specified in Clause 11 for test arrangements Figure 3 and Figure 4 are used.

6 Requirements

6.1 General preparations

6.1.1 Protection against ionizing radiation

Local, national or international safety precautions shall be strictly applied, when using ionizing radiation.

WARNING — Exposure of any part of the human body to X-rays or gamma-rays can be highly injurious to health. Wherever X-ray equipment or radioactive sources are in use, appropriate legal requirements shall be applied.

6.1.2 Surface preparation and stage of manufacture

In general, surface preparation is not necessary, but where surface imperfections can cause difficulty in detecting defects, the surface shall be ground smooth.

Unless otherwise specified radiography shall be carried out after the final stage of manufacture, e.g. after grinding or heat treatment.

6.2 Agreements

Castings with a complex geometry can include areas which cannot be tested by radiography or can only be partly tested. Such areas shall be identified before starting the radiographic testing. Areas which cannot be tested by radiography shall be noted by all contracting parties and be marked on the film position plan.

The following items shall be agreed:

- a) manufacturing stage at which castings are to be tested;
- b) extent of radiographic testing;
- c) test areas;
- d) surface condition;

prEN 12681-1:2016 (E)

- e) testing class;
- f) information about the film position plan;
- g) marking of test areas on the casting;
- h) image quality;
- i) marking of the radiographs;
- j) acceptance criteria;
- k) any additional items shall be agreed between the contracting parties;
- l) any special requirements.

All requirements shall be agreed between the contracting parties by the time of acceptance of the order.

6.3 Personnel qualification

Unless otherwise agreed, testing shall be performed by personnel qualified in accordance with EN ISO 9712 or equivalent to an appropriate level in the relevant industrial sector.

7 Test arrangements**7.1 General**

The test arrangements to be used shall be in accordance with:

- Figures 1 to 4: for single wall radiography; [EN 12681-1:2018](https://standards.iteh.ai/catalog/standards/sist/b748d01b-3dca-4b0e-8ff1-5ebc977893d/sist-en-12681-1-2018)
- Figures 5 to 7: for double wall radiography;
- Figures 8 to 12: for test areas of complex section.

If these arrangements are not applicable, other arrangements may be used.

7.2 Single wall radiography of plane areas

The test arrangement for single wall radiography of plane areas shall be in accordance with Figure 1.

7.3 Single wall radiography of curved areas

The test arrangement for single wall radiography of curved areas shall be in accordance with either Figures 2, 3 or 4.

NOTE Rigid cassettes can be used if the corresponding increase of b is considered for the calculation of the distance f between the source and source side of the test object (see Clause 10).

7.4 Double wall radiography of plane and curved areas

The test arrangement for double wall radiography of plane and curved areas shall be in accordance with either Figures 5, 6 or 7.

Double wall radiography shall be used, as an overview technique according to Figure 7, if the geometrical conditions make other test arrangements difficult to apply or if there is a better sensitivity for detecting discontinuities by using this technique. It shall be ensured that unacceptable discontinuities are detected with sufficient certainty. The required image quality shall be met.

In the case of test arrangements according to Figures 6 and 7, the discontinuities shall be classified with reference to the single wall thickness. In the case of different wall thicknesses the reference shall be the smaller one.

In the case of test arrangements according to Figure 5, the distance of the source from the surface of the test area shall be minimized provided that the requirements of IQI are met.

7.5 Choice of test arrangements for complex geometries

Unless otherwise agreed, the test arrangements for complex geometry areas shall be in accordance with Figures 8 to 12 (as appropriate).

7.6 Acceptable test area dimensions

The test area to be captured with one radiographic film should be limited in a way that the required optical density according to Clause 12, Table 5 is met in the region of interest.

In addition to the requirements above, the angle of incident radiation in the entire region of interest shall not exceed 30° .

NOTE This value can be larger, if special orientations of discontinuities can be detected in this way or if it is the only way to test areas otherwise impossible to test.

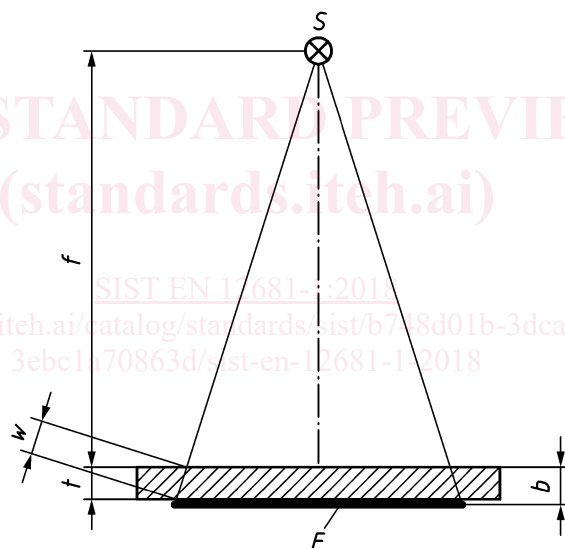


Figure 1 — Test arrangement for single wall radiography of plane areas