
**Paper and board — Determination of
tensile properties —**

**Part 2:
Constant rate of elongation method
(20 mm/min)**

iTeh STANDARD PREVIEW
Papier et carton — Détermination des propriétés de traction —
(standards.iteh.ai) Partie 2: Méthode à gradient d'allongement constant (20 mm/min)

[ISO 1924-2:2008](https://standards.iteh.ai/catalog/standards/sist/7e10a40d-5cf7-4ea2-885a-de376c336ea4/iso-1924-2-2008)

[https://standards.iteh.ai/catalog/standards/sist/7e10a40d-5cf7-4ea2-885a-
de376c336ea4/iso-1924-2-2008](https://standards.iteh.ai/catalog/standards/sist/7e10a40d-5cf7-4ea2-885a-de376c336ea4/iso-1924-2-2008)



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 1924-2:2008

<https://standards.iteh.ai/catalog/standards/sist/7e10a40d-5cf7-4ea2-885a-de376c336ea4/iso-1924-2-2008>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2008

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
Introduction.....	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	2
4 Principle.....	2
5 Apparatus	3
6 Calibration and adjustment of apparatus	4
7 Sampling and preparation of test pieces	4
7.1 Sampling.....	4
7.2 Conditioning	4
7.3 Preparation of test pieces.....	5
8 Procedure	5
9 Calculation and report	6
9.1 General	6
9.2 Tensile strength.....	6
9.3 Tensile index.....	6
9.4 Strain at break.....	6
9.5 Tensile energy absorption.....	7
9.6 Tensile energy absorption index.....	7
9.7 Modulus of elasticity	7
10 Precision.....	8
10.1 General	8
10.2 Repeatability	8
10.3 Reproducibility	8
11 Test report.....	10
Annex A (normative) Calibration of the tensile testing machine	11
Bibliography.....	12

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 1924-2 was prepared by Technical Committee ISO/TC 6, *Paper, board and pulps*, Subcommittee SC 2, *Test methods and quality specifications for paper and board*.

This third edition cancels and replaces the second edition (ISO 1924-2:1994), which has been technically revised with respect to terms and definitions (in order to be in line with the terms and definitions used in ISO 1924-3^[1]). The numbering of clauses and their contents have been changed to be congruent with ISO 1924-3.

ISO 1924 consists of the following parts, under the general title *Paper and board — Determination of tensile properties*¹⁾:

- *Part 2: Constant rate of elongation method (20 mm/min)*
- *Part 3: Constant rate of elongation method (100 mm/min)*

1) ISO 1924-1, *Constant rate of loading method*, was withdrawn in 2004 as it was considered obsolete.

Introduction

The method for determination of tensile properties specified in this part of ISO 1924 is the one most commonly used. It is related to the method specified in ISO 1924-3. In this part of ISO 1924 (ISO 1924-2), the constant rate of elongation applied is 20 mm/min, whereas in ISO 1924-3, the constant rate of elongation applied is 100 mm/min.

Since the results of a tensile test depend on the rate of elongation applied, this part of ISO 1924 and ISO 1924-3 will not give the same results. The rate dependence can vary according to paper grade and is different for tensile strength, strain at break, tensile energy absorption and modulus of elasticity.

NOTE 1 In most cases, the tensile properties can increase by 5 % to 15 % when the rate of elongation is increased from 20 mm/min (180 mm test span length) to 100 mm/min (100 mm test span length).

NOTE 2 In this part of ISO 1924, the same terminology and symbols are used as in ISO 1924-3 and in general literature concerning materials physics and mechanics.

iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 1924-2:2008

<https://standards.iteh.ai/catalog/standards/sist/7e10a40d-5cf7-4ea2-885a-de376c336ea4/iso-1924-2-2008>

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 1924-2:2008

<https://standards.iteh.ai/catalog/standards/sist/7e10a40d-5cf7-4ea2-885a-de376c336ea4/iso-1924-2-2008>

Paper and board — Determination of tensile properties —

Part 2: Constant rate of elongation method (20 mm/min)

1 Scope

This part of ISO 1924 specifies a method for measuring the tensile strength, strain at break and tensile energy absorption of paper and board, using a testing machine operating at a constant rate of elongation (20 mm/min). This part of ISO 1924 also specifies equations for calculating the tensile index, the tensile energy absorption index and the modulus of elasticity.

Testing in conformance with this part of ISO 1924 always includes the measurement of tensile strength. Measurement or calculation of other properties is subject to agreement between the parties concerned.

This part of ISO 1924 is applicable to all papers and boards, including papers with a high strain at break if the results are within the capacity of the testing machine. It also applies to the components of corrugated board but not, however, to corrugated board itself.

This part of ISO 1924 is not applicable to tissue paper and tissue products for which ISO 12625-4^[2] is applicable. For the determination of tensile properties of laboratory sheets, ISO 5270^[3] is recommended.

<https://standards.iteh.ai/catalog/standards/sist/7e10a40d-5cf7-4ea2-885a-de376c336ea4/iso-1924-2-2008>

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 186, *Paper and board — Sampling to determine average quality*

ISO 187, *Paper, board and pulps — Standard atmosphere for conditioning and testing and procedure for monitoring the atmosphere and conditioning of samples*

ISO 534, *Paper and board — Determination of thickness, density and specific volume*

ISO 536, *Paper and board — Determination of grammage*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1 tensile strength
maximum tensile force per unit width that paper and board will withstand before breaking under the conditions defined in this International Standard

3.2 tensile index
tensile strength divided by the grammage

3.3 elongation
increase in length of a test piece

NOTE Elongation is expressed in millimetres.

3.4 strain
ratio of the elongation of a test piece to the initial test length

NOTE 1 Strain is expressed as a percentage of the initial test length.

NOTE 2 The initial test length of the test piece is the same as the initial span between the clamping lines.

3.5 strain at break
ratio of the measured elongation at the moment of rupture of a test piece of paper, when extended under the conditions defined in the standard method of test, to the initial test length

3.6 tensile energy absorption
amount of energy per unit surface area of a test piece when it is strained to the maximum tensile force

NOTE Surface area is calculated as test length multiplied by width.

3.7 tensile energy absorption index
tensile energy absorption divided by the grammage

3.8 modulus of elasticity
maximum slope of the force-elongation curve multiplied by the initial length divided by the width and the thickness of the test piece

NOTE See also Figure 2.

4 Principle

A test piece of given dimensions is strained to break at a constant rate of elongation using a testing machine that records both the tensile force and, if required, the elongation. If the tensile force and elongation are continuously recorded, the strain at break, the tensile energy absorption and the modulus of elasticity may be determined.

From the recorded data, and the knowledge of the grammage of the sample, the tensile index and the tensile energy absorption index may be calculated.

5 Apparatus

5.1 Tensile testing machine, designed to extend a test piece of given dimensions at an appropriate constant rate of elongation (20 mm/min), and to measure the tensile force and, if required, the elongation produced.


The tensile testing machine includes means of measuring and indicating the tensile force to an accuracy of $\pm 1\%$ of the true force and, if required, the elongation to an accuracy of $\pm 0,1\%$ elongation. The tensile force may be recorded as a function of the elongation on an electronic integrator or an equivalent device.

NOTE 1 The accuracy of measurement of elongation is very important. An appropriate extensometer, placed directly on the test piece, is recommended for accurate measurement of true elongation (see ISO 9513, class 1 or class 0,5). This is to avoid the possibility of including in the measurement any apparent elongation which can result from undetected slippage of the test piece in the clamps or from the take-up in the joints of the apparatus. The latter is dependent upon the load applied and the error can increase due to wear of the joints of an apparatus which has been in use for some time. It is advisable that means be applied to limit additional loads, which an extensometer would apply to the test piece, to the required accuracy of the tensile force.

The tensile testing machine also includes two clamps, for holding a test piece of the required width (see 7.3). Each clamp shall be designed to grip the test piece firmly, but without damage or slippage, along a straight line across the full width of the test piece and have a means of adjusting the clamping force. The clamping surfaces of the clamps shall be in the same plane and so aligned that they hold the test piece in that plane throughout the test.

NOTE 2 It is advisable that the clamps grip the test piece between a cylindrical and a flat surface, or between two cylindrical surfaces, with the plane of the test piece tangential to the cylindrical surface. Other types of clamps can be used provided no slippage of, or damage to, the test piece occurs during test.

When the test piece is clamped, the clamping lines shall be parallel to each other within a maximum angle of 1° (see Figure 1). In addition, the clamping lines shall remain perpendicular to the direction of the applied tensile force, and to the long dimension of the test piece, to within a maximum of 1° , while under load (see Figure 1). The distances between the clamping lines shall be adjustable to the test length required to within ± 1 mm.

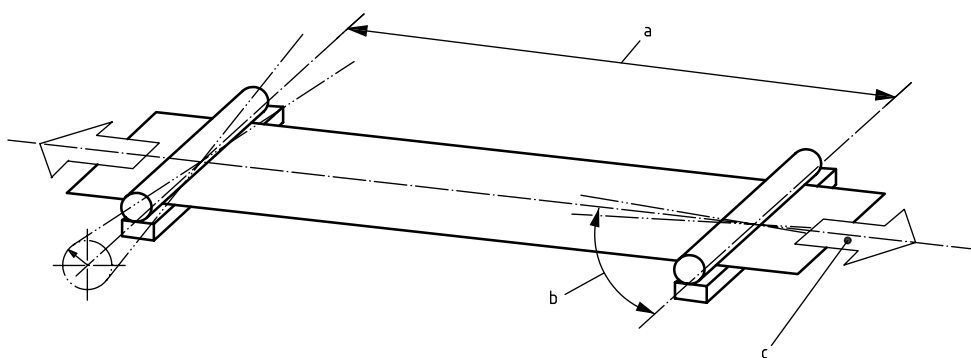

- a Clamping lines parallel to each other within a maximum angle of 1° .
- b Centreline of test piece perpendicular to clamping lines to within a maximum angle of 1° .
- c Tensile force parallel to the test piece centreline to within a maximum angle of 1° .

Figure 1 — Relationship between the clamping lines and the test piece

5.2 Device for cutting test pieces, to the dimensions required (see 7.3).

5.3 Means of measuring the work done, (e.g. an integrator) with an accuracy of $\pm 1\%$. Such devices should be programmable to take account of different initial test lengths.

This apparatus is required if tensile energy absorption is to be determined.

5.4 Means of plotting the force-elongation curve and measuring the maximum slope of the curve, required only if the modulus of elasticity is to be determined.

6 Calibration and adjustment of apparatus

Set up the apparatus as recommended by the manufacturer. If required, calibrate the force-measuring component of the apparatus and the elongation-measuring mechanism as indicated in Annex A.

Position the clamps so that the test length, i.e. the mean distance between the clamping lines, is (180 ± 1) mm.

NOTE 1 In some circumstances, for example a high-stretch paper or a product of limited size (e.g. laboratory sheets), a smaller test length can be used. When such a situation arises, it is recommended that the rate of elongation be adjusted so that its numerical value is $(10 \pm 2,5)\%$ of the unstressed test length. In such cases, it is advisable that the test length used and the rate of elongation be stated in the test report.

Verify that the test length is correct by measuring the distance between the two impressions produced by the clamps when strips of, for example, thin aluminium foil are clamped.

Adjust the rate of separation of the clamps, i.e. the rate of elongation of the test piece, to (20 ± 5) mm/min. Adjust the clamping force so that there is neither slipping of, nor damage to, the test piece.

NOTE 2 For some qualities of paper and board, the test piece can fail quickly, e.g. in less than 5 s, or require more time, e.g. in more than 30 s. In such cases, a different rate of elongation can be used, but it is advisable that this rate be stated in the test report.

7 Sampling and preparation of test pieces

7.1 Sampling

If the tests are being made to evaluate a lot, the sample shall be selected in accordance with ISO 186. If the tests are made on another type of sample, make sure that the specimens taken are representative of the sample received.

7.2 Conditioning

Condition the specimens of paper and board as specified in ISO 187. Keep them in the conditioning atmosphere throughout the test.

This test, like other mechanical tests, is very sensitive to changes in the moisture content of the test piece. Handle the test pieces carefully and avoid touching with bare hands the part of the test piece to be placed between the clamps. Keep the test pieces away from moisture, heat and other influences that may change their moisture content.

7.3 Preparation of test pieces

Carry out the preparation of the test pieces in the same atmospheric conditions used for conditioning the specimens (see 7.2).

From specimens of undamaged paper and board, cut test pieces with a width of $(15 \pm 0,1)$ mm and long enough to be clamped in the clamps. The test length, i.e. the distance between the clamping lines, is (180 ± 1) mm. Avoid touching with bare hands the part of the test piece to be placed between the clamps, and ensure that the test piece has no watermarks, folds and wrinkles. If it is necessary to include watermarks, this fact shall be noted in the test report. The long edges of the test pieces shall be straight, parallel to within $\pm 0,1$ mm over the total clamping length, cleanly cut and undamaged. Cut a sufficient number of test pieces to enable at least ten tests to be made in each direction of interest (machine direction, cross-direction).

If the tensile index or tensile energy absorption index is required, determine the grammage of the specimens as described in ISO 536.

If the modulus of elasticity is required, determine the mean thickness of each specimen in accordance with ISO 534, using a pressure of (100 ± 10) kPa.

NOTE Some papers are difficult to cut cleanly. In such cases, a pad of two or three sheets of the paper, interleaved with a harder paper, e.g. bond, can be prepared and test pieces cut from this pad.

When testing laboratory sheets, special instructions apply (see ISO 5270).

8 Procedure

iTeh STANDARD PREVIEW
(standards.iteh.ai)

Carry out the tests in the same atmospheric conditions used for the conditioning and preparation of test pieces (see 7.2 and 7.3).

Verify the zero position of the measuring device and, if used, recording devices.

Adjust the clamps to the required initial test length and place the test piece in the clamps, ensuring that the test area between the clamping lines is not touched with bare hands. The use of disposable or light weight cotton gloves is recommended when handling the test pieces. Align and tightly clamp the test piece so that any observable slack is eliminated but the test piece is not placed under any significant stress. Ensure that the test piece is clamped in such a manner that it is parallel to the direction of application of the tensile force (see Figure 1).

Commence the test and continue it until the test piece breaks. Record the maximum tensile force exerted and, if required, record either the elongation in millimetres or, for direct-reading instruments, the strain at break as a percentage.

Test at least ten test pieces in each direction of interest (machine direction, cross-direction) to obtain ten valid results in each direction of interest. Reject all readings for test pieces that break within 10 mm of the clamping lines. If more than 20 % of the test pieces cut from a particular sample break within 10 mm of the clamps, inspect the testing machine for conformity with the requirements of 5.1 and Clause 6. If the apparatus is faulty, reject all the results and take appropriate remedial action. The number of test pieces that break within 10 mm of the clamps shall be stated in the test report.

NOTE 1 For testing machines that hold the test piece in the vertical position, it can be convenient to attach a small weight, e.g. a mass of 10 g for lightweight paper, to the lower end of the test piece whilst placing it in the clamp, in order to eliminate the slack. This procedure is not necessarily suitable for high-elongation papers.

NOTE 2 With certain types of papers it can be difficult to take out the "observable slack" without applying stress to the test piece. In such cases, a minimum amount of slack might be left in the test piece.