



Designation: D 2732 – 96

## Standard Test Method for Unrestrained Linear Thermal Shrinkage of Plastic Film and Sheeting<sup>1</sup>

This standard is issued under the fixed designation D 2732; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

### 1. Scope

1.1 This test method covers determination of the degree of unrestrained linear thermal shrinkage at given specimen temperatures of plastic film and sheeting of 0.76 mm (0.030 in.) thickness or less. This test method does not cover shrinkage from loss of solvent in some materials.

1.2 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

NOTE 1—This document is similar in concept to ISO/DIS 11501, but it is unknown at this time whether both methods give comparable results.

### 2. Referenced Documents

#### 2.1 ASTM Standards:

D 618 Practice for Conditioning Plastics for Testing<sup>2</sup>

D 1204 Test Method for Linear Dimensional Changes of Nonrigid Thermoplastic Sheeting or Film at Elevated Temperature<sup>2</sup>

D 1898 Practice for Sampling of Plastics<sup>2</sup>

E 1 Specification for ASTM Thermometers<sup>3</sup>

### 3. Terminology

#### 3.1 Definitions:

3.1.1 *unrestrained linear thermal shrinkage (free shrink or shrinkage)*—the irreversible and rapid reduction in linear dimension in a specified direction occurring in film subjected to elevated temperatures under conditions where nil or negligible restraint to inhibit shrinkage is present. It is normally expressed as a percentage of the original dimension.

### 4. Significance and Use

4.1 As a result of the manufacturing process, internal

stresses may be locked into the film which can be released by heating. The temperature at which shrinkage will occur is related to the processing techniques employed to manufacture the film and may also be related to a phase transition in the base resin. The magnitude of the shrinkage will vary with the temperature of the film.

4.2 Shrinkage of a particular material produced by a particular process may be characterized by this test method by making measurements at several temperatures through the shrinkage range of the material.

4.3 Following a characterization in a particular case, it is usually sufficient thereafter to measure shrinkage at only one selected temperature for purposes of process or quality control, or both.

### 5. Apparatus

5.1 *Constant-Temperature Liquid Bath*, capable of controlling accurately to  $\pm 0.5^\circ\text{C}$ .

5.1.1 The liquid for the bath should not plasticize or react with the specimens. Poly(ethylene glycol), glycerin, and water have been found to have wide applicability.

5.2 *Thermometer*—ASTM Thermometer 1 C conforming to the requirements as prescribed in Specification E 1.

5.3 *Square Metal Stamp*, 100 by 100 mm, with engraved arrow indicating machine direction of film and stamp pad and ink. (The ink should not be soluble in the bath liquid.)

NOTE 2—A metal die or template (100 by 100 mm) can be used instead of the square metal stamp.

5.4 *Free Shrink Holder*—A holder designed for test of a single specimen, such as that shown in Fig. 1 and Fig. 2. Alternatively, a holder such as that shown in Fig. 3 may be used to immerse several specimens at a time. However, checks must be made to assure that contact among the specimens does not result in errors.

5.5 *Ruler*, graduated in millimetres.

### 6. Test Specimen

6.1 The test specimen shall consist of 100 by 100-mm samples.

6.2 A minimum of two specimens is necessary for each test temperature.


<sup>1</sup> This test method is under the jurisdiction of ASTM Committee D-20 on Plastics and is the direct responsibility of Subcommittee D20.19 on Film and Sheeting.

Current edition approved Sept. 10, 1996. Published February 1997. Originally published as D 2732 – 68 T. Last previous edition D 2732 – 83 (1989) $\epsilon$ <sup>1</sup>.

This revision has incorporated an ISO equivalency statement, a revised precision and bias statement, keywords, and some of the note material has been included in the text.

<sup>2</sup> *Annual Book of ASTM Standards*, Vol 08.01.

<sup>3</sup> *Annual Book of ASTM Standards*, Vol 14.03.

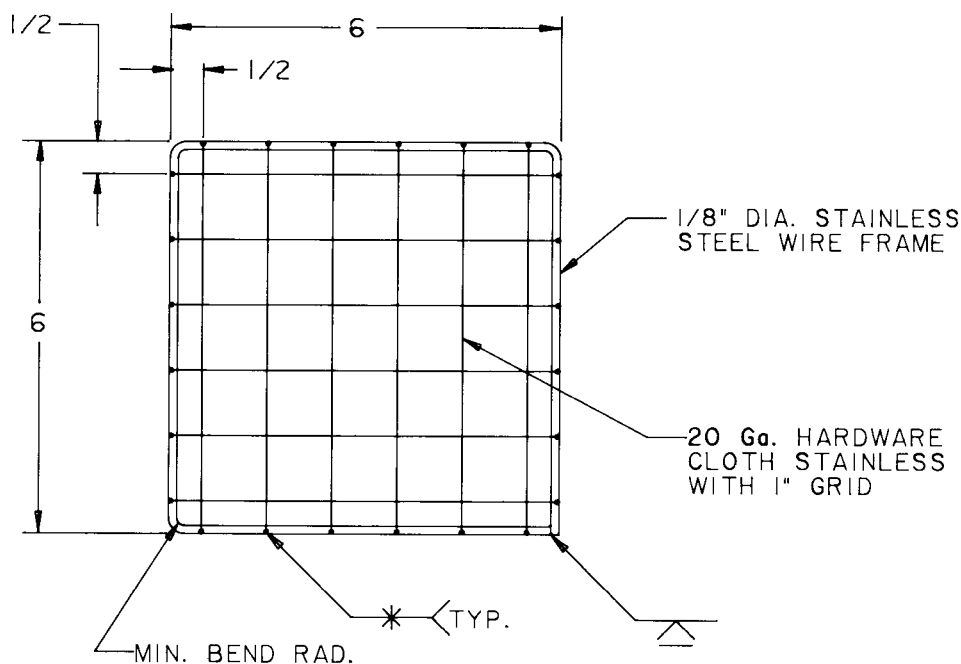

**NOTE:**

1. (A) Cut hardware cloth 6 1/8 by 6 1/8.
- (B) Form a pocket in center of cloth.
- (C) Weld cloth to frame as shown.
2. Two required for assembly.

ASTM D2732-96

**FIG. 1 Construction of Top and Bottom Grid Retainers of Specimen Holder**

6.3 The material shall be sampled in accordance with Practice D 1898.

**7. Conditioning**

7.1 *Conditioning*—Condition the test specimens at  $23 \pm 2^\circ\text{C}$  ( $73.4 \pm 3.6^\circ\text{F}$ ) and  $50 \pm 5\%$  relative humidity for not less than 40 h prior to test in accordance with Procedure A of Practice D 618, for those tests where conditioning is required. In cases of disagreement, the tolerances shall be  $\pm 1^\circ\text{C}$  ( $\pm 1.8^\circ\text{F}$ ) and  $\pm 2\%$  relative humidity.

7.2 *Test Conditions*—Set the liquid bath temperature to within  $\pm 0.5^\circ\text{C}$  of the desired temperature and allow to stabilize.

**8. Procedure**

8.1 Stamp and cut out the stamped section of film. A small border of film may be left around the stamped area.

8.1.1 As an alternative method, the specimens may be cut with a die or with the aid of a template. An edge of the die may be notched to designate film direction.

8.2 Place the specimen in a free shrink holder such that it is free from contact with the edges of the holder. The holder

should restrain the specimen from floating in the bath medium while allowing free circulation of the bath medium around the specimen. Multiple specimens can be tested but care should be exercised to prevent restraint between the specimens.

8.3 Observe and record the temperature of the bath before immersion of each specimen.

8.4 Immerse the specimen in the bath for 10 s or a time determined to be sufficient for the material to come to thermal equilibrium and undergo maximum shrinkage. Do not hold the specimen over the bath prior to immersion, as it may result in premature shrinkage or annealing, which may introduce an error.

NOTE 3—Immersion for 10 s has been determined to be generally adequate for most thermoplastics of up to 0.05 mm (0.002 in.) thickness; however, for new or thicker materials, a different time of immersion may be required to ensure maximum shrinkage at the temperature of interest.

8.5 Remove the specimen from the bath and quickly immerse in a liquid medium at room temperature preferably miscible with the bath medium.

8.6 After 5 s remove the specimen from the cooling medium and measure and record the linear dimensions of the specimen