

---

---

**Plastics — Compression-moulded sheets  
of polyethylene (PE-UHMW, PE-HD) —  
Requirements and test methods**

*Plastiques — Plaques moulées par compression en polyéthylène  
(PE-UHMW, PE-HD) — Exigences et méthodes d'essai*

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[ISO 15527:2007](https://standards.iteh.ai/catalog/standards/sist/e738f4af-3031-4c7b-80d2-ed33eec50c0a/iso-15527-2007)

[https://standards.iteh.ai/catalog/standards/sist/e738f4af-3031-4c7b-80d2-  
ed33eec50c0a/iso-15527-2007](https://standards.iteh.ai/catalog/standards/sist/e738f4af-3031-4c7b-80d2-ed33eec50c0a/iso-15527-2007)



**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO 15527:2007

<https://standards.iteh.ai/catalog/standards/sist/e738f4af-3031-4c7b-80d2-ed33eec50c0a/iso-15527-2007>



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2007

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

## Contents

Page

Foreword.....	iv
<b>1 Scope .....</b>	<b>1</b>
<b>2 Normative references .....</b>	<b>1</b>
<b>3 Material .....</b>	<b>1</b>
<b>4 Requirements .....</b>	<b>2</b>
4.1 Appearance .....	2
4.2 Dimensional tolerances .....	2
4.3 Properties .....	3
<b>5 Test methods.....</b>	<b>4</b>
5.1 Test specimens .....	4
5.2 Delivery condition.....	5
5.3 Appearance .....	5
5.4 Dimensions.....	5
5.5 Density .....	5
5.6 Determination of abrasion properties .....	5
5.7 Tensile stress at yield, $\sigma_y$ , and tensile strain at yield, $\epsilon_y$ .....	6
5.8 Modulus of elasticity in tension, $E_t$ .....	6
5.9 Impact strength of notched specimens .....	6
5.10 Melt mass-flow rate (MFR) .....	6
<b>6 Designation .....</b>	<b>6</b>
<b>7 Marking .....</b>	<b>7</b>
<b>Annex A (normative) Requirements for rectangularity .....</b>	<b>8</b>
<b>Annex B (normative) Determination of abrasion properties.....</b>	<b>9</b>
<b>Annex C (informative) Example of apparatus for the determination of abrasion properties .....</b>	<b>11</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 15527 was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 11, *Products*, in collaboration with Technical Committee CEN/TC 249, *Plastics*, of the European Committee for Standardization (CEN).

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[ISO 15527:2007](https://standards.iteh.ai/catalog/standards/sist/e738f4af-3031-4c7b-80d2-ed33eec50c0a/iso-15527-2007)

<https://standards.iteh.ai/catalog/standards/sist/e738f4af-3031-4c7b-80d2-ed33eec50c0a/iso-15527-2007>

# Plastics — Compression-moulded sheets of polyethylene (PE-UHMW, PE-HD) — Requirements and test methods

## 1 Scope

This International Standard specifies the requirements and test methods for solid flat compression-moulded sheets of polyethylene (PE-UHMW and PE-HD, see ISO 1043-1) without fillers or reinforcing materials. It applies only to thicknesses from 10 mm to 200 mm.

## 2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 291, *Plastics — Standard atmospheres for conditioning and testing*

ISO 527-2, *Plastics — Determination of tensile properties — Part 2: Test conditions for moulding and extrusion materials*

ISO 1133, *Plastics — Determination of the melt mass-flow rate (MFR) and the melt volume-flow rate (MVR) of thermoplastics*

ISO 1043-1, *Plastics — Symbols and abbreviated terms — Part 1: Basic polymers and their special characteristics*

ISO 1183 (all parts), *Plastics — Methods for determining the density of non-cellular plastics*

ISO 1872-1, *Plastics — Polyethylene (PE) moulding and extrusion materials — Part 1: Designation system and basis for specifications*

ISO 11542-1, *Plastics — Ultra-high-molecular-weight polyethylene (PE-UHMW) moulding and extrusion materials — Part 1: Designation system and basis for specifications*

ISO 11542-2, *Plastics — Ultra-high-molecular-weight polyethylene (PE-UHMW) moulding and extrusion materials — Part 2: Preparation of test specimens and determination of properties*

## 3 Material

Sheets shall consist of PE-UHMW moulding materials as defined in ISO 11542-1 or PE-HD selected from polyethylene (PE) moulding materials as defined in ISO 1872-1, without fillers or reinforcing materials. Materials and additives of unknown identity shall not be used.

NOTE Legal conditions may necessitate a specific choice of moulding material (see 4.3.2).

4 Requirements

4.1 Appearance

Sheets shall have smooth surfaces. Small grooves and any resultant irregularities in the thicknesses of sheets are acceptable as long as the requirements specified in 4.2.1 are fulfilled. Sheets shall be examined in accordance with 5.3.

Where agreed between interested parties, sheets with a smooth machined surface may be supplied.

Sheets shall be substantially free from bubbles, voids, cracks and other inhomogeneities which would make them unfit for the intended use. Specific requirements with respect to this internal integrity shall be agreed upon between the interested parties. Sheets shall be examined in accordance with 5.2.

4.2 Dimensional tolerances

4.2.1 Thickness

For any individual sheet, the thickness tolerance with reference to the nominal thickness shall be as specified in Table 1. Testing shall be in accordance with 5.4.1.

Table 1 —Tolerances on thickness of sheet

Values in millimetres

Nominal thickness $h_n$	Tolerances (standards.iteh.ai)			
	PE-UHMW		PE-HD	
	Group 1.1	Group 1.2	Group 2.1	Group 3.1
$10 \leq h_n \leq 20$	+3 0	+3 0	+3 0	+3 0
$20 < h_n \leq 40$	+5 0	+5 0	+5 0	+5 0
$40 < h_n \leq 60$	+6 0	+6 0	+6 0	+6 0
$60 < h_n \leq 80$	+8 0	+8 0	+8 0	+8 0
$80 < h_n \leq 100$	+10 0	+10 0	+10 0	+10 0
$100 < h_n \leq 120$	+12 0	+12 0	+12 0	+12 0
$120 < h_n \leq 150$	+14 0	+14 0	+14 0	+14 0
$150 < h_n \leq 200$	+16 0	+16 0	+16 0	+16 0

4.2.2 Length and width

The nominal length,  $l_n$ , and nominal width,  $b_n$ , of sheets shall be as agreed between the interested parties.

4.2.3 Rectangularity

For any individual sheet selected at random from any delivery, the rectangularity tolerance, expressed as the difference in length of the diagonals,  $|d_1 - d_2|$  (see Figure 1), shall be in accordance with Table A.1.

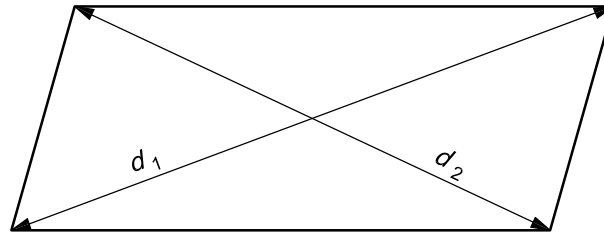


Figure 1 — Difference between lengths of diagonals,  $|d_1 - d_2|$

Testing shall be in accordance with 5.4.3.

### 4.3 Properties

#### 4.3.1 Physical properties

Requirements for physical properties are given in Table 2.

Table 2 — Physical properties

Properties	Unit	Requirements (average values)				Test method subclause
		PE-UHMW		PE-HD		
		Group 1.1	Group 1.2	Group 2.1	Group 3.1	
Density	g/cm <sup>3</sup>	0,920 to 0,945	0,920 to 0,945	0,945 to 0,960	0,940 to 0,965	5.5
Abrasion	—	70 to < 90	90 to 110	360 to 440	900 to 1 000	5.6
Tensile stress at yield	MPa	$\geq 17$	$\geq 17$	$\geq 19$	$\geq 19$	5.7
Tensile strain at yield	%	$\geq 8$	$\geq 8$	$\geq 8$	$\geq 8$	5.7
Modulus of elasticity in tension	MPa	$\geq 500$	$\geq 600$	$\geq 800$	$\geq 700$	5.8
Impact strength of double-notched specimens	kJ/m <sup>2</sup>	$\geq 40$	$\geq 170$	$\geq 15$	$\geq 5$	5.9.1
Charpy impact strength of notched specimens	kJ/m <sup>2</sup>	no breaks	no breaks	no breaks	$\geq 9$	5.9.2
MFR: 190 °C/5 kg	g/10 min	not measurable	not measurable	$\leq 0,1$	0,3 to 0,7	5.10
MFR: 190 °C/21,6 kg	g/10 min	not measurable	not measurable	$\leq 3$	7 to 20	5.10

#### 4.3.2 Physiological behaviour

Any relevant legislation for physiological behaviour shall be taken into consideration.

5 Test methods


5.1 Test specimens

5.1.1 Preparation of test specimens

Test specimens shall be obtained by machining them from the sheet.

For sheets of thickness  $\geq 10$  mm but  $\leq 20$  mm, the test specimens shall be taken as shown in Figure 2, and for sheets of thickness  $> 20$  mm but  $\leq 200$  mm they shall be taken as shown in Figure 3.

Dimensions in millimetres

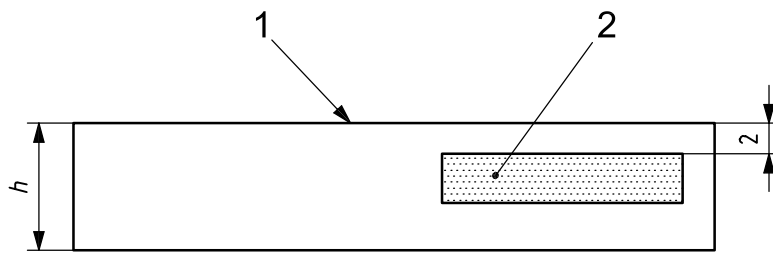

Key


- 1 surface of sheet
- 2 test specimen
- $h$  sheet thickness

**iTeh STANDARD PREVIEW**  
(standards.iteh.ai)

Figure 2 — Taking test specimens from sheets of thickness  $\geq 10$  mm but  $\leq 20$  mm

ISO 15527:2007

<https://standards.iteh.ai/catalog/standards/sist/e738f4af-3031-4c7b-80d2-ed33eec50c0a/iso-15527-2007>

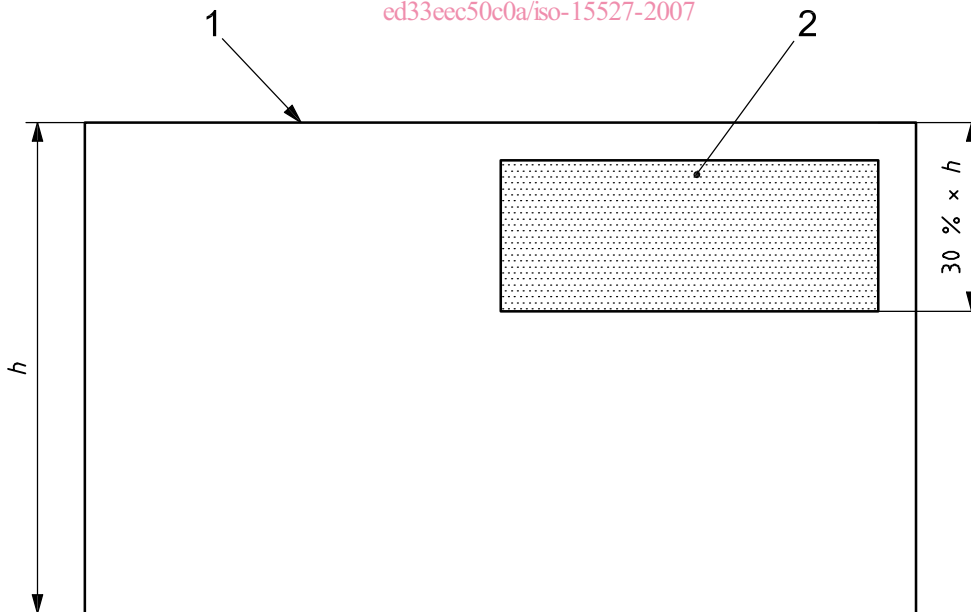

Key

- 1 surface of sheet
- 2 test specimen
- $h$  sheet thickness

Figure 3 — Taking test specimens from sheets of thickness  $> 20$  mm but  $\leq 200$  mm



The surfaces of the test specimens shall be free from damage and faults in order to avoid notch effects. Should any burrs occur on the test specimens during machining, these shall be eliminated without damaging the surfaces of the specimens. If required, the cut edges shall be finished with abrasive paper (grain size 220 or finer), the direction of abrasion being along the length of the test specimens.

### 5.1.2 Conditioning

All test specimens shall be conditioned for at least 16 h at  $23\text{ °C} \pm 2\text{ °C}$  in accordance with ISO 291 or as specified in the appropriate material standard. Shorter conditioning times may be used by agreement between the interested parties when it can be shown that there is no significant difference in the results obtained.

### 5.1.3 Testing

Testing shall be carried out in standard atmosphere 23/50 as specified in ISO 291 or as specified in the appropriate material standard unless otherwise agreed between the interested parties or specified in the individual test standards.

## 5.2 Delivery condition

Sheets shall be visually examined when delivered to ensure freedom from mechanical damage or other obvious defects. Sheets can be inspected by ultrasonic or X-ray methods where required.

## 5.3 Appearance

Where possible, sheets shall be examined for visual defects by transmitted light using a suitable light source. Otherwise, sufficiently bright reflected light shall be used. Any defects thus identified shall be compared with the agreed specification (which may be either a written specification or in the form of reference samples) and classified accordingly.

ISO 15527:2007

## 5.4 Dimensions <https://standards.iteh.ai/catalog/standards/sist/e738f4af-3031-4c7b-80d2-ed33eec50c0a/iso-15527-2007>

### 5.4.1 Thickness, $h$

The thickness,  $h$ , shall be measured using suitable calibrated equipment accurate to  $\leq 0,10$  mm.

### 5.4.2 Length, $l$ , and width, $b$

The length,  $l$ , and width,  $b$ , shall be measured to the nearest 1 mm using suitable equipment. Measurements shall be made directly across the surface of the sheet and along the cut edge.

### 5.4.3 Rectangularity

The rectangularity, expressed as the difference between the lengths of the diagonals,  $|d_1 - d_2|$ , as shown in Figure 1, shall be measured to the nearest 1 mm using a graduated ruler or tape measure.

## 5.5 Density

The density shall be determined in accordance with the appropriate part of ISO 1183.

## 5.6 Determination of abrasion properties

Preparation of test specimens and abrasion testing shall be carried out in accordance with Annex B.