



Designation: F 1645 – 00 (Reapproved 2005)

## Standard Test Method for Water Migration in Honeycomb Core Materials<sup>1</sup>

This standard is issued under the fixed designation F 1645; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

### 1. Scope

1.1 This test method covers the determination of water migration in honeycomb core materials.

1.2 The values stated in SI units are to be regarded as the standard. The inch-pound units given may be approximate.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

### 2. Referenced Documents

2.1 *ASTM Standards:*<sup>2</sup>

**C 271** Test Method for Density of Sandwich Core Materials

### 3. Significance and Use

3.1 This test method determines the rate of water migration between honeycomb core cells.

### 4. Apparatus

4.1 *Micrometer, Gage, or Caliper*, capable of measuring accurately to 0.025 mm (0.001 in.).

4.2 *Weighing Scale*, capable of measuring accurately to  $\pm 0.5\%$ .

4.3 *Water Migration Setup*, buret, rubber hose, clamps, stand.

### 5. Test Specimens

5.1 The test specimens may be any convenient size of core material as agreed upon by the purchaser and the seller. The minimum specimen size recommended is 76- by 76-mm (3- by 3-in.) cross section and 12.7 mm (0.5 in.) thick. The facings shall be of impervious, transparent material to permit visual observation into the core cells by illumination, and they shall be bonded to the core with a water-resistant adhesive.

### 6. Conditioning

6.1 It is recommended that the tests be conducted at  $23 \pm 3^\circ\text{C}$  ( $73 \pm 5^\circ\text{F}$ ),  $50 \pm 5\%$  relative humidity, and the specimens be conditioned to constant weight ( $\pm 1\%$ ) under those conditions before testing.


### 7. Procedure

7.1 Determine the density of each specimen per Test Method **C 271**, if required.

7.2 Bond the facings to the core. Clear plastic facings are recommended as this will make it possible to drill a hole in the upper facing over a single cell and observe where the water migrated. The adhesive shall be applied so that fairly heavy fillets form between the core cell walls and the facings, thus assuring a watertight joint between the facings and core. A clear adhesive is recommended.

7.3 A hole shall be drilled through the upper facing over one centrally located core cell. The hole must lead into only one cell.

7.4 A suitable connection shall be provided, such as a tube bonded over the hole, for the application of hydrostatic pressure (see **Fig. 1**).

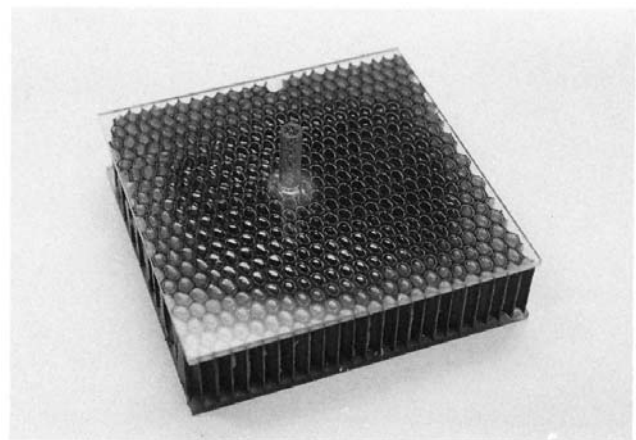

**FIG. 1 Water Migration Specimen**

7.5 The primary cell shall be filled with distilled or deionized water, measuring the volume of water required (a graduated syringe works well) or the increase in weight of the

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee D30 on Composite Materials and is the direct responsibility of Subcommittee D30.09 on Sandwich Construction.

Current edition approved Oct. 1, 2005. Published October 2005. Originally approved in 1995. Last previous edition approved in 2000 as F 1645 – 00.

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.