
**Plastics pipes and fittings — Preparation
of test piece assemblies between a
polyethylene (PE) pipe and an
electrofusion fitting**

*Tubes et raccords en matières plastiques — Préparation d'éprouvettes
par assemblage tube/raccord électrosoudable en polyéthylène (PE)*

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 11413:2008](https://standards.iteh.ai/catalog/standards/sist/073647bf-e24b-408c-b527-b3ae058283fc/iso-11413-2008)

[https://standards.iteh.ai/catalog/standards/sist/073647bf-e24b-408c-b527-
b3ae058283fc/iso-11413-2008](https://standards.iteh.ai/catalog/standards/sist/073647bf-e24b-408c-b527-b3ae058283fc/iso-11413-2008)



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 11413:2008

<https://standards.iteh.ai/catalog/standards/sist/073647bf-e24b-408c-b527-b3ae058283fc/iso-11413-2008>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2008

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 11413 was prepared by Technical Committee ISO/TC 138, *Plastics pipes, fittings and valves for the transport of fluids*, Subcommittee SC 5, *General properties of pipes, fittings and valves of plastic materials and their accessories — Test methods and basic specifications*.

This second edition cancels and replaces the first edition (ISO 11413:1996), which has been technically revised.

ISO 11413:2008

<https://standards.iteh.ai/catalog/standards/sist/073647bf-e24b-408c-b527-b3ae058283fc/iso-11413-2008>

iTeh STANDARD PREVIEW **(standards.iteh.ai)**

ISO 11413:2008

<https://standards.iteh.ai/catalog/standards/sist/073647bf-e24b-408c-b527-b3ae058283fc/iso-11413-2008>

Plastics pipes and fittings — Preparation of test piece assemblies between a polyethylene (PE) pipe and an electrofusion fitting

1 Scope

This International Standard specifies a method for the preparation of test pieces assembled from polyethylene (PE) pipes or spigot-ended fittings and electrofusion fittings (e.g. socket fittings such as couplers, or saddles).

The assembly criteria specified include parameters such as ambient temperature, fusion conditions, fitting and pipe dimensions, pipe configuration (coiled or straight pipe), taking into account the limiting service conditions specified by the relevant product standards.

This International Standard can apply to other shapes, e.g. re-rounded pipes, dependent on the manufacturer's instructions.

iTeh STANDARD PREVIEW

2 Normative references (standards.iteh.ai)

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 4427-2, *Plastics piping systems — Polyethylene (PE) pipes and fittings for water supply — Part 2: Pipes*

ISO 4427-3, *Plastics piping systems — Polyethylene (PE) pipes and fittings for water supply — Part 3: Fittings*

ISO 4437, *Buried polyethylene (PE) pipes for the supply of gaseous fuels — Metric series — Specifications*

ISO 8085-2, *Polyethylene fittings for use with polyethylene pipes for the supply of gaseous fuels — Metric series — Specifications — Part 2: Spigot fittings for butt fusion, for socket fusion using heated tools and for use with electrofusion fittings*

ISO 8085-3, *Polyethylene fittings for use with polyethylene pipes for the supply of gaseous fuels — Metric series — Specifications — Part 3: Electrofusion fittings*

ISO 14531-1, *Plastics pipes and fittings — Crosslinked polyethylene (PE-X) pipe systems for the conveyance of gaseous fuels — Metric series — Specifications — Part 1: Pipes*

ISO 15494, *Plastics piping systems for industrial applications — Polybutene (PB), polyethylene (PE) and polypropylene (PP) — Specifications for components and the system — Metric series*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1 reference time

t_R
theoretical fusion time indicated by the fitting manufacturer for the reference ambient temperature

3.2 fusion energy

electrical energy supplied during the fusion-jointing cycle as measured at the terminals of the fitting at a given ambient temperature, T_a , and for electrical parameters whose values lie within the tolerance ranges stated by the manufacturer

NOTE 1 The fitting manufacturer is generally required to state in the technical file any variations in fusion energy input required as a function of the ambient temperature in the range T_{min} to T_{max} .

NOTE 2 Where applicable, energy measurement should exclude the effect of terminal contact resistance.

3.3 reference energy

energy supplied to a fitting having a nominal electrical resistance and using the nominal fusion parameters defined by the manufacturer at the reference ambient temperature, T_R

3.4 maximum energy

maximum value of the fusion energy supplied for jointing at a given ambient temperature, T_a

3.5 minimum energy

minimum value of the fusion energy supplied for jointing at a given ambient temperature, T_a

3.6 nominal energy

nominal energy supplied for jointing at given ambient temperature, T_a

4 Symbols

4.1 General symbols (see Figure A.1)

D_{im}	mean inside diameter of the fusion zone of a fitting in the radial plane located a distance $L_3 + 0,5L_2$ from the face of the fitting socket
$D_{im,max}$	maximum theoretical value of D_{im} , as stated by the fitting manufacturer
$D_{i,max}$	maximum inside diameter of the fusion zone of the fitting
$D_{i,min}$	minimum inside diameter of the fusion zone of the fitting
d_e	outside diameter of a pipe or fitting spigot
d_{em}	mean outside diameter of a pipe or fitting spigot in conformity with the relevant International Standard for the product concerned and calculated from the measured circumference

$d_{em,p}$	mean outside diameter of a pipe or fitting spigot after preparation for assembly with the outer layer removed by scraping or peeling and calculated from the circumference measured in a radial plane coincident with the centre of the fusion zone at a distance $L_3 + 0,5L_2$ from the face of the fitting socket after assembly
L_2	nominal length of the fusion zone as indicated by the fitting manufacturer
L_3	nominal distance from the face of the fitting socket to the leading edge of the fusion zone
e_n	nominal wall thickness, in millimetres, of the pipe
e_s	depth of scraping or the thickness of material removed from the pipe surface by peeling

4.2 Clearances

4.2.1 Socket fittings

C_1 clearance between fitting bore and outside diameter of unscraped pipe

$$C_1 = D_{im} - d_{em}$$

C_2 clearance between fitting bore and outside diameter of scraped pipe

$$C_2 = C_1 + 2e_s$$

NOTE 1 C_2 may be obtained by machining the unscraped pipe to bring its mean outside diameter d_{em} to the value $d_{em,p}$ calculated from the equation (see also Note to 5.1):

$$d_{em,p} = D_{im} - C_2$$

C_3 maximum theoretical clearance between fitting bore and outside diameter of unscraped pipe

$$C_3 = D_{im,max} - d_e$$

C_4 maximum theoretical clearance between fitting bore and outside diameter of scraped pipe

$$C_4 = C_3 + 2e_s$$

NOTE 2 C_4 can be obtained by machining the unscraped pipe to bring its mean outside diameter d_{em} to the value $d_{em,p}$ calculated from the equation:

$$d_{em,p} = D_{im} - C_4$$

4.2.2 Saddles

The clearance between saddle fittings and pipes is assumed to be zero.

4.3 Ambient temperature

T_a ambient temperature at which a joint is made

NOTE The ambient temperature may vary from the minimum temperature, T_{min} , to the maximum temperature, T_{max} , as specified either in the product standard or by agreement between the manufacturer and the purchaser.

T_R reference ambient temperature of $(23 \pm 2) ^\circ\text{C}$

T_{max} maximum permitted ambient temperature for joint assembly

T_{min} minimum permitted ambient temperature for joint assembly

5 Joint assembly

5.1 General

The joints shall be made using pipes and/or spigot-ended fittings conforming to ISO 4427-2, ISO 4427-3, ISO 4437, ISO 8085-2, ISO 8085-3, ISO 14531-1, ISO 15494 or other standards, as applicable, e.g. standards for pipe renovation, and electrofusion fittings for which the dimensions conform to ISO 8085-3 or ISO 4427-3, or other standards, as applicable. Unless otherwise specified, the pipes selected for the assembly shall be of the same pressure rating as the fitting. The preparation of the assembly for testing shall be carried out in accordance with the electrofusion fitting manufacturer's written procedures.

Unless a greater scraping depth is recommended by the manufacturer, the minimum scraping depth e_s shall be 0,2 mm.

NOTE In cases where the pipes do not need to be scraped, the minimum scraping depth, e_s , may be zero.

5.2 Procedure

Carry out the following procedure, where steps d) and f) shall be carried out in a temperature-controlled environment maintaining the temperature to within $\pm 2^\circ\text{C}$ and large enough to contain the fitting, the pipes and the holding apparatus. Fittings shall not be used within 170 h of manufacture.

- a) Measure, at the reference temperature T_R , the parts to be joined to determine the dimensional characteristics defined in 4.1 and illustrated in Figure A.1.
- b) Prepare the pipes to achieve the necessary clearance conditions, at the reference temperature T_R , as given in 4.2.
- c) Mount the fitting on the pipes in accordance with the manufacturer's instructions.
- d) Condition the assembly and the associated apparatus for a period conforming to Table 1 at the applicable ambient temperature T_a specified in Annex C.


Table 1 — Conditioning periods

Nominal wall thickness, e_n mm	Minimum conditioning period h
$e_n < 3$	1
$3 \leq e_n < 8$	3
$8 \leq e_n < 16$	6
$16 \leq e_n < 32$	10
$32 \leq e_n$	16

- e) After conditioning, if applicable according to Annex C, measure the resistance of the heating coil and determine the values of the electrical parameters in accordance with Annex D. The procedure for measuring the coil resistance implies the use of measuring equipment at the reference ambient temperature T_R with the fitting at the conditioning temperature.
- f) With the assembly conditioned at ambient temperature T_a , carry out the fusion jointing in accordance with the fitting manufacturer's instructions at the energy levels indicated in Annex C.
- g) Leave the joint to cool until it reaches ambient temperature.
- h) Proceed to the tests as given in the relevant product standards.

Annex A (normative)

Symbols for dimensions of an electrofusion socket

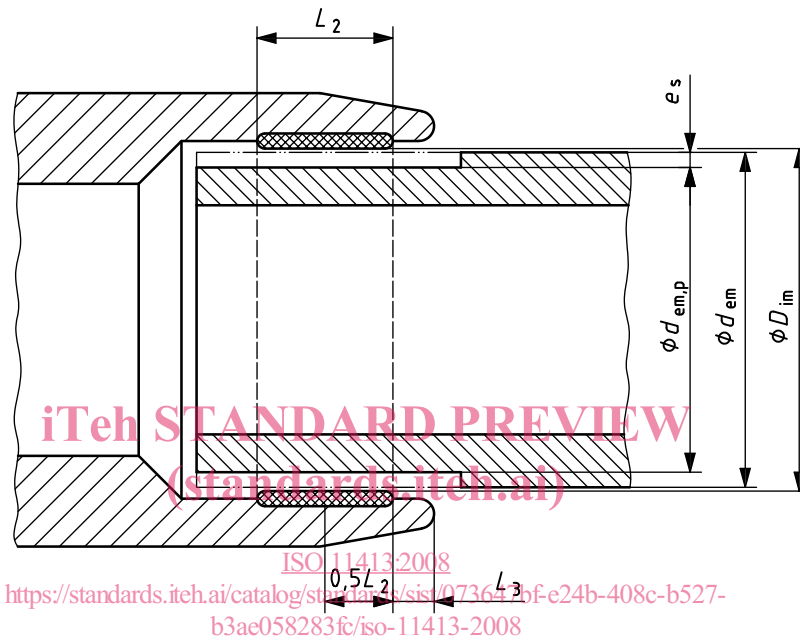

Key

L_2 nominal length of the fusion zone

L_3 length of the unheated section of the socket

$D_{im} = (D_{i,max} + D_{i,min})/2$

$d_{em} = C/\pi$ where C is the circumference of the unscrapped pipe

$d_{em,p}$ (by analogy) = C_p/π where C_p is the circumference of the pipe to be assembled with the fitting

$e_s = (d_{em} - d_{em,p})/2$

Figure A.1 — Dimensions of an electrofusion socket