
**Steel for the reinforcement and
prestressing of concrete — Test
methods —**

**Part 2:
Welded fabric**

iTeh STANDARD PREVIEW
*Aciers pour l'armature et la précontrainte du béton — Méthodes
d'essai —
(standards.iteh.ai)*
Partie 2: Treillis soudés

ISO 15630-2:2010

<https://standards.iteh.ai/catalog/standards/sist/3b0ef9e8-c7a1-4926-9fc7-9b977012066a/iso-15630-2-2010>



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 15630-2:2010](https://standards.iteh.ai/catalog/standards/sist/3b0ef9e8-c7a1-4926-9fc7-9b977012066a/iso-15630-2-2010)

<https://standards.iteh.ai/catalog/standards/sist/3b0ef9e8-c7a1-4926-9fc7-9b977012066a/iso-15630-2-2010>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2010

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
Introduction.....	v
1 Scope	1
2 Normative references	1
3 Symbols.....	1
4 General provisions concerning test pieces.....	2
5 Tensile test.....	3
5.1 Test piece	3
5.2 Test equipment.....	3
5.3 Test procedure.....	3
6 Bend test on welded intersection	4
6.1 Test piece	4
6.2 Test equipment.....	4
6.3 Test procedure.....	5
6.4 Interpretation of test results.....	5
7 Determination of the weld shear force (F_s).....	6
7.1 Test piece	6
7.2 Test equipment.....	6
7.3 Test procedure.....	11
8 Axial force fatigue test.....	11
8.1 Principle of test.....	11
8.2 Test piece	11
8.3 Test equipment.....	11
8.4 Test procedure.....	12
8.4.1 Provisions concerning the test piece.....	12
8.4.2 Upper force (F_{up}) and force range (F_r).....	12
8.4.3 Stability of force and frequency.....	12
8.4.4 Counting of force cycles.....	12
8.4.5 Frequency.....	12
8.4.6 Temperature	12
8.4.7 Validity of the test.....	12
9 Chemical analysis	12
10 Measurement of the geometrical characteristics of the fabric	13
10.1 Test piece	13
10.2 Test equipment	13
10.3 Test procedure.....	13
11 Test report.....	13
Bibliography.....	14

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 15630-2 was prepared by Technical Committee ISO/TC 17, *Steel*, Subcommittee SC 16, *Steels for the reinforcement and prestressing of concrete*.

This second edition cancels and replaces the first edition (ISO 15630-2:2002), which has been technically revised.

ISO 15630 consists of the following parts, under the general title *Steel for the reinforcement and prestressing of concrete — Test methods*:

— Part 1: Reinforcing bars, wire rod and wire

— Part 2: Welded fabric

— Part 3: Prestressing steel

iTeh STANDARD PREVIEW
(standards.iteh.ai)

<https://standards.iteh.ai/catalog/standards/sist/3b0ef9e8-c7a1-4926-9fc7-9b977012066a/iso-15630-2-2010>

Introduction

The aim of ISO 15630 is to provide all relevant test methods for reinforcing and prestressing steels in one standard. In that context, the existing International Standards for testing these products have been revised and updated. Some further test methods have been added.

Reference is made to International Standards on the testing of metals, in general, as they are applicable. Complementary provisions have been given if needed.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO 15630-2:2010](https://standards.iteh.ai/catalog/standards/sist/3b0ef9e8-c7a1-4926-9fc7-9b977012066a/iso-15630-2-2010)

<https://standards.iteh.ai/catalog/standards/sist/3b0ef9e8-c7a1-4926-9fc7-9b977012066a/iso-15630-2-2010>

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 15630-2:2010

<https://standards.iteh.ai/catalog/standards/sist/3b0ef9e8-c7a1-4926-9fc7-9b977012066a/iso-15630-2-2010>

Steel for the reinforcement and prestressing of concrete — Test methods —

Part 2: Welded fabric

1 Scope

This part of ISO 15630 specifies test methods applicable to welded fabric for the reinforcement of concrete.

NOTE In some countries, the expression “welded wire reinforcement” is used in place of “welded (wire) fabric”.

For those tests not specified in this part of ISO 15630 (e.g. bend test, rib/indentation geometry, mass per metre), ISO 15630-1 is applicable.

iTeh STANDARD PREVIEW (standards.iteh.ai)

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 6892-1, *Metallic materials — Tensile testing — Part 1: Method of test at room temperature*

ISO 7500-1, *Metallic materials — Verification of static uniaxial testing machines — Part 1: Tension/compression testing machines — Verification and calibration of the force-measuring system*

ISO 9513, *Metallic materials — Calibration of extensometers used in uniaxial testing*

3 Symbols

The symbols used in this part of ISO 15630 are given in Table 1.

Table 1 — Symbols

Symbol	Unit	Description	Reference
A	%	Percentage elongation after fracture	5.1, 5.3
A_g	%	Percentage non-proportional elongation at maximum force (F_m)	5.3
A_{gt}	%	Percentage total elongation at maximum force (F_m)	Clause 5
d	mm	Nominal diameter of the bar or wire	5.3, 7.2, 8.4.7
D	mm	Diameter of the mandrel of the bending device in the bend test on a welded intersection	6.2.1 (Figure 2), 6.3
f	Hz	Frequency of force cycles in the axial force fatigue test	8.1, 8.4.3
F_m	N	Maximum force in the tensile test	5.3
F_r	N	Force range in the axial force fatigue test	8.1, 8.3, 8.4.2, 8.4.3
F_s	N	Weld shear force	Clause 7
F_{up}	N	Upper force in the axial force fatigue test	8.1, 8.3, 8.4.2, 8.4.3
r_1	mm	Distance between the grips and the gauge length for the manual measurement of A_{gt}	5.3
r_2	mm	Distance between the fracture and the gauge length for the manual measurement of A_{gt}	5.3
R_{eH}	MPa	Upper yield strength	5.3
R_m	MPa	Tensile strength	5.3
$R_{p0,2}$	MPa	0,2 % proof strength, non-proportional extension	5.2, 5.3
S_n	mm ²	Nominal cross-sectional area of the bar or wire	8.4.2
γ	°	Angle of bend in the bend test on a welded intersection	6.3
$2\sigma_a$	MPa	Stress range in the axial force fatigue test	8.4.2
σ_{max}	MPa	Maximum stress in the axial force fatigue test	8.4.2

NOTE 1 MPa = 1 N/mm².

4 General provisions concerning test pieces

Unless otherwise agreed or specified in the product standard, the test pieces shall be taken from the welded fabric in the as-delivered condition.

In the case of a curved test piece, the test piece shall be straightened prior to any tests by a bend operation with a minimum amount of plastic deformation.

NOTE The straightness of the test piece is critical for the tensile test and the fatigue test.

The means of straightening the test piece (manual, machine) shall be indicated in the test report¹⁾.

For the determination of the mechanical properties in the tensile test and the fatigue test, the test piece may be artificially aged, depending on the requirements of the relevant product standard.

1) For routine tests conducted by the reinforcing steel producers, the test information, including the test piece condition and method of straightening, should be contained within internal documentation.

If the product standard does not specify the ageing treatment, the following conditions should be applied: heating the test piece to 100 °C, maintaining at this temperature ± 10 °C for a period of 1 h_0^{+15} min and then cooling in still air to the ambient temperature.

If an ageing treatment is applied to the test piece, the conditions of the ageing treatment shall be stated in the test report.

The test piece shall include at least one welded intersection.

Cross wires or bars, and the wire or bar not to be tested in a twin-wire or -bar sample, shall be cut off before the test without damaging the wire or bar to be tested or the weld under test.

5 Tensile test

5.1 Test piece

In addition to the general provisions given in Clause 4, the free length of the test piece shall be sufficient for the determination of percentage elongations in accordance with 5.3.

If the percentage elongation after fracture (A) is determined manually, the test piece shall be marked in accordance with ISO 6892-1.

If the percentage total elongation at maximum force (A_{gt}) is determined by the manual method, equidistant marks shall be made on the free length of the test piece (see ISO 6892-1). The distance between the marks shall be 20 mm, 10 mm or 5 mm, depending on the bar or wire diameter.

5.2 Test equipment

The testing machine shall be verified and calibrated in accordance with ISO 7500-1 and shall be at least of class 1.

If an extensometer is used, it shall be of class 1 in accordance with ISO 9513 for the determination of $R_{p0,2}$; for the determination of A_{gt} , a class 2 extensometer (see ISO 9513) may be used.

Any extensometer used for the determination of the percentage total elongation at maximum force (A_{gt}) shall have a gauge length of at least 100 mm. The gauge length shall be indicated in the test report.

5.3 Test procedure

The tensile test shall be carried out in accordance with ISO 6892-1. For the determination of $R_{p0,2}$, if the straight portion of the force-extension diagram is limited or not clearly defined, one of the following methods shall be applied:

- the procedure recommended in ISO 6892-1;
- the straight portion of the force-extension diagram shall be considered as the line joining the points corresponding to $0,2F_m$ and $0,5F_m$.

In case of dispute, the second procedure shall be applied.

The test may be considered invalid if the slope of this line differs by more than 10 % from the theoretical value of the modulus of elasticity.

For the calculation of tensile properties (R_{eH} or $R_{p0,2}$, R_m), the nominal cross-sectional area shall be used, unless otherwise specified in the relevant product standard.

Where fracture occurs in the grips or at a distance from the grips of less than 20 mm or d (whichever is the greater), the test may be considered as invalid.

For the determination of percentage elongation after fracture (A), the original gauge length shall be 5 times the nominal diameter (d), unless otherwise specified in the relevant product standard. In case of dispute, A shall be determined manually.

For the determination of the percentage total elongation at maximum force (A_{gt}), ISO 6892-1 shall be applied with the following modification:

- if A_{gt} is determined by the manual method after fracture, A_{gt} shall be calculated from the following formula:

$$A_{gt} = A_g + R_m / 2\ 000 \tag{1}$$

where A_g is the percentage non-proportional elongation at maximum force.

The measurement of A_g shall be made on the longer of the two broken parts of the test piece on a gauge length of 100 mm, as close as possible to the fracture but at a distance, r_2 , of at least 50 mm or $2d$ (whichever is the greater) away from the fracture. This measurement may be considered as invalid if the distance, r_1 , between the grips and the gauge length is less than 20 mm or d (whichever is the greater). See Figure 1.

In case of dispute, the manual method shall apply.



- a Grip length.
- b Gauge length 100 mm.

Figure 1 — Measurement of A_{gt} by the manual method

6 Bend test on welded intersection

6.1 Test piece

The general provisions given in Clause 4 apply.

For welded fabric with single wires or bars in both directions, the thicker wire or bar shall be submitted to bending.


For welded fabric with twin wires or bars, one of the twin wires or bars shall be submitted to bending.

6.2 Test equipment

6.2.1 A bending device, the principle of which is shown in Figure 2, shall be used.

NOTE Figure 2 shows a configuration where the mandrel and support rotate and the carrier is locked. It is also possible that the carrier rotates and the support or mandrel is locked.

6.2.2 The bend test may also be carried out by using a device with supports and a mandrel (e.g. see ISO 7438).

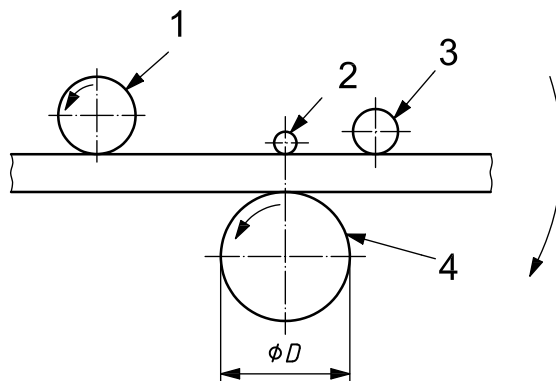

Key

- 1 support
- 2 crossing wire
- 3 carrier
- 4 mandrel

Figure 2 — Principle of a bending device

iTeh STANDARD PREVIEW
(standards.iteh.ai)

6.3 Test procedure

The bend test shall be carried out at a temperature between 10 °C and 35 °C, unless otherwise agreed by the parties involved.

[ISO 15630-2:2010](https://standards.iteh.ai/catalog/standards/sist/3b0ef9e8-c7a1-4926-9fc7-777777777777/iso-15630-2-2010)

[https://standards.iteh.ai/catalog/standards/sist/3b0ef9e8-c7a1-4926-9fc7-](https://standards.iteh.ai/catalog/standards/sist/3b0ef9e8-c7a1-4926-9fc7-777777777777/iso-15630-2-2010)

For testing at a low temperature, if the agreement does not specify all the testing conditions, a deviation of ± 2 °C on the agreed temperature should be applied. The test piece should be immersed in the cooling medium for a sufficient time to ensure that the required temperature is reached throughout the test piece (for example, at least 10 min in a liquid medium or at least 30 min in a gaseous medium). The bend test should start within 5 s from removal from the medium. The transfer device should be designed and used in such a way that the temperature of the test piece is maintained within the temperature range.

The test piece shall be bent over a mandrel so that the weld will be in the centre of the bent portion of the test piece and in the zone under tension.

The angle of bend (γ) and the diameter of the mandrel (D) shall be in accordance with the relevant product standard.

6.4 Interpretation of test results

The interpretation of the bend test shall be carried out in accordance with the requirements of the relevant product standard.

If these requirements are not specified, the absence of cracks visible to a person with normal or corrected vision is considered as evidence that the test piece has withstood the bend test.

A superficial ductile tear may occur at the base of the ribs or indentations and is not considered to be a failure. The tear may be considered superficial when the depth of the tear is not greater than the width of the tear.