

---

---

---

**Thermal insulating products for building  
applications — Determination of tensile  
strength perpendicular to faces**

*Produits isolants thermiques destinés aux applications du bâtiment —  
Détermination de la résistance à la traction perpendiculairement aux  
faces*

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[ISO 29765:2008](#)

<https://standards.iteh.ai/catalog/standards/sist/1a087502-53f1-41fa-a6cf-90778a8be61d/iso-29765-2008>



Reference number  
ISO 29765:2008(E)

© ISO 2008

**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

## iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO 29765:2008](#)

<https://standards.iteh.ai/catalog/standards/sist/1a087502-53f1-41fa-a6cf-90778a8be61d/iso-29765-2008>



### COPYRIGHT PROTECTED DOCUMENT

© ISO 2008

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

## Contents

	Page
<b>Foreword</b> .....	iv
<b>Introduction</b> .....	v
<b>1 Scope</b> .....	1
<b>2 Normative references</b> .....	1
<b>3 Terms and definitions</b> .....	1
<b>4 Principle</b> .....	1
<b>5 Apparatus</b> .....	2
<b>6 Test specimens</b> .....	3
<b>7 Procedure</b> .....	4
<b>8 Calculation and expression of results</b> .....	4
<b>9 Accuracy of measurement</b> .....	4
<b>10 Test report</b> .....	5

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO 29765:2008

https://standards.iteh.ai/catalog/standards/sist/1a087502-53f1-41fa-a6cf-  
90778a8be61d/iso-29765-2008

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 29765 was prepared by Technical Committee ISO/TC 163, *Thermal performance and energy use in the built environment*, Subcommittee SC 1, *Test and measurement methods*.

## iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO 29765:2008](#)

<https://standards.iteh.ai/catalog/standards/sist/1a087502-53f1-41fa-a6cf-90778a8be61d/iso-29765-2008>

## Introduction

This International Standard comprises the original EN 1607:1996 and EN 1607:1996/AC:1997 prepared by Technical Committee CEN/TC 88, *Thermal insulating materials and products*, which have been amended by ISO/TC 163/SC 1 with reference to conditioning and testing conditions in tropical countries.

This International Standard is one of a series of documents specifying test methods, based on existing European Standards, that are being adopted by ISO. This “package” of standards includes the following group of interrelated documents.

International Standard	Respective EN standard
ISO 29465, <i>Thermal insulating products for building applications — Determination of length and width</i>	EN 822
ISO 29466, <i>Thermal insulating products for building applications — Determination of thickness</i>	EN 823
ISO 29467, <i>Thermal insulating products for building applications — Determination of squareness</i>	EN 824
<b>iTeh STANDARD PREVIEW</b>	
ISO 29468, <i>Thermal insulating products for building applications — Determination of flatness</i>	EN 825
ISO 29469, <i>Thermal insulating products for building applications — Determination of compression behaviour</i>	EN 826
ISO 29470, <i>Thermal insulating products for building applications — Determination of the apparent density</i>	EN 1602
ISO 29471, <i>Thermal insulating products for building applications — Determination of dimensional stability under constant normal laboratory conditions (23 °C/50 % relative humidity)</i>	EN 1603
ISO 29472, <i>Thermal insulating products for building applications — Determination of dimensional stability under specified temperature and humidity conditions</i>	EN 1604
ISO 29764, <i>Thermal insulating products for building applications — Determination of deformation under specified compressive load and temperature conditions</i>	EN 1605
ISO 29765, <i>Thermal insulating products for building applications — Determination of tensile strength perpendicular to faces</i>	EN 1607
ISO 29766, <i>Thermal insulating products for building applications — Determination of tensile strength parallel to faces</i>	EN 1608
ISO 29767, <i>Thermal insulating products for building applications — Determination of short-term water absorption by partial immersion</i>	EN 1609

ISO 29768, *Thermal insulating products for building applications — Determination of linear dimensions of test specimens* EN 12085

ISO 29769, *Thermal insulating products for building applications — Determination of behaviour under point load* EN 12430

ISO 29770, *Thermal insulating products for building applications — Determination of thickness for floating-floor insulating products* EN 12431

ISO 29771, *Thermal insulating materials for building applications — Determination of organic content* EN 13820

ISO 29803, *Thermal insulation products for building applications — Determination of the resistance to impact of external thermal insulation composite systems (ETICS)* EN 13497

ISO 29804, *Thermal insulation products for building applications — Determination of the tensile bond strength of the adhesive and of the base coat to the thermal insulation material* EN 13494

ISO 29805, *Thermal insulation products for building applications — Determination of the mechanical properties of glass fibre meshes* EN 13496

## iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO 29765:2008](#)

<https://standards.iteh.ai/catalog/standards/sist/1a087502-53f1-41fa-a6cf-90778a8be61d/iso-29765-2008>

# Thermal insulating products for building applications — Determination of tensile strength perpendicular to faces

## 1 Scope

This International Standard specifies the equipment and procedures for determining the tensile strength of a product perpendicular to its faces. This International Standard is applicable to thermal insulating products.

## 2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 29768, *Thermal insulating products for building applications — Determination of linear dimensions of test specimens*

iTeh STANDARD PREVIEW

ISO 5725-1:1994, *Accuracy (trueness and precision) of measurement methods and results — Part 1: General principles and definitions*

ISO 5725-2:1994, *Accuracy (trueness and precision) of measurement methods and results — Part 2: Basic method for the determination of repeatability and reproducibility of a standard measurement method*

ISO 29765:2008

<https://standards.iteh.ar/catalog/standards/sis/1408/302-5311-41fa-doc-9078a880e01d/iso-29765-2008>

## 3 Terms and definitions

For the purposes of this document, the following term and definition apply.

### 3.1

#### tensile strength perpendicular to faces

$\sigma_{mt}$

maximum recorded tensile force perpendicular to the product faces during the pulling operation, divided by the cross-sectional area of the test specimen

## 4 Principle

A specimen is attached between two rigid plates or blocks, fastened in a tensile testing machine and pulled apart at a given speed.

The maximum tensile force is recorded and the tensile strength of the specimen is calculated.


## 5 Apparatus

Any test equipment that provides the same result with at least the same accuracy may be used.

**5.1 Tensile testing machine**, appropriate for the range of force and displacement involved, capable of having a constant crosshead speed adjusted to  $(10 \pm 1)$  mm/min and capable of measuring the force to an accuracy of  $\pm 1\%$ .

**5.2 Rigid plates or blocks**, with self-aligning attachment to avoid uneven distribution of tensile stress during the test.

Examples of suitable arrangements to bond the specimen are shown in Figure 1.

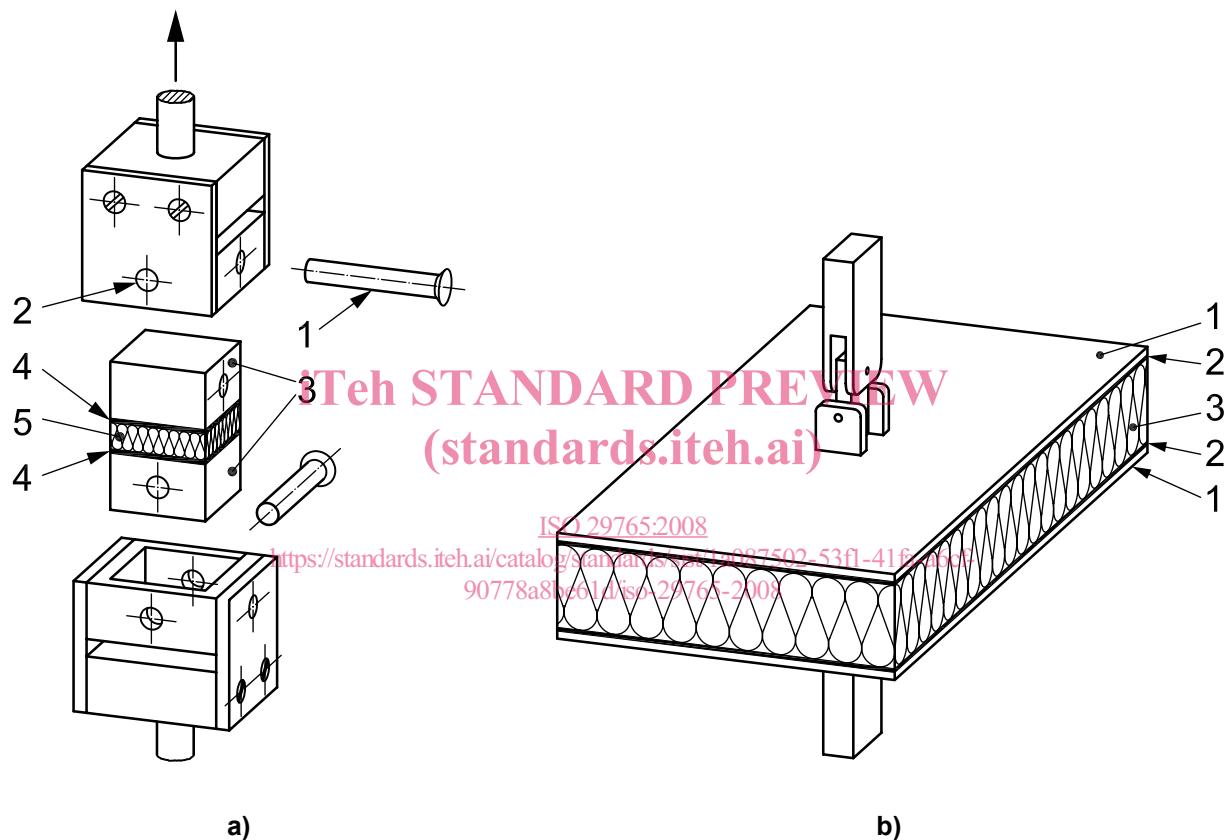

### Key

- 1 bolt
- 2 connecting shaft
- 3 metal blocks
- 4 adhesive
- 5 test specimen

### Key

- 1 rigid plate
- 2 adhesive
- 3 test specimen

**Figure 1 — Examples of suitable arrangements to bond the specimen**

**5.3 Adhesive**, used to bond the specimen between the rigid plates or blocks, with a consideration of the following.

- The adhesive shall not reinforce or damage the surface layers of the product.
- Hot adhesives shall be avoided if they damage the product.
- Any solvent used shall be compatible with the product.

## 6 Test specimens

### 6.1 Dimensions of test specimens

The thickness of specimens shall be equal to the original product thickness including any skins, facings and/or coatings.

The specimens shall be prisms of square cross section having sides of the following recommended dimensions:

- 50 mm × 50 mm; or
- 100 mm × 100 mm; or
- 150 mm × 150 mm; or
- 200 mm × 200 mm; or
- 300 mm × 300 mm.

Dimensions used shall be as specified in the relevant product standard.

In the absence of a product standard or any other international or European technical specification, the dimensions of specimens may be agreed between parties.

The linear dimensions shall be determined in accordance with ISO 29768 to an accuracy of  $\pm 0,5\%$ .

### 6.2 Number of test specimens (standards.iteh.ai)

The number of specimens shall be as specified in the relevant product standard. If the number is not specified, then at least five specimens shall be used. In the absence of a product standard or any other international or European technical specification, the number of specimens may be agreed between parties.

### 6.3 Preparation of test specimens

The specimens shall be cut from the product so that the specimen base is normal to the direction of the tensile force applied to the product in use.

Specimens shall be prepared by methods that do not change the original structure of the product. Any skins, facings and/or coatings shall be retained. The specimens shall be representative of the product and preferably not taken closer than 15 mm from the edges of the product to avoid the influence of any handling damage. For products with non-plane or non-parallel faces, or that have skins, facings and/or coatings, preparation of specimens shall be as specified in the relevant product standard.

The tolerance on parallelism and flatness between the two faces of a specimen shall be not more than 0,5 % of the specimen side length, with a maximum of 0,5 mm.

Before conditioning, the specimens shall be attached to the two rigid plates or blocks using a suitable adhesive.

### 6.4 Conditioning of test specimens

The specimens (including the two rigid plates or blocks) shall be conditioned for at least 6 h at  $(23 \pm 5)^\circ\text{C}$ . In case of dispute, they shall be conditioned at  $(23 \pm 2)^\circ\text{C}$  and  $(50 \pm 5)\%$  relative humidity for the time specified in the relevant product standard.

Other conditions may be used, provided that they give the same results.

In tropical countries, different conditioning and testing conditions can be relevant. In this case, the conditions shall be  $27^\circ\text{C}$  and 65 % RH and be stated clearly in the test report.